



DPC: 24/30459398 DC

BSI Group Headquarters

389 Chiswick High Road London W4 4AL

Tel: +44 (0)20 8996 9000

Fax: +44 (0)20 8996 7400

www.bsigroup.com

Date: 26 February 2024

Origin: European

Latest date for receipt of comments: 20 April 2024

Project No. 2022/01694

Responsible committee: ISE/104 Concrete Reinforcing and Pre-Stressing Steels

Interested committees:

Title: Draft BS EN ISO 15630-3 Steel for the reinforcement and prestressing of concrete — Test methods. Part 3: Prestressing steel.

Please notify the secretary if you are aware of any keywords that might assist in classifying or identifying the standard or if the content of this standard

- i) has any issues related to 3rd party IPR, patent or copyright
- ii) affects other national standard(s)
- iii) requires additional national guidance or information

WARNING: THIS IS A DRAFT AND MUST NOT BE REGARDED OR USED AS A BRITISH STANDARD. THIS DRAFT IS NOT CURRENT BEYOND 20 April 2024

This draft is issued to allow comments from interested parties; all comments will be given consideration prior to publication. No acknowledgement will normally be sent. **See overleaf for information on the submission of comments.**

No copying is allowed, in any form, without prior written permission from BSI except as permitted under the Copyright, Designs and Patent Act 1988 or for circulation within a nominating organization for briefing purposes. Electronic circulation is limited to dissemination by e-mail within such an organization by committee members.

Further copies of this draft may be purchased from BSI Shop <http://shop.bsigroup.com> or from BSI Customer Services, Tel: +44(0) 20 8996 9001 or email cservices@bsigroup.com. British, International and foreign standards are also available from BSI Customer Services.

Information on the co-operating organizations represented on the committees referenced above may be obtained from <https://standardsdevelopment.bsigroup.com/>.

Responsible Committee Secretary: Ms Julie Weller (BSI)

Direct tel:

E-mail: julie.weller@bsigroup.com

Full document details: 24/30459398 DC

Introduction

This draft standard is based on national and international discussions. Your comments on this draft are invited and will assist in the preparation of the consequent standard.

For international standards, comments will be reviewed by the relevant UK national committee before sending the consensus UK vote and comments to the international committee, which will then decide appropriate action. If the international standard is approved, it is usual for the text to be published as a British Standard.

For national standards, comments will be reviewed by the relevant UK national committee and the resulting standards published as a British Standard.

UK Vote

Please indicate whether you consider the UK should submit a negative (with supporting technical reasons) or positive vote on this draft. Please indicate if you are aware of any reason why this draft standard should not be published as a British Standard.

Submission of Comments

- **Annotated drafts are not acceptable and will be rejected.**
- All comments should be submitted online at <https://standardsdevelopment.bsigroup.com/>. You will need to register in order to comment.

Template for comments and secretariat observations

Date: xx/xx/20xx	Document: ISO/DIS xxxx
------------------	------------------------

1	2	(3)	4	5	(6)	7
MB	Clause No./ Subclause No./Annex (e.g. 3.1)	Paragraph/ Figure/Table/Note	Type of comment	Comment (justification for change) by the MB	Proposed change by the MB	Secretariat observations on each comment submitted
	3.1	Definition 1	ed	Definition is ambiguous and needs clarifying.	Amend to read '...so that the mains connector to which no connection...'	
	6.4	Paragraph 2	te	The use of the UV photometer as an alternative cannot be supported as serious problems have been encountered in its use in the UK.	Delete reference to UV photometer.	



DRAFT International Standard

ISO/DIS 15630-3

Steel for the reinforcement and prestressing of concrete — Test methods —

Part 3: Prestressing steel

*Aciers pour l'armature et la précontrainte du béton — Méthodes
d'essai —*

Partie 3: Aciers de précontrainte

ICS: 77.140.15

ISO/TC 17/SC 16

Secretariat: **SN**

Voting begins on:
2024-02-26

Voting terminates on:
2024-05-20

This document is circulated as received from the committee secretariat.

ISO/CEN PARALLEL PROCESSING

Reference number
ISO/DIS 15630-3:2024(en)

Full document details: 24/30459398 DC

THIS DOCUMENT IS A DRAFT CIRCULATED FOR COMMENTS AND APPROVAL. IT IS THEREFORE SUBJECT TO CHANGE AND MAY NOT BE REFERRED TO AS AN INTERNATIONAL STANDARD UNTIL PUBLISHED AS SUCH.

IN ADDITION TO THEIR EVALUATION AS BEING ACCEPTABLE FOR INDUSTRIAL, TECHNOLOGICAL, COMMERCIAL AND USER PURPOSES, DRAFT INTERNATIONAL STANDARDS MAY ON OCCASION HAVE TO BE CONSIDERED IN THE LIGHT OF THEIR POTENTIAL TO BECOME STANDARDS TO WHICH REFERENCE MAY BE MADE IN NATIONAL REGULATIONS.

RECIPIENTS OF THIS DRAFT ARE INVITED TO SUBMIT, WITH THEIR COMMENTS, NOTIFICATION OF ANY RELEVANT PATENT RIGHTS OF WHICH THEY ARE AWARE AND TO PROVIDE SUPPORTING DOCUMENTATION.

© ISO 2024

AVA Documents
Document Sharing Hub



COPYRIGHT PROTECTED DOCUMENT

© ISO 2024

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

© ISO 2024 – All rights reserved

Contents

Page

Foreword	vi
Introduction	vii
1 Scope	1
2 Normative references	1
3 Terms, definitions and symbols	1
4 General provisions concerning test pieces	3
5 Tensile test	4
5.1 Test piece	4
5.2 Test equipment	4
5.3 Test procedure	4
5.3.1 General	4
5.3.2 Determination of the modulus of elasticity	5
6 Bend test	6
6.1 Test piece	6
6.2 Test equipment	6
6.3 Test procedure	6
6.4 Interpretation of test results	6
7 Reverse bend test	7
7.1 Test piece	7
7.2 Test equipment	7
7.3 Test procedure	8
8 Wrapping test	8
8.1 Test piece	8
8.2 Test equipment	8
8.3 Test procedure	8
9 Isothermal stress relaxation test	8
9.1 Principle of test	8
9.2 Test piece	9
9.3 Test equipment	9
9.3.1 Frame	9
9.3.2 Force-measuring device	10
9.3.3 Length-measuring device (extensometer)	10
9.3.4 Anchoring device	10
9.3.5 Loading device	10
9.4 Test procedure	10
9.4.1 Provisions concerning the test piece	10
9.4.2 Application of force	10
9.4.3 Initial force	11
9.4.4 Force during the test	11
9.4.5 Maintenance of strain	11
9.4.6 Temperature	12
9.4.7 Frequency of force recording	12
9.4.8 Frequency of strain recording	12
9.4.9 Duration of the test	12
10 Axial force fatigue test	12
10.1 Principle of test	12
10.2 Test piece	13
10.3 Test equipment	13
10.4 Test procedure	13
10.4.1 Provisions concerning the test piece	13
10.4.2 Stability of force and frequency	13

10.4.3	Counting of force cycles	14
10.4.4	Frequency	14
10.4.5	Temperature	14
10.4.6	Validity of the test	14
11	Stress corrosion test in a solution of thiocyanate	14
11.1	Principle of test	14
11.2	Sample and test piece	14
11.3	Test equipment	14
11.3.1	Frame	14
11.3.2	Force-measuring device	14
11.3.3	Time-measuring device	15
11.3.4	Test cell containing the test solution	15
11.3.5	Test solution	15
11.4	Test procedure	15
11.4.1	Provisions concerning the test pieces	15
11.4.2	Application and maintenance of force	16
11.4.3	Filling of the test cell	16
11.4.4	Temperature during the test	16
11.4.5	Termination of the test	16
11.4.6	Determination of median lifetime to fracture	16
12	Deflected tensile test	16
12.1	Principle of test	16
12.2	Sample and test pieces	17
12.3	Test equipment	17
12.3.1	General description	17
12.3.2	Dimensions	17
12.3.3	Anchorage	18
12.3.4	Mandrel	18
12.3.5	Loading device	19
12.4	Test procedure	19
13	Chemical analysis	20
14	Measurement of the geometrical characteristics	20
14.1	Test piece	20
14.2	Test equipment	20
14.3	Test procedures	20
14.3.1	Rib measurements	20
14.3.2	Indentation measurements	21
14.3.3	Lay length of strand (P)	22
14.3.4	Straightness	22
15	Determination of the relative rib area (f_R)	22
15.1	General	22
15.2	Calculation of f_R	23
15.2.1	Relative rib area	23
15.2.2	Simplified formulae	23
15.2.3	Formula used for the calculation of f_R	24
16	Determination of deviation from nominal mass per metre	24
16.1	Test piece	24
16.2	Accuracy of measurement	25
16.3	Test procedure	25
17	Test report	25
Annex A (informative) Options for agreement between the parties involved		26
Annex B (informative) Stress corrosion test in thiocyanate solution with galvanostatic current		27
Annex C (informative) Stress corrosion test in distilled water		33

Bibliography	38
---------------------------	-----------

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO [had/had not] received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 16, *Steels for the reinforcement and prestressing of concrete*.

This fourth edition cancels and replaces the third edition (ISO 15630-3:2019), which has been technically revised.

The main changes are as follows:

- addition of the informative [Annex B](#) which specifies a stress corrosion test in thiocyanate solution with galvanostatic current;
- addition of the informative [Annex C](#) which specifies a stress corrosion test in distilled water.

A list of all parts in the ISO 15360 series can be found on the ISO website.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

The aim of ISO 15630 (all parts) is to provide all relevant test methods for reinforcing and prestressing steels in one standard series.

This document covers standard test methods, as well as specialized test methods that are not commonly used in routine testing and that should only be considered where relevant (or specified) in the applicable product standard.

Reference is made to International Standards on the testing of metals, in general, as they are applicable. Complementary provisions have been given if needed.

Steel for the reinforcement and prestressing of concrete — Test methods —

Part 3: Prestressing steel

1 Scope

This document specifies test methods applicable to prestressing steel (bar, wire or strand) for concrete.

This document does not cover the sampling conditions that are dealt with in the product standards.

A list of options for agreement between the parties involved is provided in [Annex A](#).

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4957, *Tool steels*

ISO 4965-1, *Metallic materials — Dynamic force calibration for uniaxial fatigue testing — Part 1: Testing systems*

ISO 4965-2, *Metallic materials — Dynamic force calibration for uniaxial fatigue testing — Part 2: Dynamic calibration device (DCD) instrumentation*

ISO 6508-1, *Metallic materials — Rockwell hardness test — Part 1: Test method*

ISO 6892-1, *Metallic materials — Tensile testing — Part 1: Method of test at room temperature*

ISO 7500-1, *Metallic materials — Calibration and verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Calibration and verification of the force-measuring system*

ISO 7801, *Metallic materials — Wire — Reverse bend test*

ISO 7802, *Metallic materials — Wire — Wrapping test*

ISO 9513, *Metallic materials — Calibration of extensometer systems used in uniaxial testing*

ISO 16020, *Steel for the reinforcement and prestressing of concrete — Vocabulary*

3 Terms, definitions and symbols

For the purposes of this document, the terms and definitions given in ISO 16020 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

For the purposes of this document, the following symbols apply.

ISO/DIS 15630-3:2023(en)

Symbol	Unit	Description	Reference
a_m	mm	Rib height at the mid-point	14.3 , 15.2
a_{max}	mm	Maximum height of rib or depth of indentation	14.3
$a_{s,i}$	mm	Average height of a portion i of a rib subdivided into p parts of length Δl	15.2
$a_{1/4}$	mm	Rib height at the quarter-point	14.3 , 15.2
$a_{3/4}$	mm	Rib height at the three-quarters point	14.3 , 15.2
A	%	Percentage elongation after fracture	5.1 , 5.3
A_{gt}	%	Percentage total extension at maximum force	Clause 5
A_r	%	Percentage uniform elongation after fracture	5.3
b	mm	Width of transverse rib at the mid-point	14.3.1.6
c	mm	Rib or indentation spacing	14.3
C	mm	Groove width at nominal diameter of the mandrel, d_a , used for the deflected tensile test	12.3.4
d	mm	Nominal diameter of the bar, wire or strand	5.3.1 , 7.2 , Table 3 , 10.4.6 , Table 4
d_a	mm	Nominal diameter of the mandrel used for the deflected tensile test	12.3.4
d_b	mm	Diameter to be obtained after placing two gauge cylinders in the groove of the mandrel used for the deflected tensile test	12.3.4
d_e	mm	Diameter of the gauge cylinder used for the deflected tensile test	12.3.4
d_g	mm	Diameter of guide hole	7.2
d_i	mm	Inner diameter of the groove of the mandrel used for the deflected tensile test	12.3.4
D	%	Average coefficient of reduction of the maximum force in the deflected tensile test	12.2 , 12.4
D_c	mm	Inner diameter of the test cell in the stress corrosion test	11.3.4
D_i	%	Individual percentage of reduction of the maximum force in the deflected tensile test	12.4
D_m	mm	Diameter of the mandrel of the bending device in the bend test	Figure 2
e	mm	Average gap between two adjacent ribs or indentation rows	14.3.1.4 , 14.3.2.5
E	MPa	Modulus of elasticity	5.2 , 5.3
f	Hz	Frequency of force cycles in the axial force fatigue test	10.1 , 10.4.2
f_R	—	Relative rib area	Clause 15
$F_{a,i}$	N	Individual breaking force in the deflected tensile test	12.4
F_m	N	Maximum force in the tensile test	5.3
$\bar{F}_m$	N	Mean value of the maximum force	9.2 , 11.2 , 12.2 , 12.4
$F_{p0,1}$	N	0,1 % proof force, plastic extension	5.2 , 5.3
$F_{p0,2}$	N	0,2 % proof force, plastic extension	5.2 , 5.3
F_r	N	Force range in the axial force fatigue test	Figure 6 , 10.3 , 10.4.2
F_{rt}	N	Residual force in the test piece at time t in the isothermal stress relaxation test	9.1
ΔF_{rt}	N	Force loss in the test piece at time t in the isothermal stress relaxation test	9.1
F_R	mm ²	Area of longitudinal section of one rib	15.2
F_{up}	N	Upper force in the axial force fatigue test	Figure 6 , 10.3 , 10.4.2
F_0	N	Initial force in the isothermal stress relaxation test and the stress corrosion test	9.1 , 9.2 , 9.3 , 9.4 , 11.1 , 11.2 , 11.4.2
G	mm	Depth of the groove of the mandrel used for the deflected tensile test	12.3.4

NOTE 1 MPa = 1 N/mm².

Symbol	Unit	Description	Reference
h	mm	Distance from the top tangential plane of cylindrical supports to the bottom face of the guide	7.2
h_b	mm	Bow height in the plane of the bow	14.3.4
l	mm	Length of indentation	14.3.2.4
L_t	mm	Length of the test piece in the stress corrosion test	11.2
L_0	mm	Gauge length (without force on the test piece) in the isothermal stress relaxation test Length of the test piece in contact with the solution in the stress corrosion test	9.1 , 9.3 , 9.4 11.2 , 11.3.4 , 11.4.1 , 11.4.3 , 11.4.5
L_1	mm	Length of the passive side in the deflected tensile test	12.3.2
L_2	mm	Length of the active side in the deflected tensile test	12.3.2
m, n	—	Coefficients or numbers	9.4.9 , 14.3 , 15.2
P	mm	Lay length of a strand	14.3.3
r	mm	Radius of cylindrical supports	7.2
R	mm	Radius at the base of the mandrel used for the deflected tensile test	12.3.4
r_1	mm	Distance between the grips and the gauge length for the manual measurement of A_{gt}	5.3
r_2	mm	Distance between the fracture and the gauge length for the manual measurement of A_{gt}	5.3
R_a	μm	Surface roughness of the mandrel used for the deflected tensile test	12.3.4
S_n	mm^2	Nominal cross-sectional area of the test piece	5.3.2
t_a	h	Maximum agreed time for the stress corrosion test	11.4.5
$t_{f,i}$	h	Individual lifetime to fracture in the stress corrosion test	11.4.5
$t_{f,m}$	h	Median lifetime to fracture in the stress corrosion test	11.4.6
t_0	s	Starting time in the isothermal stress relaxation test and in the stress corrosion test	9.4.2 , 11.4
y	mm	Distance from a plane, defined by the axes of the cylindrical supports, to the nearest point of contact with the test piece	Figure 3
V_0	mm^3	Volume of test solution to fill the test cell in the stress corrosion test	11.4.3
Z	%	Percentage reduction of area	5.3.1
α	°	Angle of deviation in the deflected tensile test	12.3.2
β	°	Rib or indentation angle to the bar or wire axis	14.3
$\varepsilon_{x F_m}$	—	Value of the strain for a force equal to $x F_m$	5.3.2
ρ	%	Relaxation	9.4.9
Σe_i	mm	Part of the circumference without indentation or rib	14.3.1.4 , 14.3.2.5 , 15.2

NOTE 1 MPa = 1 N/mm².

4 General provisions concerning test pieces

Unless otherwise agreed or specified in the product standard, the samples shall be taken from the finished product before packaging.

Special care should be taken when samples are taken from the packaged product (e.g. coil or bundle) in order to avoid plastic deformation, which could change the properties of the samples used to provide the test pieces.

Specific complementary provisions concerning the test pieces are indicated in the relevant clauses of this document, if needed.

5 Tensile test

5.1 Test piece

In addition to the general provisions given in [Clause 4](#), the free length of the test piece shall be sufficient for the determination of the percentage total extension at maximum force (A_{gt}) in accordance with [5.3.1](#).

If the percentage elongation after fracture (A) is determined manually, the test piece shall be marked in accordance with ISO 6892-1.

If the percentage total extension at maximum force (A_{gt}) is determined by the manual method for a bar or wire, equidistant marks shall be made on the free length of the test piece (see ISO 6892-1). The distance between the marks shall be 20 mm, 10 mm or 5 mm, depending on the test piece diameter.

5.2 Test equipment

The test equipment shall be verified and calibrated in accordance with ISO 7500-1 and shall be at least of class 1.

If an extensometer is used, it shall be of class 1 in accordance with ISO 9513 for the determination of E , $F_{p0,1}$ or $F_{p0,2}$; for the determination of A_{gt} , a class 2 extensometer (see ISO 9513) may be used.

Grips shall be such as to avoid breaks in or very near the grips.

5.3 Test procedure

5.3.1 General

The tensile test for the determination of the modulus of elasticity (E), 0,1 % and 0,2 % proof force ($F_{p0,1}$ and $F_{p0,2}$), maximum force (F_m), percentage total extension at maximum force (A_{gt}) and/or percentage elongation after fracture (A) and percentage reduction of area (Z) shall be performed in accordance with ISO 6892-1.

An extensometer shall be used for the determination of the modulus of elasticity (E), 0,1 % and 0,2 % proof force ($F_{p0,1}$ and $F_{p0,2}$) and percentage total extension at maximum force (A_{gt}). The extensometer gauge length shall be as specified in the relevant product standard.

Accurate values of A_{gt} can only be obtained with an extensometer. If it is not possible to leave the extensometer on the test piece to fracture or until the maximum force has been passed, the extension may be measured as follows.


- Continue loading until the extensometer records an extension just greater than the extension corresponding to $F_{p0,2}$, at which the extensometer is removed; the distance between the testing machine crossheads is noted. The loading is continued until fracture occurs. The final distance between the crossheads is noted.
- The difference between the crosshead measurements is calculated as a percentage of the original distance between the cross-heads and this value is added to the percentage obtained by the extensometer.

For wire and bars, it is also permissible to determine A_{gt} by the manual method. If A_{gt} is determined by the manual method after fracture, A_{gt} shall be calculated from [Formula \(1\)](#):

$$A_{gt} = A_r + R_m / 2000 \quad (1)$$

where A_r is the percentage uniform elongation after fracture.

The measurement of A_r shall be made, as the measurement of A (see ISO 6892-1), on the longer of the two fractured parts of the test piece on a gauge length of 100 mm, as close as possible to the fracture but at a distance, r_2 , of at least 50 mm or $2d$ (whichever is the greater) away from the fracture. This measurement may be considered as invalid if the distance, r_1 , between the grips and the gauge length is less than 20 mm or d (whichever is the greater). See [Figure 1](#).

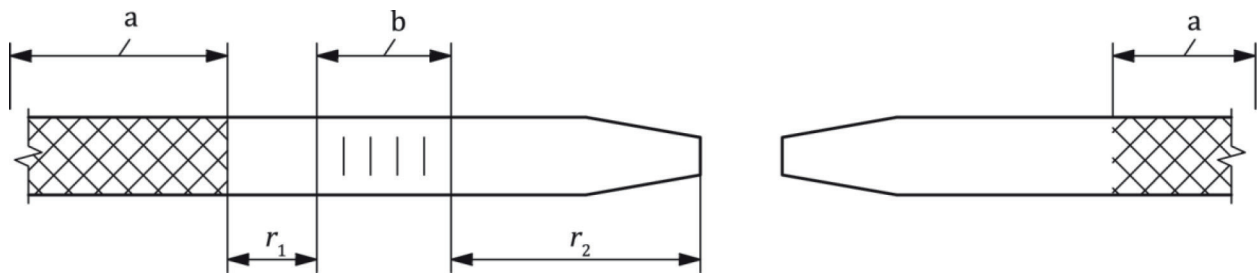

- a Grip length.
- b Gauge length 100 mm.

Figure 1 — Measurement of A_{gt} by the manual method

It is preferable to apply a preliminary force to the test piece, e.g. to about 10 % of the expected maximum force before placing the extensometer.

If A_{gt} is not completely determined with an extensometer, this shall be indicated in the test report.

For routine tests conducted by prestressing steel producers, the test information should be described within internal documentation.

Tensile properties ($F_{p0,1}$, $F_{p0,2}$, F_m) are recorded in force units.

For the determination of percentage elongation after fracture (A), the original gauge length shall be eight times the nominal diameter (d), unless otherwise specified in the relevant product standard. In case of dispute, A shall be determined manually.

If the fracture occurs within a distance of 3 mm from the grips, the test shall, in principle, be considered as invalid and it shall be permissible to perform a retest. However, it shall be permitted to take into account the test results if all values meet the relevant specified values.

5.3.2 Determination of the modulus of elasticity

The modulus of elasticity (E) shall be determined from the slope of the linear portion of the force-extension diagram divided by the nominal cross-sectional area of the test piece (S_n).

In general, for cold-drawn prestressing products (e.g. strands and plain wires), the slope can be determined in the range between $0,2F_m$ and $0,7F_m$, as shown by [Formula \(2\)](#):

$$E = \left[(0,7F_m - 0,2F_m) / (\epsilon_{0,7F_m} - \epsilon_{0,2F_m}) \right] / S_n \quad (2)$$

The slope may be calculated either by a linear regression of the measured data stored in a data storage facility or by a best-fit visual technique over the above-defined portion of the recorded curve.

In some special cases, e.g. hot-rolled and stretched bars, the above-mentioned method cannot be applied; a secant modulus between $0,05F_m$ and $0,7F_m$ may then be determined as shown by [Formula \(3\)](#):

$$\left[(0,7F_m - 0,02F_m) / (\epsilon_{0,7F_m} - \epsilon_{0,02F_m}) \right] / S_n \quad (3)$$

In addition to the provisions given in [5.3.1](#), it shall be ensured that the stress rate is not changed within the force range over which the modulus of elasticity is determined.