



Association of Textile, Apparel & Materials Professionals

AATCC takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this test method. Users of this test method are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This test method is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reaffirmed or withdrawn. Your comments are invited either for revision of this test method or for additional procedures and should be addressed to the AATCC Technical Center. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing, you should make your views known to Diana A. Wyman, Technical Director, at the address shown below.

This test method is copyrighted by AATCC, PO Box 12215, Research Triangle Park, NC 27709 USA. Individual reprints (single or multiple copies) of this method may be obtained by contacting AATCC at the above address or tel: 919-549-3526; fax: 919-549-8933, or e-mail: orders@aatcc.org.

AATCC License Agreement: This test method is copyrighted by the American Association of Textile Chemists and Colorists (AATCC), PO Box 12215, 1 Davis Drive, Research Triangle Park, NC USA. All rights reserved.

AATCC grants you a license as follows: The right to download one electronic file of this AATCC test method for temporary storage on one computer for purposes of viewing, and/or printing one copy of the AATCC test method for individual use. Neither the electronic file nor the hard copy print may be reproduced in any way. In addition, the electronic file may not be distributed elsewhere over computer networks or otherwise. The hard copy print may only be distributed to other employees for their internal use within your organization.

This test method is not for resale.

Water Repellency: Spray Test

Developed in 1941 by AATCC Committee RA63; revised 1952, 1996, 2001, 2005; reaffirmed 1943, 1961, 1964, 1967, 1971, 1974, 1977, 1980, 1985, 1989, 2010, 2014; editorially revised 1987, 2008. Technically equivalent to ISO 4920.

1. Purpose and Scope

1.1 This test method is applicable to any textile fabric, which may or may not have been given a water-repellent finish. It measures the resistance of fabrics to wetting by water. It is especially suitable for measuring the water-repellent efficacy of finishes applied to fabrics.

1.2 The results obtained with this test method depend on the resistance to wetting or water repellency of the fibers, yarns and finishes on the fabric, and upon the construction of the fabric.

2. Principle

2.1 Water sprayed against the taut surface of a test specimen under controlled conditions produces a wetted pattern whose size depends on the repellency of the fabric. Evaluation is accomplished by comparing the wetted pattern with pictures on a standard chart.

3. Terminology

3.1 **water repellency**, *n.*—*in textiles*, the characteristic of a fiber, yarn or fabric to resist wetting.

3.2 **face**, *n.*—*in textiles*, the side of a fabric that is intended to be the outer visible surface in an end product.

4. Safety Precautions

NOTE: These safety precautions are for information purposes only. The precautions are ancillary to the testing procedures and are not intended to be all inclusive. It is the user's responsibility to use safe and proper techniques in handling materials in this test method. Manufacturers MUST be consulted for specific details such as material safety data and other manufacturer's recommendations. All OSHA standards and rules must also be consulted and followed.

4.1 Good laboratory practices should be followed. Wear safety glasses in all laboratory areas.

5. Uses and Limitations

5.1 The portability and simplicity of the instrument, and the shortness and simplicity of the test procedure, make

this method of test especially suitable for screening finishes. It is not intended, however, for use in predicting the probable rain penetration resistance of fabrics, since it does not measure penetration of water through the fabric. For testing rain penetration, AATCC Test Method (TM) 35, Water Resistance: Rain Test, should be used.

6. Apparatus and Materials (see 11.1)

- 6.1 AATCC Spray Tester (see 11.2, Figs. 1, 2, 2A and 3).
- 6.2 Graduated cylinder, 250 mL.
- 6.3 Water, distilled.
- 6.4 Stopwatch (see 8.3)

7. Test Specimens

- 7.1 Three test specimens 180.0 × 180.0 mm (7.0 × 7.0 in.) are needed and should

be conditioned at $65 \pm 2\%$ relative humidity and $21 \pm 1^\circ\text{C}$ ($70 \pm 2^\circ\text{F}$) for a minimum of 4 h before testing.

7.2 Where possible, each specimen should contain different groups of lengthwise and widthwise yarns.

8. Procedure

8.1 Calibrate the apparatus by pouring 250 mL of distilled water at $27 \pm 1^\circ\text{C}$ ($80 \pm 2^\circ\text{F}$) into the funnel of the tester and measure the time required for the funnel to empty.

8.1.1 The spray time must be between 25-30 s, otherwise the nozzle should be checked to see if the holes are enlarged or blocked.

8.2 Fasten the test specimen securely in the 152.4 mm (6.0 in.) diameter hoop so that the face of the fabric specimen will be exposed to the water spray. The

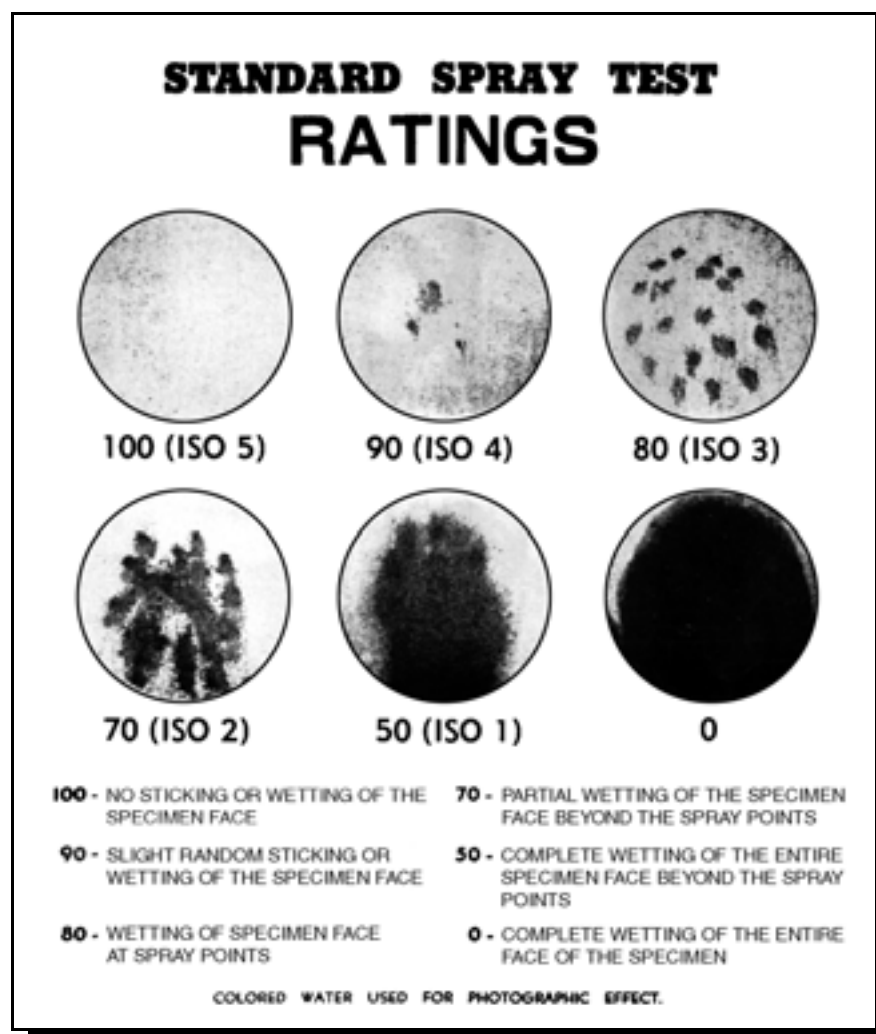


Fig. 1—Spray test rating chart.