



Designation: C 1292 – 00

## Standard Test Method for Shear Strength of Continuous Fiber-Reinforced Advanced Ceramics at Ambient Temperatures<sup>1</sup>

This standard is issued under the fixed designation C 1292; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

### 1. Scope

1.1 This test method covers the determination of shear strength of continuous fiber-reinforced ceramic composites (CFCCs) at ambient temperature. The test methods addressed are (1) the compression of a double-notched specimen to determine interlaminar shear strength and (2) the Iosipescu test method to determine the shear strength in any one of the material planes of laminated composites. Specimen fabrication methods, testing modes (load or displacement control), testing rates (load rate or displacement rate), data collection, and reporting procedures are addressed.

1.2 This test method is used for testing advanced ceramic or glass matrix composites with continuous fiber reinforcement having uni-directional (1-D) or bi-directional (2-D) fiber architecture. This test method does not address composites with (3-D) fiber architecture or discontinuous fiber-reinforced, whisker-reinforced, or particulate-reinforced ceramics.

1.3 The values stated in SI units are to be regarded as the standard and are in accordance with Practice E 380.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* Specific hazard statements are given in 8.1 and 8.2.

### 2. Referenced Documents

#### 2.1 ASTM Standards:

C 1145 Terminology of Advanced Ceramics<sup>2</sup>

D 695 Test Method for Compressive Properties of Rigid Plastics<sup>3</sup>

D 3846 Test Method for In-Plane Shear Strength of Reinforced Plastics<sup>4</sup>

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee C-28 on Advanced Ceramics and is the direct responsibility of Subcommittee C28.07 on Ceramic Matrix Composites.

Current edition approved April 10, 2000. Published July 2000. Originally published as C 1292 – 95. Last previous edition C 1292 – 95a.

<sup>2</sup> Annual Book of ASTM Standards, Vol 15.01.

<sup>3</sup> Annual Book of ASTM Standards, Vol 08.01.

<sup>4</sup> Annual Book of ASTM Standards, Vol 08.02.

D 3878 Terminology for High-Modulus Reinforcing Fibers and Their Composites<sup>5</sup>

D 5379/D 5379M Test Method for Shear Properties of Composite Materials by the V-Notched Beam Method<sup>5</sup>

E 4 Practices for Force Verification of Testing Machines<sup>6</sup>

E 6 Terminology Relating to Methods of Mechanical Testing<sup>6</sup>

E 122 Practice for Choice of Sample Size to Estimate a Measure of Quality for a Lot or Process<sup>7</sup>

E 177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods<sup>7</sup>

E 337 Test Method for Measuring Humidity with Psychrometer (the Measurement of Wet- and Dry-Bulb Temperatures)<sup>8</sup>

E 380 Practice for Use of International System of Units (SI)<sup>7</sup>

E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method<sup>7</sup>

### 3. Terminology

3.1 *Definitions*—The definitions of terms relating to shear strength testing appearing in Terminology E 6 apply to the terms used in this test method. The definitions of terms relating to advanced ceramics appearing in Terminology C 1145 apply to the terms used in this test method. The definitions of terms relating to fiber-reinforced composites appearing in Terminology D 3878 apply to the terms used in this test method. Additional terms used in conjunction with this test method are defined in the following.

3.1.1 *advanced ceramic*—an engineered high-performance predominately nonmetallic, inorganic, ceramic material having specific functional attributes.

3.1.2 *continuous fiber-reinforced ceramic matrix composite (CFCC)*—a ceramic matrix composite in which the reinforcing phase consists of a continuous fiber, continuous yarn, or a woven fabric.

<sup>5</sup> Annual Book of ASTM Standards, Vol 15.03.

<sup>6</sup> Annual Book of ASTM Standards, Vol 03.01.

<sup>7</sup> Annual Book of ASTM Standards, Vol 14.02.

<sup>8</sup> Annual Book of ASTM Standards, Vol 11.03.

3.1.3 *shear failure load*—the maximum load required to fracture a shear loaded test specimen.

3.1.4 *shear strength*—the maximum shear stress that a material is capable of sustaining. Shear strength is calculated from the shear fracture load and the shear loaded area.

#### 4. Summary of Test Method

4.1 This test method addresses two methods to determine the shear strength of CFCCs: (1) the compression of a double-notched specimen test method to determine interlaminar shear strength<sup>9</sup> and (2) the Iosipescu test method to determine the shear strength in any one of the material planes of laminated CFCCs.<sup>10</sup>

4.1.1 *Shear Test by Compression Loading of Double-Notched Specimens*—The interlaminar shear strength of CFCCs, as determined by this method is measured by loading in compression a double-notched specimen of uniform width. Failure of the specimen occurs by shear between two centrally located notches machined halfway through the thickness and spaced a fixed distance apart on opposing faces. Schematics of the test setup and the specimen are shown in Fig. 1 and Fig. 2.

4.1.2 *Shear Test By the Iosipescu Method*—The shear strength of one of the different material shear planes of laminated CFCCs may be determined by loading a coupon in the form of a rectangular flat strip with symmetric centrally located V-notches using a mechanical testing machine and a four-point asymmetric fixture. The loading can be idealized as asymmetric flexure by the shear and bending diagrams in Fig. 3. Failure of the specimen occurs by shear between the V-notches. Different specimen configurations are addressed for this test method. Schematics of the test setup and specimen are shown in Fig. 4 and Fig. 5. The determination of shear

<sup>9</sup> Whitney, J., M., "Stress Analysis of the Double Notch Shear Specimen," Proceedings of the American Society for Composites, 4th Technical Conference, Blacksburg Virginia, Oct. 3–5, 1989, Technomic Publishing Co, pp. 325.

<sup>10</sup> Iosipescu, N., "New Accurate Procedure for Shear Testing of Metals," *Journal of Materials*, 2, 3, Sept. 1967, pp. 537–566.


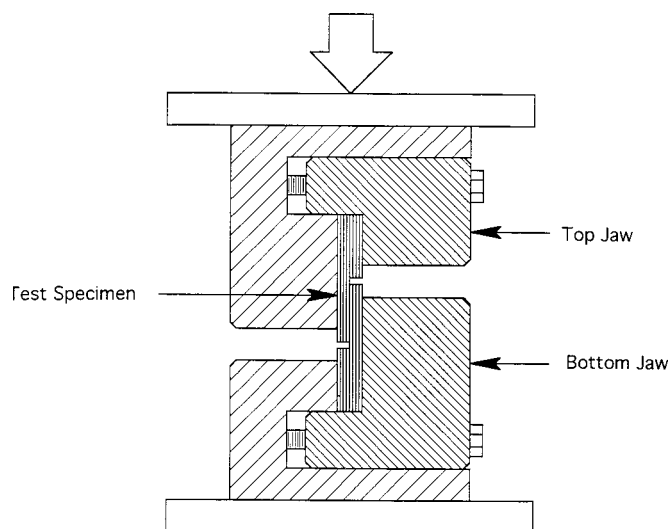


FIG. 1 Schematic of Test Fixture for the Double-Notched Compression Specimen

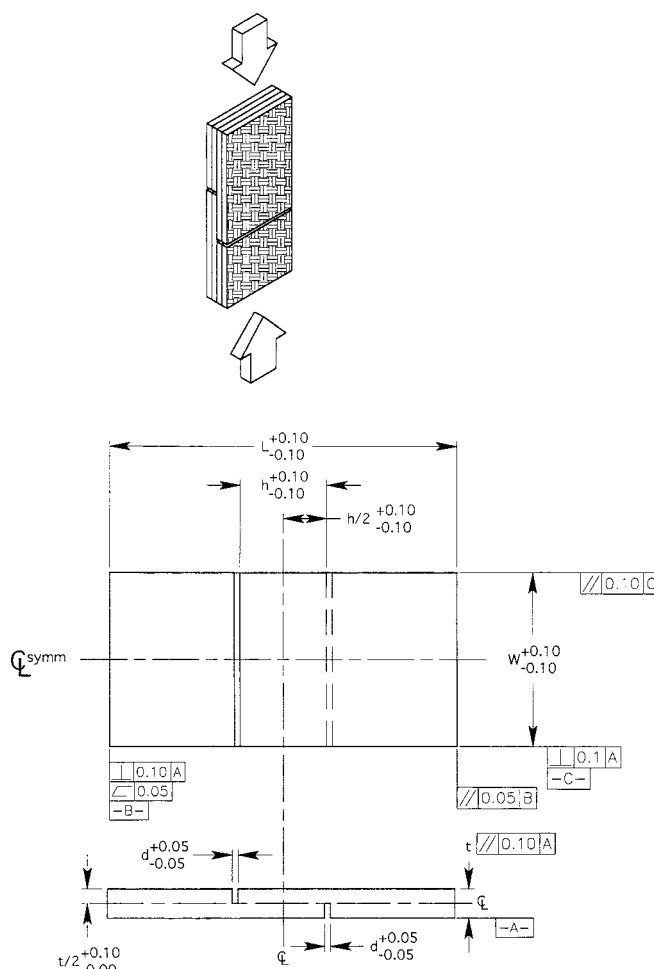

NOTE 1—All tolerances are in millimetres.

FIG. 2 Schematic of Double-Notched Compression Specimen

properties of polymer matrix composites by the Iosipescu method has been presented in Test Method D 5379.

#### 5. Significance and Use

5.1 Continuous fiber-reinforced ceramic composites are candidate materials for structural applications requiring high degrees of wear and corrosion resistance, and damage tolerance at high temperatures.


5.2 Shear tests provide information on the strength and deformation of materials under shear stresses.

5.3 This test method may be used for material development, material comparison, quality assurance, characterization, and design data generation.

5.4 For quality control purposes, results derived from standardized shear test specimens may be considered indicative of the response of the material from which they were taken for given primary processing conditions and post-processing heat treatments.

#### 6. Interferences

6.1 Test environment (vacuum, inert gas, ambient air, etc.) including moisture content (for example, relative humidity) may have an influence on the measured shear strength.

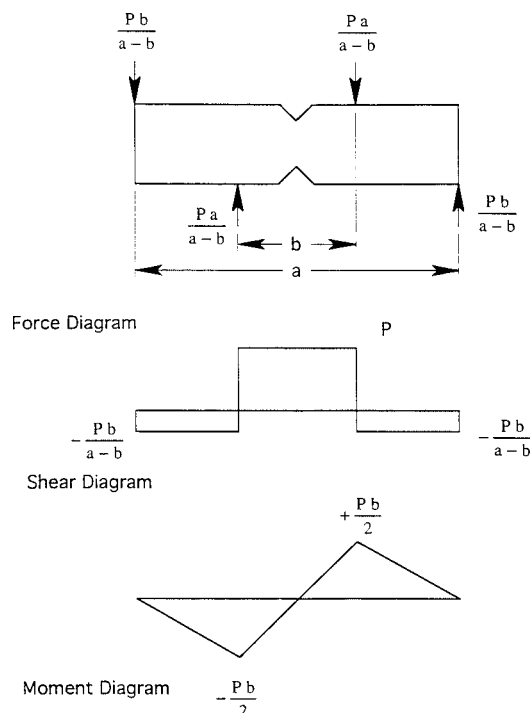

NOTE 1—The loads are depicted as being concentrated, whereas they are actually distributed over an area.

**FIG. 3 Idealized Force, Shear, and Moment Diagrams for Asymmetric Four-Point Loading**



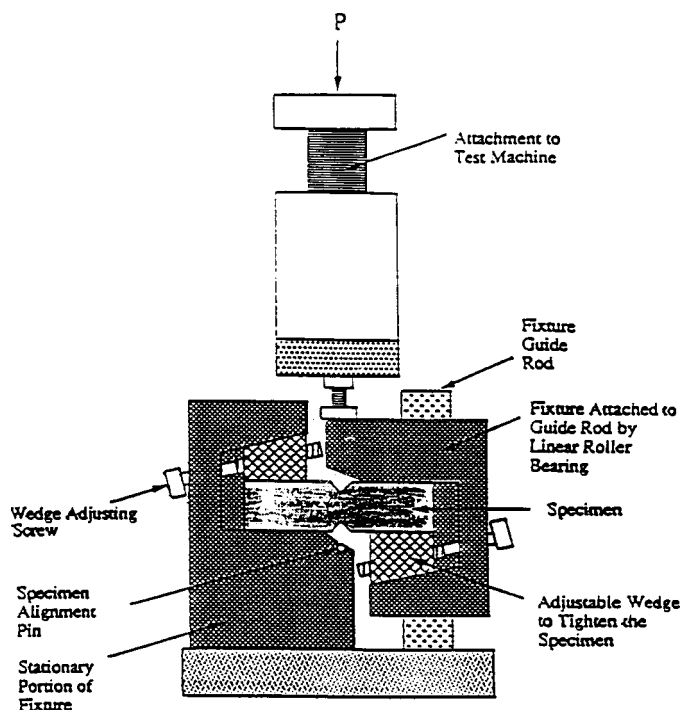


**FIG. 4 Schematic of Test Fixture for the Iosipescu Test**

particular, the behavior of materials susceptible to slow crack growth fracture will be strongly influenced by test environment and testing rate. Testing to evaluate the maximum strength potential of a material shall be conducted in inert environments or at sufficiently rapid testing rates, or both, so as to minimize

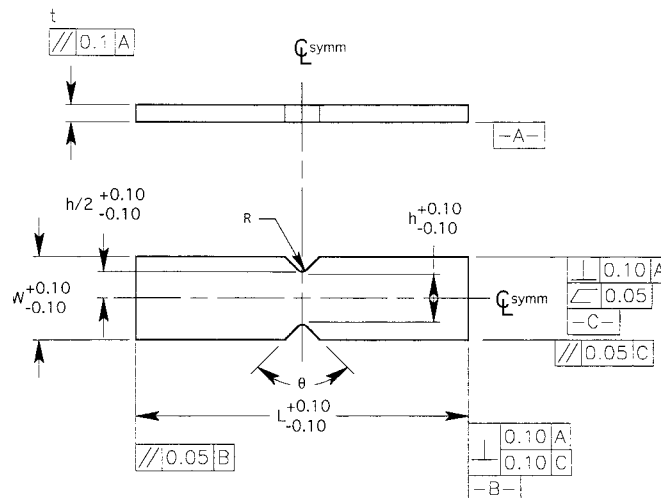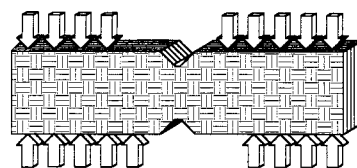

NOTE 1—All tolerances are in millimetres.

**FIG. 5 Schematic of the Iosipescu Specimen**

slow crack growth effects. Conversely, testing can be conducted in environments and testing modes and rates representative of service conditions to evaluate material performance under those conditions. When testing is conducted in uncontrolled ambient air with the intent of evaluating maximum strength potential, relative humidity and temperature must be monitored and reported. Testing at humidity levels >65 % RH is not recommended and any deviations from this recommendation must be reported.

6.2 Preparation of test specimens, although normally not considered a major concern with CFCCs, can introduce fabrication flaws which may have pronounced effects on the mechanical properties and behavior (for example, shape and level of the resulting load-displacement curve and shear strength). Machining damage introduced during specimen preparation can be either a random interfering factor in the determination of shear strength of pristine material, or an inherent part of the strength characteristics to be measured. Universal or standardized test methods of surface preparation do not exist. Final machining steps may, or may not negate machining damage introduced during the initial machining. Thus, specimen fabrication history may play an important role in the measured strength distributions and shall be reported.

6.3 Bending in uniaxially loaded shear tests can cause or promote nonuniform stress distributions that may alter the desired uniform state of stress during the test.