



Designation: D 519 – 90 (Reapproved 1995)^{ε1}

Standard Test Method for Length of Fiber in Wool Top¹

This standard is issued under the fixed designation D 519; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

^{ε1} NOTE—Editorial changes were made throughout in June 1995.

1. Scope

1.1 This test method covers the measurement of the average length and length distribution of fibers in wool top, on a mass-biased basis. The method is applicable to all types of fibers in sliver formed from long parallelized fibers.

NOTE 1—The determination of fiber length of wool is covered in Test Method D 1575, Test Method for Fiber Length of Wool in Scoured Wool and in Card Sliver, the staple length of grease wool is covered in Test Method D 1234, Test Method of Sampling and Testing Staple Length of Grease Wool.

NOTE 2—This test method specifically requires length in inches and mass in SI units and is not contrary to ASTM policy. The SI units in parentheses are provided for information only.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

D 123 Terminology Relating to Textiles²

D 1234 Test Method of Sampling and Testing Staple Length of Grease Wool²

D 1575 Test Method for Fiber Length of Wool in Scoured Wool and Card Sliver²

D 1776 Practice for Conditioning Textiles for Testing²

D 2130 Test Method for Diameter of Wool and Other Animal Fibers by Microprojection²

3. Terminology

3.1 Definitions:

3.1.1 *top, n—in wool*, a continuous untwisted strand of wool fibers from which the shorter fibers or noils have been removed by combing.

3.1.2 For definitions of textile terms used in this test

method, refer to Terminology D 123.

4. Summary of Test Method

4.1 The weight (mass) of fibers, in definite length increments, is determined for each specimen or group of specimens forming one sample. From the data obtained, the weight-biased average fiber length and the weight-biased distribution is calculated. A cumulative weight average length frequency curve may be plotted.

5. Significance and Use

5.1 Knowledge of the average fiber length and the distribution of fibers is of primary importance to users of top in further processing.

5.2 Acceptance specifications for the fiber length and length distribution may be established by the user based on the type of yarn-making equipment employed and the desired end uses.

5.3 Test Method D 519 for testing wool top for fiber length is considered satisfactory for acceptance testing of commercial shipments since the method has been used extensively in the trade for acceptance testing and the current estimates of the between-laboratory precisions are acceptable.

5.3.1 In case of a dispute arising from differences in reported test results when using this test method for acceptance testing of commercial shipments, the purchaser and the supplier should conduct comparative testing to determine if there is a statistical bias between their laboratories. Competent statistical assistance is recommended for the investigation of bias. As a minimum, the two parties should take a group of test specimens that are as homogenous as possible and that are from a lot of the type material in question. The test specimens should then be assigned in equal numbers to each laboratory for testing. The average results from the two laboratories should be compared using Student's *t*-test for unpaired data and an acceptable probability level chosen by the two parties before testing is begun. If a bias is found either its cause must be found and corrected or the purchaser and supplier must agree to interpret future test results in the light of the known bias.

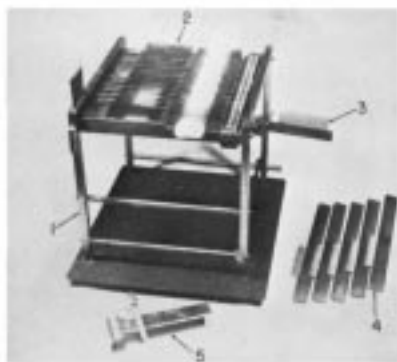
6. Apparatus

6.1 *Comb Sorter*, which can be used to separate long fibers

¹ This test method is under the jurisdiction of ASTM Committee D-13 on Textiles, and is the direct responsibility of Subcommittee D13.13 on Wool and Wool Felt.

Current edition approved Feb. 23, 1990. Published July 1990. Originally published as D 519 – 38 T. Last previous edition D 519 – 78 (1983).

² *Annual Book of ASTM Standards*, Vol 07.01.

 D 519


(Front View)
1—Frame.
2—Faller bars.
3—Side comb.
4—Retaining bars.



(Rear View)
5—Drawing clamp.
6—Depressor.
7—Plush board.
8—Faller bar lifting plate.

FIG. 1 Wool Fiber Stapling Apparatus

TABLE 1 Form with Recorded Data Showing the Calculation of the Average Fiber Length of Wool, the Standard Deviation, and Coefficient of Variation

NOTE 1—When using equipment graduated in metric units, use class intervals 10 mm long, and calculate the average and standard deviation to the nearest 0.2 mm.

Class Intervals, in.	Mass, g	Percentages	Cumulative Frequencies	
			First Cumulative, less than	Second Cumulative, less than
6.0 to 6.5	0.014	2.4	100.0	840.1
5.5 to 6.0	0.010	1.7	97.6	740.1
5.0 to 5.5	0.013	2.2	95.9	642.5
4.5 to 5.0	0.018	3.1	93.7	546.6
4.0 to 4.5	0.038	6.5	90.6	452.9
3.5 to 4.0	0.051	8.7	84.1	362.3
3.0 to 3.5	0.062	10.6	75.4	278.2
2.5 to 3.0	0.072	12.3	64.8	202.8
2.0 to 2.5	0.079	13.5	52.5	138.0
1.5 to 2.0	0.080	13.6	39.0	85.5
1.0 to 1.5	0.065	11.0	25.4	46.5
0.5 to 1.0	0.045	7.7	14.4	21.1
0 to 0.5	0.039	6.7	6.7	6.7
Totals	0.586	100.0 = Σ	840.1	4363.3
		Divided by Σ percentages	$F_1 = 8.40$	$F_2 = 43.63$

B = the largest midpoint value for which a frequency is recorded = 6.25 in.

m = the class interval = 0.5 in.

Percentage of fibers under 2 in. = 39.0 %.

Calculations:

$$\bar{X} = B - m(F_1 - 1) = 6.25 - 0.5(8.40 - 1) = 2.55 \text{ in.}$$

$$s = m\sqrt{2F_2 - F_1 - F_1^2} = 0.5\sqrt{87.26 - 8.40 - 70.56} = 1.44 \text{ in.}$$

$$v = 100 (\sigma/\bar{X}) = 100 \times (1.4/2.6) = 56.47 \text{ %.}$$

where:

$\bar{X}$ = average fiber length of wool,

s = standard deviation, and

v = coefficient of variation.

into 0.50-in. (12.7-mm) groups and the shorter fibers into 0.25-in. (6.4-mm) groups.³ The essential parts are shown in

Fig. 1. The bar or comb intervals are set at 0.5 in. (12.7 mm) and 0.25 in. (6.4 mm).

NOTE 3—Essentially, the same facilities can be secured with two Baer or two Zweigle sorters, or two Shirley units.

6.1.1 *Faller Bars*, free of broken, missing, crooked, dull, or

³ Apparatus meeting these requirements furnished by Alfred Suter Co., Prell Plaza, Orangeburg, NY, has been found satisfactory.