



Designation: D 7084 – 04

Standard Test Method for Determination of Bulk Crush Strength of Catalysts and Catalyst Carriers¹

This standard is issued under the fixed designation D 7084; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the determination of bulk crush strength of a bed of formed catalyst particles $\frac{1}{32}$ to $\frac{3}{16}$ in. (0.8 to 4.8 mm) in diameter and is intended to provide information concerning the ability of the catalyst material to maintain physical integrity.

1.2 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are provided for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

D 3766 Terminology Relating to Catalysts and Catalysis

D 4180 Test Method for Vibratory Packing Density of Formed Catalyst Particles and Catalyst Carriers

E 177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods

E 456 Terminology for Relating to Quality and Statistics

E 691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method

3. Terminology

3.1 *Definitions:*

3.1.1 See also Terminology **D 3766**.

3.1.2 *bulk crush strength*—pressure that generates 1 % fines for a sample contained in a cylindrical sample holder and crushed with a piston.

3.1.3 *generated fines*—particle size after crushing that passes through a sieve one-half of the diameter of the catalyst pellet.

4. Summary of Test Method

4.1 A representative sample is placed in a cylindrical sample holder, which is fitted with a piston. The piston is allowed to compress the catalyst at a known pressure. The percent of generated fines is determined by sieving.

5. Significance and Use

5.1 This test method is a means of determining the crushing strength of a catalyst in a bed. Techniques to measure the crushing strength of formed catalyst particles is limited to crushing of individual particles, which may not be related to how the catalyst will crush in a reactor or bed. For some catalysts, such as granules, this technique may be the only viable method for obtaining crushing strength. The production of fines in a reactor is not desired because of the potential of bed compaction and the pressure buildup in the reactor.

6. Apparatus

6.1 *Hydraulic Press*, capable of 3200 lb (1450 kg) loading, including a force gage. Maximum load capacity of the press should match with the accuracy measuring the applied force.

NOTE 1—Lower maximum load may be acceptable for testing less strong materials.

6.2 *U.S. Standard Sieves*, set (Tyler Equivalent).

6.3 *Test Cell*, (**Fig. 1**).

NOTE 2—A top loading cell can be used, but reproducibility of this test is a function of the volume being crushed and therefore the constant volume cell, as shown in **Fig. 1**, is recommended. A smaller *l/d* ratio for the cell will alter the results, and for certain applications, it may be more desirable.^{3,4}

6.4 *Drying Oven*.

6.5 *Balance*, having a sensitivity of 0.1 g.

6.6 *Glass Cylinders*, with 250-mL feed capacity. Measure in accordance with Test Method **D 4180**.

6.7 *Vibrator*, conventional, handheld, with hard rubber or metal impactor, in accordance with Test Method **D 4180**.

¹ This test method is under the jurisdiction of ASTM Committee D32 on Catalysts and is the direct responsibility of Subcommittee D32.02 on Physical-Mechanical Properties.

Current edition approved Oct. 1, 2004. Published October 2004.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Bradley, S. A., Pitzer, E., and Koves, W. J., "Bulk Crush Testing of Catalysts," *Characterization and Catalyst Development*, ACS Symposium Series 411, Bradley, S. A., Gattuso, M. J., and Bertolacini, R. J., Eds., 1989, pp. 398-406.

⁴ Adams, A. R., Sartor, A. F., and Welsh, J. G., "Problems in Standardizing Catalyst Tests," *Chemical Engineering Progress*, Vol 71, 1975, pp. 35-37.

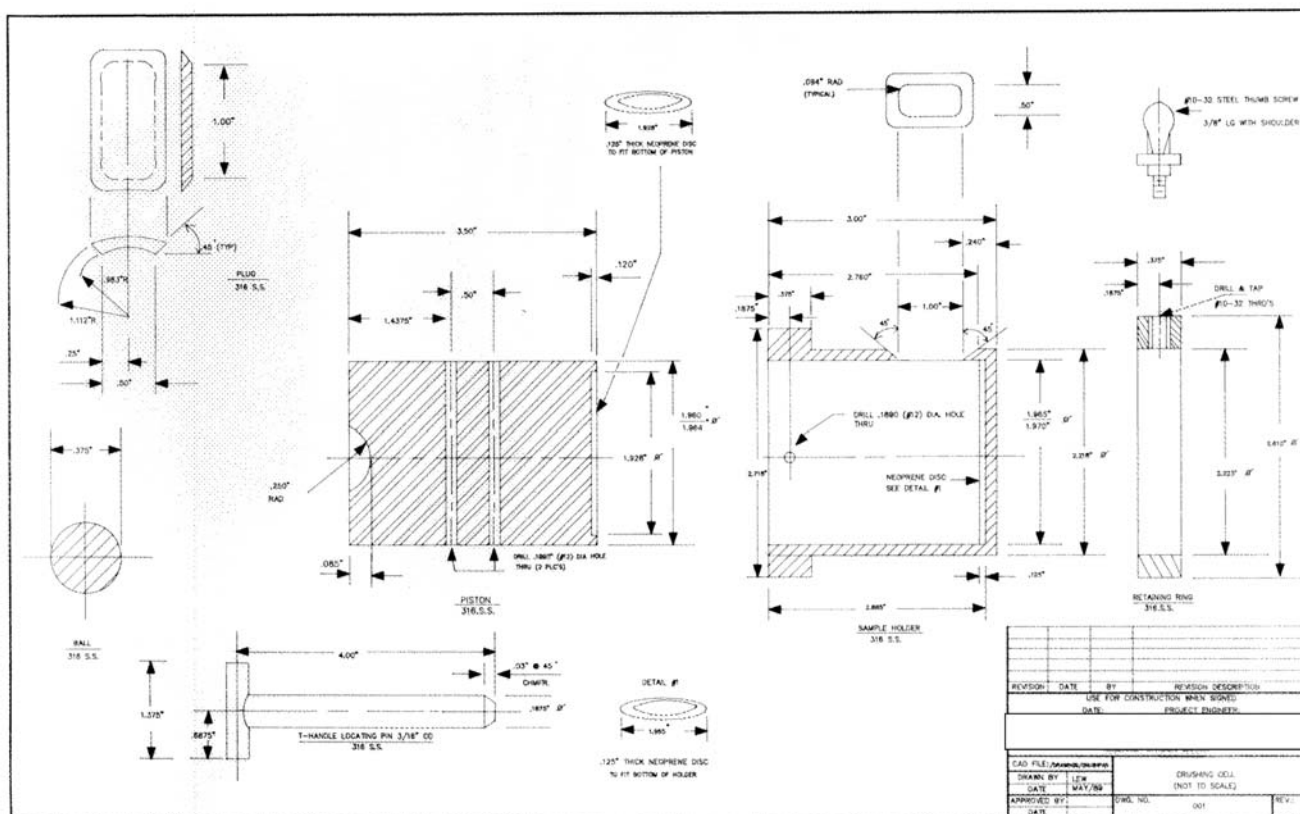


FIG. 1 Test Cell

6.8 Feed Funnel.

6.9 Desiccator, with grade molecular sieve, such as 4A.

7. Procedure

7.1 Determine the bulk density in accordance with Test Method D 4180.

7.2 Weigh 100 mL of the sample and dry at 673 ± 15 K (400°C) for 3 h. Cool the sample in a desiccator using freshly regenerated 4A molecular sieves as a desiccant.

NOTE 3—These conditions may not be appropriate for all materials.

NOTE 4—Since many catalyst formulations are strong adsorbents, the use of No. 4A indicating (cobalt treated) molecular sieve as a desiccating medium is suggested. The desiccant should be regenerated at 493 to 523 K (220 to 260°C) as required.

7.3 Weigh the sample to determine the loss during heating. Calculate the dry bulk density by the following equation:

$$DBD = BD (1 - (OW - DW)/OW) \quad (1)$$

where:

DBD = dry bulk density (see Test Method D 4180),

BD = bulk density,

OW = weight of original sample, and

DW = weight of dried sample.

7.4 Calculate the weight of dried sample required to fill a volume of 49 cm^3 , and then calculate the original weight of this sample.

7.5 Weigh sufficient sample for nine crushing operations. Sieve the sample using a sieve that is one-half the diameter of the catalyst pellet. If 10 % of the material passes through the

screen, use a smaller sieve size. Dry the sample at 673 K for 3 h; do not exceed a bed height of 1 in. Cool the sample in a desiccator.

7.6 Weigh a sample required to fill a volume of 49 cm^3 , as determined in 7.4. Keep the remaining sample in the desiccator.

7.7 Fill the cell with the 49-cm^3 dried sample. Tap the cell while filling it. Place the entire catalyst sample into the cell. Place and center the cell into the hydraulic press.

7.8 Apply a pressure to the cell at a rate of $50 \text{ lb/in.}^2/\text{s}$ (35 kPa/s), and read the pressure. Hold the prescribed pressure for 30 s, and then slowly release the pressure.

7.9 Remove the cell from the press, and then remove the piston from the cell. Brush all of the particles from the end of the piston into the sieve in 7.5. Pour the contents of the cell onto the sieve, and brush all particles from the cell into the sieve.

7.10 After sieving the fines for 60 s into a weighing pan, weigh the catalyst in the pan. Perform sieving so as not to produce additional fines.

7.11 Crush strengths are determined in triplicate for at least two different pressures that will produce both less than and more than 1 weight percent fines. Typical loads are between 150 and 500 lb/in.^2 (1 and 3.5 MPa) for larger formed materials and 15 and 50 lb/in.^2 (0.1 and 0.35 MPa) for granules.

7.12 Use a fresh charge of catalyst for each loading in order to prevent bias of damaged catalyst or being left with stronger pellets.