



Designation: E 1304 – 97 (Reapproved 2002)

Standard Test Method for Plane-Strain (Chevron-Notch) Fracture Toughness of Metallic Materials¹

This standard is issued under the fixed designation E 1304; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the determination of plane-strain (chevron-notch) fracture toughnesses, K_{Iv} or K_{IvM} , of metallic materials. Fracture toughness by this method is relative to a slowly advancing steady state crack initiated at a chevron-shaped notch, and propagating in a chevron-shaped ligament (Fig. 1). Some metallic materials, when tested by this method, exhibit a sporadic crack growth in which the crack front remains nearly stationary until a critical load is reached. The crack then becomes unstable and suddenly advances at high speed to the next arrest point. For these materials, this test method covers the determination of the plane-strain fracture toughness, K_{Ivj} or K_{IvM} , relative to the crack at the points of instability.

NOTE 1—One difference between this test method and Test Method E 399 (which measures K_{Ic}) is that Test Method E 399 centers attention on the start of crack extension from a fatigue precrack. This test method makes use of either a steady state slowly propagating crack, or a crack at the initiation of a crack jump. Although both methods are based on the principles of linear elastic fracture mechanics, this difference, plus other differences in test procedure, may cause the values from this test method to be larger than K_{Ic} values in some materials. Therefore, toughness values determined by this test method cannot be used interchangeably with K_{Ic} .

1.2 This test method uses either chevron-notched rod specimens of circular cross section, or chevron-notched bar specimens of square or rectangular cross section (Figs. 1-10). The terms “short rod” and “short bar” are used commonly for these types of chevron-notched specimens.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

- E 4 Practices for Force Verification of Testing Machines
- E 8 Test Methods for Tension Testing of Metallic Materials
- E 399 Test Method for Linear-Elastic Plane-Strain Fracture Toughness K_{Ic} of Metallic Materials
- E 1823 Terminology Relating to Fatigue and Fracture Testing

3. Terminology

3.1 *Definitions:*

3.1.1 The terms described in Terminology E 1823 are applicable to this test method.

3.1.2 *stress-intensity factor*, K_I (dimensional units $FL^{-3/2}$)—the magnitude of the ideal crack-tip stress field singularity for mode I in a homogeneous linear-elastic body.

3.1.2.1 *Discussion*—Values of K for mode I are given by:

$$K_I = \text{limit } \sigma_y [2\pi r_x]^{1/2}$$

$$r_x \rightarrow 0$$

where:

r_x = a distance directly forward from the crack tip to a location where the significant stress is calculated and

σ_y = the principal stress r_x normal to the crack plane.

3.2 *Definitions of Terms Specific to This Standard:*


3.2.1 *plane-strain (chevron-notch) fracture toughness*, K_{Iv} or K_{Ivj} ($FL^{-3/2}$)—under conditions of crack-tip plane strain in a chevron-notched specimen: K_{Iv} relates to extension resistance with respect to a slowly advancing steady-state crack. K_{Ivj} relates to crack extension resistance with respect to a crack which advances sporadically.

3.2.1.1 *Discussion*—For slow rates of loading the fracture toughness, K_{Iv} or K_{Ivj} , is the value of stress-intensity factor as measured using the operational procedure (and satisfying all of the validity requirements) specified in this test method.

¹ This test method is under the jurisdiction of ASTM Committee E08 on Fracture Fatigue and is the direct responsibility of Subcommittee E08.02 on Standards and Terminology.

Current edition approved April 10, 1997. Published June 1997. Originally published as E 1304 – 89. Last previous edition E 1304 – 89.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

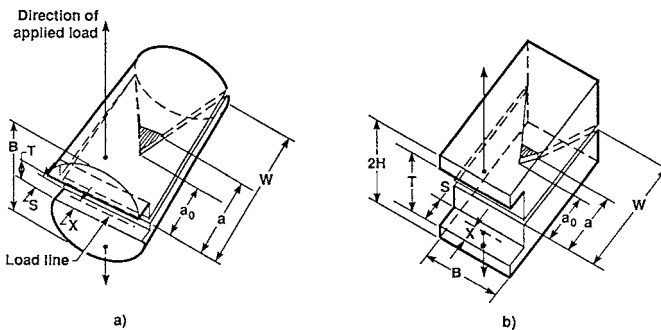

NOTE 1—The crack commences at the tip of the chevron-shaped ligament and propagates (shaded area) along the ligament, and has the length “a” shown. (Not to scale.)

FIG. 1 Schematic Diagrams of Chevron-Notched Short Rod (a) and Short Bar (b) Specimens

3.2.2 *plane-strain (chevron-notch) fracture toughness, K_{IVM} ($FL^{-3/2}$)*—determined similarly to K_{IV} or K_{Ivj} (see 3.2.1) using the same specimen, or specimen geometries, but using a simpler analysis based on the maximum test force. The analysis is described in Annex A1. Unloading-reloading cycles as described in 3.2.6 are not required in a test to determine K_{IVM} .

3.2.3 *smooth crack growth behavior*—generally, that type of crack extension behavior in chevron-notch specimens that is characterized primarily by slow, continuously advancing crack growth, and a relatively smooth force displacement record (Fig. 4). However, any test behavior not satisfying the conditions for crack jump behavior is automatically characterized as smooth crack growth behavior.

3.2.4 *crack jump behavior*—in tests of chevron-notch specimens, that type of sporadic crack growth which is characterized primarily by periods during which the crack front is nearly stationary until a critical force is reached, whereupon the crack becomes unstable and suddenly advances at high speed to the next arrest point, where it remains nearly stationary until the force again reaches a critical value, etc. (see Fig. 5).

3.2.4.1 *Discussion*—A chevron-notch specimen is said to have a crack jump behavior when crack jumps account for more than one half of the change in unloading slope ratio (see 3.2.6) as the unloading slope ratio passes through the range from $0.8r_c$ to $1.2r_c$ (see 3.2.6 and 3.2.7, and 8.3.5.2). Only those sudden crack advances that result in more than a 5 % decrease in force during the advance are counted as crack jumps (Fig. 5).

3.2.5 *steady-state crack*—a crack that has advanced slowly until the crack-tip plastic zone size and crack-tip sharpness no longer change with further crack extension. Although crack-tip conditions can be a function of crack velocity, the steady-state crack-tip conditions for metals have appeared to be independent of the crack velocity within the range attained by the loading rates specified in this test method.

3.2.6 *effective unloading slope ratio, r* —the ratio of an effective unloading slope to that of the initial elastic loading slope on a test record of force versus specimen mouth opening displacement.

3.2.6.1 *Discussion*—This unloading slope ratio provides a method of determining the crack length at various points on the

test record and therefore allows evaluation of stress intensity coefficient Y^* (see 3.2.11). The effective unloading slope ratio is measured by performing unloading-reloading cycles during the test as indicated schematically in Fig. 4 and Fig. 5. For each unloading-reloading trace, the effective unloading slope ratio, r , is defined in terms of the tangents of two angles:

$$r = \tan \theta / \tan \theta_o$$

where:

$\tan \theta_o$ = the slope of the initial elastic line, and

$\tan \theta$ = the slope of an effective unloading line.

The effective unloading line is defined as having an origin at the high point where the displacement reverses direction on unloading (slot mouth begins to close) and joining the low point on the reloading line where the force is one half that at the high point.

3.2.6.2 *Discussion*—For a brittle material with linear elastic behavior the unloading-reloading lines of an unloading-reloading cycle would be linear and coincident. For many engineering materials, deviations from linear elastic behavior and hysteresis are commonly observed to a varying degree. These effects require an unambiguous method of obtaining an effective unloading slope from the test record (1-4).³

3.2.6.3 *Discussion*—Although r is measured only at those crack positions where unloading-reloading cycles are performed, r is nevertheless defined at all points during a chevron-notch specimen test. For any particular point it is the value that would be measured for r if an unloading-reloading cycle were performed at that point.

3.2.7 *critical slope ratio, r_c* —the unloading slope ratio at the critical crack length.

3.2.8 *critical crack length*—the crack length in a chevron-notch specimen at which the specimen's stress-intensity factor coefficient, Y^* (see 3.2.11 and Table 3), is a minimum, or equivalently, the crack length at which the maximum force would occur in a purely linear elastic fracture mechanics test. At the critical crack length, the width of the crack front is approximately one third the dimension B (Figs. 2 and 3).

3.2.9 *high point, High*—the point on a force-displacement plot, at the start of an unloading-reloading cycle, at which the displacement reverses direction, that is, the point at which the specimen mouth begins closing due to unloading (see points labeled High in Figs. 4 and 5).


3.2.10 *low point, Low*—the point on the reloading portion of an unloading-reloading cycle where the force is one half the high point force (see points labeled Low in Figs. 4 and 5).

3.2.11 *stress-intensity factor coefficient, Y^** —a dimensionless parameter that relates the applied force and specimen geometry to the resulting crack-tip stress-intensity factor in a chevron-notch specimen test (see 9.6.3).

3.2.11.1 *Discussion*—Values of Y^* can be found from the graphs in Fig. 10, or from the tabulations in Table 4 or from the polynomial expressions in Table 5.


3.2.12 *minimum stress-intensity factor coefficient, Y^*_{m}* —the minimum value of Y^* (Table 3).

³ The boldface numbers in parentheses refer to the list of references at the end of this standard.

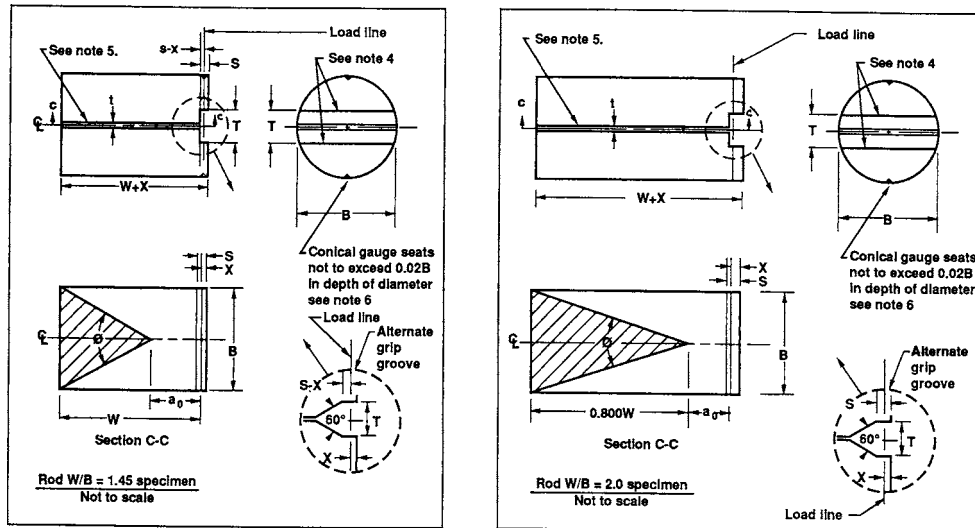

NOTE 1—See Table 1 for tolerances and other details.

FIG. 2 Rod Specimens Standard Proportions

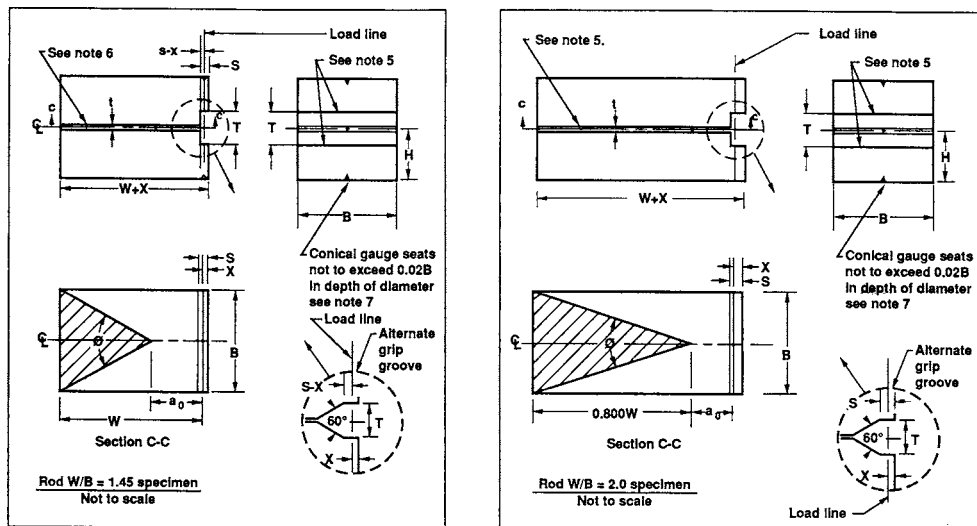

NOTE 1—See Table 2 for tolerances and other details.

FIG. 3 Bar Specimens Standard Proportions

4. Summary of Test Method

4.1 This test method involves the application of a load to the mouth of a chevron-notched specimen to induce an opening displacement of the specimen mouth. An autographic record is made of the load versus mouth opening displacement and the slopes of periodic unloading-reloading cycles are used to calculate the crack length based on compliance techniques. These crack lengths are expressed indirectly as slope ratios. The characteristics of the force versus mouth opening displacement trace depend on the geometry of the specimen, the specimen plasticity during the test, any residual stresses in the specimen, and the crack growth characteristics of the material being tested. In general, two types of force versus displacement traces are recognized, namely, smooth behavior (see 3.2.3) and crack jump behavior (see 3.2.4).

4.1.1 In metals that exhibit smooth crack behavior (3.2.3), the crack initiates at a low force at the tip of a sufficiently sharp chevron, and each incremental increase in its length corresponds to an increase in crack front width and requires further increase in force. This force increase continues until a point is reached where further increases in force provide energy in excess of that required to advance the crack. This maximum force point corresponds to a width of crack front approximately one third the specimen diameter or thickness. If the loading system is sufficiently stiff, the crack can be made to continue its smooth crack growth under decreasing force. Two unloading-reloading cycles are performed to determine the location of the crack, the force used to calculate K_{Iv} , and to provide validity checks on the test. The fracture toughness is calculated from the force required to advance the crack.

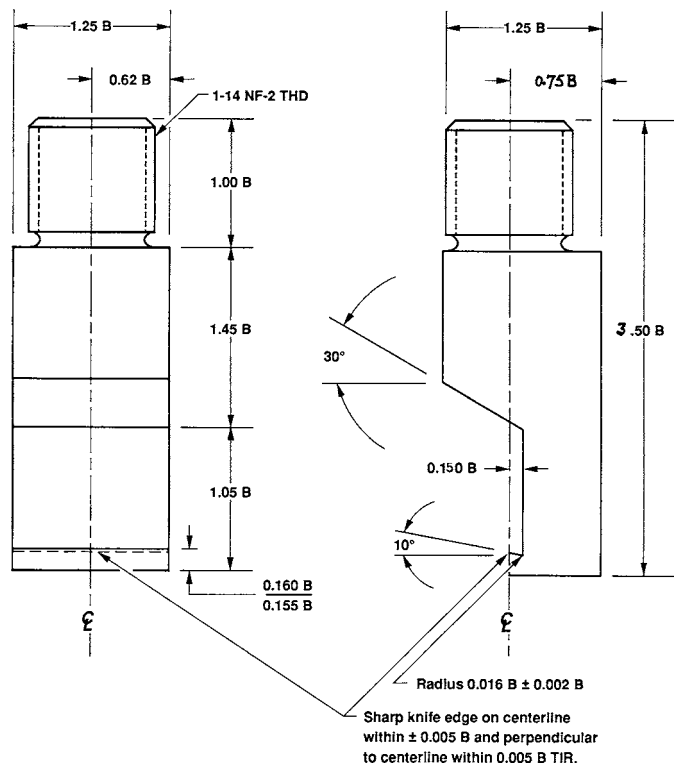


Figure 1 is a graph showing Force, P (Y-axis) versus Mouth Opening Displacement (X-axis). The graph illustrates the relationship between force and displacement during a bite test. A jagged line represents the force profile. Several dashed lines with different slope ratios (r_1, r_2, r_3) and angles ($\theta_0, \theta_1, \theta_2, \theta_3$) are shown. A 'Valid data range' is indicated between r_1 and r_3 . Points $P_1, P_2,$ and P_3 are marked on the force profile. A 'High' force level is indicated, and a 'Low' force level is indicated. An arrow points to the 'Unload to 3% to 10% of High force' region.

critical crack length (see 3.2.8). The plane-strain fracture toughness determined by this procedure is termed K_{Iv} . An alternative procedure, described in Annex A1, omits the unloading cycles and uses the maximum test force to calculate a plane-strain fracture toughness K_{IvM} , where M signifies the use of the maximum force. Values of K_{Iv} versus K_{IvM} are discussed in Annex A1.

$R \leq 0.010B$
 $\phi_s \leq 60^\circ$
 $t \leq 0.03B$

FIG. 6 Slot Bottom Configuration



NOTE 3—Grip hardness should be RC = 45 or greater.

crack front is in a defined region near the center of the specimen. The K_{Ivj} values so determined have the same significance as K_{Iv} .

4.2 The specimen size required for testing purposes increases as the square of the ratio of fracture toughness to yield