



Designation: E2141 – 06

Standard Test Methods for Assessing the Durability of Absorptive Electrochromic Coatings on Sealed Insulating Glass Units¹

This standard is issued under the fixed designation E2141; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 These test methods cover the accelerated aging and monitoring of the time-dependent performance of electrochromic windows. Cross sections of typical electrochromic windows are shown² in which devices have four or five-layers of coatings that include the two or three active layers sandwiched between transparent conducting electrodes (TCEs, see Section 3).

1.2 The test methods are applicable only for multilayered (two or more coatings between the TCEs) absorptive electrochromic coatings on sealed insulating glass (IG) units fabricated for vision glass (superstrate and substrate) areas for use in buildings, such as sliding doors, windows, skylights, and exterior wall systems. The multilayers used for electrochromically changing the optical properties may be inorganic or organic materials between the superstrate and substrate.

1.3 The electrochromic coatings used in this test method are exposed to solar radiation and are deployed to control the amount of radiation by absorption and reflection and thus, limit the solar heat gain and amount of solar radiation that is transmitted into the building.

1.4 The test methods are not applicable to other chromogenic devices, such as, photochromic and thermochromic devices.

1.5 The test methods are not applicable to electrochromic devices consisting of three layers of coatings including the two transparent conducting electrodes (see Section 3).

1.6 The test methods are not applicable to electrochromic windows that are constructed from superstrate or substrate materials other than glass.

1.7 The test methods referenced herein are laboratory tests conducted under specified conditions. These tests are intended

to simulate and, in some cases, to also accelerate actual in-service use of the electrochromic windows. Results from these tests cannot be used to predict the performance with time of in-service units unless actual corresponding in-service tests have been conducted and appropriate analyses have been conducted to show how performance can be predicted from the accelerated aging tests.

1.8 The values stated in SI units are to be regarded as the standard.

1.9 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*³

C168 Terminology Relating to Thermal Insulation

C1199 Test Method for Measuring the Steady-State Thermal Transmittance of Fenestration Systems Using Hot Box Methods

E122 Practice for Calculating Sample Size to Estimate, With Specified Precision, the Average for a Characteristic of a Lot or Process

E632 Practice for Developing Accelerated Tests to Aid Prediction of the Service Life of Building Components and Materials

E892 Tables for Terrestrial Solar Spectral Irradiance at Air Mass 1.5 for a 37° Tilted Surface

E903 Test Method for Solar Absorptance, Reflectance, and Transmittance of Materials Using Integrating Spheres (Withdrawn 2005)⁴

E1423 Practice for Determining Steady State Thermal Transmittance of Fenestration Systems

G113 Terminology Relating to Natural and Artificial Weathering Tests of Nonmetallic Materials

¹ This test method is under the jurisdiction of ASTM Committee E06 on Performance of Buildings and is the direct responsibility of Subcommittee E06.22 on Durability Performance of Building Constructions.

Current edition approved May 15, 2006. Published May 2006. Originally approved in 2001. Last previous edition approved in 2002 as E2141 – 02 DOI: 10.1520/E2141-06.

² A. W. Czanderna and C. M. Lampert, "Evaluation Criteria and Test Methods for Electrochromic Windows," SERI/PR-255-3537 (July 1990), Golden, CO: Solar Energy Research Institute.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

⁴ The last approved version of this historical standard is referenced on www.astm.org.

2.2 Canadian Standards: CAN/CGSB 12.8 Insulating Glass Units⁵

3. Terminology

3.1 *Definitions*—Refer to Terminology in C168, E632, and G113 for descriptions of general terms.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *accelerated aging test*—an aging test in which the rate of degradation of building components or materials is intentionally accelerated from that expected in actual service.

3.2.2 *bleached state*—a descriptor for an ECW when no ions reside in the electrochromic layer or after ions have been removed (or inserted, depending on the type of material) from the electrochromic layer(s) and if applicable, the maximum number of ions have been returned to the counterelectrode layer to restore the τ_b from that of the photopic optical specular transmittance in the colored state (τ_c).

3.2.3 *colored state*—a descriptor for an ECW after ions have been inserted (or removed, depending on the type of material) into the electrochromic layer and, if applicable, removed from the counterelectrode layer to reduce the photopic optical specular transmittance (of wavelengths from 400 nm to 730 nm) from that in the bleached state (τ_b).

3.2.4 *durability*—the capability of maintaining the serviceability of a product, component, assembly or construction over a specified time.

3.2.5 *electrochromic coating*—the multilayered materials that include the electrochromic layers, other layers, and transparent conducting oxide layers required for altering the optical properties of the coating.

3.2.6 *electrochromic layer(s)*—the material(s) in an ECW that alter its optical properties in response to the insertion or removal of ions, that is, Li^+ or H^+ .

3.2.7 *electrochromic window (ECW)*—a window consisting of several layers of electrochromic and attendant materials, which are able to alter their optical properties in response to a change in an applied electric field. The changeable optical properties include transmittance, reflectance, and absorptance.

3.2.8 *ion conducting layer*—the material in an ECW through which ions are transported between the electrochromic layer and the ion storage layer and electron transport is minimized.

3.2.9 *ion storage layer or counter electrode layer*—the material in an ECW that serves as a reservoir for ions that can be inserted into the electrochromic layer.

3.2.10 *performance parameters*—the photopic transmittance ratio (PTR), of at least 5:1 ($\text{PTR} = \tau_b/\tau_c$) between the bleached (that is, τ_b of 60 % to 70 %) and colored (that is, τ_c of 12 % to 14 %) states; coloring and bleaching times of a few minutes; switching with applied voltages from ~1-3 V; and open-circuit memory of a few hours, that is, contemporary ECWs typically have open circuit memories of 6 to 24 h.

3.2.11 *serviceability*—the capability of a building product, component, assembly or construction to perform the function(s) for which it was designed and constructed.

3.2.12 *service life (of a building component or material)*—the period of time after installation during which all properties exceed minimum acceptable values when routinely maintained.

4. Significance and Use

4.1 The test methods are intended to provide a means for evaluating the durability of ECWs as described in 1.2.^{1,2,6} (See Appendix X1).

5. Background

5.1 Observations and measurements have shown that some of the performance parameters of ECWs have a tendency to deteriorate over time. In selecting the materials, device design, and glazing for any application, the ability of the glazing to perform over time is an indication of that glazing's durability. The ability of the product to perform over time, at or better than specified requirements, is an indication of the service life of the glazings. While these two indicators are related, the purpose of this standard test method is to assess the durability of ECWs.

5.2 ECWs perform a number of important functions in a building envelope including: minimizing the solar energy heat gain; providing for passive solar energy gain; controlling a variable visual connection with the outside world; enhancing human comfort (heat gain), security, ventilation, illumination, and glare control; providing for architectural expression, and (possibly) improving acoustical performance. Some of these functions may deteriorate in performance over time. Solar heat gain through an ECW is decreased because of two principal processes. Energy from the visible part of the spectrum is absorbed by an ECW in the colored state. In addition, infrared radiation is either absorbed by the ECW materials or is reflected by the transparent conducting oxide layers that are used for applying the coloring or bleaching potentials across the other layers in the ECW.

5.3 It is possible, but difficult to predict the time-dependent performance of ECWs from accelerated aging tests because of the reasons listed below. Users of this document should be aware of these limitations when reviewing published performance results and their connection to durability.

5.3.1 The degradation mechanisms of ECW materials or glazings, or both, are complex. In some cases, however, these mechanisms may be determined and quantified.

5.3.2 The external factors that affect the performance of ECWs are numerous and may be difficult to quantify. However, in some cases, the use, the environmental factors, and other information that influence performance may be known.

⁵ Available from Canadian General Standards Board (CGSB), Place du Portage III, 6B1 11 Laurier Street Gatineau, Quebec, Canada.

⁶ A. W. Czanderna, D. K. Benson, G. J. Jorgensen, J.-G. Zhang, C. E. Tracy, and S. K. Deb, "Durability Issues and Service Lifetime Prediction of Electrochromic Windows for Buildings Applications," NREL/TP-510-22702, May 1997, National Renewable Energy Laboratory, Golden, CO; Solar Energy Materials and Solar Cells, 56 (1999) pp. 419-436.

5.3.3 Fenestration units with tested ECWs may be different from those planned for use in service. Some companies have a database of in-service performance that can be compared to laboratory results.

5.4 Degradation factors (or stresses) for ECWs include the ion insertion and removal processes; temperature; solar radiation (especially UV); water vapor; atmospheric gases and pollutants; thermal stresses such as shock from sudden rain, as well as during the diurnal and annual temperature cycles; electrochemically induced stresses in the multilayer thin-film device; hail, dust, and wind; condensation and evaporation of water; and thermal expansion mismatches^{2,6}. These factors may singularly or collectively limit the stability and durability of ECWs. Because the ECWs are expected to have the multilayer of coatings on one of the surfaces in the air space of double-pane or triple-pane IG units with an inert gas fill in the sealed space, many factors such as high humidity, atmospheric gases and pollutants, condensation and evaporation of water, and dust should not affect the durability of electrochromic coatings in IG units².

5.4.1 Establishing test procedures from which ECW durability can be predicted and validated for in-service use is an extremely crucial element for the commercialization of ECWs, even for niche markets. To reduce the number of accelerated test parameters that are required to predict the long-term performance of ECWs, accepted procedures or methods have not been established for testing ECWs.² Because no uniformly accepted procedures or methods have been established for the real-time testing of ECWs and because manufacturers and

users cannot wait 20 or more years for the real-time evaluation of each window design, accelerated life testing (ALT) methods and procedures must be used for evaluating ECW stability^{2,6}. These include (a) rapid but realistic current-voltage (I-V) cyclic tests emphasizing the electrical properties, (b) ALT parameters that are typically used in durability tests by standards organizations, (c) ALT parameters that are realistic for the intended use of large-area ECWs, and (d) how the ALT results must be related to real-time testing². The purpose of this test method is to assess the durability of ECWs (at least $250 \pm 6 \text{ mm} \times 250 \pm 6 \text{ mm}$ ($10 \pm 1/4 \text{ in.} \times 10 \pm 1/4 \text{ in.}$)).

NOTE 1—Caution—The seals in IGUs may fail at lower temperatures than those planned for testing, that is, 70 to 105°C. A seal failure will virtually guarantee failure of the ECW coating, so no assessment of the ECW coating will be made if a seal fails during a test.

NOTE 2—the test method may also be used for smaller ECWs to assess the durability of prototype devices. The testing parameters chosen only provide modest acceleration factors. However, the quantitative parameters discussed in (a)–(c) above are presented and include a detailed description of the procedures for using an accelerated weathering unit (AWU) (See Practice E122).

6. Apparatus (See Figs. 1 and 2 and Section 8.3 for Descriptive Detail)

6.1 *Accelerated Weathering Unit (AWU)* consisting of properly filtered xenon-arc lamps to simulate over the applicable degradative wavelength region (UV plus visible) at least one-sun of solar irradiance at AM 1.5 (global) at sea level (E892), a controlled temperature chamber, and humidity control in the chamber.


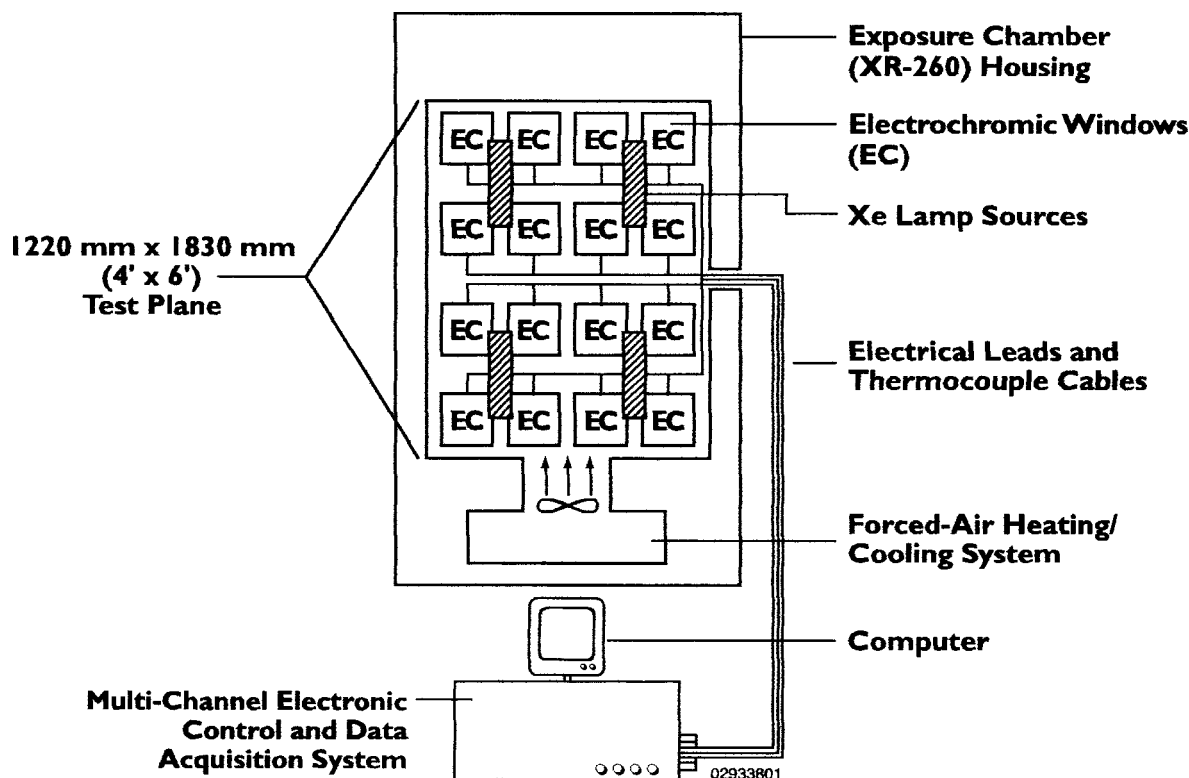


FIG. 1 Top-View Schematic Diagram of the Essential Components of an Environmental Test Chamber and Computer-Controlled Electrical Cycling and Data Acquisition System for Accelerated Weathering of Electrochromic Window Devices

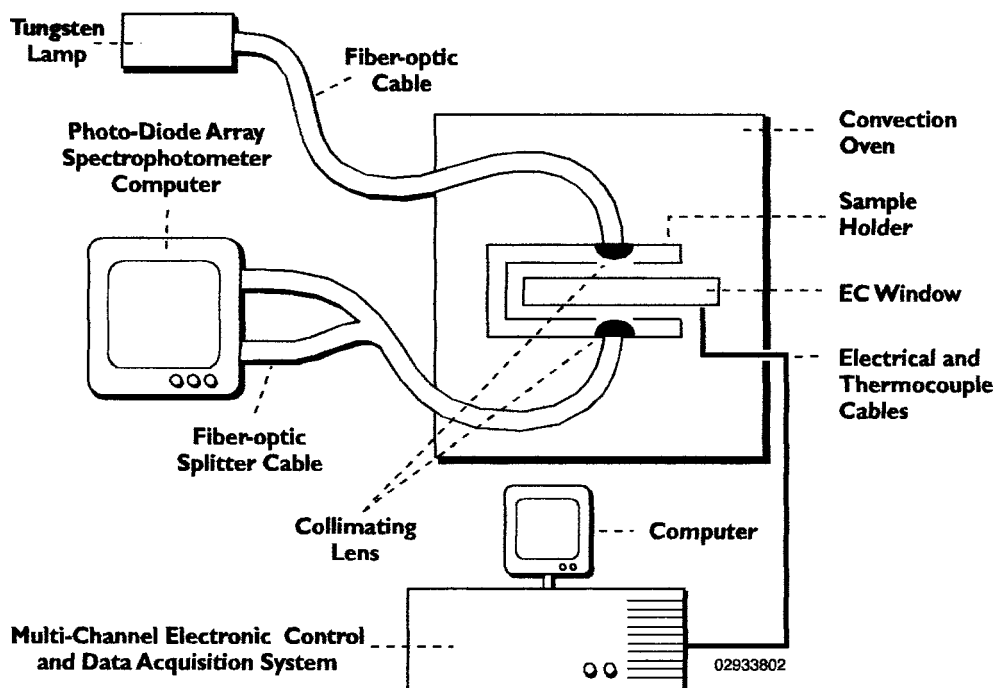

Note: The measurements are used to determine the photopic transmittance ratio and record electro-optic degradation data after cyclic testing in the accelerated weathering unit.

FIG. 2 Schematic of the (Essential) Elements of the Electro-Optic Measurement System Used for Recording 300–1100 Nm Transmittance Spectra for a Color/Bleach Cycle of EC Window Devices at Controlled Temperatures

6.2 *Voltage Cycling Unit* for imposing voltage cycles to alternately and repeatedly color and bleach the ECWs from a fully bleached state to the colored state and back to the bleached state.

6.3 *Computer Controlled Photodiode Array Spectrophotometer* that is, for obtaining and storing data from the electro-optical characterization of the optical transmittance in the colored and bleached state and measuring the rate of coloring and bleaching.

6.4 *Oven* that is large enough for the largest ECW to be tested and that can reach the ECW testing temperature. The oven must also be designed to permit using the equipment in 6.3 for optical measurements while the ECW is maintained at the temperature chosen for testing in the AWU described in 6.1.

6.5 *Tungsten Lamp*. A spectrum from the source must be compatible with the fiber optic illumination of the photodiode array spectrophotometer described in 6.3.

6.6 *Digital Camera*.

6.7 *Video Camera and Recorder*.

6.8 *Calibrated Thermocouples*.

6.9 *Electrical Leads* from the Unit in 6.2 to each ECW in the AWU described in 6.1.

7. Test Specimens

7.1 Test specimen size, design, and construction shall be established and specified by the user of this standard, except the specimens shall be at least $250 \pm 6 \text{ mm} \times 250 \pm 6 \text{ mm}$ ($10 \pm 1/4 \text{ in.} \times 10 \pm 1/4 \text{ in.}$).

7.2 Six to 10 test specimens that are represented to be “identical” shall be the minimum number used to assess the durability of a particular design and construction. (See Item 2 in [Appendix X1](#)).

8. Procedure⁷

8.1 *Overview*. Expose the ECWs to simulated solar irradiance in a temperature- and humidity-controlled chamber at selected sample temperatures ranging from 70°C (158°F) to 105°C (221°F) while the ECWs are cyclically colored and bleached with the ability to pause during the duty cycles, depending on the control strategy prescribed by the manufacturer. The “testing” temperature shall be that in the colored state; the average ECW temperature will be less because of a typical decrease of about 5°C (9°F) when the ECW is in the bleached state. Accept the prevailing relative humidity in the chamber (that is, 5 % to 20 %) because the prototype multi-layer coatings will be sealed inside double-pane or triple-pane IG units for in-service use. Measure transmittances in a manner analogous to that described in [E903](#).

8.2 *Electro-optical Characterization of ECWs* is accomplished by using a computer-controlled, multichannel potentiostat and a photodiode array spectrophotometer. The optical transmittance of all ECWs is initially measured at room temperature (ca. 22°C), as shown schematically in [Fig. 2](#). The

⁷ The procedure is based in part on the paper by A. Czanderna, et al., in “Optical Materials Technology for Energy Efficiency and Solar Energy Conversion XV,” C. M. Lampert, C. Granqvist, M. Grätzel, and S. K. Deb, eds., SPIE Vol. 3138, 68 (1997).