



Designation: F 109 – 91 (Reapproved 1996)

AMERICAN SOCIETY FOR TESTING AND MATERIALS
100 Barr Harbor Dr., West Conshohocken, PA 19428
Reprinted from the Annual Book of ASTM Standards. Copyright ASTM

Standard Terminology Relating to Surface Imperfections on Ceramics¹

This standard is issued under the fixed designation F 109; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This terminology describes and illustrates imperfections observed on whitewares and related products. For additional definitions of terms relating to whitewares and related products, refer to Terminology C 242. To observe these defects, examination shall be performed visually, with or without the aid of a dye penetrant, as described in Test Method C 949. Agreement by the manufacturer and the purchaser regarding specific techniques of observation is strongly recommended.

2. Referenced Documents

2.1 ASTM Standards:


C 242 Terminology of Ceramic Whitewares and Related Products²

C 949 Test Method for Porosity in Vitreous Whitewares by Dye Penetration²

E 165 Practice for Liquid Penetrant Inspection Method³

3. Terminology


blemish—strained or discolored area attributable to normal composition or forming, or both. (See also **inclusion**.)

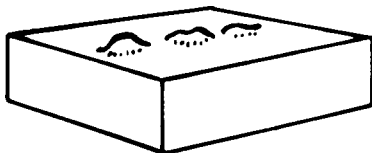


blister—bubble or gaseous inclusion at the surface which if broken could form a pit, pock, or hole.




burr—fragment of excess material or foreign particle adhering to the surface.

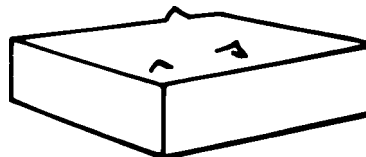

camber—a single arch of curvature. (See also **waviness**.)

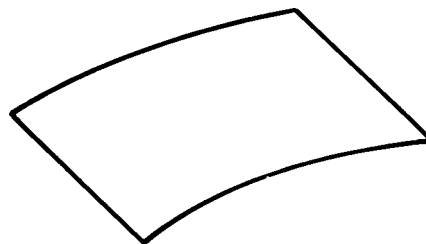

chip—area along an edge or corner where the material has broken off.

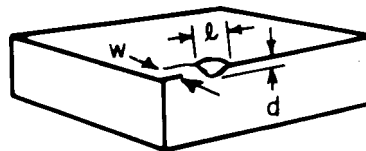


where:

w = width

l = length, and

d = depth.

closed chip—fractured area on the edge or corner when the material has not broken off (Syn. *potential chip*).

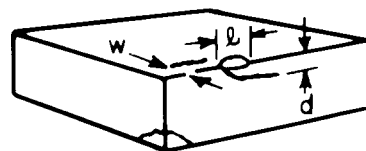

where:

W = width

¹ This terminology is under the jurisdiction of ASTM Committee C-21 on Ceramic Whitewares and Related Products and is the direct responsibility of Subcommittee C21.01 on Nomenclature.


Current edition approved Dec. 15, 1991. Published February 1992. Originally published as F 109 – 69 T. Last previous edition F 109 – 73 (1991) ^{ϵ 1}.

² Annual Book of ASTM Standards, Vol 15.02.


³ Annual Book of ASTM Standards, Vol 03.03.

l = length, and
 d = depth.


crack—line of fracture without complete separation.

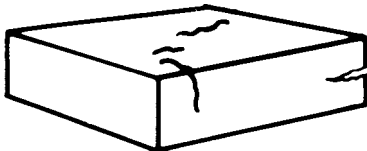


fin—fine feather-edge protrusion from the surface (Syn. *flash*).

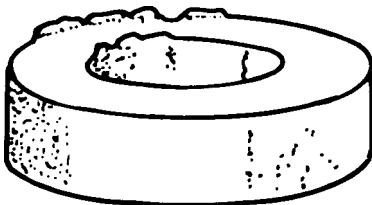

flow line—one or more streaks distinguished by a difference in light reflectance from the surrounding area, characteristic of injection-molded parts. (See also **weld mark**.)

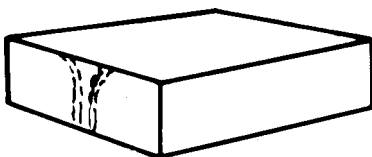

grinding mark—a pattern of fine striations or scoring, usually directional, resulting from machining, as distinct from **surface marks**

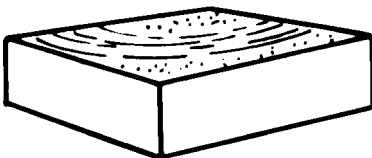


hole—a deep depression or void, the bottom of which is not visible by normal (20/20) vision under 200 fc illumination.



inclusion—embedded foreign material or a stain other than from normal composition or forming, or both (see **blemish**).

kink—a type of waviness occurring interior to the edges, not to be confused with the more abrupt departures as ridges or surface marks. (See also **waviness**.)

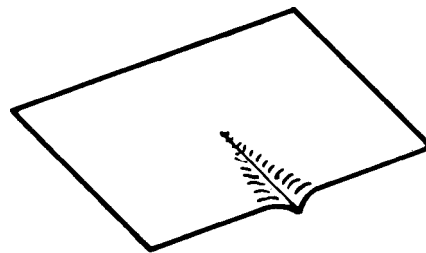


lump—a raised area on the surface having the appearance of being solid.

pit—a shallow depression or crater in which all surfaces are visible by normal (20/20) vision under 200 fc of illumination.




pock—a partially closed surface cavity.

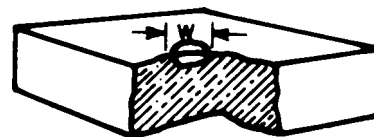


where:

w = width.

pore—an internal cavity which may be exposed by cutting, grinding, or polishing to become a pit, pock, or hole.

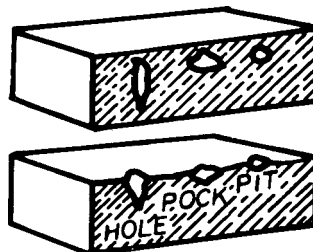

porous area—an area that will retain dye when tested in accordance with Practice E 165 and, if broken through at the porous area, will show evidence of dye penetration into the body.

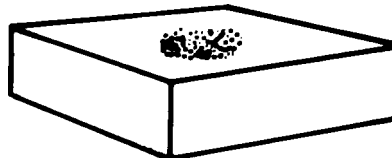

ridge—long, narrow protrusion on any surface.