

ANSI/AWWA **C205-24**
(Revision of ANSI/AWWA C205-18)

AWWA Standard

Cement–Mortar Protective Lining and Coating for Steel Water Pipe—4 In. (100 mm) and Larger—Shop Applied

Effective date: Dec. 1, 2024.

First edition approved by Board of Directors June 26, 1941.

This edition approved June 8, 2024.

Approved by American National Standards Institute June 10, 2024.




AWWA Standard

This document is an American Water Works Association (AWWA) standard. It is not a specification. AWWA standards describe minimum requirements and do not contain all of the engineering and administrative information normally contained in specifications. AWWA standards usually contain options that must be evaluated by the user of the standard. Until each optional feature is specified by the user, the product or service is not fully defined. AWWA publication of a standard does not constitute endorsement of any product or product type, nor does AWWA test, certify, or approve any product. The use of AWWA standards is entirely voluntary. This standard does not supersede or take precedence over or displace any applicable law, regulation, or code of any governmental authority. AWWA standards are intended to represent a consensus of the water industry that the product described will provide satisfactory service. When AWWA revises or withdraws this standard, an official notice of action will be placed in the Official Notice section of *Journal AWWA*. The action becomes effective on the first day of the month following the month of *Journal AWWA* publication of the official notice.

American National Standard

An American National Standard implies a consensus of those substantially concerned with its scope and provisions. An American National Standard is intended as a guide to aid the manufacturer, the consumer, and the general public. The existence of an American National Standard does not in any respect preclude anyone, whether that person has approved the standard or not, from manufacturing, marketing, purchasing, or using products, processes, or procedures not conforming to the standard. American National Standards are subject to periodic review, and users are cautioned to obtain the latest editions. Producers of goods made in conformity with an American National Standard are encouraged to state on their own responsibility in advertising and promotional materials or on tags or labels that the goods are produced in conformity with particular American National Standards.

CAUTION NOTICE: The American National Standards Institute (ANSI) approval date on the front cover of this standard indicates completion of the ANSI approval process. This American National Standard may be revised or withdrawn at any time. ANSI procedures require that action be taken to reaffirm, revise, or withdraw this standard no later than five years from the date of ANSI approval. Purchasers of American National Standards may receive current information on all standards by writing to the American National Standards Institute, 1180 Avenue of the Americas, 10th Floor, New York, NY 10036; calling (212) 642-4900; or e-mailing info@ansi.org.

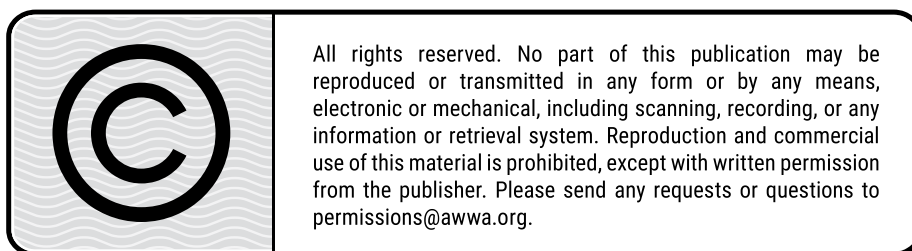

ISBN-13, print: 978-1-64717-207-7

ISBN-13, electronic: 978-1-61300-732-7

DOI: <http://dx.doi.org/10.12999/AWWA.C205.24>

All rights reserved. No part of this publication may be reproduced or transmitted in any form or by any means, electronic or mechanical, including scanning, recording, or any information or retrieval system. Reproduction and commercial use of this material is prohibited, except with written permission from the publisher.

Copyright © 2024 by American Water Works Association
Printed in USA

Committee Personnel

The Steel Water Pipe Manufacturers Technical Advisory Committee (SWPMTAC) Task Group on ANSI/AWWA C205, which revised this standard, had the following personnel at the time:

Henry H. Bardakjian, *Chair*
D.W. Dunker, *Vice-Chair*

H.H. Bardakjian, Consultant, Glendale, Calif.
R.J. Card, Manufacturing Consultant, Sugar Hill, Ga.
D.A. Dechant, Dechant Infrastructure Service, Aurora, Colo.
D.W. Dunker, Thompson Pipe Group, Rialto, Calif.
J. Forni, Jifco, Inc., Livermore, Calif.
B.D. Keil, Northwest Pipe Company, Salt Lake City, Utah
J.L. Luka, American SpiralWeld Pipe Company, Columbia, S.C.
L. McKinney, Womble Company, Houston, Tex.
R.D. Mielke, Northwest Pipe Company, Raleigh, N.C.
B. Simpson, American SpiralWeld Pipe Company, Birmingham, Ala.
C.J. Walsh, W. Walsh Company, Attleboro, Mass.

The AWWA Standards Committee on Steel Pipe, which reviewed and approved this standard, had the following personnel at the time of approval:

John H. Bambei, Jr., *Chair*
Robert J. Card, *Vice-Chair*
John L. Luka, *Secretary*

General Interest Members

S.A. Arnaout (*alternate*), Stantec, Plano, Tex.
J.H. Bambei, Jr., Bambei Engineering Services, Arvada, Colo.
R.J. Card, Lockwood, Andrews & Newnam, Inc., Suwanee, Ga.
R.L. Gibson, Freese and Nichols, Inc., Fort Worth, Tex.
M.D. Gossett, HDR, Inc., Denver, Colo.
M.B. Horsley (*alternate*), Horsley Engineering LLC, Overland Park, Kans.
R. Issa, AECOM, McKinney, Tex.
C.H. Kirby (*alternate*), Lockwood Andrews & Newnam, Inc., Houston, Tex.

R.A. Kufaas, Norske Corrosion & Inspection Services, Ltd., Abbotsford, B.C.
A.S. Maughn (*alternate*), Freese & Nichols, Inc., Dallas, Tex.
D.L. McPherson (*alternate*), HDR, Inc., Charlotte, N.C.
A. Murdock, Jacobs, Holladay, Utah
R. Ortega, Aurora Technical Services, Houston, Tex.
E.S. Ralph (*liaison, nonvoting*), Standards Engineer Liaison, AWWA, Denver, Colo.
A.E. Romer (*alternate*), AECOM, Huntington Beach, Calif.
J.R. Snow, Stantec, Colorado Springs, Colo.
A.M. Stanton, Black & Veatch, Pasadena, Calif.
W.R. Whidden, Woolpert, Orlando, Fla.

Producer Members

H.R. Bardakjian, Consultant, Glendale, Calif.
D.A. Dechant, Dechant Infrastructure Service, Aurora, Colo.
D.W. Dunker, Thompson Pipe Group, Rialto, Calif.
B.D. Keil, Northwest Pipe Company, Salt Lake City, Utah
J.L. Luka, American SpiralWeld Pipe Company, Columbia, S.C.
R. Mielke (*alternate*), Northwest Pipe Company, Raleigh, N.C.
L. Prinsloo, Victaulic, Easton, Pa.
B.E. Ripley (*alternate*), Victaulic, Lexington, S.C.
G.F. Ruchti (*alternate*), LAN, Inc., Punta Gorda, Fla.
B.P. Simpson (*alternate*), American Cast Iron Pipe Company, Birmingham, Ala.
R. Wu (*alternate*), Thompson Pipe Group, Grand Prairie, Tex.

User Members

L. Adams, US Bureau of Reclamation, Denver, Colo.
G.A. Andersen, New York City Bureau of Water Supply, Little Neck, N.Y.
B. Cheng, Metro Vancouver, Burnaby, B.C.
B. Fountain, San Diego County Water Authority, San Diego, Calif.
J. Fox, Tampa Bay Water, Clearwater, Fla.
J. Garcia (*alternate*), Metropolitan Water District of Southern California, La Verne, Calif.
S. Hattan, Tarrant Regional Water District, Fort Worth, Tex.
M. Lobik, Springfield Water and Sewer Commission, Agawam, Mass.
T. Peng, Metropolitan Water District of Southern California, Los Angeles, Calif.

G. Ramon (*liaison, nonvoting*), Standards Council Liaison, Little Rock Water Reclamation Authority, Little Rock, Ark.

V. Scutelnicu, Los Angeles Water & Power, Los Angeles, Calif.

J. Shieh (*alternate*), Los Angeles Water & Power, Los Angeles, Calif.

M. Turney (*alternate*) Denver Water, Denver, Colo.

This page intentionally blank.

Contents

All AWWA standards follow the general format indicated subsequently. Some variations from this format may be found in a particular standard.

SEC.	PAGE	SEC.	PAGE
<i>Foreword</i>		3	Definitions 4
I Introduction.....	ix	4	Requirements
I.A Background.....	ix	4.1	General 5
I.B History.....	ix	4.2	Material..... 6
I.C Acceptance	x	4.3	Surface Preparation..... 7
II Special Issues	xi	4.4	Cement–Mortar Lining..... 8
II.A Soft, Aggressive Waters	xi	4.5	Cement–Mortar Coating..... 12
II.B Intermittent Operations	xi	4.6	Cement–Mortar Overcoat..... 16
II.C Flow Velocity.....	xi	4.7	Field Joints 19
II.D Strain Limitations.....	xi	5	Verification
II.E Weld-After-Backfill	xi	5.1	Sampling and Testing Cement Mortar for Linings 20
II.F Cement–Mortar-Lining Thickness	xii	5.2	Testing Cement Mortar for Coatings..... 21
III Use of This Standard	xii	5.3	Calibration of the Manufacturer’s Equipment..... 22
III.A Purchaser Options and Alternatives	xii	5.4	Inspection and Testing by Purchaser..... 22
III.B Modification to Standard	xiii	5.5	Basis for Rejection 23
IV Major Revisions.....	xiii	6	Delivery
V Comments	xiv	6.1	General 23
<i>Standard</i>		6.2	Plastic End Covers..... 23
1 General		6.3	Affidavit of Compliance 23
1.1 Scope.....	1	<i>Table</i>	
1.2 Purpose	2	1	Cement–Mortar-Lining Thickness..... 8
1.3 Application.....	2		
2 References	2		

This page intentionally blank.

Foreword

This foreword is for information only and is not a part of ANSI/AWWA C205.*

I. Introduction.

I.A. *Background.* Cement–mortar-lined-and-coated steel pipe was first used in the United States in the late 1800s. Some of the first pipelines were in service for almost a century by the time the first national standard was written. However, it was not until the 1920s that a practical method of plant-applied cement–mortar lining was developed. The first plant-applied linings were installed by standing the pipe on end, placing a tapered plug with a rope attached to the leading end inside the pipe, placing enough cement mortar on top of the plug to coat the pipe, and then pulling the plug up through the pipe. Improvements in the lining process were developed, and the centrifugal process for plant-applied cement–mortar lining emerged.

Cement–mortar-lined and cement–mortar-coated steel pipe combines the physical strength of steel with the protective qualities of cement mortar. The lining, applied centrifugally, creates a smooth, dense finish that protects the pipe from tuberculation and provides corrosion protection with an alkaline cement environment that passivates the steel. The smooth interior surface provides a high flow coefficient for the design life of the pipeline under normal operating conditions. In addition, the cement–mortar coating results in a tough, durable, and rugged coating that forms an alkaline environment where oxidation or corrosion of the steel is inhibited.

I.B. *History.* The first edition of this standard—designated 7A.7-41, Standard Specifications for Cement–Mortar Protective Coating for Steel Water Pipe of Sizes 30 Inches and Over—was approved by the AWWA Board of Directors on June 26, 1941. Before that, a tentative draft had been published in the January 1940 *Journal—American Water Works Association* for review and comment.

The first edition provided a section for the field application of cement–mortar lining, which was deleted by action of the Board of Directors effective June 30, 1951. Pending the promulgation of AWWA C602, Cement–Mortar Lining of Water Pipelines—4 In. (100 mm) and Larger—in Place, the ninth, tenth, and eleventh printing of 7A.7 (AWWA C205) continued to carry the withdrawn section.

The next edition, published in 1962, was a major revision and provided for pipe sizes of 4 in. (100 mm) and larger. The standard was subsequently revised in 1971,

* American National Standards Institute, 1180 Avenue of the Americas, 10th Floor, New York, NY 10036.

1980, 1985, 1989, 1995, 2000, 2007, 2012, and 2018. This edition was approved on June 8, 2024.

I.C. *Acceptance.* In May 1985, the US Environmental Protection Agency (USEPA) entered into a cooperative agreement with a consortium led by NSF International (NSF) to develop voluntary third-party consensus standards and a certification program for direct and indirect drinking water additives. Other members of the original consortium included the Water Research Foundation (formerly AwwaRF) and the Conference of State Health and Environmental Managers (COSHEM). AWWA and the Association of State Drinking Water Administrators (ASDWA) joined later.

In the United States, authority to regulate products for use in or in contact with drinking water rests with individual states.[†] Local agencies may choose to impose requirements more stringent than those required by the state. To evaluate the health effects of products and drinking water additives from such products, state and local agencies may use various references, including

1. Specific policies of the state or local agency.
2. Four standards developed under the direction of NSF[‡]: NSF/ANSI/CAN[§] 60, Drinking Water Treatment Chemicals—Health Effects; NSF/ANSI/CAN 61, Drinking Water System Components—Health Effects; NSF/ANSI/CAN 372, Drinking Water System Components—Lead Content; and NSF/ANSI/CAN 600, Health Effects Evaluation and Criteria for Chemicals in Drinking Water.
3. Other references, including AWWA standards, *Food Chemicals Codex*, *Water Chemicals Codex*,[¶] and other standards considered appropriate by the state or local agency.

Various certification organizations may be involved in certifying products in accordance with NSF/ANSI/CAN 61. Individual states or local agencies have authority to accept or accredit certification organizations within their jurisdictions. Accreditation of certification organizations may vary from jurisdiction to jurisdiction.

NSF/ANSI/CAN 600 (which formerly appeared in NSF/ANSI/CAN 60 and 61 as Annex A, “Toxicology Review and Evaluation Procedures”) does not stipulate a maximum allowable level (MAL) of a contaminant for substances not regulated by a USEPA final maximum contaminant level (MCL). The MALs of an unspecified list of

[†] Persons outside the United States should contact the appropriate authority having jurisdiction.

[‡] NSF International, 789 North Dixboro Road, Ann Arbor, MI 48105.

[§] Standards Council of Canada, 55 Metcalfe Street, Suite 600, Ottawa, ON K1P 6L5 Canada.

[¶] Both publications available from National Academy of Sciences, 500 Fifth Street, NW, Washington, DC 20001.

“unregulated contaminants” are based on toxicity testing guidelines (noncarcinogens) and risk characterization methodology (carcinogens). Use of NSF/ANSI/CAN 600 procedures may not always be identical, depending on the certifier.

ANSI/AWWA C205 does not address additives requirements. Thus, users of this standard should consult the appropriate state or local agency having jurisdiction in order to

1. Determine additives requirements, including applicable standards.
2. Determine the status of certifications by parties offering to certify products for contact with or treatment of drinking water.
3. Determine current information on product certification.

II. Special Issues. The purchaser of cement–mortar linings or coatings is cautioned about the following concerns:

II.A. *Soft, Aggressive Waters.* Soft, aggressive waters, as well as prolonged contact with heavily chlorinated water, may be injurious to cement–mortar linings. When this environment is anticipated, further studies may be necessary to determine the suitability of this type of lining.

II.B. *Intermittent Operations.* Cement–mortar linings are best suited for pipelines that are continuously filled with water. When cement–mortar-lined pipelines are operated under prolonged empty conditions, special precautions may have to be taken to prevent excessive drying out of the cement–mortar lining.

II.C. *Flow Velocity.* Cement–mortar linings perform best when flow velocities are in normal ranges. When the flow velocity exceeds approximately 20 ft/s (6.1 m/s), special studies may be required to determine the suitability of this type of lining material.

II.D. *Strain Limitations.* Consideration should be given to limiting the maximum strains (or stresses) developed in the steel cylinder of cement–mortar-lined or cement–mortar-coated steel water pipe from internal pressure to ensure the long-term design life of the system.

II.E. *Weld-After-Backfill.* Weld-after-backfill is the sequence of assembling a lap-welded joint, welding the outside (if required), applying the exterior coating, backfilling the pipe, and then welding the inside joint at a later time (where inside welding is safe and practical). Welding inside field joints after backfill may damage or compromise the performance of shop-applied and field-applied dielectric coatings. Prior to specifying or approving weld-after-backfill, consult with the manufacturers regarding recommended products, installation, and backfill procedures required for the weld-after-backfill sequence. At the request of the purchaser, the manufacturer shall

provide testing or historical information to verify that the exterior coating complies with this standard after completion of welding.

II.F. *Cement–Mortar-Lining Thickness.* Properly applied cement mortar will inherently have some variations of thickness. The mortar-lining thickness may be slightly less than the minimum or slightly more than the maximum at localized areas provided the average thickness is not outside of the thickness tolerances given in Table 1 of the standard.

III. Use of This Standard. It is the responsibility of the user of an AWWA standard to determine that the products described in that standard are suitable for use in the particular application being considered.

III.A. *Purchaser Options and Alternatives.* When purchasing protective cement–mortar lining or coating for steel water pipe under the provisions of this standard, the following items (including specific details where applicable) should be specified by the purchaser:

1. Standard used—that is, ANSI/AWWA C205, Cement–Mortar Protective Lining and Coating for Steel Water Pipe—4 In. (100 mm) and Larger—Shop Applied, of latest revision.
2. Whether compliance with NSF/ANSI/CAN 61, Drinking Water System Components—Health Effects, is required.
3. If interior lining only, exterior coating only, or both lining and coating are required.
4. Footage, inside diameter after lining, lengths of pipe sections, steel-wall thickness, type of joint, and information regarding fittings.
5. Details of federal, state, provincial, territorial, and local requirements (Sec. 4.1.3).
6. Whether reinforcing wire should be galvanized (Sec. 4.2.1.1).
7. Type of wire-fabric reinforcement required, if limited to a single type (Sec. 4.2.1.2).
8. Type of cement required (Sec. 4.2.2.1).
9. Lining options or restrictions, if any, such as thickness of lining, thickness tolerances, and length of lining holdback (Sec. 4.4.3).
10. Coating options or restrictions, if any, such as type of undercoat (Sec. 4.5.1), length of coating holdback (Sec. 4.5.3), thickness of mortar coating (Sec. 4.5.3), minimum thickness (Sec. 4.5.3), type of reinforcement (Sec. 4.5.5), and method of curing (Sec. 4.5.9).