
British Standard

Lining of equipment with polymeric materials for the process industries

Part 1. Specification for lining with sheet thermoplastics

Revêtements intérieurs à base de polymères des matériels pour industries de procédés
Partie 1. Revêtements thermoplastiques en feuilles — Spécifications

Auskleidung von betriebstechnischen Anlagen in der verarbeitenden Industrie
Teil 1. Auskleidung mit Platten aus thermoplastischen Kunststoffen

Foreword

This Part of BS 6374 has been prepared under the direction of the Pressure Vessels Standards Committee. It is one of five Parts of a new standard that will supersede Parts 1, 4, 5 and 6 of CP 3003, the change in format arising from the fresh approach adopted to conform with developments in the associated lining technology.

The Technical Committee would like to acknowledge the contributions made by the Rubber and Plastics Research Association of Great Britain which supplied the initial draft document, and the users and the manufacturers on whose submissions the document was based.

The plastics linings referred to in this standard are used for a number of different duties, including protection against corrosive environments, prevention of contamination of products and provision of surfaces that do not foul easily or that can be cleaned easily. Specific linings are used for protection against abrasion or erosion.

The thermoplastic materials considered are those in general use for lining equipment and are as tabulated below. It is common practice to refer to these materials by initials; these are also listed and referred to in the text.

Unplasticized polyvinylchloride	UPVC
Plasticized polyvinylchloride	Plasticized PVC
Polyethylene	PE
Polypropylene	PP
Polyvinylidene fluoride	PVDF
Fluorinated ethylene propylene copolymer	FEP
Perfluoroalkoxy	PFA
Polytetrafluoroethylene	PTFE
Ethylene-chlorotrifluoroethylene copolymer	E-CTFE

It has been assumed in the drafting of this British Standard that the execution of its provisions is entrusted to appropriately qualified and experienced people.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Contents

	Page
Foreword	Inside front cover
Committees responsible	Back cover
Specification	
Section one. General	
1.1 Scope	2
1.2 Definitions	2
1.3 Exchange of information	2
1.4 Compliance	3
Section two. Design, fabrication and surface finish of equipment to be lined	
2.1 General	4
2.2 Design of metal equipment to be lined	4
2.3 Fabrication of metal equipment to be lined	4
2.4 Design of concrete equipment to be lined	9
2.5 Construction of concrete equipment to be lined	9
Section three. Selection and quality of linings	
3.1 Selection of lining	10
3.2 Quality of lining	10
3.3 Continuity of finished linings	10
Section four. Method of lining	
4.1 Surface preparation	11
4.2 Lining process	11
Section five. Inspection and testing	
5.1 Responsibility for inspection and testing	12
5.2 Inspection	12
Section six. Methods of test	
6.1 Continuity testing	13
Section seven. Rectification of faults	
7.1 General	14
Section eight. Storage, handling, transportation and installation	
8.1 General	15
Appendices	
A Characteristics of thermoplastics used as sheet linings specified in 3.1	16
B Continuity testing	17
C Effect of materials on water quality	19
Figures	
1 Pipework details	5
2 Weld profile details: butt welds	6
3 Weld profile details: external corners and edges	6
4 Weld profile details: internal corners and edges	7
5 Weld profile details: concave heads	8
6 Weld profile details: flanges	8

Section one. General

1.1 Scope

This Part of BS 6374 specifies requirements for the lining of equipment for the process industries using sheet thermoplastics.

It includes requirements for the choice of lining and its application and also requirements for inspection of the lining and the rectification of faults. It applies to equipment fabricated in metal or concrete and to both bonded and loose linings.

NOTE 1. The linings may be applied at the applicator's works or on site.

Requirements for design and fabrication of the equipment and the state of preparation necessary for the surfaces to be lined are specified in section two.

Requirements for storage, handling, transportation and installation of the lined equipment are specified in section eight.

NOTE 2. The titles of the publications referred to in this standard are listed on the inside back cover.

1.2 Definitions

For the purposes of this Part of BS 6374, the following definitions apply.

1.2.1 plastic* (noun). A material that contains as an essential ingredient a high polymer and which at some stage in its processing into finished products can be shaped by flow.

NOTE 1. Elastomeric materials, which are also shaped by flow, are not considered as plastics.

NOTE 2. In some countries, particularly in the United Kingdom, the official position now is that it is a permitted option to use the term 'plastics' as the singular form as well as the plural form.

1.2.2 resin*. A solid, semisolid, or pseudosolid organic material that has an indefinite and often high relative molecular mass, exhibits a tendency to flow when subjected to stress, usually has a softening or melting range and, usually fractures conchoidally. In a broad sense, the term is used to designate any polymer that is a basic material for plastics.

1.2.3 thermoset* (noun). A plastic which, when cured by heat or by other means, changes into a substantially infusible and insoluble product.

NOTE. This term includes both thermosetting plastics and thermoset plastics.

1.2.4 purchaser†. The organization or individual who buys the lined equipment for its own use or as an agent for the owner.

1.2.5 fabricator†. The organization or individual responsible for the fabrication of the equipment to be lined.

1.2.6 applicator†. The organization or individual responsible for the application of the lining.

1.2.7 inspection authority†. The body or association appointed by the purchaser (or owner) to check that the design, fabrication and lining comply with this standard.

1.2.8 lining. Thermoplastics applied as sheet linings which may or may not be bonded to the substrate.

NOTE. Although in common usage the terms 'linings' and 'coating' are interchangeable, in this document 'lining' will be used.

1.2.9 cure. The chemical reaction resulting in the final polymerized product.

1.2.10 pinhole. A small defect in the lining that would permit corrosion of the substrate under the conditions for which the lining is designed.

NOTE. The word 'pinhole' is synonymous with 'holiday' and 'pore'.

1.2.11 blister. A gas or liquid filled cavity within the lining material or between the lining and substrate.

1.3 Exchange of information

Early consultation shall be arranged between all parties concerned with the application of this standard, to establish the following information which shall be fully documented. Both the definitive requirements specified in this standard and the documented items shall be satisfied before a claim of compliance with the standard can be made and verified.

- (a) Design and fabrication details of the equipment to be lined and provision of drawings (see 2.2 and 2.3 or 2.4 and 2.5).
- (b) Details of gasket materials (see 2.2.9 and 2.2.10).
- (c) Details of the contents of the vessels or equipment, including trace materials (see 3.1.1(a)).
- (d) The design temperature (see 3.1.1(b)).
- (e) The design pressure (see 3.1.1(c)).
- (f) The details of any solids to be handled (see 3.1.1(e)).
- (g) The methods of heating and/or cooling (see 3.1.1(b)).
- (h) Cleaning methods, for example, water washing, solvent washing, boiling out or steaming (see 3.1.1(a)).
- (i) Where the lining work will be done.
- (j) Site conditions that may affect the work, for example availability of services.
- (k) Any special requirements for materials used in blast cleaning (see 4.1.1.4 and 4.1.2.3).
- (l) The type of material to be used for lining (see 3.1.1).

* These terms have been extracted from BS 1755 : Part 1.

† Where the words 'purchaser', 'fabricator', 'applicator' and 'inspection authority' occur in the text, they are intended also to include representatives of the purchaser, fabricator, applicator and inspection authority.

- (m) The minimum thickness of the lining and where applicable the maximum thickness (see **3.2.2**).
- (n) The suitability of the adhesive if the lining is to be bonded to the substrate (see **3.2.3**).
- (o) When the lining is to be applied outside the applicator's works and the adhesive as applied contains solvents, the types of solvents shall be stated, together with their flash points and threshold limit values.
- (p) The specified adhesive system (see **3.2.3** and **4.2**).
- (q) The provision of test plates (see **3.2.1** and **5.2.4**).
- (r) The minimum and maximum allowable temperature which is required for the correct application of a lining including the curing of the adhesive if used (see **4.2**).
- (s) Inspection techniques/procedures to be employed, acceptance levels and stages of inspection (see **5.1** and **5.2**).
- (t) Handling, transport, storage and installation procedure (see **3.1.1(g)** and **8.1.1** to **8.1.7**).

1.4 Compliance

1.4.1 Fabricator

The fabricator shall comply with the following:

- (a) section two (see **1.3(a)**);
- (b) **5.1(a)** and (b);
- (c) section eight as agreed in **1.3(t)**.

1.4.2 Applicator

The applicator shall comply with the following:

- (a) section three (but see **3.2.1**);
- (b) section four;
- (c) **5.1(c)**, (d), (e) and (f);
- (d) section six;
- (e) section seven;
- (f) section eight as agreed in **1.3(t)**.

Section two. Design, fabrication and surface finish of equipment to be lined

2.1 General

The basic design, fabrication and testing for mechanical reliability of the equipment to be lined shall be carried out to appropriate British Standards and shall comply with 2.2 and 2.3 or 2.4 and 2.5 before the lining operation commences.

2.2 Design of metal equipment to be lined

2.2.1 Equipment to be lined shall be sufficiently rigid that there is no possibility of deformation which would result in damage to the lining during transportation, installation and operation. When stiffeners are required, they shall normally be applied to the unlined side of the equipment.

2.2.2 The arrangements for the lifting of equipment shall be determined at the design stage.

2.2.3 The design of all equipment shall allow for access during the preparation of the surface and application of the lining and for venting of fumes evolved during the operation.

In completely enclosed vessels there shall be at least one manhole that after lining complies with BS 470 and one additional branch of not less than 75 mm bore to permit adequate circulation of air.

NOTE. It is recommended that, where practicable, the minimum diameter of a manhole should be 600 mm.

2.2.4 Riveted constructions shall not be used.

2.2.5 Bolted joints shall be permitted only if they can be dismantled for lining.

2.2.6 Surfaces to be lined shall be of a smooth contour.

2.2.7 Discontinuities, crevices and sharp projections shall be avoided.

2.2.8 Fittings that have to be installed after the completion of the lining process shall be designed to be lined or fabricated from materials that will not be affected by the process conditions.

2.2.9 Normally all connections to lined parts of equipment shall be flanged. If for any reason screwed connections are required, then these parts shall be fabricated in corrosion-resistant materials.

2.2.10 All nozzles and outlets shall be as short as possible, straight and flanged. Flange faces shall have a plain surface to allow the lining to continue over the face.

2.2.11 Heating coils, immersion heaters and sparger pipes shall be installed after the completion of the lining process and shall be located so that no part is closer than 100 mm from a lined surface. In the case of nozzles through which heating coils, etc., enter equipment, a smaller clearance is permitted provided that the temperature of the pipe through the nozzle does not exceed 80 °C. In no case shall this clearance be less than 25 mm. Fluid introduced through sparger pipes or dip pipes shall not impinge directly on to the lining. External heating of equipment shall not be permitted without full consultation with the applicator of the lining.

2.2.12 The design of pipework shall be such as to allow ready access to welds and bends for weld and surface preparation and permit the fitting of extruded liners (see figure 1).

Systems shall be made up from straight lengths with separate bends and tees.

2.2.13 The design of equipment shall be such that there is easy hand access to areas where thermoplastic sheets need to be welded.

2.3 Fabrication of metal equipment to be lined

2.3.1 All welds shall be continuous on surfaces to be lined. Only butt joints shall be permitted on surfaces to be lined.

Stitch welding, spot welding and other non-continuous welding processes shall not be used.

2.3.2 Weld surfaces shall be smooth. Some welding procedures provide surfaces of adequate smoothness but, in other cases surfaces shall be ground wholly or partly to remove weld ripples. The grinding process shall be done so that the remaining weld does not have sharp edges.

2.3.3 Welding procedures shall be chosen to avoid porosity on the side of the weld to be lined.

NOTE. It is preferable that capping runs are applied to the lining side in order to minimize this effect.

All welds shall be free from the following surface defects:

- (a) undercutting;
- (b) cracks;
- (c) porosity;
- (d) any other type of surface cavity;
- (e) lack of fusion.

Weld defects that are exposed either on initial inspection or after blast cleaning shall be repaired.

Repairs shall be by grinding or by welding (with or without subsequent grinding) provided that the requirements for equipment design and fabrication are met.

2.3.4 Weld profile details shall be generally in accordance with figures 2 to 6.

NOTE. Incorrect details are also illustrated.

2.3.5 Filler materials, such as resin, putties, fillers and low melting point solders and brazes, shall not be used.

2.3.6 Before the equipment is passed for lining, all attachments to be made by welding, for example lagging cleats and lifting lugs, shall be complete.

2.3.7 All drilling shall be completed before the equipment is passed for lining.

2.3.8 When the lining is to be thermo-formed at corners, those corners shall be finished to a radius of not less than 5 mm. When the lining is to be welded at corners, those corners shall be finished to a radius of a nominal 1.5 mm.


2.3.9 All slag, anti-spatter compounds or similar materials shall be removed.

All weld spatter shall be removed by chipping and/or grinding.

2.3.10 Surface defects such as scores, pitting and rolling defects, shall be removed by grinding, or where necessary

repaired by welding provided that the requirements of design and construction are met.

2.3.11 Rotating parts shall be balanced before and after lining.

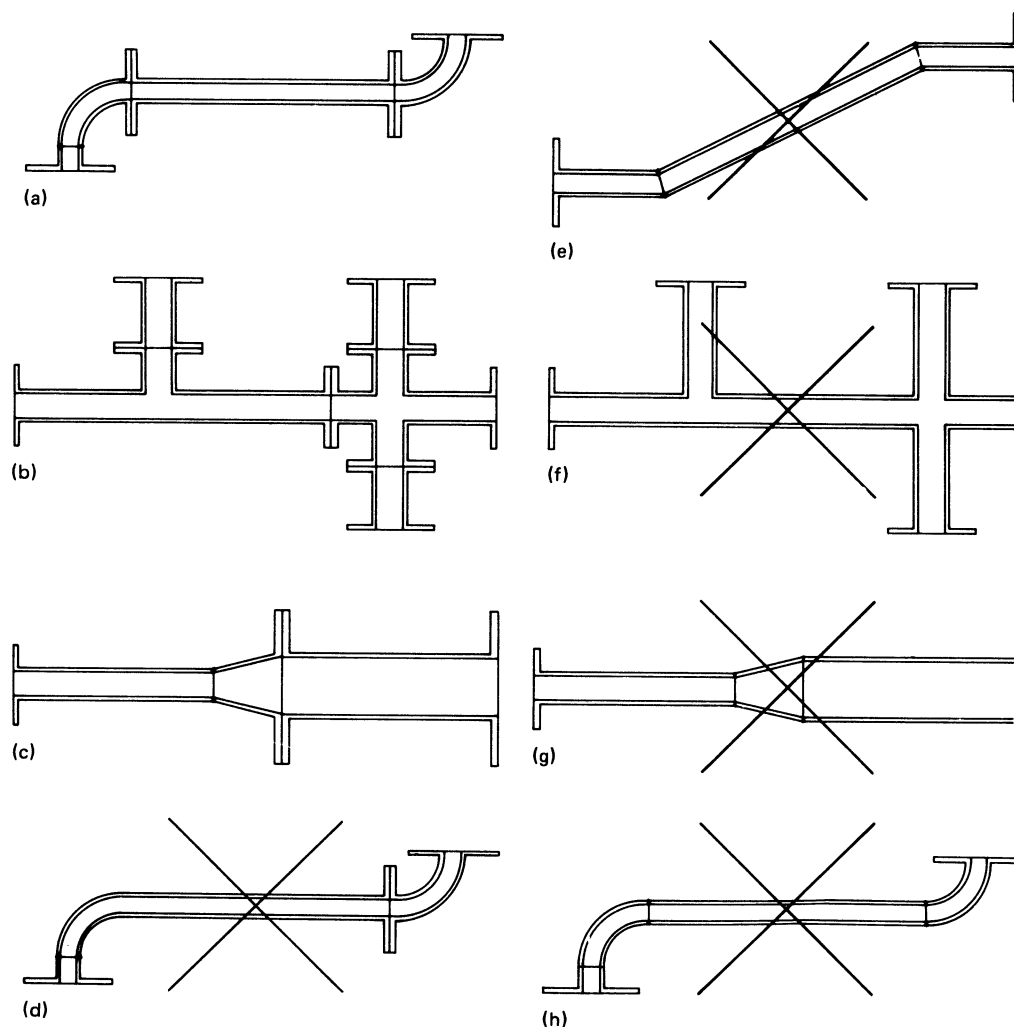

NOTE. The details shown in (a), (b) and (c) are permissible; those shown in (d), (e), (f), (g) and (h) are not permissible.

Figure 1. Pipework details

