

Wood preservatives — Laboratory method for determining the protective effectiveness of a preservative treatment against blue stain in service —

Part 2: Application by methods other than brushing

This European Standard EN 152-2 has the status of a
British Standard.

UDC 674.04:620.197:620.193.82

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW



Document Sharing Hub

Cooperating organizations

The European Committee for Standardization, under whose supervision this European Standard was prepared, comprises the national standards organizations of the following Western European countries.

Austria	Oesterreichisches Normungsinstitut
Belgium	Institut belge de normalisation
Denmark	Dansk Standardiseringsraad
Finland	Suomen Standardisoimisliitto, r.y.
France	Association française de normalisation
Germany	Deutsches Institut für Normung e.V.
Greece	Hellenic Organization for Standardization
Ireland	National Standards Authority of Ireland
Italy	Ente Nazionale Italiano di Unificazione
Netherlands	Nederlands Normalisatie-instituut
Norway	Norges Standardiseringsforbund
Portugal	Instituto Português da Qualidade
Spain	Instituto Español de Normalización
Sweden	Standardiseringskommissionen i Sverige
Switzerland	Association suisse de normalisation
United Kingdom	British Standards Institution

This British Standard, having been prepared under the direction of the Wood Preservation Standards Policy Committee, was published under the authority of the Board of BSI and comes into effect on 31 May 1990

© BSI 01-2000

The following BSI references relate to the work on this standard:
Committee reference WPC/10
Draft for comment 80/51735 DC

ISBN 0 580 18273 8

Amendments issued since publication

Amd. No.	Date of issue	Comments

Contents

	Page
Cooperating organizations	Inside front cover
National foreword	ii
Brief history	2
Text of EN 152-2	3
National appendix A	Inside back cover

National foreword

This Part of BS 7066 has been published under the direction of the Wood Preservation Standards Policy Committee.

This Part of BS 7066 is identical with EN 152-2:1988 “*Test methods for wood preservatives; Laboratory method for determining the protective effectiveness of a preservative treatment against blue stain in service — Part 2: Application by methods other than brushing*”, published by the European Committee for Standardization (CEN). EN 152-2:1988 was prepared as a result of discussion in CEN Technical Committee 38 “Methods of test of wood preservatives”, in which the UK participated. It incorporates the corrigendum AC 1 published in April 1989.

National appendix A gives the constitution of the committee responsible for the UK participation in the preparation of this standard.

BS 7066 currently consists of the following Parts:

- *Part 1: Brushing procedure;*
- *Part 2: Application by methods other than brushing.*

The symbol “l” has been used to denote litre (and in its submultiples). In British Standards it is current practice to use the symbol “L”.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN title page, pages 2 to 22, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

Key words: Wood preservatives, pest control, fungi, preventive, effectiveness, laboratory tests, procedure, test results.

English version

Test methods for wood preservatives;
Laboratory method for determining the protective
effectiveness of a preservative treatment against blue stain
in service
Part 2: Application by methods other than brushing

Méthodes d'essais des produits de préservation
des bois; Méthode de laboratoire pour
déterminer l'efficacité préventive d'un
traitement de protection du bois ouvré
contre le bleuissement fongique
Partie 2: Application par des méthodes autres
que le brossage

Prüfverfahren für Holzschutzmittel;
Laboratoriumsverfahren zur Bestimmung der
vorbeugenden Wirksamkeit einer
Schutzbehandlung von verarbeitetem Holz
gegen Bläuepilze;
Teil 2: Anwendung durch andere Verfahren als
Streichen

This European Standard was accepted by CEN on 26 March 1987. CEN members are bound to comply with the requirements of the CEN/CENELEC Rules which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Central Secretariat or to any CEN member.

This European Standard exists in the official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to CEN Central Secretariat has the same status as the official versions.

CEN members are the national standards organizations of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Ireland, Italy, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Brief history

This European Standard was drawn up by the Technical Committee CEN/TC 38 “*Methods of test for wood preservatives*”, the Secretariat of which is held by AFNOR.

In accordance with the CEN/CENELEC Common Rules, all CEN members are bound to implement this European Standard:

Austria, Belgium, Denmark, Finland, France, Germany, Greece, Ireland, Italy, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland, United Kingdom.

Contents

	Page
Brief history	2
0 Introduction	3
1 Object	3
2 Field of application	3
3 Working principle	4
4 Materials	4
5 Sample of wood preservative	6
6 Wood specimens	6
7 Test method	7
8 Reporting the results	10
9 Test report	10
Annex A Glossary	12
Annex B Preparation of a spore suspension of the test fungi	12
Annex C Detailed information on chemicals	13
Annex D Information regarding sterilization procedures	14
Annex E	15
Annex F Instructions on the test procedure	20
Annex G Example of a test report	21
Figure 1 — Designation of different types of preparations for preventing blue stain in service	3
Figure 2 — Culture vessel	15
Figure 3 — Diagram of the mounting of the weathering blocks in the weathering racks	16
Figure 4 — Rack for drying treatment sticks	16
Figure 5 — Preparation of twin panel assemblies	17
Figure 6 — Preparation of weathering block	18
Figure 7 — Treated panel prepared from weathering block	18
Figure 8 — Schematic presentation of twin panel assembly	19
Table 1	21
Table 2 — Results of determinations of extent of blue-stain development	22

0 Introduction

The test method described in this European Standard is a laboratory method combined with natural weathering, which provides a basis for assessment of the effectiveness of a wood preservative in preventing the development of blue staining fungi in wood in service where disfigurement may be considered important, such as external decorative timber and joinery. The method permits the determination of the effectiveness of undiluted preservatives applied to the wood by specified methods other than superficial treatments such as brushing¹⁾.

The method may also be used to test preparations in which the proportions of the individual components have been varied and so establish for the active ingredients the limit of their effectiveness.

The method is only suitable for testing preparations which are intended to prevent the occurrence of blue staining fungi in wood in service. It is not suitable for assessing the temporary preventive effectiveness of anti-stain preservatives on roundwood or on freshly cut wood. The method does not permit the determination of the fungicidal properties of the surface coating applied to the wood after the priming coat.

It should be used to assess the value of the protection, taking into account the method of application in question and in particular the manufacturer's specifications. It is recommended that the results of these tests should be supplemented by further suitable tests and especially by practical experience.


1 Object

This European Standard lays down a method for determining the effectiveness of water-borne and oil-solvent type wood preservatives applied by methods other than brushing in preventing blue stain fungi in wood in service. This method is applicable to preservatives applied by immersion processes, soaking, double vacuum or vacuum pressure techniques. It is also applicable where a primer paint is used in conjunction with the preservative system²⁾.

2 Field of application

This method is applicable to the following types of preparations applied by methods other than brushing or similar superficial treatment resulting in an equivalent retention of preservative (Figure 1):

- A fungicidal preparations with or without pigment, used in conjunction with unspecified varnishes or paint coatings,
- B fungicidal preparations with or without pigment, used in conjunction with specified varnishes or paint coatings,
- C fungicidal preparations with or without pigment, used without subsequent varnish or paint coatings.

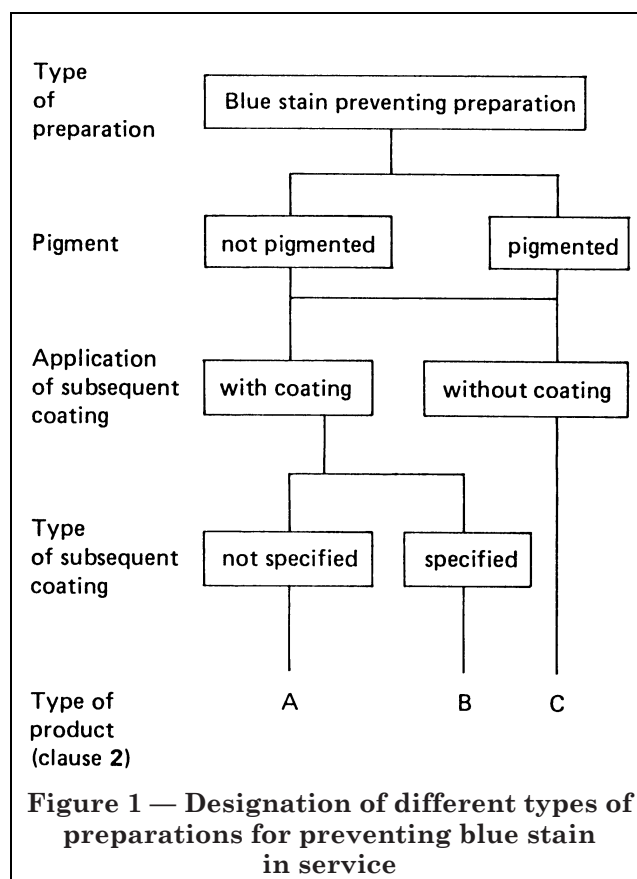

It is also possible to test the effectiveness of a combined protective system which involves the application of one preparation by one of the non-brushing techniques prescribed in Part 2 followed by a subsequent application of a different preparation by the brushing procedures prescribed in Part 1.

¹⁾ Part 1 of this standard lays down the method for determining the effectiveness of a wood preservative applied against blue stain by brushing.

²⁾ The method may also be used in conjunction with first coat (primer) paints required to give protection during storage of components on site. These are to be applied as specified coatings as defined for preparations of type B.

3 Working principle

The basic principles of the test method are to provide for infection by blue-stain fungi into the treated face and into the untreated part behind the treated one and observe the development of infection into the treated face. In order to achieve this a twin panel form of test assembly has to be used incorporating an untreated backing panel affixed to the panel which receives the specified treatment (see Annex A for glossary).

Treatments according to the specified methods are applied to “treatment sticks” from which the treated test panels are subsequently cut. The treatment differs according to the type of preparation and method of application (clause 2):

- Type A Preparations designed to be used with unspecified varnish or paint coatings are tested using the application rate appropriate to the preparation or as otherwise specified by the manufacturer followed by the standard test varnish
- Type B Preparations designed to be used with specified varnish or paint coatings are tested using the application rate appropriate to the preparation or as otherwise specified by the manufacturer followed by a surface coating strictly according to the manufacturer’s specification
- Type C Preparations designed to be used without subsequent varnish or paint coatings are tested using the application rate appropriate to the product or as otherwise specified by the manufacturer but with no subsequent application of coating.

Since the efficacy of the treating schedule used can be judged only on the basis of the uptake of treatment by each “treatment stick” it is essential that each treatment stick be accurately cut to the specified dimensions and shall not contain heartwood.

The “treated sticks” are cross cut to yield the “weathering blocks” from which, after weathering, the “treated test panels” are prepared. These after being joined with untreated “backing panels” make up the “twin panel assemblies” which are then exposed in suitable test vessels to attack by a mixed culture of blue stain fungi.

A comparison of the extent of blue staining of these test assemblies with control assemblies which were not treated with a wood preservative shows the effectiveness of the preparation under test.

For purposes of comparison it is recommended that an appropriate reference product of known performance be included in the test.

4 Materials

4.1 Biological material

The test fungi to be used in all tests are³⁾:

- *Aureobasidium pullulans* (de Barry) Arnaud, strain P 268⁴⁾ Source Hann-Münden
- *Sclerophoma pithyophila* (Corda) v. Höhn, strain S 231⁵⁾ Source Hann-Münden

Use the test fungi as a mixed culture in the form of a spore suspension. The technique for the preparation of this spore suspension is described in Annex B.

If desired, spore suspensions of further blue stain fungi of national importance can be used in additional series of tests. The type and extent of the growth of these fungi are to be described in the test report.

4.2 Chemicals

4.2.1 Nutrient medium

For the preparation of a spore suspension of test fungi a solution of malt buffered to pH 4.2 with citric acid shall be used. It shall contain 20 g/l concentrated malt extract or dried malt with a nitrogen content of $0,9 \pm 0,3$ % *m/m* (see Annex B example of a nutrient solution).

4.2.2 Coating material

Unpigmented varnish based on low viscosity, long oil alkyd resin, with driers and without any fungicidal or fungistatic components (see Annex C).

The varnish may be stored unopened for up to 2 years but once the container has been opened, unused quantities shall not be stored longer than 1 week for further use.

³⁾ Maintain the strains on 2 % malt agar and subculture them at intervals not exceeding 6 months. Obtain new cultures if there is evidence of degeneration such as loss of pigmentation or the ability to produce conidia. Cultures can be obtained from Bundesanstalt für Materialprüfung, Unter den Eichen 87, D-1000 Berlin 45 and from Commonwealth Mycological Institute, Ferry Lane, Kew, London UK.

⁴⁾ Identical to strain no. IMI 269 216 of culture deposited at CMI, Kew.

⁵⁾ Identical to strain no. IMI 269 217 of culture deposited at CMI, Kew.

4.2.3 *Priming coating material for control specimens*

Linseed oil varnish based on water-free and filtered sample (see Annex C).

4.2.4 *White spirit*

For the characteristics of the white spirit, see Annex C.

4.2.5 *End sealer*

Any appropriate material which is resistant to the solvents employed and to the weathering procedure. The varnish (4.2.2) is suitable for oil solvent systems. With water-borne solutions certain 2-component epoxy resins resist swelling of the treatment sticks.

4.2.6 *Sterilant* (if necessary see 7.3.2)

An ethylene oxide-based sterilant or propylene oxide (see Annex D).

4.2.7 *Adhesive for “twin-panel assembly”*

E.G. 2-component resorcinol phenol formaldehyde adhesive or similar adhesive capable of resisting distortion of twin panels due to changes in moisture content.

4.2.8 *An hydrated, laminar, aluminium-iron-magnesium silicate*

Exfoliated to give particles of 1 mm to 3 mm with an apparent density of 80 kg/m³ to 90 kg/m³. Particles of less than 1 mm shall be eliminated by sieving prior to use, to ensure the absence of free water and prevent any significant agglomeration of the particles.

4.3 Apparatus

4.3.1 *Incubation room* with the following climatic conditions: 22 ± 1 °C and 70 ± 5 % relative humidity.

4.3.2 *Conditioning room* at 20 ± 2 °C and 65 ± 5 % relative humidity.

In place of a conditioning room, a closed vessel containing a saturated ammonium nitrate solution with solid material at 20 ± 2 °C can be used.

4.3.3 *Weathering site* for open air weathering of wood specimens in special racks:

— Weathering racks: frames to take the weathering blocks on horizontal bars at 45° (see Figure 3 in Annex E). The frames shall be constructed of inert material (e.g. plastics, aluminium). In the racks the wood specimens shall be free on all sides and be secured against slipping.

— As a weathering site, any free area without extremes of environmental conditions with regard to humidity, dryness, UV radiation or industrial pollution is suitable. The site shall be free from tall vegetation.

— Erection of the weathering racks, the following are to be observed:

- they shall at no time be in the shade of trees, houses or other structures
- the wood specimens shall face the direction in which the exposure conditions are expected to be most severe. In Central Europe and France, this is to the South West and in the UK to the South.
- the wood specimens shall be placed 1 m to 1,5 m above the ground.
- the wood specimens shall be situated at least 0,5 m above any possible vegetation.

4.3.4 *Culture vessels* with a capacity of 400 cm³ to 600 cm³ and an internal area of base of 90 cm² to 120 cm² (see in Annex E an example of culture vessel).

4.3.5 *Sterilizer*

— Apparatus for chemical sterilization or access to ionizing radiation service (Annex D).

— Autoclave, adjustable up to 120 °C, or if no autoclave is available: steaming chamber.

4.3.6 *Measuring magnifying glass* with reading accuracy of 0,5 mm.

4.3.7 *Usual laboratory equipment*, especially:

- top-pan balance with accuracy 0,001 g
- various brushes
- abrasive paper, grit size 80 and 180
- viscometer (outlet tube 4, ISO 2431⁶⁾)
- drying oven, adjustable up to 150 °C.

⁶⁾ ISO 2431:1984 “Paints and varnishes — Determination of flow time by use of flow cups”.