

Specification for lac and shellac —

Part 2: Machine-made shellac

ICS 87.040

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW



Document Sharing Hub

Committees responsible for this British Standard

The preparation of this British Standard was entrusted to Technical Committee STI/3, Paints, media and related products, upon which the following bodies were represented:

- British Coatings Federation Ltd.
- European Resin Manufacturers' Association
- FOSFA International
- Ministry of Defence
- Oil and Colour Chemists Association
- Seed Crushers' and Oil Processors' Association

This British Standard, having been prepared under the direction of the Sector Board for Materials and Chemicals, was published under the authority of the Standards Board and comes into effect on 15 August 1997

© BSI 09-1999

The following BSI references relate to the work on this standard:
Committee reference STI/3
Draft for comment 95/120412

ISBN 0 580 27941 3

Amendments issued since publication

Amd. No.	Date	Comments

Contents

	Page
Committees responsible	Inside front cover
National foreword	ii
Foreword	ii
0 Introduction	1
1 Scope and field of application	1
2 Definitions	1
3 Form and condition	1
4 Types and grades	2
5 Mandatory requirements	2
6 Optional requirements	2
7 Sampling	3
Annex A Determination of matter insoluble in hot alcohol	4
Annex B Detection of rosin (Halphen-Hicks method)	9
Annex C Detection of orpiment	9
Annex D Determination of arsenic content	10
Annex E Determination of volatile matter (moisture) content	14
Annex F Determination of colour index	15
Annex G Determination of wax	16
Annex H Determination of ash	19
Annex J Determination of matter soluble in water and test for neutrality of aqueous extract	19
Annex K Flow test	19
Annex L Heat polymerization test	22
Annex M Determination of acid value	24
Annex N Determination of lead content	24
Annex P Determination of grit content	26
Annex Q Determination of iodine value	26
Annex R Test for clarity of solution	28
Annex S Sampling	28
Figure 1 — Extraction apparatus for determination of matter insoluble in hot alcohol (method I)	5
Figure 2 — Hot water bath for determination of matter insoluble in hot alcohol (method I)	6
Figure 3 — Siphon tube and adaptor	7
Figure 4 — Folding of filter paper	8
Figure 5 — Kjeldahl distillation apparatus for use in the determination of arsenic content (method I)	11
Figure 6 — Apparatus for the determination of arsenic content (method I)	14
Figure 7 — Apparatus for flow test	20
Figure 8 — Essential features of the testing fixture F	21
Figure 9 — Heat polymerization test apparatus	23
Table 1	2
Table 2	2

National foreword

This Part of BS 7897 has been prepared by Technical Committee STI/3. It is identical with ISO 56-2:1979 (*Incorporating Amendment No. 1:1996*), *Shellac — Specification — Part 2: Machine-made shellac*.

ISO 56-2 was prepared by Technical Committee ISO/TC 50, Lac, with the active participation and approval of the UK.

This standard supersedes BS 3722:1964 which is withdrawn.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the ISO title page, page ii, pages 1 to 29 and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

INTERNATIONAL STANDARD



56 / II

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Shellac — Specification — Part II : Machine-made shellac

Gomme laque en feuilles — Spécification — Partie II : Gomme laque en feuilles de fabrication mécanique

First edition — 1979-04-01

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO member bodies). The work of developing International Standards is carried out through ISO technical committees. Every member body interested in a subject for which a technical committee has been set up has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 56/11 was developed by Technical Committee ISO/TC 50, *Lac*, and was circulated to the member bodies in November 1976.

It has been approved by the member bodies of the following countries:

Australia	Korea, Rep. of	Sweden
Austria	Mexico	Turkey
Czechoslovakia	Netherlands	Yugoslavia
India	Romania	

The member body of the following country expressed disapproval of the document on technical grounds:

Canada

This International Standard cancels and replaces ISO Recommendation R 56-1957 of which it constitutes a technical revision.

Descriptors: Shellac, materials specifications, chemical analysis, tests, sampling.

0 Introduction

0.1 ISO/R 56, published in 1957, covered shellac, hand-made as well as machine-made. It has been revised into two parts, one for each kind.

0.2 The types and grades of machine-made shellac have been found to require modification in order that the characteristics of a given consignment of this material may be clearly defined. Machine-made shellac has now been divided into four main types, on the basis of the method of manufacture, and then into grades, within each type, on the basis of colour. Requirements for matter insoluble in hot alcohol, colour index and ash have now been prescribed based on the new system of types and grades.

0.3 Whereas in ISO/R 56 the limit for wax was left subject to agreement between the purchaser and the supplier, definite values have now been included. New requirements have been laid down for grit, iodine value, clarity of solution, and alkalinity of the aqueous extract.

0.4 The requirement for non-volatile matter soluble in cold alcohol has not been retained as the requirement is applied in practice to waste products of lac only. The methods for quantitative determination of rosin have also been dropped since this type of adulteration is no longer in evidence. In ISO/R 56, an alternative method (the Westinghouse method) was given for determination of flow. In this International Standard it has been dropped.

0.5 Three of the requirements for machine-made shellac, namely those for

- a) matter insoluble in hot alcohol,
- b) absence of rosin, and
- c) absence of orpiment,

are included in this International Standard as essential clauses.

The remaining requirements, namely those for

- d) volatile matter (moisture),
- e) colour index,
- f) wax,
- g) ash,
- h) matter soluble in water,
- j) flow test,
- k) heat polymerization test,
- m) acid value,
- n) lead content,
- p) grit,
- q) iodine value, and
- r) clarity of solution,

are optional.

0.6 The sizes of sieves given in the text of this International Standard have been indicated in terms of aperture dimensions, in accordance with ISO 565, *Test sieves — Woven metal wire cloth and perforated plate — Nominal sizes of apertures*.

0.7 For the purpose of deciding whether a particular requirement of this International Standard is complied with, the final value, observed or calculated, expressing the result of a test or an analysis, shall be rounded off to the same number of places as the specified value, it being always understood that the analyst will carry out the determination to at least one place more than in the specified value.

1 Scope and field of application

1.1 This International Standard specifies requirements and corresponding methods of test for machine-made shellac.

1.2 This International Standard is intended chiefly to cover the technical provisions for guidance in the purchase of the material, but does not include all the necessary provisions of a contract.

1.3 The limits prescribed in this International Standard are limits for rejection.

2 Definitions

For the purpose of this International Standard, the following definitions apply.

2.1
sticklac

the natural product of lac insects

2.2
seedlac

the product obtained by washing crushed sticklac

2.3
shellac

the product obtained by refining seedlac by heat process or by solvent process or by both heat and solvent processes

2.4
approved sample

the sample agreed upon between the purchaser and the supplier as the standard for colour and appearance

3 Form and condition

Machine-made shellac shall be in the form of flakes, sheets, buttons, or any other form agreed between the purchaser and the supplier.

4 Types and grades

4.1 Four types of machine-made shellac are specified, namely

Type I — produced by heat process.

Type II — produced by hot solvent process.

Type III — de-waxed.

Type IV — decolorized and de-waxed.

4.2 Five grades in each of types I and II, namely grades 1, 2, 3, 4 and 5 are specified. Four grades in each of types III and IV, namely grades 1, 2, 3, and 4 are specified.

5 Mandatory requirements

5.1 Matter insoluble in hot alcohol

Machine-made shellac shall not contain matter insoluble in hot alcohol, determined by either of the methods specified in Annex A, as agreed between the purchaser and the supplier, in excess of the limits given in Table 1.

Table 1

Type	Maximum % (<i>m/m</i>)
I	0,6
II	0,3
III	0,2
IV	0,2

5.2 Rosin

Machine-made shellac shall not contain any rosin, when tested by the method specified in Annex B.

5.3 Orpiment

5.3.1 Machine-made shellac shall not contain any orpiment, when tested by the method specified in Annex C, except when a specified percentage is agreed to between the purchaser and the supplier, in which case the determination shall be carried out as specified in Annex D, method I.

5.3.2 When the material is required for food or drug preparations, the determination of traces of arsenic, too small for titration by method I in Annex D, shall be carried out by method II in Annex D.

6 Optional requirements

The optional requirements given below shall be subject to agreement between the purchaser and the supplier.

6.1 Volatile matter (moisture)

Machine-made shellac shall not contain more than 2,0 % (*m/m*) volatile matter (moisture) as determined by the method specified in Annex E.

6.2 Colour index or colour and appearance

6.2.1 The colour index of machine-made shellac, as determined by the method specified in Annex F, shall not exceed the limits given in Table 2.

Table 2

Type	Grade				
	A	B	C	D	E
I, II	8	12	22	35	50
III	9	20	35	50	—
IV	0,9	2,0	3,5	5,0	—

6.2.2 Alternatively, the appearance and colour of the shellac shall be not inferior to those of an approved sample when judged by visual examination.

6.3 Wax

Machine-made shellac of type I and type II shall not contain more than 5,5 % (*m/m*) of wax, and that of type III and type IV not more than 0,2 % (*m/m*) of wax, when tested in accordance with method I and method II respectively, specified in Annex G.

6.4 Ash

Machine-made shellac shall yield not more than 0,3 % (*m/m*) of ash, as determined by the method specified in Annex H.

6.5 Matter soluble in water

Machine-made shellac shall not contain more than 0,5 % (*m/m*) of matter soluble in water and the aqueous extract shall not be acidic to methyl red or alkaline to bromothymol blue. Matter soluble in water shall be determined by the method specified in Annex J.

6.6 Flow test

Machine-made shellac shall have a flow within the range agreed to between the purchaser and the supplier, when tested by the method specified in Annex K.

6.7 Heat polymerization test

Machine-made shellac shall have a heat polymerization time within the range agreed to between the purchaser and the supplier, when tested by the method specified in Annex L. Unless otherwise agreed, the temperature of test shall be 150 °C.

6.8 Acid value

The acid value of the machine-made shellac shall be fixed, if desired, by agreement between the purchaser and the supplier. It shall be determined by the method specified in Annex M.

6.9 Lead content

The maximum limit for lead content shall be subject to agreement between the purchaser and the supplier and the lead content shall be determined by the method specified in Annex N.

6.10 Grit content

The maximum limit for grit content shall be as agreed to between the purchaser and the supplier. When required, it shall be determined by the method specified in Annex P.

6.11 Iodine value

The maximum limit for the iodine value shall be as agreed to between the purchaser and the supplier. When required, it shall be determined by either of the two methods specified in Annex Q.

6.12 Clarity of solution

This requirement is applicable to type III and type IV shellac and shall be subject to agreement between the purchaser and the supplier. The shellac shall show no turbidity when tested by the method specified in Annex R.

7 Sampling

Samples shall be taken in the manner specified in Annex S.

Annex A Determination of matter insoluble in hot alcohol (See 5.1)

A.1 Principle

Extraction of a test portion with 95 % (V/V) ethanol and weighing of the undissolved residue.

A.2 Method I

A.2.1 Reagent

Alcohol, 95 % (V/V) ethanol or 95 % (V/V) denatured spirit.

A.2.2 Apparatus

Ordinary laboratory apparatus and

A.2.2.1 Extraction apparatus, comprising

A.2.2.1.1 Condenser, all glass, of the type and dimensions shown in Figure 1, the tip of which is cut at an angle of 45°. The condenser has two holes in its tip through which passes the wire holding the siphon tube (A.2.2.1.2).

A.2.2.1.2 Siphon tube, of glass, of the type and dimensions shown in Figure 1. The siphon tube has two holes near the top for a wire to be fastened to the condenser tip, leaving about 6 mm space between the top of the tube and the condenser tip.

A.2.2.1.3 Conical flask, heat resistant, wide mouthed, conical, preferably of borosilicate glass of height approximately 175 mm and approximately 50 mm inside diameter at the top. The flask has a tight-fitting cork of depth 25 mm, bored to fit the stem of the condenser. The bottom of the cork is just above the holes for the wire in the condenser. To support the flask, a suitable ring support with iron clamp and nickel-chromium or iron gauze is used. The gauze has no asbestos covering.

A.2.2.1.4 Carbon filter tube, of the type and dimensions shown in Figure 1, having a light spiral spring at the bottom to hold up the extraction cartridge (A.2.2.2). The stem of the filter tube is fitted with a rubber stopper and firmly held in the hot water bath (A.2.2.4).

A.2.2.2 Extraction cartridges, of fat-free paper, of diameter approximately 25 mm and height approximately 60 mm.

A.2.2.3 Weighing bottle, glass-stoppered, of height approximately 80 mm and diameter approximately 40 mm.

A.2.2.4 Hot water bath, made of copper or stainless steel, having a width of approximately 100 mm and other dimensions as given in Figure 2.

The cover has a flanged hole of diameter 57 ± 1 mm, for a 200 ml beaker, and also a hole of diameter 35 ± 1 mm through which the top of the filter tube (A.2.2.1.4) projects. Directly below this hole, in the bottom of the bath, is a flanged hole, of diameter 25 ± 1 mm, to hold the rubber stopper, through which the stem of the filter tube extends, to discharge into the flask (A.2.2.1.3). The hot water bath is mounted on a low tripod or stand.

A.2.2.5 Gas burner, low form, adjustable, Bunsen type, carrying a draught shield, or any other suitable heating device.

A.2.2.6 Electric oven, capable of being maintained at 100 ± 2 °C.

A.2.2.7 Desiccator, containing sulphuric acid (ρ 1,84 g/ml).

A.2.2.8 Balance, accurate to 0,002 g.

A.2.2.9 Stop-watch or good two-minute sand-glass


A.2.3 Preparation of extraction cartridge

A.2.3.1 Place 125 ml of the alcohol (A.2.1) in the conical flask (A.2.2.1.3) and a new extraction cartridge (A.2.2.2) in the siphon tube (A.2.2.1.2). Introduce the siphon tube into the flask and connect it to the condenser (A.2.2.1.1), making sure that there is an ample flow of cold water through the condenser. Adjust the rate of heating so as to give a cycle of filling and emptying in the siphon tube every 2 min and extract for 30 min. Dry the cartridge in the oven (A.2.2.6), maintained at 100 ± 2 °C. After 2 h, weigh it in the tared weighing bottle (A.2.2.3), which has been kept in the desiccator (A.2.2.7), lifting the stopper of the bottle momentarily before weighing. Repeat the operations of drying, for periods of 1 h, and weighing, until the loss in mass between two successive weighings does not exceed 0,002 g.

A.2.3.2 Use only new cartridges. A number of cartridges may be extracted, dried, weighed and kept in weighing bottles in the desiccator until needed for use.

A.2.4 Test portion

Before analysis, thoroughly mix the “test sample” (see S.3.1 of Annex S) by rolling on paper, at least ten times, to ensure uniformity of the test sample. Weigh, directly from the paper, 4,5 to 5,5 g of the sample, to an accuracy of 0,01 g.

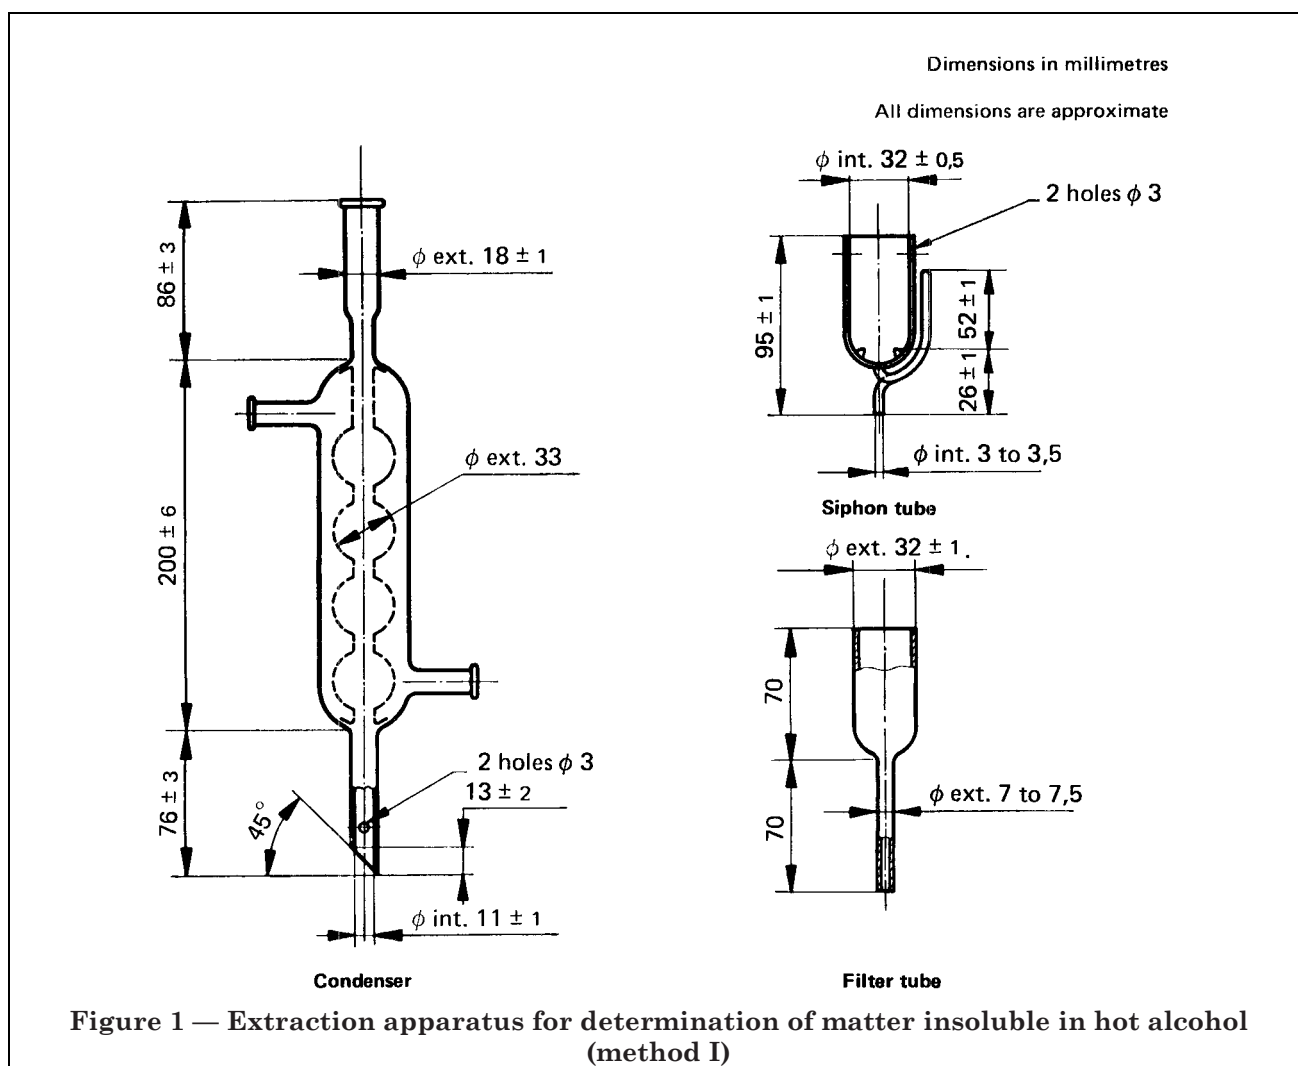

A.2.5 Determination

Place the test portion (A.2.4) in a 200 ml tall, lipped beaker, add 125 ml of the alcohol (A.2.1), cover with a watch-glass and place on the hot water bath (A.2.2.4) (see Figure 2). Boil the solution vigorously for 30 min to ensure complete solution of the shellac and dispersion of wax. Keep the volume of alcohol constant by adding from a wash-bottle, washing down the sides of the beaker.

Meanwhile, place an extracted and weighed cartridge (A.2.2.2) in the filter tube (A.2.2.1.4). Maintain the hot water around the tube at a temperature of not less than 90 °C. Wet the cartridge with hot alcohol and decant the boiling solution into the heated cartridge until the beaker is nearly empty.

Wash the remaining solution and the insoluble matter into the cartridge, using a “policeman”, if necessary, with successive portions of hot alcohol contained in a wash-bottle kept hot on the water bath. Finally, wash the cartridge from the top downwards with a fine stream of hot alcohol. A complete washing and transfer from the original beaker will require at least 75 ml of hot alcohol.