



BSI Standards Publication

Welding - Recommendation for welding of metallic materials

Part 6: Laser beam welding

National foreword

This British Standard is the UK implementation of EN 1011-6:2018. It supersedes BS EN 1011-6:2005, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee WEE/36, Qualification of welding personnel and welding procedures.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2018
Published by BSI Standards Limited 2018

ISBN 978 0 580 98146 3

ICS 25.160.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 December 2018.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

English Version

Welding - Recommendation for welding of metallic materials - Part 6: Laser beam welding

Soudage - Recommandations pour le soudage des matériaux métalliques -
Partie 6 : Soudage par faisceau laser

Schweißen - Empfehlungen zum
Schweißen metallischer Werkstoffe
- Teil 6: Laserstrahlschweißen

This European Standard was approved by CEN on 29 July 2018.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

European foreword	iii
Introduction	iv
1 Scope	5
2 Normative references	5
3 Terms and definitions	6
4 Health and safety and protection of the environment	7
5 Quality requirements	7
6 Equipment	7
6.1 General	7
6.2 Provisions for acceptance testing	7
6.3 Provisions for maintenance and calibration	8
7 Qualification of welding personnel	8
8 Welding procedure specification	8
9 Welding procedure test	8
10 Consumables	8
10.1 Filler metals	8
10.2 Gases	9
11 Design	9
11.1 Overall design of structure or product	9
11.2 Joint design	9
11.3 Joint preparation	9
12 Laser beam welding	10
12.1 Characteristics	10
12.1.1 Modes	10
12.1.2 Energy transfer	11
12.1.3 Pulsed beam welding	11
12.1.4 Beam oscillation	11
12.1.5 Ramping	12
12.1.6 Beam focussing	12
12.1.7 Gas shielding	12
12.1.8 Use of consumables	12
12.1.9 Hybrid processes	12
12.2 Advantages and limitations	12
12.3 Assembling and fixtures	13
12.4 Process control	13
12.5 Inspection and testing	13
12.6 Imperfections	13
Annex A (informative) Equipment	14
Annex B (informative) Laser beam properties	24
Annex C (informative) Information about weldability of metallic materials	26
Annex D (informative) Information about causes of weld imperfections and prevention	30
Annex E (informative) Beam control and monitoring	32
Annex F (informative) Laser beam processing	35
Bibliography	40

European foreword

This document (EN 1011-6:2018) has been prepared by Technical Committee CEN/TC 121 “Welding and allied processes”, the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2019 and conflicting national standards shall be withdrawn at the latest by June 2019.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 1011-6:2005.

The main changes compared to the previous edition are as follows:

- a) the normative references and bibliography have been updated;
- b) subclause 12.3 (Assembling and fixtures) has been modified;
- c) fiber laser has been added in Annex A (Equipment).

EN 1011 consists of the following parts, under the general title *Welding — Recommendations for welding of metallic materials*:

- *Part 1: General guidance for arc welding;*
- *Part 2: Arc welding of ferritic steels;*
- *Part 3: Arc welding of stainless steels;*
- *Part 4: Arc welding of aluminium and aluminium alloys;*
- *Part 5: Welding of clad steel;*
- *Part 6: Laser beam welding;*
- *Part 7: Electron beam welding;*
- *Part 8: Welding of cast irons.*

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Introduction

This document is being issued in several parts in order that it can be extended to cover the different types of metallic materials that will be produced to all European Standards for weldable metallic materials.

When this document is referenced for contractual purposes the ordering authority or contracting parties should state the need for compliance with the relevant parts of this document and such other annexes as are appropriate.

This document gives general guidance for the satisfactory production and control of welding and associated processes and details of some of the possible detrimental phenomena that can occur, with advice on methods by which they can be avoided. It is generally applicable to laser beam processing of metallic materials and also to some extent for non-metallic materials. It is appropriate regardless of the type of fabrication involved, although the relevant product standard, structural code or the design specification can have additional requirements. Permissible design stresses, methods of testing and inspection levels are not included because they depend on the service conditions of the fabrication. These details should be obtained from the relevant application standard or by agreement between the contracting parties.

It has been assumed in the drafting of the standard that the execution of its provisions is entrusted to appropriately qualified, experienced and trained personnel.

1 Scope

This document gives general guidance for laser beam welding and associated processes of metallic materials in all forms of product (e.g. cast, wrought, extruded, forged).

NOTE Some guidance on laser beam cutting, drilling, surface treatment and cladding is given in [Annex F](#).

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 14717, *Welding and allied processes — Environmental check list*

EN ISO 636, *Welding consumables — Rods, wires and deposits for tungsten inert gas welding of non-alloy and fine-grain steels — Classification (ISO 636)*

EN ISO 3834-2, *Quality requirements for fusion welding of metallic materials — Part 2: Comprehensive quality requirements (ISO 3834-2)*

EN ISO 3834-5, *Quality requirements for fusion welding of metallic materials — Part 5: Documents with which it is necessary to conform to claim conformity to the quality requirements of ISO 3834-2, ISO 3834-3 or ISO 3834-4 (ISO 3834-5)*

EN ISO 6520-1, *Welding and allied processes — Classification of geometric imperfections in metallic materials — Part 1: Fusion welding (ISO 6520-1)*

EN ISO 9013, *Thermal cutting — Classification of thermal cuts — Geometrical product specification and quality tolerances (ISO 9013)*

EN ISO 11145:2016, *Optics and photonics — Lasers and laser-related equipment — Vocabulary and symbols (ISO 11145)*

EN ISO 13919-1, *Welding — Electrons and laser beam welded joints — Guidance on quality levels for imperfections — Part 1: Steel (ISO 13919-1)*

EN ISO 13919-2, *Welding — Electron and laser beam welded joints — Guidance on quality levels for imperfections — Part 2: Aluminium and its weldable alloys (ISO 13919-2)*

EN ISO 13920, *Welding — General tolerances for welded constructions — Dimensions for lengths and angles — Shape and position (ISO 13920)*

EN ISO 14175, *Welding consumables — Gases and gas mixtures for fusion welding and allied processes (ISO 14175)*

EN ISO 14232-1, *Thermal spraying — Powders — Part 1: Characterization and technical supply conditions (ISO 14232-1)*

EN ISO 14341, *Welding consumables — Wire electrodes and weld deposits for gas shielded metal arc welding of non alloy and fine grain steels — Classification (ISO 14341)*

EN ISO 14343, *Welding consumables — Wire electrodes, strip electrodes, wires and rods for arc welding of stainless and heat resisting steels — Classification (ISO 14343)*

EN ISO 14732, *Welding personnel — Qualification testing of welding operators and weld setters for mechanized and automatic welding of metallic materials (ISO 14732)*

EN ISO 14919, *Thermal spraying — Wires, rods and cords for flame and arc spraying — Classification — Technical supply conditions (ISO 14919)*

EN ISO 15609-4, *Specification and qualification of welding procedures for metallic materials — Welding procedure specification — Part 4: Laser beam welding (ISO 15609-4)*

EN ISO 15614-11, *Specification and qualification of welding procedures for metallic materials — Welding procedure test — Part 11: Electron and laser beam welding (ISO 15614-11)*

EN ISO 15616-1, *Acceptance tests for CO₂-laser beam machines for high quality welding and cutting — Part 1: General principles, acceptance conditions (ISO 15616-1)*

EN ISO 15616-2, *Acceptance tests for CO₂-laser beam machines for high quality welding and cutting — Part 2: Measurement of static and dynamic accuracy (ISO 15616-2)*

EN ISO 15616-3, *Acceptance tests for CO₂-laser beam machines for high quality welding and cutting — Part 3: Calibration of instruments for measurement of gas flow and pressure (ISO 15616-3)*

EN ISO 16834, *Welding consumables — Wire electrodes, wires, rods and deposits for gas shielded arc welding of high strength steels — Classification (ISO 16834)*

EN ISO 17632, *Welding consumables — Tubular cored electrodes for gas shielded and non-gas shielded metal arc welding of non-alloy and fine grain steels — Classification (ISO 17632)*

EN ISO 17633, *Welding consumables — Tubular cored electrodes and rods for gas shielded and non-gas shielded metal arc welding of stainless and heat-resisting steels — Classification (ISO 17633)*

EN ISO 17634, *Welding consumables — Tubular cored electrodes for gas shielded metal arc welding of creep-resisting steels — Classification (ISO 17634)*

EN ISO 17662, *Welding — Calibration, verification and validation of equipment used for welding, including ancillary activities (ISO 17662)*

EN ISO 18273, *Welding consumables — Wire electrodes, wires and rods for welding of aluminium and aluminium alloys — Classification (ISO 18273)*

EN ISO 18274, *Welding consumables — Solid wire electrodes, solid strip electrodes, solid wires and solid rods for fusion welding of nickel and nickel alloys — Classification (ISO 18274)*

EN ISO 18276, *Welding consumables — Tubular cored electrodes for gas-shielded and non-gas-shielded metal arc welding of high strength steels — Classification (ISO 18276)*

EN ISO 21952, *Welding consumables — Wire electrodes, wires, rods and deposits for gas shielded arc welding of creep-resisting steels — Classification (ISO 21952)*

EN ISO 22827-1, *Acceptance tests for Nd:YAG laser beam welding machines — Machines with optical fibre delivery — Part 1: Laser assembly (ISO 22827-1)*

EN ISO 22827-2, *Acceptance tests for Nd:YAG laser beam welding machines — Machines with optical fibre delivery — Part 2: Moving mechanism (ISO 22827-2)*

EN ISO 24373, *Welding consumables — Solid wires and rods for fusion welding of copper and copper alloys — Classification (ISO 24373)*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN ISO 11145:2016 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Health and safety and protection of the environment

See EN 14717 for a general environmental checklist which is also applicable to laser beam welding.

Laser beam processing introduces additional hazards over and above those normally experienced in arc welding. Specialist advice should be sought, see e.g. EN 60825-1 and EN ISO 11553-1.

Guidance for safety aspects related to the application of industrial robots for manipulation of the focussing devices and/or the components to be welded can be found in EN ISO 10218-1 and EN ISO 10218-2.

5 Quality requirements

Laser beam welding is a complex process needing detailed process control. All processing is performed under numerical control necessitating programming of each single operation. The application shall be controlled at a level compatible with EN ISO 3834-2 and EN ISO 3834-5.

This does not entail a requirement for certification but the process control should operate in accordance with EN ISO 3834-2 and EN ISO 3834-5.

It is a condition for efficient process control that quality requirements for joint geometry and other relevant requirements have been specified prior to start of fabrication. A number of European Standards specify joint geometry and relevant quality criteria and can be used for reference, as appropriate:

Table 1 — Quality criteria

Requirements and tolerances	Standard no.
Quality requirements to beam welded joints	EN ISO 13919-1 EN ISO 13919-2
Quality requirements for cut surfaces	EN ISO 9013
General tolerances	EN ISO 13920
General requirements	EN ISO 3834-2 and EN ISO 3834-5 specify provisions for information and items to be agreed and specified prior to the start of fabrication. EN 1011-1:2009, Annex A can be used as a guide in case EN ISO 3834-2 and EN ISO 3834-5 are not called for.

6 Equipment

6.1 General

Information about particular equipment for laser beam processing shall be found as information from the supplier. A number of textbooks and a large number of articles provide background information. [Annex A](#) provides some very general information on principles and techniques. [Annex B](#) provides general information on the properties of laser beams.

6.2 Provisions for acceptance testing

Provisions for acceptance of CO₂- and Nd:YAG laser beam equipment can be found in the standards listed in [Table 2](#). There are currently no EN or ISO standards covering acceptance testing of other types of laser beam equipment.

Table 2 — Provisions for acceptance testing

Type of equipment	Standard no.
CO ₂ laser beam equipment	EN ISO 15616-1, EN ISO 15616-2 and/or EN ISO 15616-3

Type of equipment	Standard no.
Nd:YAG laser equipment	EN ISO 22827-1, EN ISO 22827-2

6.3 Provisions for maintenance and calibration

Provisions for maintenance are not standardized. The supplier's manuals shall be consulted. Principles for calibration, verification and validation and minimum requirements are specified in EN ISO 17662.

7 Qualification of welding personnel

The requirements for the qualification of personnel for fully mechanized and automatic welding and allied processes are laid down in EN ISO 14732. Among the different procedures specified in this European Standard, the functional test is particularly suitable as a basis for qualification of personnel responsible for the operation and set-up of laser beam processing. In a functional test, the operator or setter demonstrates his knowledge of working with a procedure specification and of setting, supervising and checking the laser beam processing machine.

8 Welding procedure specification

All details for the laser beam welding of components shall be recorded in a welding procedure specification (WPS) according to EN ISO 15609-4. Procedure specification for cutting, drilling, surface treatment and cladding are not standardized. EN ISO 15609-4 can, however, give some guidance.

9 Welding procedure test

Formal qualification of all procedures for laser processing is recommended for all applications and required for many applications. Qualification of procedures for laser beam welding (when required) can be performed by procedure testing, see EN ISO 15614-11. Qualification by pre-production testing can also be relevant, however, see EN ISO 15613. Qualification by pre-production testing is common practice for cutting, drilling and surface treatment. EN ISO 15613 can give some guidance.

Qualification of procedures for laser beam welding for cladding (when required) can be performed by procedure testing, see EN ISO 15614-7. Qualification by pre-production testing can also be relevant, however, see EN ISO 15613.

10 Consumables

10.1 Filler metals

Filler metals are used for laser beam cladding and sometimes for laser beam welding. The main problem in regard to filler metals for laser applications is that the market for such filler metals is rather small and that dedicated standards for filler metals for laser applications do not exist. The usual form of delivery is solid cylindrical wires but powders can also be used, in particular for cladding. What is commercially available is:

- wires marketed as consumables for gas shielded metal arc welding and tungsten inert gas welding. However, it should be noted that metal cored tubular wires might also be suitable. Small-scale (experimental) production of tubular wires can even be feasible for special applications. Relevant standards are EN ISO 14341, EN ISO 17632, EN ISO 636, EN ISO 21952, EN ISO 17634, EN ISO 14343, EN ISO 17633, EN ISO 16834, EN ISO 18276, EN ISO 24373, EN ISO 18273, EN ISO 18274;
- wires marketed as consumables for thermal spraying. The usual form of delivery is solid cylindrical wires which are standardized in EN ISO 14919;

- powders for thermal spraying are standardized in EN ISO 14232-1;
- powders for powder metallurgy.

10.2 Gases

Gases are used for shielding and plasma suppressing in laser beam welding, as cutting assists gas in laser beam cutting, for shielding in laser beam cladding, drilling and marking. Further, CO₂ lasers may need a continuous supply of laser gas.

The only relevant standard is EN ISO 14175. This standard is, however, not adequate for all gases used for laser beam processing. Careful specification of composition, tolerances, etc. is necessary for all non-standardized gases, when ordering.

11 Design

11.1 Overall design of structure or product

The main consideration is to ensure that all joints are accessible. It can be an advantage that the focussing head can be some distance from the surface of the joint. However, when shielding gas or plasma suppression jets are used, these nozzles shall be placed close to the surface. Application of sensors augment the requirements for accessibility.

11.2 Joint design

Joint design is, of course, relevant for laser beam welding. The default joint is a normal square butt weld in a butt joint. T joints are welded similarly but full penetration may not be necessary. Overlap joints are used for spot welding.

Laser beam welding can accomplish welding of components to tight tolerances. It is a condition, however, that either the fixtures hold the parts very accurately or that the joints are “self-positioning”.

Laser beam welding with root backing can be employed if spatter, spiking defects and undercut are to be avoided.

For axial circular welds on components with narrow dimensional tolerances, a press fit like H7/r6 to H7/n6 (EN ISO 286-2) is recommended. For circular welds with a clearance fit tacking is essential.

11.3 Joint preparation

The quality of laser beam welding relies on accuracy and cleanliness of the joint preparation. Joints can be prepared by machining or cutting. Attention should be paid to the resulting surface condition. Cleaning of weld joint surfaces should be carried out if they are contaminated by oxides, oil, grease, coolant and paint.


The specific cleaning method used will be dependent on the material type, component size and the quality requirements as well as the operational circumstances. The following treatments can be used:

- manual degreasing with a solvent;
- cleaning in a closed solvent vapour unit or in an ultrasonic bath;
- pre-treatment by steam cleaning with a slightly alkaline additive, following by drying;
- acid pickling neutralization, washing in distilled water, drying, short-term storage;
- mechanical cleaning by grinding, brushing, etc.;

- primers and similar layers on steel plates can be burnt away by de-focussing the laser beam and move it along the joint prior to welding. Very high speeds of in excess of 100 mm/s can be used during this treatment.

Where components have surface layers produced by carburizing, anodizing, cadmium plating, nitriding, phosphating, galvanizing, etc. these layers shall usually be removed, preferentially by machining of the surface in the weld joint region.

If the component cannot be machined in the weld start and finish regions to remove the end crater, run-on or run-off plates should be used (see [Figure 1](#)). These run-on/ run-off plates also suppress heat accumulation at the work piece ends. The run-on/run-off plates should be attached to the work piece by clamping or welding to achieve good thermal contact and will be removed subsequently.

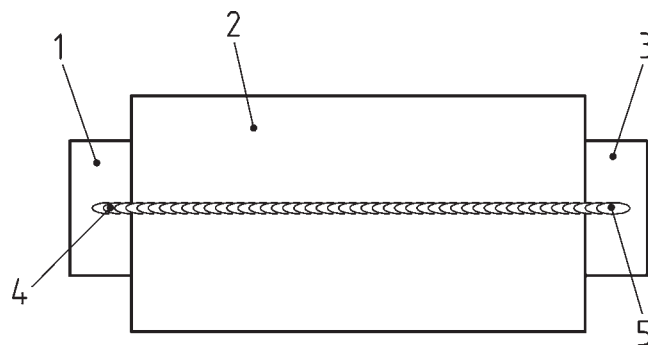

Key

- | | |
|---|---------------|
| 1 | run-on plate |
| 2 | work piece |
| 3 | run-off plate |
| 4 | start of weld |
| 5 | end of weld |

Figure 1 — Work piece with run-on and run-off plate for separating the weld start and weld end

12 Laser beam welding

12.1 Characteristics

12.1.1 Modes

Laser beam welding is a fusion welding process and the joint is characterized by heat affected zones in the parts, joined by weld metal.

Laser beam welding is often performed as keyhole mode welding. Keyhole mode welding requires a beam with a high power density, able to vaporize the material at the point of interaction. The beam then is able to create (by the vapour pressure) a deep cavity, roughly cylindrical in shape. The walls of the cavity are covered by molten material. When the process is under control, the cavity is propagated with the beam along the joint. Heat and material propagation is essentially two-dimensional. The material melts at the front of the cavity and moves to the trailing edge, where it solidifies, creating the weld metal. A small proportion of the material evaporates or is ejected as spatter and this part of the material is transported in the direction along the axis of the beam. Keyhole mode welding is the usual mode for full and partial penetration butt welds of thick workpieces.

Another mode is conduction mode welding. In this mode, the intensity of the beam is insufficient to create a keyhole and the heat distribution becomes similar to the heat distribution in arc welding. Conduction mode welding occurs when the beam (of low intensity) is de-focussed or oscillated. Conduction mode welding can result in a three-dimensional heat distribution and the weld cross

section is then approximately circular with a width at the surface approximately 2 times the depth of penetration. However, the heat input can be spread over a wider area resulting in a weld with a width larger than 2 times the depth of penetration. A similar technique is used for laser beam cladding where penetration usually is minimized.

In spot welding, the focussing head is kept stationary in relation to the parent material during welding. Welding time for each spot can be measured in milliseconds. Pulsed lasers are commonly used for this purpose. The resulting weld profile is usually intermediate between conduction and keyhole welds.

12.1.2 Energy transfer

The energy is transferred from the laser beam into the base material where it melts the material and creates the keyhole (in the keyhole mode). Energy transfer is influenced primarily by the following factors:

- reflection of (a part of) the beam energy from the surface of the workpiece and liquid weld material;
- creation of a plume of vaporized elements and/or of a plasma cloud (CO₂ laser);
- the wavelength of the used laser beam.

Laser beams are reflected from the surface of workpieces. The proportion of the energy reflected depends on the surface condition (at the microscopic level), e.g. the surface roughness and also the surface temperature. The proportion reflected can be very high, close to 90 % for polished materials and wavelength above 1 µm at room temperature. The proportion is much lower, below 50 % for shorter wavelength and less reflective surfaces. However, if the beam has enough power to establish a keyhole, reflection becomes of minor importance. Consideration of the reflectivity of the material has become less important with the general availability of high power and high beam quality lasers. When reflectivity causes problems this can result in the process becoming unstable and the keyhole not being established locally where for some reason a higher percentage of the beam energy is reflected.

Laser beam welding is usually accompanied by vaporization of part of the base material. This results in a plume of vapour above the keyhole. High power CO₂ lasers induce such high temperatures that at least a part of the plume is ionized and a cloud of plasma is created in and above the joint (the keyhole). The plasma cloud can attenuate the beam and the usual precaution is to apply a jet of helium, blowing the plasma away.

Helium is the preferred gas for plasma suppression. However, other gases such as Nitrogen or Argon have been used on an experimental basis. The plasma cannot be entirely suppressed, but welding appears to be feasible none the less.

Vaporization affects the various chemical constituents of the base material selectively. Components with a high vapour pressure will vaporize more readily. The weld metal will consequently be depleted in such components compared to the base material.

12.1.3 Pulsed beam welding

Pulsed beam welding can be used for spot welding and (micro) welding with limited heat input. The high peak power in pulsed lasers can for certain applications be used for establishment of keyhole mode welds in comparatively thick workpieces. However, the welding speed is less than for a powerful laser having a continuous output.

12.1.4 Beam oscillation

Oscillation of the beam can be used to establish a wider weld profile and can be beneficial where gaps shall be bridged. The augmented welded cross section is accompanied by diminished cooling rates.

12.1.5 Ramping

The numerical control of laser beam power sources usually permits ramping (slope-up and slope-down) which – together with focus control – can be used to obtain satisfactory welds in the start and stop positions. This is of course very important for welding of circumferential and orbital welds.

12.1.6 Beam focussing

The laser beam is usually focussed at or near the surface of the workpiece.

12.1.7 Gas shielding

Some gas shielding is needed for most applications. The weld pool, the hot part of the weld immediately behind the weld pool and the underside (for full penetration welding) may have to be protected. Gas nozzles of a suitable design should be used to obtain a flow without turbulence. The need for shielding and the type of shielding gas to be used depends on the workpiece welded. Sufficient shielding of all hot parts is of key importance, e.g. when welding stainless steels in order to maintain good resistance to corrosion. Full penetration welds in mild steel can, however, often be welded without any gas shielding at the weld root. High speed welding of thin materials can also be carried out without a gas shield.

12.1.8 Use of consumables

Consumables may be needed e.g. when welding with a gap, in order to avoid underfill. Consumables may also be needed for metallurgical reasons. However, very accurate positioning of the wire is necessary. A hybrid arc process can be a better solution.

12.1.9 Hybrid processes

Hybrid processes involve a combination of laser beam welding with an arc welding process such as plasma arc welding, TIG welding, MAG welding, etc. This can be a good solution when addition of a filler material is needed. High welding speed and low heat input can still be achieved. Combined butt/fillet weld is another option when a hybrid process is used. EN 1011-1 can be consulted as regards recommendations for arc welding.

12.2 Advantages and limitations

Laser beam welding using keyhole mode has a number of advantages compared to other fusion welding processes:

- joining is established by creation of a minimum of weld metal. This is associated by a minimum of heat input, narrow heat affected zones and minimal shrinkage and distortion;
- high welding speeds are possible and most joints are established by one or at most two runs, one from each side;
- welds can be established in materials down to a few hundreds of millimetres thickness. The upper limit is presently of the order 25 mm for full penetration butt welds in steels welded from one side only.

Compared to electron beam welding, laser beam welding has the advantage of being performed under normal atmospheric conditions and there is no generation of X-rays.

The limitations are mainly:

- high cooling rates that call for special attention in some materials in order to avoid unacceptable materials properties;
- cracking and/or porosity can occur in certain materials;