

Piezoelectric properties of ceramic materials and components —

Part 2: Methods of measurement — Low power

The European Standard EN 50324-2:2002 has the status of a
British Standard

ICS 31.140

National foreword

This British Standard is the official English language version of EN 50324-2:2002.

The UK participation in its preparation was entrusted by Technical Committee GEL/15, Insulating materials, to Subcommittee GEL/15/3/1, Ceramics and glass, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

This British Standard, having been prepared under the direction of the Electrotechnical Sector Policy and Strategy Committee, was published under the authority of the Standards Policy and Strategy Committee on 10 October 2002

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 26, an inside back cover and a back cover.

The BSI copyright date displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

© BSI 10 October 2002

ISBN 0 580 40537 0

Piezoelectric properties of ceramic materials and components
Part 2: Methods of measurement -
Low power

Propriétés piézoélectriques des matériaux
et composants en céramique
Partie 2: Méthodes de mesure -
Faible puissance

Piezoelektrische Eigenschaften
von keramischen Werkstoffen
und Komponenten
Teil 2: Meßverfahren -
Kleinsignal

This European Standard was approved by CENELEC on 2001-12-01. CENELEC members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CENELEC member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CENELEC member into its own language and notified to the Central Secretariat has the same status as the official versions.

CENELEC members are the national electrotechnical committees of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CENELEC

European Committee for Electrotechnical Standardization
Comité Européen de Normalisation Electrotechnique
Europäisches Komitee für Elektrotechnische Normung

Central Secretariat: rue de Stassart 35, B - 1050 Brussels

Foreword

This European Standard was prepared by the CENELEC BTTF 63-2, Advanced technical ceramics.

The text of the draft was submitted to the formal vote and was approved by CENELEC as EN 50324-2 on 2001-12-01.

The following dates were fixed:

- latest date by which the EN has to be implemented
at national level by publication of an identical
national standard or by endorsement (dop) 2002-12-01
- latest date by which the national standards conflicting
with the EN have to be withdrawn (dow) 2004-12-01

This part 2 is to be used in conjunction with EN 50324-1.

Contents

	Page
1 Scope.....	4
2 Symbols and units.....	4
3 Dimensions and finish of standard test specimen.....	5
4 Electrodes.....	6
5 Environmental requirements	6
6 Small signal data - Timing of measurement	6
7 Number of test specimens.....	6
8 Methods of measurement.....	7
9 Determination of a complete set of material parameters - Systematic procedure.....	15
10 Errors in calculated coefficients.....	23
11 Determination of the temperature coefficient of the parameters.....	24
12 Temperature coefficients of calculated parameters.....	25
13 Calculation of ageing rates.....	26

1 Scope

The methods of measurement described in this European Standard are for use with piezoelectric components produced from the ceramic materials described in EN 50324-1 “Terms and definitions”. Methods of measurement for specific dielectric, piezoelectric and elastic coefficients are generally applicable to piezoelectric ceramics.

The polycrystalline nature of ceramics, statistical fluctuations in composition and the influence of the manufacturing process, result in specified material coefficients being typical mean values. These values are provided for design information only.

Piezoelectric transducers can have widely differing shapes and may be employed in a range of vibrational modes. Material parameters however, are measured on simple test-pieces (discs, rods etc. see EN 50324-1, Figure 2) using specific geometric and electrical boundary conditions. Consequently, the results of the tests provide basic material parameters only and must only be used as a guide to the actual properties of manufactured commercial components.

2 Symbols and units

All material constants and equations appearing in this standard are given according to the International System of Units (SI-units).

Table 1 lists the symbols and, where appropriate, shows the units associated with the physical quantities designated by the symbols.

Table 1 - List of symbols and their units

Symbol	Meaning	SI-unit
A	Area	m ²
c	Ageing rate	See note
c _{ij}	Elastic stiffness constant	N/m ²
C	Capacitance	F
C ^T	Free capacitance	F
d	Diameter	m
d _{ij}	Piezoelectric charge (strain) constant	C/N or m/V
e _{ij}	Piezoelectric stress constant	C/m ² or N/Vm
E _i	Component of the electric field strength	V/m
E _m	Measuring field strength	V/m
f	Frequency	Hz
f _a	Antiresonance frequency (zero reactance)	Hz
f _m	Frequency of minimum impedance	Hz
f _n	Frequency of maximum impedance	Hz
f _p	Parallel resonance frequency	Hz
	(maximum resistance)	
f _r	Resonance frequency	Hz
f _s	Motional (series) resonance frequency	Hz
	(maximum conductance)	
f ₁	Frequency at first overtone	Hz
f ₃	Frequency at third overtone	Hz
g _{ij}	Piezoelectric voltage (stress) constant	m ² /C or Vm/N

Table 1 - List of symbols and their units (continued)

Symbol	Meaning	SI-unit
$J_0(z)$	Bessel function of first kind and zero order	
$J_1(z)$	Bessel function of first kind and first order	
$J_m(z)$	Modified Bessel function of first order	
k_{eff}	Effective electromechanical coupling factor	
k_{31}	Transverse coupling factor	
k_{33}	Longitudinal coupling factor	
k_{15}	Shear coupling factor	
k_p	Planar coupling factor	
k_t	Thickness coupling factor	
l	Length	m
M	Figure of merit	
n	Overtone order	
N_t	Frequency constant for thickness mode	Hz·m
N_p	Frequency constant for radial mode	Hz·m
Q_m	Mechanical quality factor	
R_i	Isolation resistance	Ω
S_i	Strain component	
s_{ij}	Elastic compliance constant	m^2/N
t	Thickness	m
TC	Temperature coefficient	K^{-1}
T_i	Stress component	N/m^2
$\tan \delta_d$	Dielectric dissipation factor	
$\tan \delta_m$	Mechanical dissipation factor	
v	Sound velocity	m/s
w	Width	m
Z	Impedance	Ω
δ_r	Relative frequency spacing	
ϵ_{ij}	Absolute permittivity	
ϵ_0	Permittivity of free space	F/m
ϑ	Temperature	$^{\circ}\text{C}$
ϑ_C	Curie temperature	$^{\circ}\text{C}$
φ	Phase angle	$^{\circ}$
ρ	Density	Mg/m^3
ρ_e	Resistivity	Ωm
σ^E	Planar Poisson's ratio	
ω	Angular frequency	rads/sec

NOTE Ageing rate is commonly expressed as % per decade.

3 Dimensions and finish of standard test specimen

The surface of standard test specimens for characterisation of piezoceramics for transducers should have an average roughness $R_a < 1 \mu\text{m}$ before electroding and deviations from flatness and parallelism of the surfaces should not exceed $50 \mu\text{m}$ per length.

The geometric dimensions of standard test specimens should correspond to the ratios indicated in Figure 2 of EN 50324-1.

At smaller ratios of the geometric dimensions of the piezoceramic parts, deviations of the respective vibration modes appear, only allowing imprecise characterisation of the piezoceramic.

Thickness shear vibrators with rectangular electrode faces have to be polarized in the direction of the long edge.

4 Electrodes

The electrodes for measurement (and for operation) are deposited by

- firing on of precious metal pastes (e.g. Ag, AgPd, Au),
- electroless plating (e.g. Ni, NiAu),
- vacuum coating: evaporation, sputtering (e.g. Ni, CuNi, Au).

5 Environmental requirements

The electrical measurements shall be carried out at temperatures between 20 °C and 25 °C. Before each electrical measurement (after electroding), the test specimen must be stored at these temperatures for at least 24 hours. The test specimen shall be clean and dry.

During measurement, the relative humidity of air in the test laboratory shall be below 65 %.

6 Small signal data - Timing of measurement

The material parameters specified for piezoelectric ceramics (dielectric and electromechanical properties) require essentially linear relationships between the components of mechanical stress and strain on the one hand and of electric field strength and displacement or polarization on the other hand. The material parameters are therefore only valid for a limited range of input level (under measurement and operating conditions).

The limits of linear behaviour can vary significantly between piezoelectric ceramics of different composition.

The dielectric and electromechanical parameters of piezoelectric ceramics are subject to a natural ageing on the basis of the physical phenomenology. Therefore the parameters have to be measured at a defined time not earlier than 24 h after poling. The parameters have to be corrected for measurements in longer intervals after poling, bearing in mind the ageing rates determined according to clause 11.

The parameters of piezoelectric ceramic parts designed as transducers for practical application should be measured within the second decade of ageing, normally 30 days after poling.

7 Number of test specimens

The characteristic material parameters shall be determined on a minimum of 10 test specimens.

8 Methods of measurement

8.1 Determination of relative permittivity and dielectric dissipation factor

The relative permittivity of piezoceramic materials is determined by measurement of the capacitance by means of capacitance measuring meters at $f = (1\,000 \pm 200)$ Hz and $E_m < 1$ V/mm.

The dissipation factor $\tan \delta$ results from the same measuring procedure.

The Curie temperature ϑ_C results from the maximum of temperature dependent capacitance. This maximum is generally far above the operating temperature range (see 9.2.2 and 11).

8.2 Determination of the electromechanical properties

8.2.1 Dynamic method of measurement

The determination of the electromechanical coupling factors, frequency constants, and the mechanical quality factor is made in principle by dynamic methods of measurement, that is the excitation of piezoelectric vibrators to vibration modes at mechanical resonance.

The value of excitation voltages shall be corresponding to a maximum field strength of 0,01 V/mm in general. The dynamic methods of measurement are based on the impedance diagram (Figure 1) and the admittance diagram respectively of the equivalent circuits of a piezoelectric resonator.

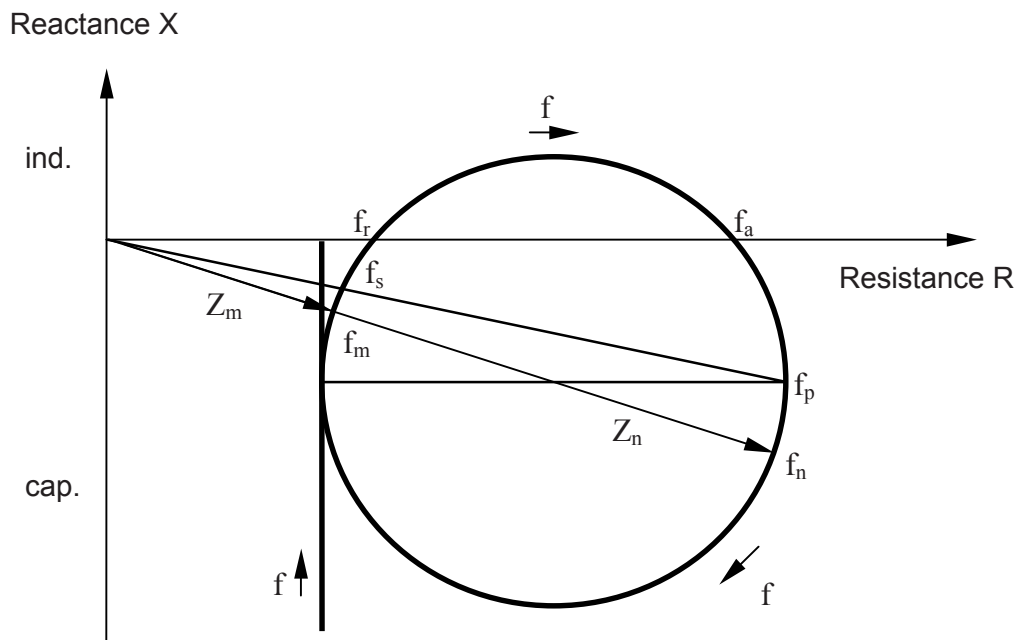


Figure 1 - Vector impedance diagram of a piezoceramic transducer

Three pairs of characteristic frequencies which are significant for the specification of the piezoelectric activity are shown in Figure 1.