

Crystalline silicon terrestrial photovoltaic (PV) modules — Design qualification and type approval

The European Standard EN 61215:2005 has the status of a
British Standard

ICS 27.160

National foreword

This British Standard is the official English language version of EN 61215:2005. It is identical with IEC 61215:2005. It supersedes BS EN 61215:1995 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee GEL/82, Solar photovoltaic energy systems, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 48, an inside back cover and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2005

© BSI 31 October 2005

ISBN 0 580 46268 4

Amendments issued since publication

Amd. No.	Date	Comments

English version

Crystalline silicon terrestrial photovoltaic (PV) modules –
Design qualification and type approval
(IEC 61215:2005)

Modules photovoltaïques (PV) au silicium
cristallin pour application terrestre -
Qualification de la conception
et homologation
(CEI 61215:2005)

Terrestrische kristalline Silizium-
Photovoltaik-(PV)-Module –
Bauartegnung und Bauartzulassung
(IEC 61215:2005)

This European Standard was approved by CENELEC on 2005-05-01. CENELEC members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CENELEC member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CENELEC member into its own language and notified to the Central Secretariat has the same status as the official versions.

CENELEC members are the national electrotechnical committees of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

CENELEC

European Committee for Electrotechnical Standardization
Comité Européen de Normalisation Electrotechnique
Europäisches Komitee für Elektrotechnische Normung

Central Secretariat: rue de Stassart 35, B - 1050 Brussels

© 2005 CENELEC - All rights of exploitation in any form and by any means reserved worldwide for CENELEC members.

Foreword

The text of document 82/376/FDIS, future edition 2 of IEC 61215, prepared by IEC TC 82, Solar photovoltaic energy systems, was submitted to the IEC-CENELEC parallel vote and was approved by CENELEC as EN 61215 on 2005-05-01.

This European Standard supersedes EN 61215:1995.

The following dates were fixed:

- | | | |
|--|-------|------------|
| – latest date by which the EN has to be implemented at national level by publication of an identical national standard or by endorsement | (dop) | 2006-02-01 |
| – latest date by which the national standards conflicting with the EN have to be withdrawn | (dow) | 2008-05-01 |

Annex ZA has been added by CENELEC.

Endorsement notice

The text of the International Standard IEC 61215:2005 was approved by CENELEC as a European Standard without any modification.

CONTENTS

1	Scope and object.....	5
2	Normative references	5
3	Sampling	6
4	Marking	6
5	Testing	7
6	Pass criteria	7
7	Major visual defects.....	7
8	Report	8
9	Modifications	11
10	Test procedures	11
10.1	Visual inspection	11
10.2	Maximum power determination	11
10.3	Insulation test	12
10.4	Measurement of temperature coefficients	13
10.5	Measurement of nominal operating cell temperature (NOCT)	16
10.6	Performance at STC and NOCT.....	24
10.7	Performance at low irradiance	25
10.8	Outdoor exposure test	26
10.9	Hot-spot endurance test	27
10.10	UV preconditioning test.....	32
10.11	Thermal cycling test.....	33
10.12	Humidity-freeze test.....	35
10.13	Damp-heat test.....	36
10.14	Robustness of terminations test.....	37
10.15	Wet leakage current test.....	38
10.16	Mechanical load test.....	39
10.17	Hail test.....	40
10.18	Bypass diode thermal test.....	43
Annex A (informative) Changes in this second edition with respect to the first edition of IEC 61215.....		45
Figure 1 – Qualification test sequence		9
Figure 2 – NOCT correction factor		22
Figure 3 – Reference plate.....		23
Figure 4 – NOCT measurement by reference plate method		23
Figure 5 – Wind correction factor		24
Figure 6 – Hot-spot effect in Type A cell		27
Figure 7 – Reverse characteristics		28
Figure 8 – Hot-spot effect in type B cell		28
Figure 9 – Case SP: Series-parallel connection		29

Figure 10 – Case SPS: series-parallel-series connection	30
Figure 11 – Thermal cycling test	34
Figure 12 – Humidity-freeze cycle	36
Figure 13 – Hail-test equipment	41
Figure 14 – Impact locations illustrated	43
Table 1 – Summary of test levels	10
Table 2 – Ice-ball masses and test velocities	41
Table 3 – Impact locations	42

CRYSTALLINE SILICON TERRESTRIAL PHOTOVOLTAIC (PV) MODULES – DESIGN QUALIFICATION AND TYPE APPROVAL

1 Scope and object

This International Standard lays down IEC requirements for the design qualification and type approval of terrestrial photovoltaic modules suitable for long-term operation in general open-air climates, as defined in IEC 60721-2-1. It applies only to crystalline silicon modules types. A standard for thin-film modules has been published as IEC 61646.

This standard does not apply to modules used with concentrated sunlight.

The object of this test sequence is to determine the electrical and thermal characteristics of the module and to show, as far as is possible within reasonable constraints of cost and time, that the module is capable of withstanding prolonged exposure in climates described in the scope. The actual lifetime expectancy of modules so qualified will depend on their design, their environment and the conditions under which they are operated.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60068-1:1988, *Environmental testing – Part 1: General and guidance*

IEC 60068-2-21:1999, *Environmental testing – Part 2-21: Tests – Test U: Robustness of terminations and integral mounting devices*

IEC 60068-2-78:2001, *Environmental testing – Part 2-78: Tests – Test Cab: Damp heat, steady state*

IEC 60410:1973, *Sampling plans and procedures for inspection by attributes*

IEC 60721-2-1:1982, *Classification of environmental conditions – Part 2: Environmental conditions appearing in nature – Temperature and humidity*

IEC 60891:1987, *Procedures for temperature and irradiance corrections to measured I-V characteristics of crystalline silicon photovoltaic devices*
Amendment 1 (1992)

IEC 60904-1:1987, *Photovoltaic devices – Part 1: Measurements of photovoltaic current-voltage characteristics*

IEC 60904-2:1989, *Photovoltaic devices – Part 2: Requirements for reference solar cells*

IEC 60904-3:1989, *Photovoltaic devices – Part 3: Measurement principles for terrestrial photovoltaic (PV) solar devices with reference spectral irradiance data*

IEC 60904-6:1994, *Photovoltaic devices – Part 6: Requirements for reference solar modules*

IEC 60904-7:1998, *Photovoltaic devices – Part 7: Computation of spectral mismatch error introduced in the testing of a photovoltaic device*

IEC 60904-9:1995, *Photovoltaic devices – Part 9: Solar simulator performance requirements*

IEC 60904-10:1998, *Photovoltaic devices – Part 10: Methods of linearity measurements*

IEC 61853: *Performance testing and energy rating of terrestrial photovoltaic (PV) modules* ¹

ISO/IEC 17025:1999, *General requirements for competence of testing and calibration laboratories*.

3 Sampling

Eight modules for qualification testing (plus spares as desired) shall be taken at random from a production batch or batches, in accordance with the procedure given in IEC 60410. The modules shall have been manufactured from specified materials and components in accordance with the relevant drawings and process sheets and have been subjected to the manufacturer's normal inspection, quality control and production acceptance procedures. The modules shall be complete in every detail and shall be accompanied by the manufacturer's handling, mounting and connection instructions, including the maximum permissible system voltage.

If the bypass diodes are not accessible in the standard modules, a special sample can be prepared for the bypass diode thermal test (10.18). The bypass diode should be mounted physically as it would be in a standard module, with a thermal sensor placed on the diode as required in 10.18.2. This sample does not have to go through the other tests in the sequence depicted in Figure 1.

When the modules to be tested are prototypes of a new design and not from production, this fact shall be noted in the test report (see Clause 8).

4 Marking

Each module shall carry the following clear and indelible markings:

- name, monogram or symbol of manufacturer;
- type or model number;
- serial number;
- polarity of terminals or leads (colour coding is permissible);
- maximum system voltage for which the module is suitable.

The date and place of manufacture shall be marked on the module or be traceable from the serial number.

¹ Under consideration.

5 Testing

Before beginning the testing, all modules, including the control, shall be exposed to sunlight (either real or simulated) to an irradiation level of $5 \text{ kWh}\cdot\text{m}^{-2}$ to $5,5 \text{ kWh}\cdot\text{m}^{-2}$ while open-circuited.

The modules shall be divided into groups and subjected to the qualification test sequences in Figure 1, carried out in the order laid down. Each box refers to the corresponding subclause in this standard. Test procedures and severities, including initial and final measurements where necessary, are detailed in Clause 10.

NOTE 1 Where the final measurements for one test serve as the initial measurements for the next test in the sequence, they need not be repeated. In these cases, the initial measurements are omitted from the test.

In carrying out the tests, the tester shall strictly observe the manufacturer's handling, mounting and connection instructions. Tests given in 10.4, 10.5, 10.6 and 10.7 may be omitted if future IEC 61853 has been or is scheduled to be run on this module type.

Test conditions are summarized in Table 1.

NOTE 2 The test levels in Table 1 are the minimum levels required for qualification. If the laboratory and the module manufacturer agree, the tests may be performed with increased severities.

6 Pass criteria

A module design shall be judged to have passed the qualification tests, and therefore to be IEC type approved, if each test sample meets all the following criteria:

- a) the degradation of maximum output power does not exceed the prescribed limit after each test nor 8 % after each test sequence;
- b) no sample has exhibited any open circuit during the tests;
- c) there is no visual evidence of a major defect, as defined in Clause 7;
- d) the insulation test requirements are met after the tests;
- e) the wet leakage current test requirements are met at the beginning and the end of each sequence and after the damp heat test;
- f) specific requirements of the individual tests are met.

If two or more modules do not meet these test criteria, the design shall be deemed not to have met the qualification requirements. Should one module fail any test, another two modules meeting the requirements of Clause 3 shall be subjected to the whole of the relevant test sequence from the beginning. If one or both of these modules also fail, the design shall be deemed not to have met the qualification requirements. If, however, both modules pass the test sequence, the design shall be judged to have met the qualification requirements.

7 Major visual defects

For the purposes of design qualification and type approval, the following are considered to be major visual defects:

- a) broken, cracked, or torn external surfaces, including superstrates, substrates, frames and junction boxes;


- b) bent or misaligned external surfaces, including superstrates, substrates, frames and junction boxes to the extent that the installation and/or operation of the module would be impaired.
- c) a crack in a cell the propagation of which could remove more than 10 % of that cell's area from the electrical circuit of the module;
- d) bubbles or delaminations forming a continuous path between any part of the electrical circuit and the edge of the module;
- e) loss of mechanical integrity, to the extent that the installation and/or operation of the module would be impaired.

8 Report

Following type approval, a certified report of the qualification tests, with measured performance characteristics and details of any failures and re-tests, shall be prepared by the test agency in accordance with ISO/IEC 17025. The report shall contain the detail specification for the module. Each certificate or test report shall include at least the following information:

- a) a title;
- b) name and address of the test laboratory and location where the tests were carried out;
- c) unique identification of the certification or report and of each page;
- d) name and address of client, where appropriate;
- e) description and identification of the item tested;
- f) characterization and condition of the test item;
- g) date of receipt of test item and date(s) of test, where appropriate;
- h) identification of test method used;
- i) reference to sampling procedure, where relevant;
- j) any deviations from, additions to or exclusions from the test method, and any other information relevant to a specific tests, such as environmental conditions;
- k) measurements, examinations and derived results supported by tables, graphs, sketches and photographs as appropriate including temperature coefficients of short-circuit current, open-circuit voltage and peak power, NOCT, power at NOCT, STC and low irradiance, spectrum of the lamp used for the UV pre-screening test, maximum power loss observed after all of the tests, and any failures observed;
- l) a statement of the estimated uncertainty of the test results (where relevant);
- m) a signature and title, or equivalent identification of the person(s) accepting responsibility for the content of the certificate or report, and the date of issue;
- n) where relevant, a statement to the effect that the results relate only to the items tested;
- o) a statement that the certificate or report shall not be reproduced except in full, without the written approval of the laboratory.

A copy of this report shall be kept by the manufacturer for reference purposes.

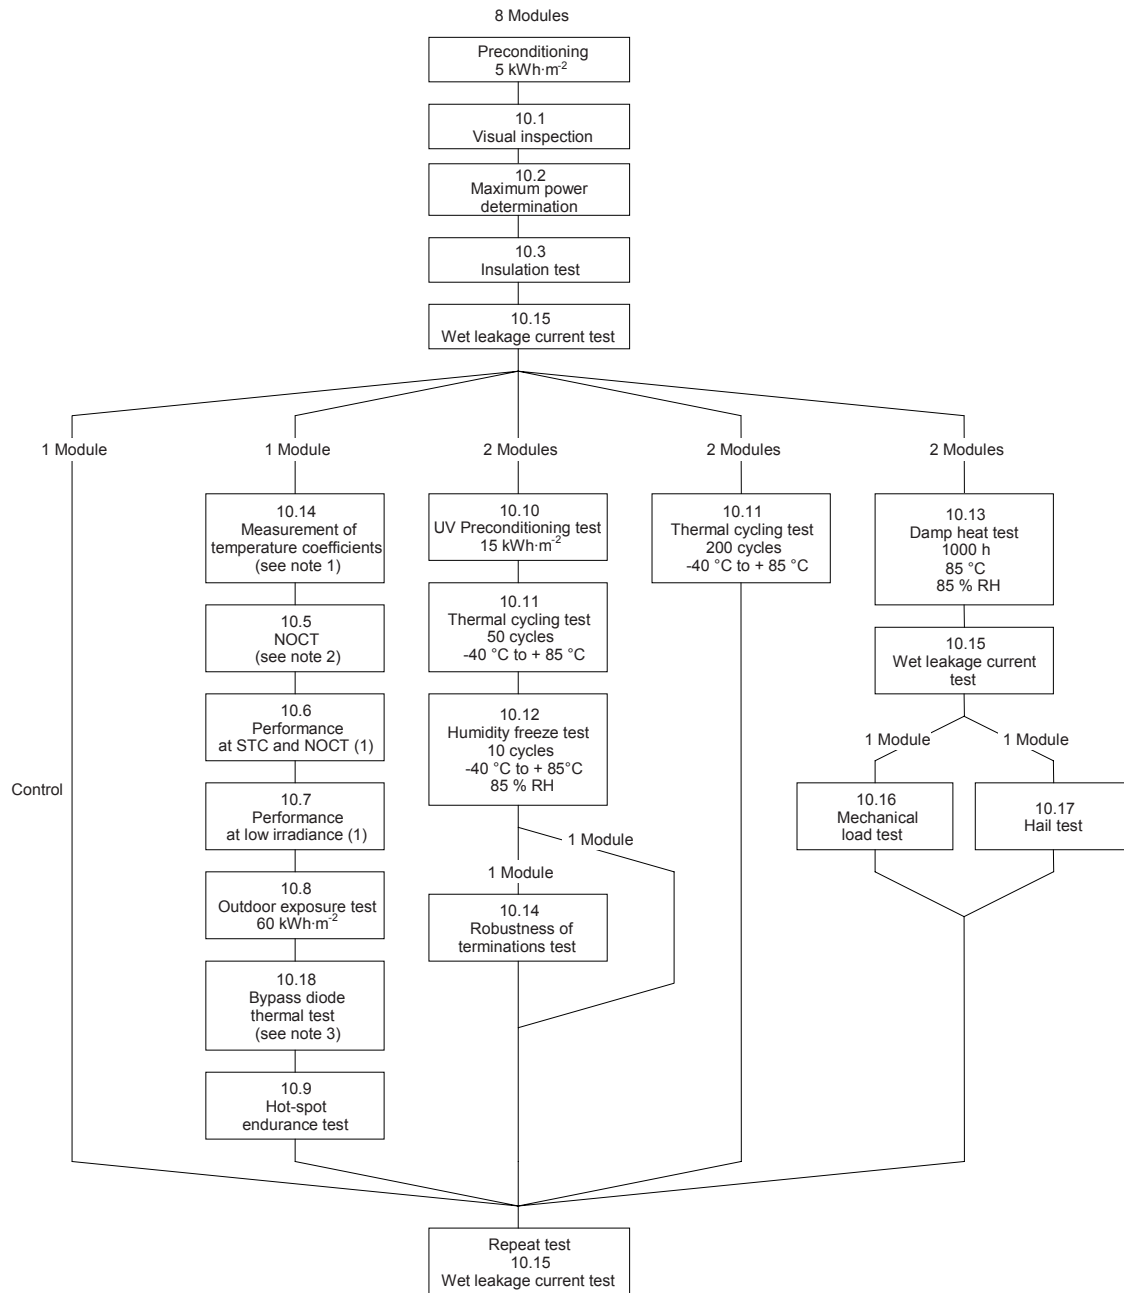

IEC 584/05

NOTE 1 May be omitted if IEC 61853 has been performed.

NOTE 2 In the case of modules not designed for open-rack mounting, the NOCT may be replaced by the equilibrium mean solar cell junction temperature in the standard

Figure 1 – Qualification test sequence

Table 1 – Summary of test levels

Test	Title	Test conditions
10.1	Visual inspection	See detailed inspection list in 10.1.2
10.2	Maximum power determination	See IEC 60904-1
10.3	Insulation test	Dielectric withstand at 1 000 V d.c. + twice the maximum systems voltage for 1 min. For modules with an area of less than 0,1 m ² the insulation resistance shall be not less than 400 MΩ. For modules with an area larger than 0,1 m ² the measured insulation resistance times the area of the module shall be not less than 40 MΩ·m ² measured at 500 V or maximum systems voltage, whichever is greater
10.4	Measurement of temperature coefficients (See note 1)	See details in 10.4 See IEC 60904-10 for guidance.
10.5	Measurement of NOCT (See note 1)	Total solar irradiance: 800 W·m ⁻² Ambient temperature: 20 °C Wind speed: 1 m·s ⁻¹
10.6	Performance at STC and NOCT (See note 1)	Cell temperature: 25 °C and NOCT Irradiance: 1000 and 800 W·m ⁻² with IEC 60904-3 reference solar spectral irradiance distribution
10.7	Performance at low irradiance (see note 1)	Cell temperature: 25 °C Irradiance: 200 W·m ⁻² with IEC 60904-3 reference solar spectral irradiance distribution
10.8	Outdoor exposure test	60 kWh·m ⁻² total solar irradiation
10.9	Hot-spot endurance test	Five-hour exposure to 1 000 W·m ⁻² irradiance in worst-case hot-spot condition
10.10	UV preconditioning	15 kWh·m ⁻² total UV irradiation in the wavelength range from 280 nm to 385 nm with 5 kWh·m ⁻² UV irradiation in the wavelength range from 280 nm to 320 nm
10.11	Thermal cycling test	50 and 200 cycles from –40 °C to + 85 °C with STC peak power current during 200 cycles
10.12	Humidity freeze test	10 cycles from + 85 °C, 85 % RH to –40 °C
10.13	Damp heat test	1 000 h at + 85 °C, 85 % RH
10.14	Robustness of termination test	As in IEC 60068-2-21
10.15	Wet leakage current test	See details in 10.15 For modules with an area of less than 0,1 m ² the insulation resistance shall be not less than 400 MΩ. For modules with an area larger than 0,1 m ² the measured insulation resistance times the area of the module shall be not less than 40 MΩ·m ² to be measured at 500 V or maximum systems voltage, whichever is greater
10.16	Mechanical load test	Three cycles of 2 400 Pa uniform load, applied for 1 h to front and back surfaces in turn. Optional snow load of 5 400 Pa during last front cycle
10.17	Hail test	25 mm diameter ice ball at 23,0 m·s ⁻¹ , directed at 11 impact locations
10.18	Bypass diode thermal test	One hour at I_{sc} and 75 °C One hour at 1,25 times I_{sc} and 75 °C

NOTE 1 These tests may be omitted if future IEC 61853 has been performed on this module type.

9 Modifications

Any change in the design, materials, components or processing of the module may require a repetition of some or all of the qualification tests to maintain type approval.

10 Test procedures

10.1 Visual inspection

10.1.1 Purpose

To detect any visual defects in the module.

10.1.2 Procedure

Carefully inspect each module under an illumination of not less than 1 000 lux for the following conditions:

- cracked, bent, misaligned or torn external surfaces;
- broken cells;
- cracked cells;
- faulty interconnections or joints;
- cells touching one another or the frame;
- failure of adhesive bonds;
- bubbles or delaminations forming a continuous path between a cell and the edge of the module;
- tacky surfaces of plastic materials;
- faulty terminations, exposed live electrical parts;
- any other conditions which may affect performance.

Make note of and/or photograph the nature and position of any cracks, bubbles or delaminations, etc. which may worsen and adversely affect the module performance in subsequent tests.

10.1.3 Requirements

Visual conditions other than the major visual defects listed in Clause 7 are acceptable for the purposes of type approval.

10.2 Maximum power determination

10.2.1 Purpose

To determine the maximum power of the module before and after the various environmental tests. Repeatability of the test is the most important factor.

10.2.2 Apparatus

- a) A radiant source (natural sunlight or a solar simulator class B or better in accordance with IEC 60904-9).

- b) A PV reference device in accordance with IEC 60904-2 or IEC 60904-6. If a class B simulator is used the reference device shall be a reference module of the same size with the same cell technology (to match spectral response) as the test specimen.
- c) A suitable mount for supporting the test specimen and the reference device in a plane normal to the radiant beam.
- d) A means for monitoring the temperature of the test specimen and the reference device to an accuracy of ± 1 °C and repeatability of $\pm 0,5$ °C.
- e) Equipment for measuring the current of the test specimen and reference device to an accuracy of $\pm 0,2$ % of the reading;
- f) Equipment for measuring the voltage of the test specimen and reference device to an accuracy of $\pm 0,2$ % of the reading.

10.2.3 Procedure

Determine the current-voltage characteristic of the module in accordance with IEC 60904-1 at a specific set of irradiance and temperature conditions (a recommended range is a cell temperature between 25 °C and 50 °C and an irradiance between 700 W·m⁻² and 1 100 W·m⁻²) using natural sunlight or a class B or better simulator conforming to the requirements of IEC 60904-9. In special circumstances when modules are designed for operation under a different range of conditions, the current-voltage characteristics can be measured using temperature and irradiance levels similar to the expected operating conditions. Temperature and irradiance corrections can be made in accordance with IEC 60891 in order to compare sets of measurements made on the same module before and after environmental tests. However, every effort should be made to assure that peak power measurements are made under similar operating conditions, that is minimize the magnitude of the correction by making all peak power measurements on a particular module at approximately the same temperature and irradiance. Repeatability of the maximum power measurement must be better than ± 1 %.

NOTE Use the control module as a check every time the test modules are measured.

10.3 Insulation test

10.3.1 Purpose

The purpose is to determine whether or not the module is sufficiently well-insulated between current-carrying parts and the frame or the outside world.

10.3.2 Apparatus

- a) DC voltage source, with current limitation, capable of applying 500 V or 1 000 V plus twice the maximum system voltage of the module according to 10.3.4 c).
- b) An instrument to measure the insulation resistance.

10.3.3 Test conditions

The test shall be made on modules at ambient temperature of the surrounding atmosphere (see IEC 60068-1) and in a relative humidity not exceeding 75 %.

10.3.4 Procedure

- a) Connect the shorted output terminals of the module to the positive terminal of a d.c. insulation tester with a current limitation.
- b) Connect the exposed metal parts of the module to the negative terminal of the tester. If the module has no frame or if the frame is a poor electrical conductor, wrap a conductive foil around the edges and over the back of the module. Connect the foil to the negative terminal of the tester.
- c) Increase the voltage applied by the tester at a rate not exceeding $500 \text{ V}\cdot\text{s}^{-1}$ to a maximum equal to 1 000 V plus twice the maximum system voltage (i.e. the maximum system voltage marked on the module by the manufacturer). If the maximum system voltage does not exceed 50 V, the applied voltage shall be 500 V. Maintain the voltage at this level for 1 min.
- d) Reduce the applied voltage to zero and short-circuit the terminals of the test equipment to discharge the voltage build-up in the module.
- e) Remove the short circuit.
- f) Increase the voltage applied by the test equipment at a rate not to exceed $500 \text{ V}\cdot\text{s}^{-1}$ to 500 V or the maximum system voltage for the module, whichever is greater. Maintain the voltage at this level for 2 min. Then determine the insulation resistance.
- g) Reduce the applied voltage to zero and short-circuit the terminals of the test equipment to discharge the voltage build-up in the module.
- h) Remove the short circuit and disconnect the test equipment from the module.

NOTE If the module does not have a metal frame nor a glass superstrate, the insulation test should be repeated with the metallic plate placed on the front of the module as in 10.3.4b).

10.3.5 Test requirements

The following requirements are necessary:

- no dielectric breakdown or surface tracking during step c);
- for modules with an area of less than $0,1 \text{ m}^2$ the insulation resistance shall be not less than $400 \text{ M}\Omega$;
- for modules with an area larger than $0,1 \text{ m}^2$ the measured insulation resistance times the area of the module shall be not less than $40 \text{ M}\Omega\cdot\text{m}^2$.

10.4 Measurement of temperature coefficients

10.4.1 Purpose

The purpose is to determine the temperature coefficients of current (α), voltage (β) and peak power (δ) from module measurements. The coefficients so determined are valid at the irradiance at which the measurements were made. See IEC 60904-10 for evaluation of module temperature coefficients at different irradiance levels.

10.4.2 Apparatus

The following apparatus is required to control and measure the test conditions:

- a) a radiant source (natural sunlight or solar simulator, class B or better in accordance with IEC 60904-9) of the type to be used in subsequent tests;

- b) a PV reference device having a known short-circuit current versus irradiance characteristic determined by calibrating against an absolute radiometer in accordance with IEC 60904-2 or IEC 60904-6;
- c) any equipment necessary to change the temperature of the test specimen over the range of interest;
- d) a suitable mount for supporting the test specimen and the reference device in the same plane normal to the radiant beam;
- e) a means for monitoring the temperature of the test specimen and reference device to an accuracy of ± 1 °C, and repeatability of $\pm 0,5$ °C;
- f) equipment for measuring the current of the test specimen and reference device to an accuracy of $\pm 0,2$ % of the reading;
- g) equipment for measuring the voltage of the test specimen and reference device to an accuracy of $\pm 0,2$ % of the reading;

10.4.3 Procedure

There are two acceptable procedures for measuring the temperature coefficients.

10.4.3.1 Procedure in natural sunlight

- a) Measurement in natural sunlight shall only be made when:
 - the total irradiance is at least as high as the upper limit of the range of interest;
 - the irradiance variation caused by short-term oscillations (clouds, haze, or smoke) is less than ± 2 % of the total irradiance as measured by the reference device;
 - the wind speed is less than $2 \text{ m}\cdot\text{s}^{-1}$.
- b) Mount the reference device co-planar with the test module so that both are normal to the direct solar beam within $\pm 5^\circ$. Connect to the necessary instrumentation.

NOTE The measurements described in the following subclauses should be made as expeditiously as possible within a few hours on the same day to minimize the effect of changes in the spectral conditions. If not, spectral corrections may be required.
- c) If the test module and reference device are equipped with temperature controls, set the controls at the desired level.
- d) If temperature controls are not used, shade the specimen and the reference device from the sun and wind until its temperature is uniform within ± 1 °C of the ambient air temperature, or allow the test specimen to equilibrate to its stabilized temperature, or cool the test specimen to a point below the required test temperature and then let the module warm up naturally. The reference device should also stabilize within ± 1 °C of its equilibrium temperature before proceeding.
- e) Record the current-voltage characteristic and temperature of the specimen concurrently with recording the short-circuit current and temperature of the reference device at the desired temperatures. If necessary, make the measurements immediately after removing the shade.
- f) The irradiance G_o shall be calculated in accordance with IEC 60891 from the measured current (I_{sc}) of the PV reference device, and its calibration value at STC (I_{rc}). A correction should be applied to account for the temperature of the reference device T_m using the specified temperature coefficient of the reference device α_{rc} .