



BSI Standards Publication

Wearable electronic devices and technologies

Part 401-1: Devices and systems: functional elements — Evaluation
method of the stretchable resistive strain sensor

National foreword

This British Standard is the UK implementation of EN IEC 63203-401-1:2023. It is identical to IEC 63203-401-1:2023.

The UK participation in its preparation was entrusted to Technical Committee AMT/9, Printed Electronics.

A list of organizations represented on this committee can be obtained on request to its committee manager.

Contractual and legal considerations

This publication has been prepared in good faith, however no representation, warranty, assurance or undertaking (express or implied) is or will be made, and no responsibility or liability is or will be accepted by BSI in relation to the adequacy, accuracy, completeness or reasonableness of this publication. All and any such responsibility and liability is expressly disclaimed to the full extent permitted by the law.

This publication is provided as is, and is to be used at the recipient's own risk.

The recipient is advised to consider seeking professional guidance with respect to its use of this publication.

This publication is not intended to constitute a contract. Users are responsible for its correct application.

© The British Standards Institution 2023
Published by BSI Standards Limited 2023

ISBN 978 0 539 01308 5

ICS 31.020; 31.180

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 November 2023.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

English Version

Wearable electronic devices and technologies - Part 401-1:
Devices and systems: functional elements - Evaluation method
of the stretchable resistive strain sensor
(IEC 63203-401-1:2023)

Technologies et dispositifs électroniques prêt-à-porter -
Partie 401-1 : Dispositifs et systèmes: éléments de
fonctionnement - Méthode d'évaluation de la jauge de
contrainte extensible de type résistif
(IEC 63203-401-1:2023)

Tragbare elektronische Geräte und Technologien - Teil 401-
1: Produkte und Systeme - Funktionselemente -
Bewertungsverfahren für dehnbare Widerstandssensoren
(IEC 63203-401-1:2023)

This European Standard was approved by CENELEC on 2023-11-13. CENELEC members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CENELEC member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CENELEC member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CENELEC members are the national electrotechnical committees of Austria, Belgium, Bulgaria, Croatia, Cyprus, the Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, the Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and the United Kingdom.



European Committee for Electrotechnical Standardization
Comité Européen de Normalisation Electrotechnique
Europäisches Komitee für Elektrotechnische Normung

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

European foreword

The text of document 124/223/FDIS, future edition 1 of IEC 63203-401-1, prepared by IEC/TC 124 "Wearable electronic devices and technologies" was submitted to the IEC-CENELEC parallel vote and approved by CENELEC as EN IEC 63203-401-1:2023.

The following dates are fixed:

- latest date by which the document has to be implemented at national (dop) 2024-08-13 level by publication of an identical national standard or by endorsement
- latest date by which the national standards conflicting with the (dow) 2026-11-13 document have to be withdrawn

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CENELEC shall not be held responsible for identifying any or all such patent rights.

Any feedback and questions on this document should be directed to the users' national committee. A complete listing of these bodies can be found on the CENELEC website.

Endorsement notice

The text of the International Standard IEC 63203-401-1:2023 was approved by CENELEC as a European Standard without any modification.

In the official version, for Bibliography, the following notes have to be added for the standard indicated:

IEC 63203-101-1:2021	NOTE	Approved as EN IEC 63203-101-1:2021 (not modified)
IEC 62047-22:2014	NOTE	Approved as EN 62047-22:2014 (not modified)
IEC 62047-2:2006	NOTE	Approved as EN 62047-2:2006 (not modified)

Annex ZA (normative)

Normative references to international publications with their corresponding European publications

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

NOTE 1 Where an International Publication has been modified by common modifications, indicated by (mod), the relevant EN/HD applies.

NOTE 2 Up-to-date information on the latest versions of the European Standards listed in this annex is available here: www.cencenelec.eu.

<u>Publication</u>	<u>Year</u>	<u>Title</u>	<u>EN/HD</u>	<u>Year</u>
IEC 62899-202-4	2021	Printed electronics - Part 202-4: Materials - Conductive ink - Measurement methods for properties of stretchable printed layers (conductive and insulating)	-	-
ISO 291	2008	Plastics - Standard atmospheres for conditioning and testing	EN ISO 291	2008
ISO/TS 12901-2	2014	Nanotechnologies - Occupational risk management applied to engineered nanomaterials - Part 2: Use of the control banding approach	-	-

CONTENTS

FOREWORD	4
1 Scope	6
2 Normative references	6
3 Terms and definitions	6
3.1 Terms and definitions	6
3.2 Symbols and abbreviated terms	7
4 Test environments	7
5 Test specimen	8
5.1 Shape of the test specimen of the stretchable strain sensor	8
5.2 Measurement of dimensions	8
6 Test method and test apparatus	9
6.1 General	9
6.2 Test apparatus and measurement	9
7 Test procedure	13
8 Measurement of sensor performance and endurance	13
8.1 Gauge factor	13
8.1.1 General	13
8.1.2 Purpose	13
8.1.3 Test procedure	14
8.2 Linearity	14
8.2.1 Purpose	14
8.2.2 Test procedure	14
8.3 Response characteristics	14
8.3.1 General	14
8.3.2 Purpose	15
8.3.3 Test procedure	15
8.4 Hysteresis	15
8.4.1 General	15
8.4.2 Purpose	15
8.4.3 Test procedure	15
9 Test report	16
Annex A (informative) Strain sensor resistance measurement	17
Annex B (informative) Effects of strain rate on performances of the stretchable strain sensor	18
Annex C (informative) Measurement of response time of the stretchable strain sensor	19
Annex D (normative) Examples of hysteresis calculations	20
Bibliography	22
Figure 1 – Shape of a test specimen of the stretchable strain sensor	8
Figure 2 – Example of stretching test machine	9
Figure 3 – Schematic drawing of a stretching test machine and two-wire measurement method	10
Figure 4 – Schematic drawing of a stretching test machine and four-wire measurement method	12
Figure 5 – Linearity measurement of the stretchable strain sensor	14

Figure A.1 – Changes in electrical resistances when the strain sensor is stretched.....	17
Figure B.1 – Examples of the effects of strain rate on performances of the stretchable strain sensor	18
Figure C.1 – Examples of the response time of the stretchable strain sensors	19
Figure D.1 – Example of the hysteresis behaviour of a stretchable strain sensor	20
Figure D.2 – Example calculation of hysteresis behaviour.....	20
Figure D.3 – Calculation of hysteresis behaviour of the stretchable strain sensor	21
Figure D.4 – Example of calculation of the degree of hysteresis	21

INTERNATIONAL ELECTROTECHNICAL COMMISSION

WEARABLE ELECTRONIC DEVICES AND TECHNOLOGIES –

Part 401-1: Devices and systems: functional elements – Evaluation method of the stretchable resistive strain sensor

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

IEC 63203-401-1 has been prepared by IEC technical committee 124: Wearable electronic devices and technologies. It is an International Standard.

The text of this International Standard is based on the following documents:

Draft	Report on voting
124/223/FDIS	124/239/RVD

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/publications.

A list of all parts in the IEC 63203 series, published under the general title *Wearable electronic devices and technologies*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

IMPORTANT – The "colour inside" logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

WEARABLE ELECTRONIC DEVICES AND TECHNOLOGIES –

Part 401-1: Devices and systems: functional elements – Evaluation method of the stretchable resistive strain sensor

1 Scope

This part of IEC 63203-401 specifies a measurement method of tensile strain for stretchable, resistive strain sensors. This document describes characterization procedures for evaluation of the gauge factor, linearity, response characteristics, and hysteresis of unimodal tension sensors but is not appropriate for assessment of the physical properties of the sensor material such as the elastic modulus, elastic limit, and Poisson's ratio.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 62899-202-4:2021, *Printed electronics – Part 202-4: Materials – Conductive ink – Measurement methods for properties of stretchable printed layers (conductive and insulating)*

ISO 291:2008, *Plastics – Standard atmospheres for conditioning and testing*

ISO/TS 12901-2:2014, *Nanotechnologies – Occupational risk management applied to engineered nanomaterials – Part 2: Use of the control banding approach*

3 Terms and definitions

3.1 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

3.1.1

stretchable substrate

stretchable material

substrate or material able to recover original size and shape immediately after the removal of the extending force causing deformation

Note 1 to entry: In this document, the notion of "stretchability" is based on the elasticity of the substrate.

[SOURCE: IEC 63203-101-1:2021, 3.10 [1]]

3.1.2**gauge factor** G_F

ratio of the change in electrical resistance divided by the original resistance (R_0 , resistance in the undeformed configuration) to engineering strain (e) along the axis of the stretching

Note 1 to entry: Gauge factor is expressed as $G_F = \frac{(R - R_0)/R_0}{e}$, where R_0 is the initial resistance in the undeformed configuration, R is the electrical resistance in the deformed configuration, and e is the tensile strain.

[SOURCE: IEC 62047-22:2014, 3.1.1 [2] modified – "along the axis of the stretching" has been added to the definition, and, in the note to entry, "where R is the electrical resistance in the deformed configuration" has been replaced with "where R_0 is the initial resistance in the undeformed configuration, R is the electrical resistance in the deformed configuration, and e is the tensile strain".]

3.1.3**gauge length**

length of the strain-sensitive section of a stretchable strain sensor in the direction of the measurement axis

3.2 Symbols and abbreviated terms

Symbol	Unit	Description
a	mm	Width of the resistive thin film
h	μm	Thickness of the resistive thin film
l_0	mm	Gauge length of the sensor
l_1	mm	Length of the stretchable resistive thin film

4 Test environments


The tests shall be performed under constant temperature and humidity conditions. As environmental conditions, including temperature and humidity, can affect the electrical and mechanical properties of resistive materials and substrates, the testing temperature and humidity shall be monitored during testing. Fluctuations in temperature during a test shall be kept to less than ± 2 °C. Thus, when testing such materials, the change in relative humidity (RH) in the testing laboratory shall be kept to less than ± 10 % RH. The recommended temperature and relative humidity are 23 °C ± 2 °C and relative humidity of 50 ± 10 %, respectively, conforming to standard atmosphere class 2 specified in ISO 291. Whenever testing is conducted, the environmental conditions shall be recorded.

5 Test specimen

5.1 Shape of the test specimen of the stretchable strain sensor

The shape of the stretchable strain sensor to be tested shall be rectangular or square. The test specimen has a stretchable substrate, and the resistive thin film is deposited on this stretchable substrate or on a single layer of resistive composite materials. Figure 1 presents the basic shape of the test specimen including pads or metal layer for electrical connection. For the pad, the thin metal film or coating is deposited or fabricated on the resistive sensor layer. The film materials with low stiffness are fabricated as thin as possible (for example, less than a few micrometers in thickness) so that the stretching of the resistive sensor material is not restricted due to the pad material. Some resistive composite sensor materials can be sensitive to the deposition process. Thus, there will be a possibility that the resistive sensor materials can be damaged during the deposition process. In this case, metal clips can be used for electrical connection instead of metal pads. The length of the stretchable resistive thin film l_1 can be the same as the length of the stretchable substrate. The width of stretchable substrate is more than or equal to the width of the resistive thin film.

For uniform strain distribution, a rectangular strip shape is recommended. Since the change in electrical resistance is related to the strain, the electrical resistance is measured in a region of nearly uniform strain within the gauge length. The gauge length is chosen as the region where the strain of the stretchable sensor layer is uniform over the cross-sectional area.

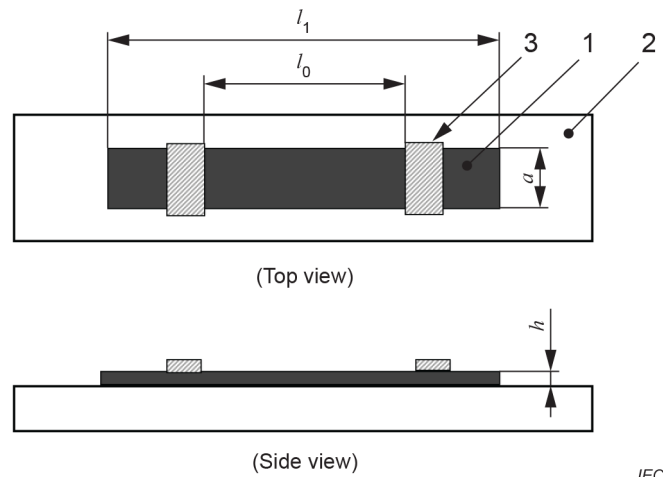

Key

- | | |
|--------------------------------------|-------------------------|
| 1 Stretchable strain sensor material | 2 Stretchable substrate |
| 3 Pad for electrical connection | |

Figure 1 – Shape of a test specimen of the stretchable strain sensor

5.2 Measurement of dimensions

The length of the stretchable strain sensor, in particular the gauge length of the sensor shall be measured accurately, because the dimension of the length can be used to determine the mechanical and electrical properties of the strain sensor. Each test specimen should be measured directly. The test specimens' dimensions shall be specified within the maximum error of $\pm 5\%$.


6 Test method and test apparatus

6.1 General

The test is performed by applying a tensile load to a test specimen. The tensile strain induced by the tensile load shall be uniform in a pre-defined gauge section in the elastic region of the substrate or the thin resistive material. To measure the change in electrical resistance along with the change in mechanical strain, the section of gauge shall be selected carefully. The gauge section used to measure the mechanical strain shall be coincident with or scalable to the section used to measure the electrical resistance.


6.2 Test apparatus and measurement

The stretching test machine includes the grips to hold a test sample, the actuating motor which regulates moving distance and moving speed while testing. Stretching shall be applied along the tensile axis of the test sample to avoid the bending or twisting of the test piece. An example of a stretching test machine is shown in Figure 2.

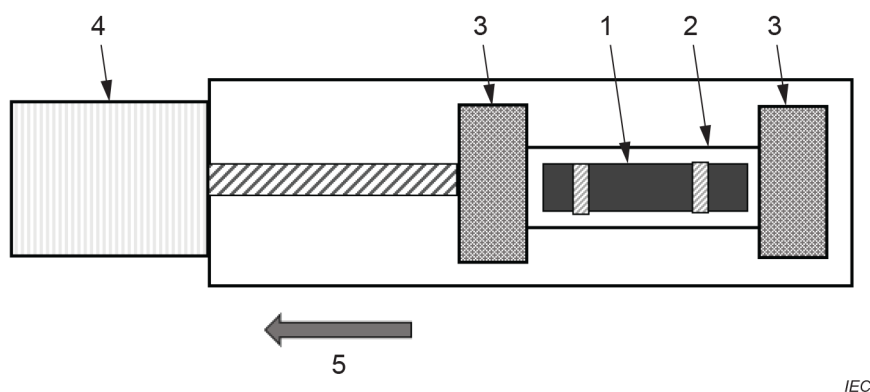

IEC

(a) Schematic drawing of stretching test machine (top view)

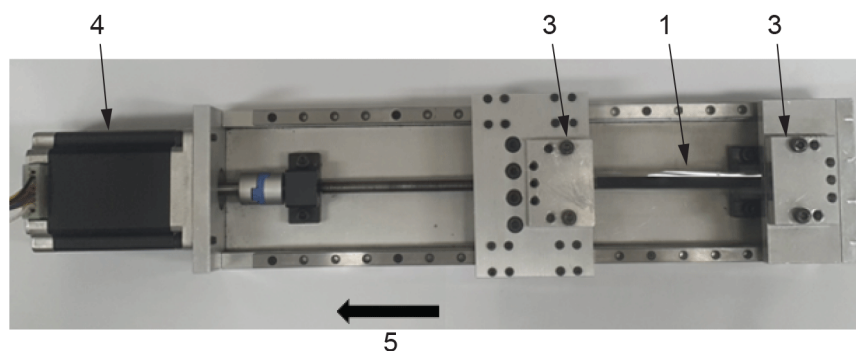

IEC

(b) Photograph of example of a stretching test machine (top view)


Key

- | | |
|-----------------------------|-------------------------|
| 1 Stretchable strain sensor | 2 Stretchable substrate |
| 3 Grip | 4 Actuating motor |
| 5 Actuating direction | |

Figure 2 – Example of stretching test machine

A vertical stretching test machine can be used if the deformation of the stretchable sensor due to its own weight can be ignored. The electrical measurement circuit can use two-wire or four-wire methods depending on the magnitude of the electrical resistance of the sensor. For a sensor that has an electrical resistance greater than 1 k Ω , a two-wire method can be used for ease of measurement. For a sensor that has an electrical resistance 1 k Ω or less, the four-wire method shall be used to eliminate contact- and lead-wire resistance.

Figure 3 shows the schematic drawing of the two-wire method and test machine setup. The test machine consists of grips, load cell (or strain measurement sensor), motor or actuator. Prepare a stretchable specimen with a gauge length longer than the distance between the grips. The resistance measurement setup consists of a constant-current source, a voltmeter, metal clips or electrodes. The clips that are made of rust-resistant metal or that have a surface treatment (such as gold plating) to prevent rust shall be used.

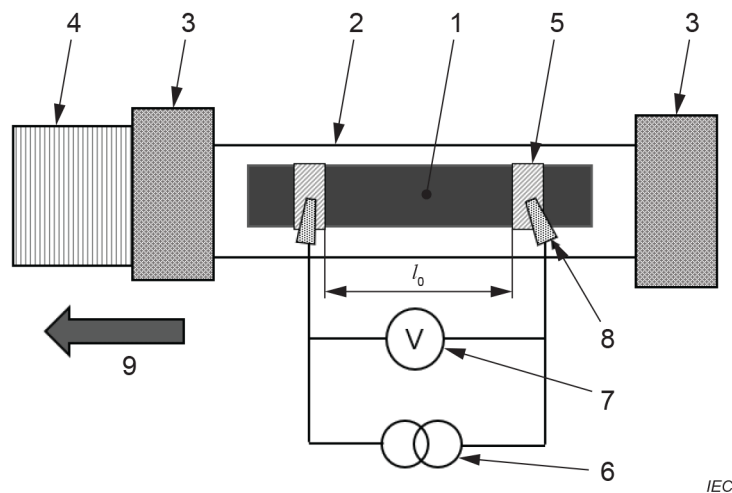

Key

- | | |
|-------------------------------|-----------------------------------|
| 1 Stretchable sensor material | 2 Stretchable substrate |
| 3 Grip | 4 Motor or actuator |
| 5 Pad | 6 Constant current source |
| 7 Voltmeter | 8 Metal electrode (or metal clip) |
| 9 Actuating direction | |

Figure 3 – Schematic drawing of a stretching test machine and two-wire measurement method


Figure 4 shows the schematic drawing of the four-wire method and test machine setup. The resistance measurement setup consists of a constant-current source, a voltmeter, metal electrodes or metal clips (voltage electrode), and metal electrodes (current electrode). Therefore, the constant-current source pad and voltmeter pad for electrical connection are required at each side of the sample. The fabrication of pads is explained in 5.1. Figure 4 a) illustrates the initial test setup, and Figure 4 b) illustrates the test setup during stretching. The examples of sensor resistance or changes in resistance during stretching test are illustrated in Annex A.

The quality-certified rulers or mechanical extensometer are used to measure the stretched gauge length (l_s). Several optical methods using laser, interference light, camera, and image systems such as digital image correlation (DIC) systems can be utilized to measure the stretched gauge length. Several methods are available to measure resistance changes of the sensor with sufficient resolution and accuracy.

During stretching, there will be slippage or friction between the pad and metal electrode or metal clip which will cause the distortion of the electrical resistance value of the sensor. In this case, more stable electrical connection such as soldering of electrical wire to the pad shall be used. In particular, the continuous cyclic stretching test shall require stable electrical connection. Figure 4 c) illustrates an example of the test setup during stretching.


Figure 4 d) illustrates another example of test setup. This test setup and test method are described in detail and shall be as described in IEC 62899-202-4:2021. When this test method is used, it is noted that the stress is not relatively uniform across the sample in lateral direction.

The test machine shall use the gripping system which holds the test sample evenly and firmly to avoid the slippage of the sample during the stretching test. The gripping system shall not cause premature damage, failure and scratch in the sample. For highly stretchable samples, including elastomers, over-tightening of the gripping is also to be avoided to prevent concentrating the local stress, scratching, or damaging the substrate in the area that is clamped. The sample shall not twist or bend during stretching.

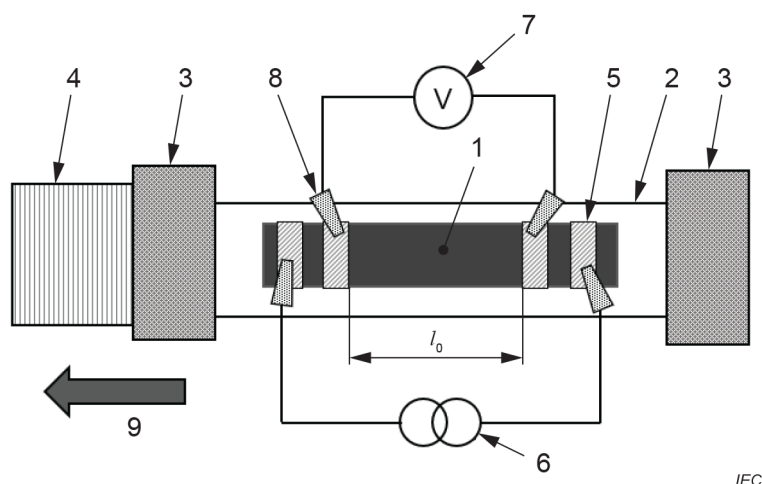

IEC

a) Initial test setup using four-wire method

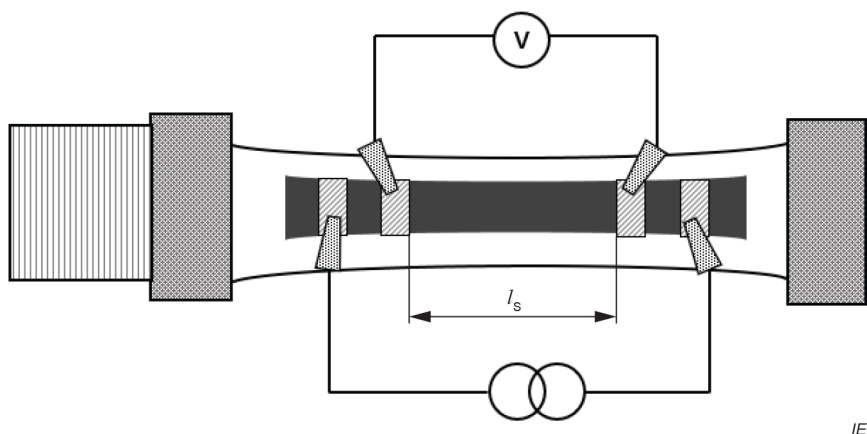

IEC

b) Test setup during stretching using four-wire method