



BSI Standards Publication

Protective clothing — Mechanical properties — Determination of resistance to cutting by sharp objects

National foreword

This British Standard is the UK implementation of EN ISO 13997:2024. It is identical to ISO 13997:2024. It supersedes BS EN ISO 13997:2023, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PH/3/14, Mechanical Impact and Protective Gloves Personal Protective Equipment.

A list of organizations represented on this committee can be obtained on request to its committee manager.

Contractual and legal considerations

This publication has been prepared in good faith, however no representation, warranty, assurance or undertaking (express or implied) is or will be made, and no responsibility or liability is or will be accepted by BSI in relation to the adequacy, accuracy, completeness or reasonableness of this publication. All and any such responsibility and liability is expressly disclaimed to the full extent permitted by the law.

This publication is provided as is, and is to be used at the recipient's own risk.

The recipient is advised to consider seeking professional guidance with respect to its use of this publication.

This publication is not intended to constitute a contract. Users are responsible for its correct application.

© The British Standards Institution 2024
Published by BSI Standards Limited 2024

ISBN 978 0 539 30647 7

ICS 13.340.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2024.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN ISO 13997

October 2024

ICS 13.340.10

Supersedes EN ISO 13997:2023

English Version

Protective clothing - Mechanical properties -
Determination of resistance to cutting by sharp objects
(ISO 13997:2024)

Habillement de protection - Propriétés mécaniques -
Détermination de la résistance à la coupure par des
objets tranchants (ISO 13997:2024)

Schutzkleidung - Mechanische Eigenschaften -
Bestimmung des Widerstandes gegen Schnitte mit
scharfen Gegenständen (ISO 13997:2024)

This European Standard was approved by CEN on 19 October 2024.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

© 2024 CEN All rights of exploitation in any form and by any means reserved
worldwide for CEN national Members.

Ref. No. EN ISO 13997:2024 E

European foreword

This document (EN ISO 13997:2024) has been prepared by Technical Committee ISO/TC 94 "Personal safety -- Personal protective equipment" in collaboration with Technical Committee CEN/TC 162 "Protective clothing including hand and arm protection and lifejackets" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 2025, and conflicting national standards shall be withdrawn at the latest by April 2025.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 13997:2023.

Any feedback and questions on this document should be directed to the users' national standards body/national committee. A complete listing of these bodies can be found on the CEN website.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and the United Kingdom.

Endorsement notice

The text of ISO 13997:2024 has been approved by CEN as EN ISO 13997:2024 without any modification.

Contents		Page
Foreword.....		iv
Introduction.....		v
1	Scope.....	1
2	Normative references.....	1
3	Terms and definitions.....	1
4	Sampling.....	2
4.1	General.....	2
4.2	Textiles and other materials.....	2
4.3	Gloves.....	2
4.4	Conditioning.....	3
5	Test method.....	4
5.1	Principle.....	4
5.2	Test apparatus.....	5
5.3	Calibration.....	9
5.3.1	Beam balancing procedure.....	9
5.3.2	Cutting speed adjustment.....	9
5.3.3	Validation of blades.....	9
5.4	Test procedure.....	10
5.4.1	Specimen mounting.....	10
5.4.2	Test procedure for measuring the cutting stroke length.....	11
5.4.3	Test procedure for determining the calculated cutting force.....	11
5.4.4	Calculations.....	12
6	Test report.....	12
Annex A (informative) Inter-laboratory test data analysis.....		14
Annex B (normative) Calculated cutting force determination.....		16
Annex C (normative) Testing of the calibration material (see 5.3.3.1).....		21
Bibliography.....		22

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO document should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

ISO draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). ISO takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, ISO had not received notice of (a) patent(s) which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at www.iso.org/patents. ISO shall not be held responsible for identifying any or all such patent rights.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 94, *Personal safety — Personal protective equipment*, Subcommittee SC 13, *Protective clothing*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 162, *Protective clothing including hand and arm protection and lifejackets*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This third edition cancels and replaces the second edition (ISO 13997:2023), of which it constitutes a minor revision.

The main changes are as follows:

- [Figure 7 a\)](#) was replaced;
- Footnote 2 was moved to the [Figure 7](#) title;
- the Excel file that can be downloaded using the link in the note to [Table B.2](#) was replaced (there was a correction because in few specific cases Excel did not work as planned).

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

Although textiles, composites, leather, rubbers and reinforced materials may resist cutting by sharp edges in different ways, a test method for evaluating the resistance to cut of materials in protective clothing should be applicable to all materials. The test described in this document provides a method that allows calculations of the downwards (normal) force required to cause a blade drawn across the sample for a fixed distance to cut through the specimen.

The performance of protective clothing materials may be classified using the numerical values obtained from this test.

Protective clothing — Mechanical properties — Determination of resistance to cutting by sharp objects

1 Scope

This document specifies a tomodynamometer cut test method and related calculations, for use on materials and assemblies designed for protective clothing, including gloves. The test determines resistance to cutting by sharp edges, such as knives, sheet metal parts, swarf, glass, bladed tools and castings.

When this document is cited as a test method in a material or product requirement standard, that standard contains the necessary information to permit the application of this document to the particular product.

This test does not provide data on the resistance to penetration by pointed objects such as needles and thorns, or the point of sharp-edged blades. The test described in this document is not considered suitable for testing materials made from chain mail and metal plates. The text of this document does not include provisions for the safeguard of the operator.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 34-1, *Rubber, vulcanized or thermoplastic — Determination of tear strength — Part 1: Trouser, angle and crescent test pieces*

ISO 37, *Rubber, vulcanized or thermoplastic — Determination of tensile stress-strain properties*

ISO 48-4, *Rubber, vulcanized or thermoplastic — Determination of hardness — Part 4: Indentation hardness by durometer method (Shore hardness)*

ISO 2781, *Rubber, vulcanized or thermoplastic — Determination of density*

ISO 11610, *Protective clothing — Vocabulary*

ISO 23388:2018, *Protective gloves against mechanical risks*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11610 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

3.1

cut-through

event which has occurred when the blade edge first contacts the conducting material below the test specimen

3.2

cutting force

calculated force that would be required to be applied to a blade of standard sharpness to cut through a material in a blade stroke of length 20 mm

3.3

cutting stroke length

distance the cutting-edge travels before *cut-through* (3.1) occurs

4 Sampling

4.1 General

Unless otherwise specified, specimen dimensions should not be less than 25 mm by 100 mm as this allows for several cuts on the same sample (see 5.2.4 and 5.2.5). If this specimen size is not possible, the smallest specimen on which single cuts are made shall not be less than 25 mm by 25 mm.

NOTE The test requires at least 15 cuts therefore at least two specimens are necessary.

4.2 Textiles and other materials


Specimens shall be taken from regions of the sample product representative of the range of construction present in protective areas or as defined in product requirement standard. In the case of an irregular design, the test specimen shall be taken from the area where the least protection is expected.

Specimens from textile materials shall be prepared so that test cuts are made at an angle of $(45 \pm 5)^\circ$ to the warp and weft direction as defined in Figure 1. Only one result (cutting force, see 5.4.4.2) shall be reported.

Materials that have no clear orientation shall be tested in two directions at 90° to each other and both cutting forces (see 5.4.4.2) shall be reported and the final result is the lowest one.

If the material is known to have homogenous properties in all directions, only one result (cutting force see 5.4.4.2) needs to be reported.

NOTE Materials that have no clear orientation are for example, unoriented materials, or those in which the machine direction either does not exist or is uncertain such as some non-woven.

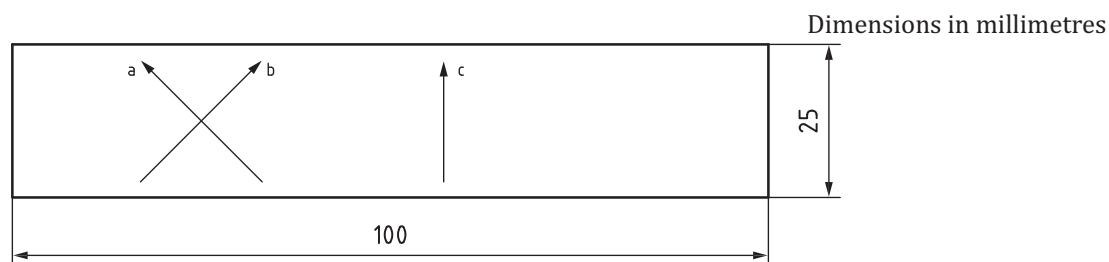

- a Warp or longitudinal direction.
- b Weft or transversal direction.
- c Cut test direction.

Figure 1 — Control specimen dimensions and cut direction for garments

4.3 Gloves

For gloves, take the specimen from the palm area cut on the bias such that the size of the specimen is adequate but at an angle as close as possible to 45° as shown in Figure 2.