



BSI Standards Publication

Protective clothing for firefighters - Physiological impact

Part 1: Measurement of coupled heat and moisture
transfer with the sweating torso

National foreword

This British Standard is the UK implementation of EN ISO 18640-1:2018+A1:2019. It is identical to ISO 18640-1:2018, incorporating amendment 1:2019. It supersedes [BS EN ISO 18640-1:2018](#), which is withdrawn.

The start and finish of text introduced or altered by amendment is indicated in the text by tags. Tags indicating changes to ISO text carry the number of the ISO amendment. For example, text altered by ISO amendment 1 is indicated by **A1** **A1**.

The UK participation in its preparation was entrusted to Technical Committee PH/14, Firefighters' personal protective equipment.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2019
Published by BSI Standards Limited 2019

ISBN 978 0 539 02889 8

ICS 13.340.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 June 2018.

Amendments/corrigenda issued since publication

Date	Text affected
30 November 2019	Implementation of ISO amendment 1:2019 with CEN endorsement A1:2019

English Version

Protective clothing for firefighters — Physiological
impact — Part 1: Measurement of coupled heat and
moisture transfer with the sweating torso (ISO
18640-1:2018)

Vêtements de protection pour sapeurs-
pompiers — Impact physiologique — Partie
1: Mesurage du transfert de masse et de la
chaleur couplé de chaleur et d'humidité à l'aide
du torse transpirant (ISO 18640-1:2018)

Schutzkleidung für die Feuerwehr — Physiologische
Wärmebelastung — Teil 1: Messung von
gekoppelter Wärme und Stoffaustausch mit
dem schwitzenden Torso (ISO 18640-1:2018)

This European Standard was approved by CEN on 2 January 2018.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

European foreword

This document (EN ISO 18640-1:2018) has been prepared by Technical Committee ISO/TC 94 "Personal safety - Personal protective equipment" in collaboration with Technical Committee CEN/TC 162 "Protective clothing including hand and arm protection and lifejackets" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2018, and conflicting national standards shall be withdrawn at the latest by December 2018.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive.

For relationship with EU Directive, see informative [Annex ZA](#), which is an integral part of this document.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 18640-1:2018 has been approved by CEN as EN ISO 18640-1:2018 without any modification.

Foreword to amendment A1

This document (EN ISO 18640-1:2018/A1:2019) has been prepared by Technical Committee ISO/TC 94 "Personal safety -- Personal protective equipment" in collaboration with Technical Committee CEN/TC 162 "Protective clothing including hand and arm protection and lifejackets" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 2020, and conflicting national standards shall be withdrawn at the latest by April 2020.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 18640-1:2018/Amd 1:2019 has been approved by CEN as EN ISO 18640-1:2018/A1:2019 without any modification.

Annex ZA (informative)

Relationship between this European Standard and the Essential Requirements of EU Regulation (EU) 2016/425

This European Standard has been prepared under a Commission's standardization request M/031 to provide a means of conforming to Essential Requirements of the Regulation (EU) 2016/425 of the European Parliament and of the Council of 9 March 2016 on personal protective equipment.

Once this standard is cited in the Official Journal of the European Union under that Regulation (EU) 2016/425, compliance with the normative clauses of this standard given in [Table ZA.1](#) confers, within the limits of the scope of this standard, a presumption of conformity with the corresponding Essential Requirements of that Regulation (EU) 2016/425 and associated EFTA regulations.

Table ZA.1 — Correspondence between this European Standard and Regulation 2016/425/EU

Essential Requirements (ERs) of Regulation 2016/425/EU	Clause(s)/sub-clause(s) of this EN	Qualifying remarks/Notes
1.2.1 Absence of risks and other inherent nuisance factors	Complete standard	Together with the requirements in the product standard

WARNING 1 Presumption of conformity stays valid only as long as a reference to this European Standard is maintained in the list published in the Official Journal of the European Union. Users of this standard should consult frequently the latest list published in the Official Journal of the European Union.

WARNING 2 Other Union legislation may be applicable to the product(s) falling within the scope of this standard.

Contents

Page

Foreword	vi
Introduction	vii
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols and abbreviations	4
5 Apparatus	4
5.1 Sweating torso	5
5.1.1 General	5
5.1.2 Heated cylinder	6
5.1.3 Thermal guard sections	6
5.1.4 Heating and temperature control	6
5.1.5 Temperature measurement	6
5.1.6 Simulation of perspiration	6
5.1.7 Wicking layer	6
5.1.8 Balance torso weight	7
5.2 Computer, control system and data acquisition	7
5.2.1 General	7
5.2.2 Computer and measurement software	7
5.2.3 Control system	7
5.2.4 Data acquisition	7
5.2.5 Measurement control options	7
5.3 Climatic chamber	8
5.3.1 General	8
5.3.2 Climatic chamber sensors	8
5.4 Fan system	8
5.5 Sweat water supply	8
5.5.1 Gravimetric sweat water control system	9
5.6 Simulation of air layers	10
6 Sampling and test specimens	11
6.1 General	11
6.1.1 Size of samples	11
6.1.2 Type of test specimen	11
6.1.3 Garment/ensemble specification	11
6.2 Number of test specimens	11
7 Specimen preparation	11
7.1 Pre-treatment	12
7.2 Conditioning	12
8 Measurement procedure	12
8.1 Test preparation	12
8.1.1 Preparation of climatic chamber	12
8.1.2 Wind speed	12
8.2 Specimen testing	13
8.2.1 General	13
8.2.2 Dressing the torso	14
8.2.3 Recording specimen identification and test observations	14
8.2.4 Starting the test	14
8.2.5 Calculated values	15
9 Test report	18
9.1 General	18
9.2 Specimen identification	18

9.3	Experiment conditions.....	18
9.4	Calculated results.....	18
10	Maintenance and calibration.....	19
10.1	Maintenance.....	19
10.1.1	Sweat water tank.....	19
10.1.2	Valve checks.....	19
10.2	Calibration.....	19
10.2.1	General.....	19
10.2.2	Correction value for thermal resistance, R_{ct0} (torso).....	19
10.2.3	Wicking layer.....	19
10.2.4	torso temperature sensors.....	20
10.2.5	torso heating power.....	20
10.2.6	torso sweat rate.....	20
10.2.7	Environmental conditions.....	20
10.3	Experiments with a standard fabric (optional).....	20
Annex A	(A1) normative (A1) torso size and materials definition.....	21
Annex B	(A1) normative (A1) Calibration.....	25
Annex C	(informative) Example of data evaluation.....	27
Annex D	(informative) Sample check list.....	31
Annex E	(informative) Validation of the measurement device.....	32
Annex F	(informative) Example Matlab code.....	33
Bibliography		37

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 94, *Personal safety*, Subcommittee SC 14, *Firefighters PPE*.

A list of all parts in the ISO 18640 series can be found on the ISO website.

Introduction

The main functions of protective clothing are protection against hazards and maintenance of health and comfort for the wearer. Furthermore, protective clothing against heat and flame prevents the wearer from health risks or even life threatening heat stress in extreme environmental conditions. Today's standards provide requirements for the protective properties of protective clothing against heat and flame. However, the higher the protective properties of such clothing, the less the heat originating from the human body is dissipated. Firefighters reach metabolic rates above 500 W/m² during their work[5][6]. Thereof 75-85 % is released as heat[7], which has to be dissipated from the human body by thermo-regulative processes to avoid an increase in body core temperature. If heat dissipation is not restricted, the human body is able to maintain its temperature in the range of 36,5 °C to 37,5 °C (normothermia)[8]. However, in harsh environmental conditions and/or in situations of restricted heat dissipation due to protective clothing the human body is not able to maintain body core temperature within normothermia and suffers from heat stress. The working performance is gradually reduced and any further increases in body core temperature can become life threatening[16]. To reduce the risk of heat stress during high intensity physical activities, protective clothing should additionally be assessed with regard to its impact on human thermoregulation and heat stress.

Different approaches exist for the assessment of thermo-physiological impact. On the one hand, established standard parameters such as water vapour resistance, R_{et} , and thermal insulation, R_{ct} , of fabric samples are considered with regard to thermo-regulative impact. However, these parameters do not fully reflect the real impact of protective clothing; for example, moisture management properties and the combined effect of heat and moisture transfer are not considered. On the other hand, human subject trials reveal real thermo-physiological responses for a specific environmental condition and protective clothing ensemble. However, the outcome of this methodology does not only refer to the intrinsic properties of material samples but are influenced also by the design of the clothing and trapped air layers within the clothing. Furthermore, human subject trials are very time consuming and expensive, constricted by ethical guidelines and provide findings related to the collective of participants included. Thus, reproducibility between laboratories might be limited. The use of thermal manikins overcomes the limitations for human subject trials. As for human subject trials, full body manikins provide findings on ready-made protective garments including design and fit. Hence, the attribution to intrinsic material properties remains difficult.

A methodology referring to intrinsic clothing properties and taking into account combined heat and moisture transfer is the Sweating torso[9][10]. Sweating torso device is an upright standing heated cylinder, representing the surface of a human trunk, with the ability for perspiration[11]. The clothing sample is investigated by wrapping specimens around the sweating torso. Three phases are run to measure dry thermal insulation, dry and wet heat transfer and drying properties. Findings from the Sweating torso have been validated with standard methodologies, such as sweating guarded hotplate, and were shown to be highly reproducible[11]. Furthermore, validation studies have been conducted to relate human thermos-physiological measurements to Sweating torso findings under realistic environmental conditions and activities for firefighters. Based on this knowledge, guidelines are provided for intrinsic textile properties based on thermo-physiological responses. In addition to the standard procedure described above, the impact of more complex protective clothing systems including underwear, air gaps and/or design features is investigated optionally applying the same experimental protocol described in this document.

This page deliberately left blank

Protective clothing for firefighters - Physiological impact —

Part 1:

Measurement of coupled heat and moisture transfer with the sweating torso

1 Scope

This document provides a test method for evaluating the physiological impact of protective fabric ensembles and potentially protective clothing ensembles in a series of simulated activities (phases) under defined ambient conditions. This standard test method characterizes the essential properties of fabric assemblies of a representative garment or clothing ensemble for thermo-physiological assessment:

- dry thermal insulation;
- cooling properties during average metabolic activity and moisture management (dry and wet heat transfer);
- drying behaviour.

Default measurements are done on fabric samples representing the garment or protective clothing combination. Optionally and in addition to the standard test method, the same testing protocol can be applied to characterise more complex protective clothing ensembles including underwear, air layer and certain design features¹⁾. In addition, measurements on readymade garments are possible.

This test method is intended to be used to measure and describe the behaviour of fabric assemblies of a garment or clothing ensemble in response to a simulated series of activities under controlled laboratory conditions, with the results used to optimize garment combinations and material selection. Furthermore, this document together ISO 18640-2, is intended to be used to describe the thermo-physiological impact of protective clothing but not the risk for heat stress under actual fire conditions. The results of this test can be used as elements of a risk assessment with respect to thermo-physiological load.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

[ISO 3696](#), *Water for analytical laboratory use — Specification and test methods*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

1) A study conducted by Empa (Swiss Federal Laboratories for Materials Science and Technology, Switzerland) showed good correlation between results of standard torso tests (without underwear and air layers on fabrics) to tests on fabrics with underwear, tests on fabrics with underwear and air layers and test on readymade garments (with underwear and with or without air layers) of the same material composition. Due to the added thermal insulation values of the additional layers direct comparison of results between different measurement configurations is not possible, however.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1
cooling delay
CD

time delay until the effect of evaporation cooling will be detected in an experimental phase with simulated activity and sweating

Note 1 to entry: The cooling delay is given in minutes.

3.2
evaporated sweat water
fraction of supplied sweat water which is evaporated in active phase with sweating

3.3
experimental phase

part of an experiment with a defined sweat rate and surface temperature or heating power; an experiment can consist of multiple phases

Note 1 to entry: Each phase simulates a specific situation with defined temperature or heating power and sweat rate settings. A standard experiment consists of three phases.

3.4
initial cooling
IC

rate at which temperature changes after cooling delay CD in an experimental phase simulating activity with sweating

Note 1 to entry: The initial cooling is given in degrees (°C) per hour.

3.5
moisture uptake
amount of moisture stored in clothing system determined by torso weight

Note 1 to entry: The moisture uptake is given in grams.

3.6
post cooling
PC

end of cooling period in an experimental phase without sweating and heating power corresponding to a human being at rest following a simulated activity

Note 1 to entry: The evaporation of stored moisture will extract energy from the sweating torso which can be detected in a decrease of the surface temperature.

Note 2 to entry: The post cooling is given in minutes.

3.7
phase profile
series of experimental phases which define the experiment

3.8
sustained cooling
SC

rate at which temperature changes towards the end of an experimental phase simulating activity with sweating (steady state of cooling)

Note 1 to entry: The sustained cooling is given in degrees (°C) per hour.

3.9 spacer air layer

frame or setup to add a defined air layer between torso surface and protective garment to be tested

Note 1 to entry: Simulation of air layers which are typically observed in real use. An air layer influences overall thermal resistance and moisture transport. A spacer may be used to simulate a defined air layer.

3.10 sweat water

supply of water used to simulate sweating

3.10.1 gravimetric system to deliver sweat water

control of sweat water delivery using a tank on a balance with a defined height difference to the sweat nozzles to deliver the set amount of water by opening and closing valves in a calibrated interval

Note 1 to entry: Other ways of sweat water deliver may be used as long as the requirements of this document are fulfilled.

3.11 thermal resistance

$R_{ct(torso)}$
calculated at steady state from the difference between torso surface temperature and ambient temperature, the surface area of the device and the heating power needed to maintain the temperature difference

Note 1 to entry: The thermal insulation is given in $m^2 \cdot K/W$.

3.11.1 correction value for $R_{ct(torso)}$

$R_{ct0(torso)}$
thermal resistance measurement without a sample on the sweating torso to determine a system specific correction value for the thermal resistance $R_{ct(torso)}$

Note 1 to entry: Thermal resistance as defined above depends on the geometry of the apparatus, convective conditions (wind or still air) and ambient conditions. $R_{ct0(torso)}$ is a cumulative measure of this and might differ slightly from device to device and installation to installation. By taking it into account differences in results from different installations can be reduced.

3.12 torso balance

device used to measure torso weight

3.13 torso surface temperature

average temperature on the surface of the measurement area of the torso

3.14 torso weight

overall weight of the sweating torso and test object during a test

3.15 total sweat water

amount of water supplied to torso surface during an active phase with sweating

3.16 wicking layer

thin hydrophilic textile layer with defined moisture transport and thermal properties used for homogeneous sweat water distribution

3.17

wind speed

ambient velocity of air flow around the torso during an experiment

Note 1 to entry: To avoid undefined boundary air layers due to random air exchange in the chamber and the temperature difference between torso surface and climatic chamber a fan system is used. The fan system consists of ventilators to achieve a set homogeneous wind speed at the torso surface of 1 m/s (turbulence level of up to 25 % measured with a hot-wire anemometer).

4 Symbols and abbreviations


CD	Cooling delay, in minutes
HDPE	High Density Polyethylene
IC	Initial cooling in °C/h
PC	Post cooling, in minutes
PTFE	Polytetrafluoroethylene
R_{ct} (torso)	Thermal resistance in $m^2 \cdot K/W$
R_{ct0} (torso)	Correction value for R_{ct} (torso)
RH	Relative humidity
SC	Sustained cooling, in °C/h
THS	Thermal Human Simulator

5 Apparatus

The sweating torso is an upright standing cylindrical test apparatus, simulating the human trunk with thermal guards on the upper and lower end (see [Figure 1](#)). The apparatus is equipped with heating foils, sweating nozzles, a multi-layer shell (simulation of the skin layers) and electronics to control the valves and sensors.

The whole measurement system (see [Figure 1](#)) consists of the sweating torso (key element 1) on a balance (key element 2) positioned in a climatic chamber. A fan system (key element 3) is used to set the wind speed. The control system (key element 4) power supplies, controllers, and computer with data acquisition) can be placed either inside or outside the chamber. A sweat water tank positioned outside the climatic chamber placed on a balance (key element 5) provides the water to the sweating nozzles. The water supply is controlled by valves.

NOTE The design and control system of the sweating torso has been validated in numerous research projects with respect to different types of clothing systems for the assessment of coupled heat and mass transfer (see [Annex E](#)).

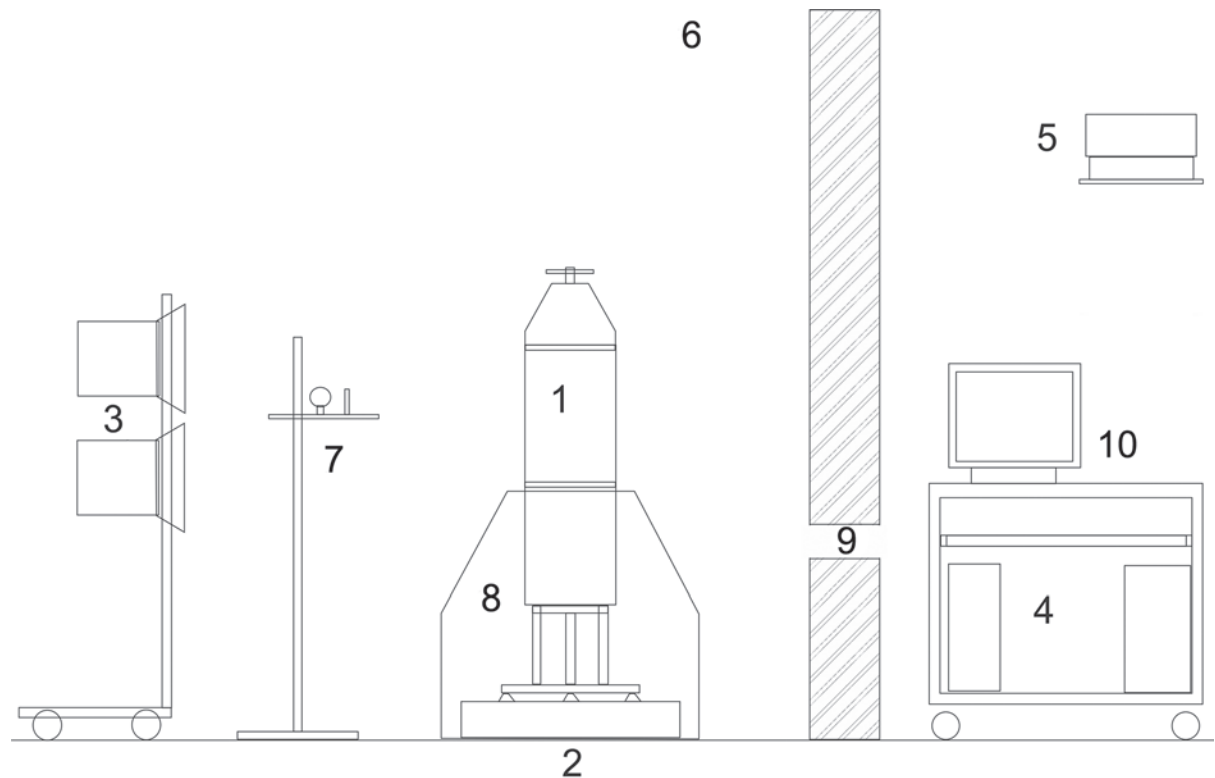

Key

1	torso	6	climatic chamber
2	torso balance	7	environmental sensors
3	fan system	8	frame to minimize influence of wind
4	control system	9	wall of climatic chamber with opening for cables
5	sweat water balance	10	computer, monitor and printer

Figure 1 — Example of torso system

5.1 Sweating torso

5.1.1 General

The sweating torso was designed to simulate the human trunk. The cylinder shall consist of an aluminium tube a layer each of HDPE-²⁾ and PTFE which has an outer diameter of $(30,0 \pm 0,25)$ cm (circumference of $\sim 94,25$ cm) and a length of $(46,0 \pm 0,25)$ cm. Heating foils are situated inside the aluminium tube. On the lower and upper end of the upright standing cylinder there are thermal guards with individually controlled heating. There are temperature sensors in the aluminium part (Pt-100 sensors or equivalent) as well as on the surface of the measurement cylinder (Ni wires or equivalent).

The electronic components to control the valves for the 54 sweating nozzles can be situated in the lower guard (see [Figure A.1](#)) or in an electronic box outside the torso. Transducers converting the resistance values of the temperature sensors may also be located here. Also data acquisition and temperature controlling electronics or parts of these may be placed in the cavity of the guards. Care has to be taken that the heating power of these components shall not disturb temperature control of lower guards and, hence, affect measures obtained from main cylinder.

2) HDPE: High density Polyethylene. E.g. PAS-PE3, thermal conductivity: $(0,41 \pm 0,02)$ W/(m·K); thermal capacity: $(2,0 \pm 0,3)$ kJ/(kg·K).