

BS ISO 15654:2015



BSI Standards Publication

Fatigue test method for transmission precision roller chains and leaf chains

bsi.

...making excellence a habit.
AVA Documents™
Document Sharing Hub

National foreword

This British Standard is the UK implementation of ISO 15654:2015.

The UK participation in its preparation was entrusted to Technical Committee MCE/1, Chains and chain sprockets for power transmission and conveyors.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015.

Published by BSI Standards Limited 2015

ISBN 978 0 580 80797 8

ICS 21.220.30

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 September 2015.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

INTERNATIONAL STANDARD

BS ISO 15654:2015

ISO
15654

Second edition
2015-09-15

Fatigue test method for transmission precision roller chains and leaf chains

*Méthode d'essai de fatigue pour chaînes de transmission de précision
à rouleaux et chaînes de levage à mailles jointives*



Reference number
ISO 15654:2015(E)
Documents
Document Sharing Hub
© ISO 2015



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	v
1 Scope	1
2 Normative references	1
3 Symbols	1
4 Principle	3
5 Apparatus	4
5.1 Testing machine	4
5.2 Test fixtures	4
6 Test specimens	4
7 Test procedure	5
7.1 Test forces	5
7.1.1 Minimum force	5
7.1.2 Maximum force	5
7.1.3 Test force	5
7.1.4 Force application	6
7.2 Conformity test	6
7.2.1 Purpose	6
7.2.2 Endurance	6
7.2.3 Minimum test force	6
7.2.4 Maximum test force	7
7.2.5 Number of tests	7
7.2.6 Acceptance	7
7.3 Staircase test	7
7.3.1 Purpose	7
7.3.2 Description	7
7.3.3 Endurance	7
7.3.4 Rules for conducting a staircase test	7
7.3.5 Determining step size	8
8 Staircase test data analysis	8
8.1 Data	8
8.2 Plotting staircase data	8
8.3 Statistical calculations	9
8.3.1 Mean fatigue strength: 0,50 probability of survival	9
8.3.2 Standard deviations	9
8.3.3 Fatigue limit: 0,998 65 probability of survival	9
9 Report of test results	9
9.1 Test chain information	9
9.2 Test equipment and procedures	10
9.2.1 Test equipment	10
9.2.2 Test procedures	10
9.3 Test results for conformity and staircase tests	10
Annex A (informative) Survival test with abridged Probit analysis	11
Annex B (informative) Combined test methods	15
Annex C (informative) Justification for adding one step to fatigue limit in staircase analysis	21
Annex D (informative) Adding an additional “phantom” point at the end of staircase test	24
Annex E (informative) Reporting fatigue test results	25
Annex F (informative) Establishing chain application fatigue ratings	33
Annex G (informative) Extrapolating fatigue strength from 3×10^6 to 10^7 cycles	39

Annex H (informative) Finite life testing and data analysis	43
Bibliography	48

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT), see the following URL: [Foreword — Supplementary information](#).

The committee responsible for this document is ISO/TC 100, *Chains and chain sprockets for power transmission and conveyors*.

This second edition cancels and replaces the first edition (ISO 15654:2004), which has been technically revised.

Fatigue test method for transmission precision roller chains and leaf chains

1 Scope

This International Standard specifies an axial force fatigue test method for transmission roller chains and leaf chains. The tests being of the fluctuating tension type, carried out at room temperature in air, with the force applied along the longitudinal axis of the chain. It also specifies procedures for statistically analysing the test results and gives formats and elements for presenting the results of fatigue tests and analyses.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 606, *Short-pitch transmission precision roller and bush chains, attachments and associated chain sprockets*


ISO 4347:2015, *Leaf chains, clevises and sheaves — Dimensions, measuring forces, tensile strengths and dynamic strengths*

ISO 10190, *Motorcycle chains — Characteristics and test methods*

3 Symbols

Symbol	Description	Unit
d	Step size — the interval between adjacent force levels in a staircase test [see Formula (5)]	N
$F_{\max}$	Maximum force — maximum value of force in the cycle	N
$F_{\min}$	Minimum force — minimum value of force in the cycle	N
F_m	Mean force — half the sum of the maximum and minimum forces in the force cycle [see Formula (1)]	N
F_a	Force amplitude — half the difference between the maximum force and minimum force [see Formula (2)]	N
F_b	Mean Fatigue Strength — the test force, corrected to zero minimum force, at which there is a 50 % probability of failure at endurance [see Formula (8)]	N
F_{dx}	Fatigue limit — the test force, corrected to zero minimum force, at which there is a calculated 0,135 % probability of failure at 10^7 force cycles. This approximates the force below which a chain can endure an infinite number of force cycles [see Formula (10)]	N
F_d	Test force — the maximum force, corrected to zero minimum force, at which a test was run [see Formula (3)]	N
F_u	Minimum UTS — the minimum tensile strength of chain as specified in ISO 606, ISO 10190 or ISO 4347	N
N	Cycles — the number of cycles, at a given alternating force, applied to a specimen chain at a particular time in the test	—

Symbol	Description	Unit
N_e	Endurance — the predetermined number of cycles at which a test will be discontinued without failure of the specimen chain	—
n	Number of test data points included in the analysis	—
p	Chain pitch	mm
S	Standard deviation — the standard deviation of the staircase test data [see Formula (9)]	N

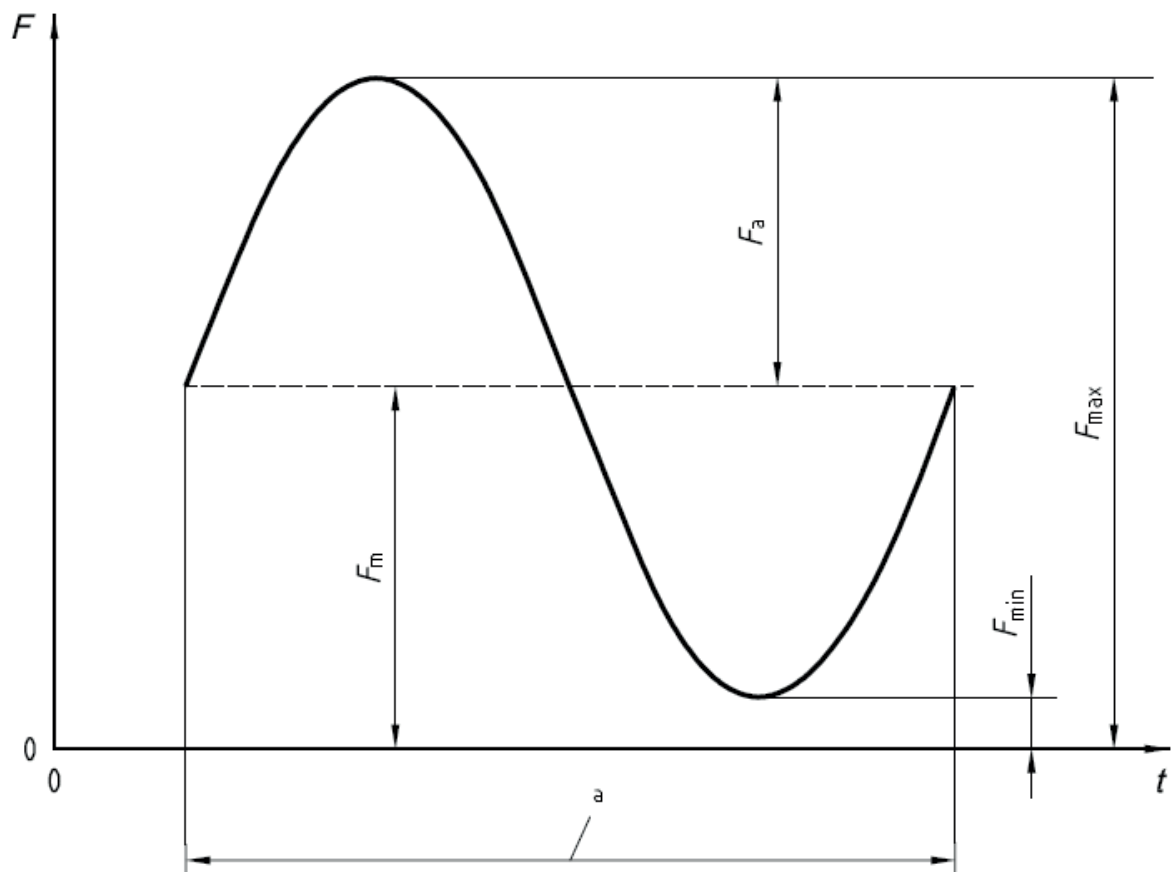

Key

- F force
 t time
 a One cycle.

$$F_m = \frac{F_{\max} + F_{\min}}{2} \quad (1)$$

$$F_a = \frac{F_{\max} - F_{\min}}{2} \quad (2)$$

Figure 1 — Typical force cycle

4 Principle

Tests are made on transmission chains and leaf chains to determine fatigue properties of chain plates such as those shown on an F - N diagram or to verify conformance to dynamic strength requirements in ISO 606, ISO 10190 and ISO 4347.

5 Apparatus

5.1 Testing machine

The size of the testing machine shall be selected so that the maximum force on the test specimen is ≥ 10 % of the maximum capacity of the machine. Tests shall be conducted on a machine capable of applying a sinusoidal fluctuating force to the test specimen in axial tension.

The test frequency shall be chosen so as not to induce a damaging temperature increase in the test specimen.

The machine shall be calibrated periodically in order to maintain suitable accuracy and should be calibrated to within ± 2 % of its maximum capacity. A force-monitoring system could be mounted in series with the test specimen to ensure that the force cycle is maintained throughout the test.

The testing machine shall also have

- a) a counter to record the number of force cycles,
- b) a device to stop the machine when the chain fails, and
- c) a device to prevent the machine from restarting after an emergency stop due to power failure, etc.

5.2 Test fixtures

The test fixtures shall be capable of transmitting an axial force to the test piece without inducing a subsidiary force caused by the fixtures. Universal type fixtures shall be used for fatigue testing of transmission chains and leaf chains.

The universal fixtures shall be designed according to the chain dimensions specified in the separate standards. Examples of the structure of the fixtures are shown in [Figure 2](#).

Universal fixtures shall permit free movement on both sides of the chain centreline in both the normal plane of articulation and in the transverse plane. For transmission chain the hole in the fixture shall be a size equal to the bush hole diameter of the chain under test. For leaf chain the hole in the fixture shall be a size equal to the clevis hole diameter d_1 shown in ISO 4347:2015, Tables 3 and 4.

NOTE The test specimens all illustrate five free pitches.

When testing chain on sheaves, the chain shall be restrained from moving around the sheaves to ensure that only specific pitches of the chain are tested.

6 Test specimens

6.1 At least five free pitches of chain shall be used as a fatigue test specimen, except for chain pitch over 50,8 mm where a minimum of three free pitches are acceptable.

NOTE Failures in links that contact the fixtures do not constitute part of the test.

Free pitches are those chain pitches that do not contact the fixtures.

6.2 The test specimens shall be unused, undamaged chains on which all phases of manufacture have been completed. The final lubricant type is discretionary.

7 Test procedure


7.1 Test forces

7.1.1 Minimum force

The minimum force for the test shall be at least 1 % but not more than 5 % of the minimum tensile strength given for the subject chain in ISO 606, ISO 10190 or ISO 4347.

7.1.2 Maximum force

The maximum force for the test shall be determined in accordance with 7.2 for a conformity test or in accordance with 7.3 for a staircase test.

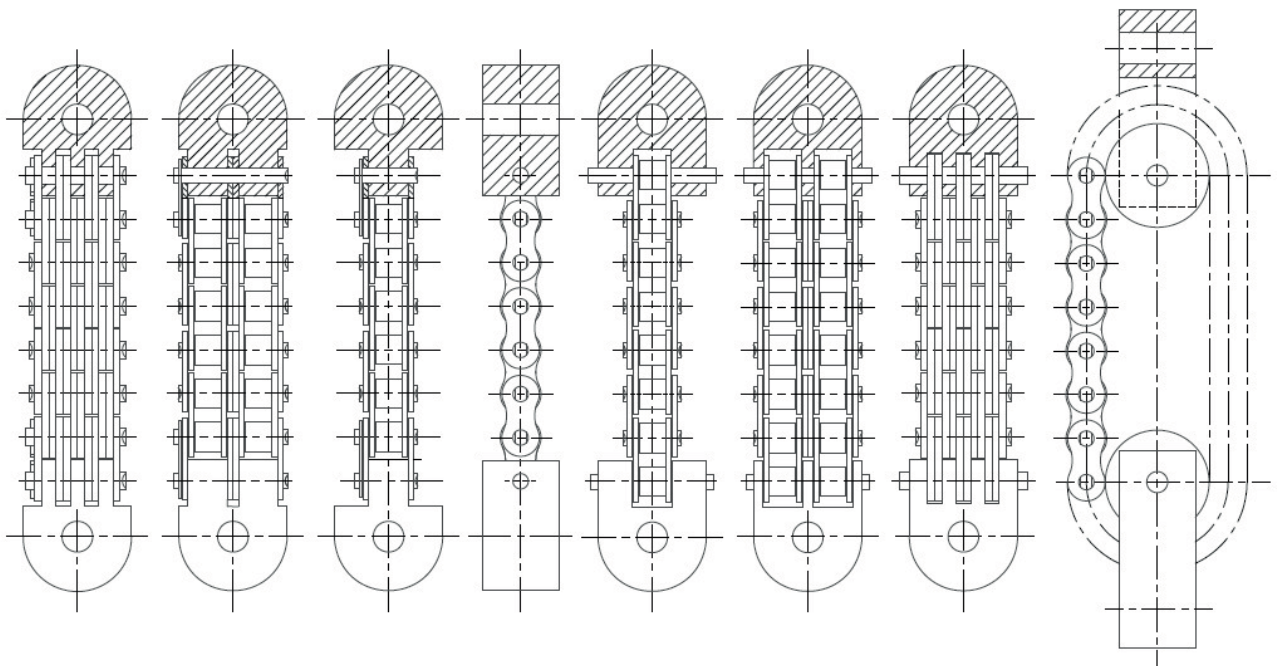


NOTE The endless loop illustration is not applicable to leaf chain.

Figure 2 — Examples of test specimens mounted in universal fixtures

7.1.3 Test force

For analyses of fatigue test data, maximum forces shall be corrected to zero minimum force. A test force is obtained by correcting the maximum force to zero minimum force by means of the Johnson-Goodman method [Formula (3)]. The Johnson-Goodman relationship is illustrated by Figure 3. Here $F_{\min}$ is $0,05 \times F_u$ and $F_{\max}$ is $0,3 \times F_u$, and the resulting F_d is $0,263 2 \times F_u$.

$$F_d = \frac{F_u (F_{\max} - F_{\min})}{F_u - F_{\min}} \quad (3)$$

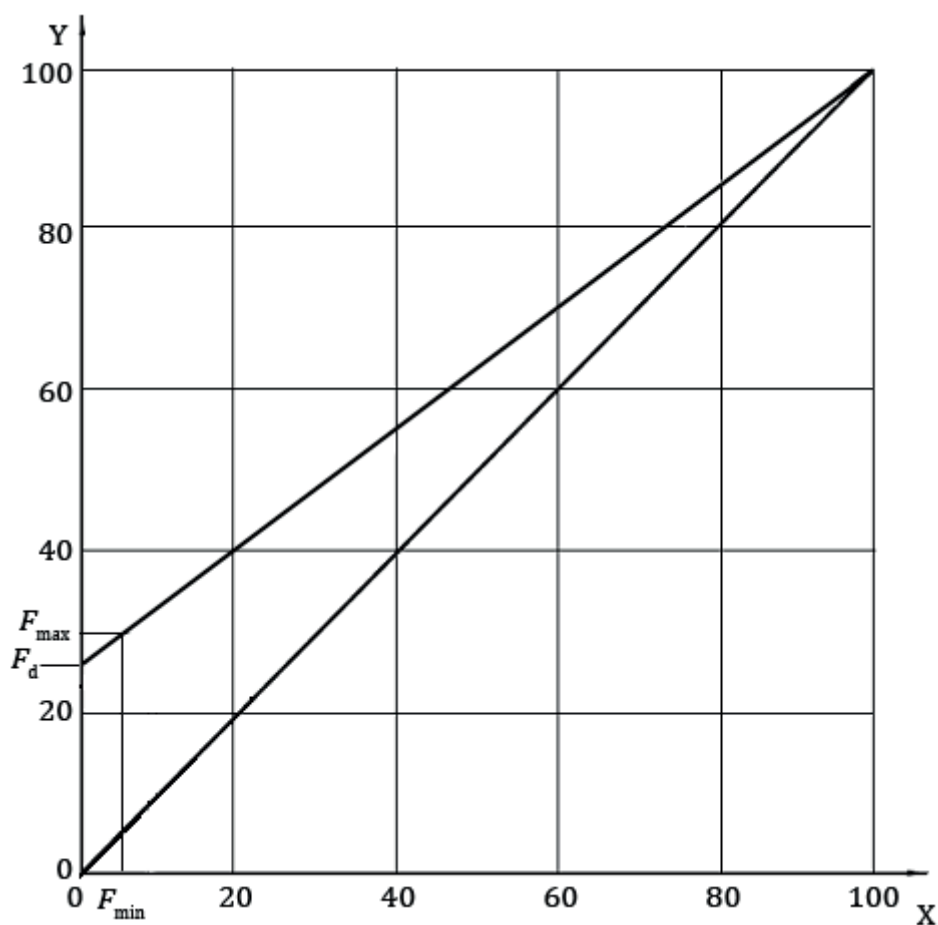

Key

X minimum force, % of F_u

Y maximum force, % of F_u

Figure 3 — Johnson-Goodman diagram

7.1.4 Force application

A longitudinal tensile force shall be applied, sinusoidally varying between the minimum test force determined according to 7.1.1 and the maximum test force determined according to 7.1.2. The test shall continue to endurance or until the specimen fails, whichever is sooner.

7.2 Conformity test

7.2.1 Purpose

The purpose of this test is to determine whether or not a chain meets the dynamic strength requirements given for it in ISO 606, ISO 10190 or ISO 4347.

7.2.2 Endurance

Endurance shall be 3×10^6 cycles.

7.2.3 Minimum test force

The minimum force for the test shall be set in accordance with 7.1.1.

7.2.4 Maximum test force

The maximum test force shall be determined using Formula (4):

$$F_{\max} = \frac{F_d F_u + [F_{\min} (F_u - F_d)]}{F_u} \quad (4)$$

7.2.5 Number of tests

Three specimens shall be tested.

7.2.6 Acceptance

All specimens shall survive to endurance without failure.

7.3 Staircase test

7.3.1 Purpose

The purpose of this test is to determine the fatigue limit of the subject chain.

7.3.2 Description

For the purposes of this International Standard, a staircase test is one in which specimens are tested sequentially at predetermined, equally spaced force levels. The first specimen is tested at a force level slightly greater than the estimated mean fatigue strength of the chain. If the first specimen runs to endurance (runs out), the next specimen is tested at the next higher predetermined force level. If the first specimen fails before endurance, the next specimen is tested at the next lower predetermined force level. Force levels for subsequent tests are determined in the same manner, and the testing continues until the required number of tests are completed.

7.3.3 Endurance

Endurance shall be 10^7 cycles when testing for fatigue limit.

7.3.4 Rules for conducting a staircase test

The test shall begin with a response reversal, then a run-out followed by a failure, or a failure followed by a run-out. The test shall have at least 10 data points to determine the mean with 95 % confidence and six data points to determine the mean with 90 % confidence. It shall have the minimum number of data points in accordance with [Table 2](#) to detect a difference in the mean of approximately one-half step size.

Table 2 — Required sample sizes

Confidence	3-step staircase	4-step staircase	5-step staircase
90 %	6	11	16
95 %	10	15	20

The highest force level in a staircase shall contain only failures.

The lowest force level in a staircase shall contain only run-outs.

Intermediate force levels in a staircase shall contain both failures and run-outs.

7.3.5 Determining step size

7.3.5.1 Using survival test with Probit analysis

See [Annex A](#). The step size shall be determined in accordance with [A.5](#).

7.3.5.2 Using combined test method (CTM)

See [Annex B](#). The step size shall be determined in accordance with [B.3.4.3](#) [see Formula (B.10)].

7.3.5.3 Using empirical method

Extensive testing has shown that reliable results can be obtained when the step size, expressed in newtons (N), is set according to Formula (5) or (6):

$$\text{For simplex roller chains: } d \approx 14p^{1,5} \quad (5)$$

$$\text{For multiplex roller chains: } d \approx 0,7 \cdot n_s \cdot 14 \cdot p^{1,5} \quad (6)$$

Where: n_s = number of strands, and n_s is 2 or more.

NOTE When the combined method is used the step size should be determined in accordance with [B.3.4.3](#). There is no established empirical method applicable to leaf chains, so step size should be determined in accordance with that shown in Formula (7). It should be noted that this formula is shown for informative purposes and is for the convenience of deducing an approximate minimum dynamic strength.

$$d \approx f_L \cdot \frac{n_L}{4} \cdot 14 \cdot p^{1,5} \quad (7)$$

where

p is the chain pitch in mm;

f_L is lacing factor, according to ISO 4347:2015, Table A.2;

n_L is total number of plates in adjacent links, e.g. $n_L = 10$ for 4×6 combination.

8 Staircase test data analysis

8.1 Data

The data for a staircase test analysis shall be gathered in accordance with [7.3](#).

An additional test point at the end of a staircase test can be determined by the rules for conducting a staircase test (see [7.3](#)). This additional test point, sometimes called a “phantom” point, shall be included in the analysis.

8.2 Plotting staircase data

It is customary to tabulate and plot the data as a staircase test progresses to ensure that the rules for constructing a staircase are followed. An example of such a data plot (three levels and 95 % confidence level) is shown in [Table 3](#).

Table 3 — Staircase data plot — Example

Test force	Invalid tests	Valid tests										
$F_d + 2d$	X											
$F_d + d$		X						X		X		#
F_d			X		X		0		0		0	
$F_d - d$				0		0						
0 = Run-Out; X = Failure; # = Phantom Point.												

8.3 Statistical calculations

8.3.1 Mean fatigue strength: 0,50 probability of survival

The mean fatigue strength shall be calculated using Formula (8),

$$F_b = \frac{\sum_{i=1}^n F_{d_i}}{n} \quad (8)$$

where n is the total number of valid tests in the staircase calculations.

8.3.2 Standard deviations

The standard deviations of the staircase data shall be calculated using Formula (9),

$$S = \left[\frac{\sum_{i=1}^n F_{d_i}^2}{n} - F_b^2 \right]^{0.5} \quad (9)$$

8.3.3 Fatigue limit: 0,998 65 probability of survival

The fatigue limit shall be calculated using Formula (10),

$$F_{dx} = F_b - 3S + d \quad (10)$$

9 Report of test results

9.1 Test chain information

The originator shall provide to the user

- the brand name or other identifying name or mark of the test chain,
- the ISO number or manufacturer's number and the pitch of the test chain, and
- the length in free pitches of the test specimens.

9.2 Test equipment and procedures

9.2.1 Test equipment

The originator shall provide to the user

- a) the brand name and type of testing machine,
- b) the maximum rated capacity of the test machine,
- c) the number of machines used if more than one,
- d) the method of dynamic force verification and monitoring, and
- e) the method of calibration and the most recent date calibrated.

9.2.2 Test procedures

The originator shall provide to the user

- a) the type of test; conformity or staircase,
- b) the number of cycles to endurance, and
- c) any ambient conditions that could affect the test results.

9.3 Test results for conformity and staircase tests

The originator shall provide a table of test results to the user, which shall include

- a) identification of the test specimen,
- b) the test sequence, the order in which the specimens were run,
- c) the maximum and minimum force for each test,
- d) the test force, corrected to zero minimum force, for each test,
- e) the force cycling frequency,
- f) the number of cycles at which each test was terminated,
- g) the reason each test was terminated and, if a failure, the component of the chain that failed,
- h) a brief summary of the post-test examination, if any, and
- i) the machine used for each test, if more than one machine was used.

For a staircase test, the originator shall also provide the user with

- the mean fatigue strength, F_b , and
- the minimum fatigue strength, or fatigue limit.