

Coke — Determination of coke reactivity index (CRI) and coke strength after reaction (CSR)

ICS 75.160.10

National foreword

This British Standard reproduces verbatim ISO 18894:2006 and implements it as the UK national standard.

The UK participation in its preparation was entrusted to Technical Committee PTI/16, Solid mineral fuels, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the ISO title page, pages ii to iv, pages 1 to 16, an inside back cover and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 May 2006

© BSI 2006

ISBN 0 580 48353 3

Amendments issued since publication

Amd. No.	Date	Comments

INTERNATIONAL STANDARD

ISO
18894

First edition
2006-04-15

Coke — Determination of coke reactivity index (CRI) and coke strength after reaction (CSR)

*Coke — Mesures de l'indice de réactivité du coke (CRI) et de la
résistance post-réactionnelle du coke (CSR)*



Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Reagents	3
6 Apparatus	3
7 Preparation of test sample	4
8 Procedure	4
9 Expression of results	5
10 Precision	6
11 Test report	9
Annex A (normative) Reactivity test apparatus “type A”, single wall	10
Annex B (normative) Reactivity test apparatus “type B”, double wall	12
Annex C (normative) Coke-strength-after-reaction tumbler	14
Annex D (informative) Determination of abrasion value	15
Annex E (informative) Reproducibility critical difference	16

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 18894 was prepared by Technical Committee ISO/TC 27, *Solid mineral fuels*, Subcommittee SC 3, *Coke*.

Coke — Determination of coke reactivity index (CRI) and coke strength after reaction (CSR)

1 Scope

This International Standard specifies the equipment and techniques used for determining lump-coke (> 20 mm) reactivity in carbon dioxide gas at elevated temperatures and its strength after reaction in carbon dioxide gas by tumbling in a cylindrical chamber.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 579, *Coke — Determination of total moisture*

ISO 3310 (all parts), *Test sieves — Technical requirements and testing*

ISO 1213-2, *Solid mineral fuels — Vocabulary — Part 2: Terms relating to sampling, testing and analysis*

ISO 2309, *Coke — Sampling*

ISO 13909-5, *Hard coal and coke — Mechanical sampling — Part 5: Coke — Sampling from moving streams*

ISO 13909-6, *Hard coal and coke — Mechanical sampling — Part 6: Coke — Preparation of test samples*

IEC 60584-1, *Thermocouples — Part 1: Reference tables*

IEC 60584-2, *Thermocouples — Part 2: Tolerances*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 1213-2 and the following apply.

3.1

abrasion value

lack of resistance to abrasion of the coke after reaction with carbon dioxide in the CRI test, measured as the percentage of a sample passing through a 0,5 mm sieve after tumbling under conditions specified in this International Standard

NOTE See Annex D.

3.2

coke reactivity index

CRI

percentage weight loss of coke after reaction with carbon dioxide to form carbon monoxide under conditions specified in this International Standard

3.3

coke strength after reaction**CSR**

strength of coke after reaction with carbon dioxide in the CRI test, measured as the percentage retained on either a 10,0 mm or a 9,5 mm sieve after tumbling under conditions specified in this International Standard

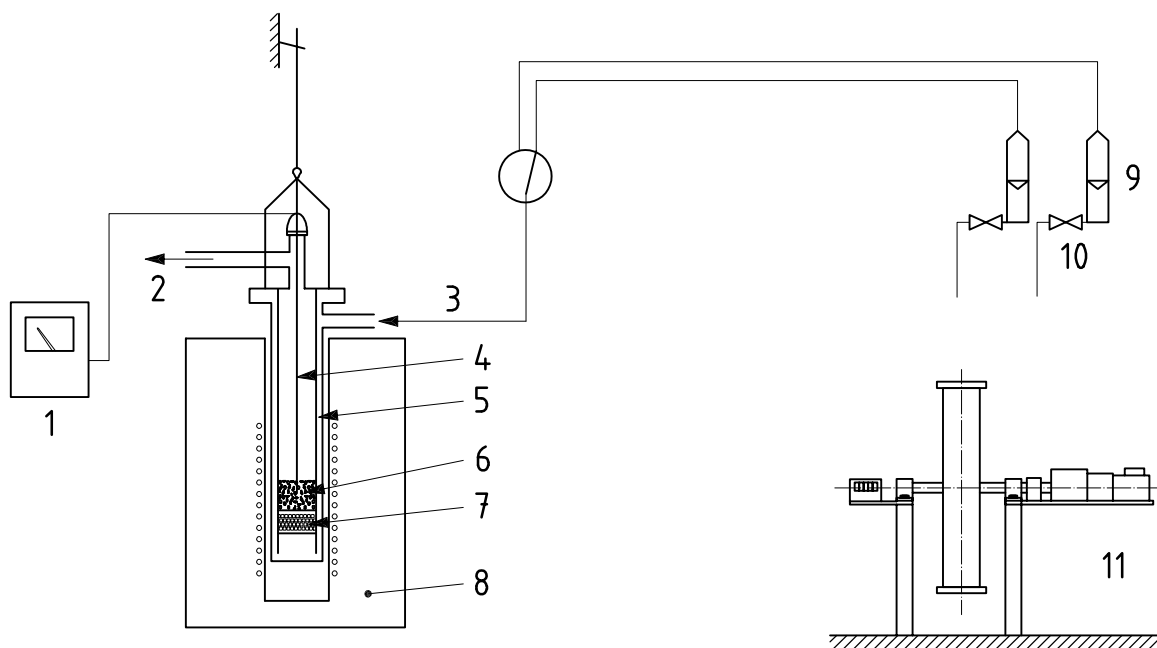
4 Principle

A test portion of the dried coke sample having a size range from 19,0 mm to 22,4 mm is heated in a reaction vessel to 1 100 °C in a nitrogen atmosphere. For the test, the atmosphere is changed to carbon dioxide for exactly 2 h. After the test, the reaction vessel is allowed to cool down to about 50 °C in a nitrogen atmosphere. The comparison of the sample weight before and after the reaction determines the coke reactivity index (CRI).

The reacted coke is treated in a specially designed tumbler for 600 revolutions for 30 min. The coke strength after reaction (CSR) value is determined by sieving and weighing the amount of coke passing through either a 10,0 mm or a 9,5 mm sieve.

An example of the arrangement of the test unit is shown in Figure 1.

NOTE During the development of this International Standard, it was found that 10,0 mm and 9,5 mm sieves are both commonly used for these types of test. When reacted coke is tumbled, abrasion usually takes place. Particles of about 20 mm lose some edges, but they do not break into pieces. Therefore, it makes almost no difference if the sieving after tumbling is made with a 10,0 mm or a 9,5 mm sieve, as the size of the coke pieces is either about 20 mm or 0 mm to 5 mm, but not in the range of 10 mm. This has been verified by experiments over a long period of time. It has been shown that the difference in CSR using both sieve sizes is within the precision range of this International Standard.

**Key**

- | | | | |
|---|---|----|-----------------------------|
| 1 | plotter for recording temperature | 7 | layer of ceramic balls |
| 2 | gas outlet to stack | 8 | electrically heated furnace |
| 3 | gas inlet | 9 | gas-flow meters |
| 4 | thermocouple | 10 | control valves |
| 5 | single or double wall retort with perforated plate as sample holder | 11 | tumbler |
| 6 | test portion | | |

Figure 1 — Example of test unit arrangement