

THE ENGINEERING EQUIPMENT AND MATERIALS USERS ASSOCIATION

**90/10 COPPER NICKEL ALLOY PIPING FOR
OFFSHORE APPLICATIONS
SPECIFICATION: FITTINGS**

PUBLICATION No. 146 — 1987



90/10 COPPER NICKEL ALLOY PIPING FOR OFFSHORE APPLICATIONS

SPECIFICATION: FITTINGS

PUBLICATION No. 146 — 1987

Copyright © 1987 The Engineering Equipment and Materials Users Association

ISBN 0 85931 108 2

45 Beech Street
London EC2Y 8AD

Tel: 0171 628 7878

Fax: 0171 628 7862

e-mail sales@eemua.co.uk

website www.eemua.co.uk

EEMUA



Documents

Document Sharing Hub

THE ENGINEERING EQUIPMENT AND MATERIALS USERS ASSOCIATION

The Engineering Equipment and Materials Users Association—EEMUA—was formed in 1983 by the Amalgamation of the Oil Companies Materials Association (OCMA) and the Engineering Equipment Users Association (EEUA). It is an organisation of substantial purchasers and users of engineering products, whose members include leading national and multi-national companies in the petroleum, gas, chemical and energy industries. A list of Full and Associate Members (the latter being limited to membership of three technical committees) is given below. EEMUA is concerned with the design, installation, operation and maintenance of the engineering plant used by members in pursuing their business activities.

The Association aims to reduce members' costs by providing the opportunity for them to share resources and expertise in order to keep abreast of technological developments and improve the effectiveness and efficiency of their engineering activities. EEMUA supports the British Standards Institution, works with other institutions, associations, government departments, regulatory authorities and the Confederation of British Industry, and is also actively involved with other standards-making bodies, both national and international, such as the American Petroleum Institute.

Work, which is carried out in-house by members alone or with the help of other organisations, may lead to the production of Association publications. These are prepared primarily for members' use, but are usually offered for sale and thus for more general use. Such publications may also be submitted, normally through the British Standards Institution, as bases for appropriate national, European or international standards.

A list of current EEMUA Publications which may be purchased from the Association is given at the end of this document.

Full Members

Associated Octel
BG
BP Amoco
Caltex Petroleum
Conoco
Dow Corning
Eastern Generation
Esso/ExxonMobil
Eutech
Foster Wheeler Energy
Lindsey Oil Refinery
National Power
PowerGen
Shell

Associate Members

AstraZeneca
BASF
D&C Engineering/MERCON [Netherlands]
Elf Exploration UK
Flexsys
Phillips Petroleum UK
Pilkington Technology
Royal Vopak (was Royal Pakhoed)
[Netherlands]
Texaco
UOP

ABOUT THIS PUBLICATION: LEGAL ASPECTS

In order to ensure that nothing in this publication can in any manner offend against or be affected by the provisions of the Restrictive Trade Practices Act 1976, the recommendations which it contains will not take effect until the day following that on which its particulars are furnished to the Office of Fair Trading.

As the subject dealt with seems likely to be of wide interest, this publication is also being made available for sale to non-members of the Association. Any person who encounters an inaccuracy or ambiguity when making use of this publication is asked to notify EEMUA without delay so that the matter may be investigated and appropriate action taken.

It has been assumed in the preparation of this publication that the user will ensure selection of those parts of its contents appropriate to the intended application and that such selection and application are correctly carried out by appropriately qualified and experienced people for whose guidance the publication has been prepared. EEMUA does not, and indeed cannot, make any representation or give any warranty or guarantee in connection with material contained in its publications, and expressly disclaims any liability or responsibility for damage or loss resulting from their use. Any recommendations contained herein are based on the most authoritative information available at the time of writing and on good engineering practice, but it is essential for the user to take account of pertinent subsequent developments or legislation.

All rights are reserved. No part of this Publication may be reproduced, stored in a retrieval system, or transmitted in any form or by any means: electronic, mechanical, photocopying, recording or other.

Infringing the copyright is not only breaking the law, but also, through reduction in Association's income, jeopardising the availability of future publications.

CONTENTS

Page

FOREWORD

viii

SPECIFICATION**SECTION ONE. 90/10 CU NI BUTT WELDING FITTINGS**

1.1	Scope and design basis	1
1.2	Information to be supplied by the purchaser	1
1.3	Freedom from defects	1
1.4	Materials and manufacture	1
1.5	Welding	2
1.6	Selection of test samples	2
1.7	Non-destructive testing	2
1.8	Repairs to welded seams	2
1.9	Retests of repairs	3
1.10	Marking	3
1.11	Inspection and testing	3
1.12	Certification	4

SECTION TWO. 90/10 CU NI SOCKET WELDING FITTINGS

2.1	Scope and design basis	19
2.2	Information to be supplied by purchaser	19
2.3	Freedom from defects	19
2.4	Materials and manufacture	19
2.5	Proof tests for adequacy of socket welding union type fittings (prototype test)	20
2.6	Marking	21
2.7	Inspection and testing	21
2.8	Certification	22

SECTION THREE. COPPER ALLOY CAPILLARY BRAZING FITTINGS

3.1	Scope and design basis	24
3.2	Information to be supplied by the purchaser	24
3.3	Freedom from defects	24
3.4	Materials and manufacture	25
3.5	Proof tests for adequacy of capillary brazing union type fittings (prototype test)	25
3.6	Marking	26
3.7	Inspection and testing	26
3.8	Certification	27

SECTION FOUR. COPPER ALLOY FLARELESS NON-MANIPULATIVE TYPE COMPRESSION FITTINGS

4.1	Scope and design basis	29
4.2	Information to be supplied by the purchaser	29

4.3	Freedom from defects	29
4.4	Materials and manufacture	29
4.5	Proof test for adequacy of compression fittings (prototype tests)	30
4.6	Marking	31
4.7	Inspection and testing	31
4.8	Certification	31

SECTION FIVE. COPPER ALLOY THREADED FITTINGS

5.1	Scope and design basis	33
5.2	Information to be supplied by the purchaser	33
5.3	Freedom from defects	33
5.4	Materials and manufacture	34
5.5	Marking	34
5.6	Inspection and testing	34
5.7	Certification	35

SECTION SIX. 90/10 CU NI SELF REINFORCED BRANCH CONNECTION FITTINGS

6.1	Scope and design basis	39
6.2	Information to be supplied by the purchaser	39
6.3	Pressure/temperature ratings	40
6.4	Freedom from defects	40
6.5	Materials and manufacture	40
6.6	Marking	40
6.7	Inspection and testing	41
6.8	Certification	41

SECTION SEVEN. 90/10 CU NI SADDLE PIECES

7.1	Scope and design basis	45
7.2	Information to be supplied by the purchaser	45
7.3	Pressure/temperature ratings	45
7.4	Freedom from defects	45
7.5	Materials and manufacture	45
7.6	Welding	46
7.7	Selection of test samples	46
7.8	Non-destructive testing	46
7.9	Repairs to weld seams	46
7.10	Retest of repairs	46
7.11	Marking	47
7.12	Inspection and testing	47
7.13	Certification	47

ADDENDUM.

Discretionary contractual clauses	53
-----------------------------------	----

APPENDICES

A	List of standards and codes referred to in this publication	54
B	Intrados thickness of long radius elbows	55

C	Chemical composition and mechanical properties of 90/10 Copper Nickel fittings	56
D	Pressure/temperature ratings — fittings	57

TABLES

1.1	Dimensions of welding ends for all butt welding components — 16 bar rating	6
1.2	Dimensions of welding ends for all butt welding components — 20 bar rating	7
1.3	Tolerances — fittings	8
1.4	Dimensions of long radius elbows	9
1.5	Intrados thickness of long radius elbows	10
1.6	Dimensions of straight (equal) tees	11
1.7.1	Dimensions of reducing outlet tees — sizes up to 159 × 159 × 108	12
1.7.2	Dimensions of reducing outlet tees — sizes 219.1 × 219.1 × 88.9 up to and including 508 × 508 × 457.2	13
1.7.3	Dimensions of reducing outlet tees — sizes 610 × 610 × 419 up to and including 914 × 914 × 813	14
1.8	Dimensions of end caps	15
1.9.1	Dimensions of butt welding reducers — sizes 30 × 25 up to and including 159 × 88.9	16
1.9.2	Dimensions of butt welding reducers — sizes 219.1 × 159 up to and including 457.2 × 323.9	17
1.9.3	Dimensions of butt welding reducers — sizes 508 × 368 up to and including 914 × 813	18
2.1	Basis for hydraulic proof pressure test of assembled union joints	20
2.2	Dimensions of socket welding fittings	23
3.1	Basis for hydraulic proof pressure test of assembled union joints	25
3.2	Dimensions of capillary brazing fittings	28
4.1	Basis for hydraulic proof pressure test of assembled non-manipulative compression joints	30
4.2	Dimensions of flareless non-manipulative compression fittings	32
5.1.1	Dimensions of copper alloy threaded plugs and bushings	36
5.1.2	Dimensions of copper alloy threaded couplings, half couplings and caps	37
5.2	Dimensions of 90/10 Cu Ni alloy tubes suitable for screwing NPT to ANSI B1.20.1	38
6.1	Self reinforced branch connection fittings (butt welding type)	42
6.2	Self reinforced branch connection fittings (socket welding type)	43
6.3	Self reinforced branch connection fittings (threaded type)	44
7.1.1	Dimensions of butt welding ends — 16 bar rating	49
7.1.2	Dimensions of butt welding ends — 20 bar rating	50
7.2.1	Tolerances — Seamless saddle pieces — 16 bar rating	51
7.2.2	Tolerances — Seamless saddle pieces — 20 bar rating	51
7.3.1	Seam-welded saddle pieces — 16 bar rating	52
7.3.2	Seam-welded saddle pieces — 20 bar rating	52

FIGURES

1.1	Dimensions of welding ends on butt welding components	4
1.2	Guidance for the design of tees	5
2.1	Welding dimensions required for socket welding fittings	21
7.1	Dimensions of welding ends on butt welding saddle pieces	48
7.2	Saddle pieces — seamless	48
7.3	Saddle pieces — seam-welded	52

FOREWORD

The Publications in this series of specifications for 90/10 copper nickel tubes, flanges and fittings are as follows:

Publication No. 144 Tubes — Seamless and Welded

Publication No. 145 Flanges — Composite and Solid

Publication No. 146 Fittings

Material selected from the series of specifications contained in EEMUA Publications Nos. 144, 145 and 146 provide for the total requirements of 90/10 copper nickel piping systems intended to operate at pressures up to 16 bar at 75°C or 20 bar at 38°C.

This publication comprises a series of sections for pipe fittings suitable for use with 90/10 Cu Ni tube. The sections are as follows:—

Section one 90/10 Cu Ni butt welding fittings.

Section two 90/10 Cu Ni socket welding fittings (including unions)

Section three copper alloy capillary brazing fittings (including unions)

Section four copper alloy flareless, non manipulative type compression fittings

Section five copper alloy threaded fittings

Section six 90/10 Cu Ni reinforced branch connectors

Section seven 90/10 Cu Ni saddle pieces

Fittings other than butt weld tube may be suitable for design pressures and temperatures higher than those required by this specification. Where this is required the manufacturer of such fittings should be consulted.

In order that a more satisfactory match than hitherto is obtained between the bores of fittings (and other butt welding components) and the bores of tubes to which they would be butt welded, a greater emphasis has been placed on the bore dimensions and tolerances of the fittings. The mean bore dimensions of butt weld fittings (See section one of this publication) correspond to the mean bore dimensions of the corresponding 16 or 20 bar rated tubes covered by EEMUA Publication 144: 1987: Tubes — seamless and welded.

The "building in" dimensions of butt-welding fittings, apart from end caps, have been based on ANSI B16.9. End caps have been based on DIN 28011 (with suitable amendments) since the majority of manufacturers tend to follow this particular specification.

Additional compensatory thicknesses have been applied to the intrados of long radius (butt welded) elbows and to the end caps, (see section one of this publication).

Socket weld type fittings are included as an alternative to capillary brazed fittings or flareless, non manipulative fittings.

Threaded fittings including caps, plugs and bushings have also been included in this publication.

Materials of manufacture for each type of fitting are covered in the relevant sections within this publication. Where other copper base or non ferrous materials are covered in the various sections, the purchaser may select accordingly. All materials covered are compatible with the 90/10 Cu Ni alloy. However, reference should also be made to BS MA18 for design limitations.

The basic dimensions, based on ANSI B16.11, together with the acceptance criteria are included with additional test requirements for union type fittings. With reference to capillary brazed fittings, appropriate tests to establish that sufficient brazing alloy has been included as an integral part of the fitting design are outlined, together with the extra test requirements for the acceptance of union type fittings.

A list of other standards and codes referred to in this publication is given in Appendix A.

The correlation between nominal inch sizes and the specified sizes in millimetres are given below:

Nominal size in	Specified O/D mm
1/2	16
3/4	25
1	30
1 1/4	38
1 1/2	44.5
2	57
2 1/2	76.1
3	88.9
4	108
6	159
8	219.1
10	267
12	323.9
14	368
16	419
18	457.2
20	508
24	610
28	711
32	813
36	914

Note: For threaded fittings see table 5.2.

SECTION ONE — 90/10 CU NI BUTT WELDING FITTINGS

1.1 Scope and design basis

Section one covers wrought butt welding fittings in sizes 1 in/30 mm up to and including 36 in/914 mm in 90/10 Cu Ni alloy UNS 7060X* as modified in Appendix C of this publication, for maximum allowable working pressures (MAWP) of 16 bar and 20 bar for temperatures up to and including 75°C and 38°C respectively (see appendix D). The dimensions and tolerances are such that they are suitable for butt welding to seamless or seam-welded 90/10 Cu Ni tubes to EEMUA Publication No. 144 sections 1 and 2 respectively.

This section also covers the acceptance criteria and proof testing requirements for butt welding fittings.

The design features and wall thicknesses of butt welding tees and reducers shall be established by mathematical analysis given in a nationally recognised pressure vessel or piping code acceptable to the purchaser. The design of fittings which cannot be qualified by such analyses shall be established in accordance with the proof testing procedure in clause 9 of ANSI B16.9 – 1978.

1.2 Information to be supplied by the purchaser

The purchaser shall state in the enquiry and order the following information:

- (a) The title and number of this section (EEMUA Publication No. 146: 1987: section 1).
- (b) The type of fitting and size in inches and millimetres — and material designation (see appendix C).
- (c) The pressure rating — 16 or 20 bar.
- (d) Whether manufacturer's certificates are required; (see clause 1.12).
- (e) Whether it is his intention to inspect the material at supplier's works (see Addendum).
- (f) Whether any additional identification marking other than that specified herein is required.
- (g) Whether any test samples or individual test analyses are required to be supplied (see Addendum).

1.3 Freedom from defects

The fittings shall be visually clean, smooth and free from defects greater than 0.5 mm in depth, irregularities, scale or deposits, and shall be free from deleterious films in the bore. Repairs by welding shall be limited to seam welds only.

1.4 Materials and manufacture

The fittings shall be seamless or seam-welded and manufactured from tube sheet or plate as follows:

Tubes (seamless) shall have chemical composition and mechanical properties in accordance with EEMUA Publication No 144:1987 section 1, "Specification for 90/10 Cu Ni seamless tubes."

* Alloy UNS 7060X is a modified form of the following national designated alloys — UNS 70600, BS CN102 and DIN 2.0872. See Appendix C of this specification for chemical composition and mechanical properties.

Butt welding fittings

Tubes (seam-welded) shall have chemical composition and mechanical properties in accordance with EEMUA Publication No 144: Section 2, "Specification for 90/10 copper nickel seam-welded tubes."

Sheets or plates shall be hot rolled or cold rolled and annealed in accordance with BS 2870, BS 2875, ASTM B171 or ASTM B402 but with chemical composition as modified in this specification (see appendix C).

The dimensions and tolerances of seamless and seam-welded fittings shall comply with the requirements of tables 1.1 to 1.9.

The chemical composition and mechanical properties of butt-welding fittings to this specification are given in appendix C.

1.5 Welding**1.5.1 Consumables**

The composition of the filler wire or rods used for the production of seam welds shall be selected from BS 2901 : Part 3, Table 1 – Alloy C18.

Alternatively filler wires and rods shall be selected from the American Welding Society Specification AWS-A5.7 – Class ER Cu Ni. Flux coated electrodes shall be selected from the American Welding Society Specification AWS A5.6 – Class E Cu Ni.

1.5.2 Welding procedure qualification

The welding procedure qualifications shall be as quoted in ASME Code Section IX – "Qualification Standard for Welding and Brazing Procedures, Welders, Brazers, and Welding and Brazing Operators."

1.5.3 Welder qualification

The welder qualification shall be in accordance with ASME Code Section IX.

1.6 Selection of test samples

- (a) Fittings made from seamless or seam-welded tube to EEMUA Publication No. 144: 1987 sections 1 or 2 do not require any additional testing other than hardness testing in order to ensure compliance with Appendix C of this specification.
- (b) Fittings formed from sheet or plate shall be subject to the relevant requirements of EEMUA Publication 144: 1987: Section 2.

1.7 Non-destructive testing**1.7.1 Liquid dye penetrant test**

The weld seams of all welded fittings shall be examined externally by the liquid dye penetrant method in accordance with ASME Code Section V, Article 6 and shall meet the acceptance requirements of ASME Code Section VIII, Division 1, Appendix 8.

1.7.2 Radiography

Radiographic examination shall be performed for the complete length of each weld to meet the requirements of ASME Code, Section VIII, UW51.

1.8 Repairs to welded seams

Visible defects such as cracks, pinholes and incomplete fusion and defects detected by the tests performed under clause 1.7 shall be removed and repaired in accordance with clause 1.5.

1.9 Retests of repairs

A repaired weld seam shall meet the requirements of the original weld and be re-examined and retested in accordance with clause 1.7.

1.10 Marking

1.10.1 All fittings shall be individually permanently marked and identified by clear, legible printing by means of a vibratory etching tool, electro chemical etching, paint or ink stencilling and where applicable, in such colours as to be clearly visible as follows:

- (a) Purchase order number (PO).
- (b) The number of this section (EEMUA Publication No. 146: 1987: section 1).
- (c) Material designation UNS 7060X (See appendix C).
- (d) Size: inches and millimetres.
- (e) Pressure rating — 16 or 20 bar.
- (f) Manufacturer's name and/or trademark (MTM).
- (g) Test certificate number (TCN).
- (h) Cast number.
- (j) Where applicable — welder identity (WI).

Example of marking:

PO 146/1 7060X 14/368 16 MTM TCN Cast No WI

1.10.2 On fittings 44.5 mm and smaller and where it is not practical to apply the full requirements of 1.10.1 to the fitting the marking shall detail:

- (a) Material designation.
- (b) Cast Number.
- (c) Manufacturer's name or trademark.
- (d) Size: inches and millimetres.
- (e) Pressure rating — 20 bar.

The remainder of the marking requirements shall be applied to indestructible type labels securely attached to the components. The labels shall be clearly and permanently marked. Alternatively the additional marking requirements shall be applied to the carton in which the fittings are packed.

Note 1: Stamping with metallic stamps is not permitted.

Note 2: Manufacturers shall ensure that any marking materials used shall not be detrimental to the material of the fittings.

1.11 Inspection and testing

This section does not make provision for routine pressure testing of fittings. They shall, however, be dimensionally correct and be marked in accordance with this section. All fittings shall be capable of withstanding without leakage or signs of distress a hydraulic pressure of 1.5 times the maximum design pressure at ambient temperatures as follows:

16 bar rated fittings, test pressure = 24 bar

20 bar rated fittings, test pressure = 30 bar

Butt welding fittings**1.12 Certification**


Certificate(s) shall be supplied, either:

- 1.12.1** A certificate of compliance which shall state that the fittings have been made in accordance with all the requirements of this section (EEMUA Publication No. 146: section 1: 1987) or:
- 1.12.2** A manufacturer's certificate which shall state that the fittings have been made in accordance with all the requirements of this section (EEMUA Publication No. 146: section 1: 1987) and:
- (a) State the actual compositional limits determined for each of the elements designated in appendix C of the casts used in the manufacture of each order for seamless tubes used to manufacture fittings and/or:
State the actual compositional limits determined for each of the elements designated in appendix C of each cast used in the manufacture of each sheet or plate used in the manufacture of fittings.
Note: Individual cast analyses shall be retained by the manufacturer – see Addendum.
 - (b) State the results of mechanical tests performed on the seamless tubes used to manufacture fittings in accordance with appendix C and/or state the results of mechanical tests performed on sheets or plates formed into fittings in accordance with appendix C.
 - (c) State the results of the dye penetrant and radiographic examination of each weld on each fitting carried out in accordance with and complying with clauses 1.7, 1.8 and 1.9.

Figure 1.1

Dimensions of welding ends on butt welding components

See Tables 1.1 and 1.2 for dimensions A, B and t, for 16 and 20 bar ratings respectively.

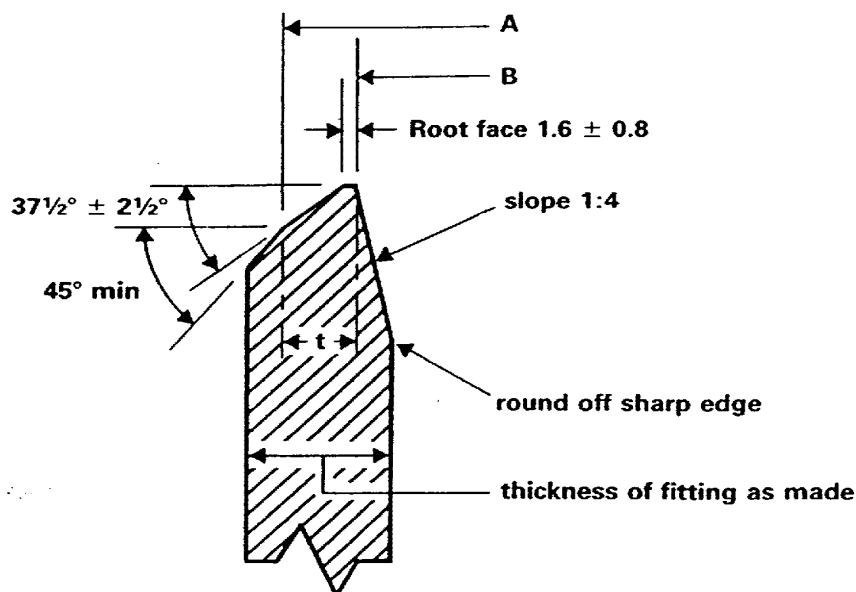

Note: In the case of specified wall thicknesses (t) of less than 3mm, the weld bevel of $37\frac{1}{2}^\circ \pm 2\frac{1}{2}^\circ$ may be omitted.

Figure 1.2


Guidance for the design of tees

(See also appendix D of ANSI/ASME B31.3 1984 edition)

Welding tee per
ANSI B16.9 with

$$r_x \geq 1/8 D_b$$


$$T_c \geq 1.5 \bar{T}$$

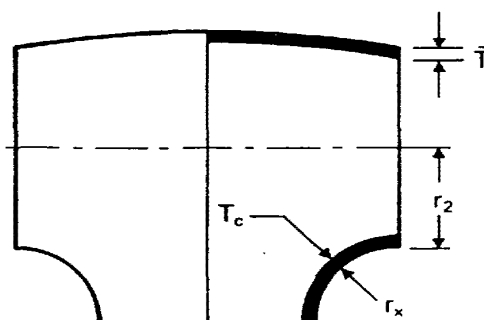where: $\bar{T}$ = nominal thickness of the
matching pipe. T_c = crotch thickness of tees. r_2 = mean radius of matching
pipe. r_x = see definition in 304.3.4(c)
of ANSI/ASME B31.3 – 1984
edition. D_b = outside diameter of
branch pipe.

Extruded welding tee

$$r_x \geq 0.05 D_b$$

$$T_c < 1.5 \bar{T}$$

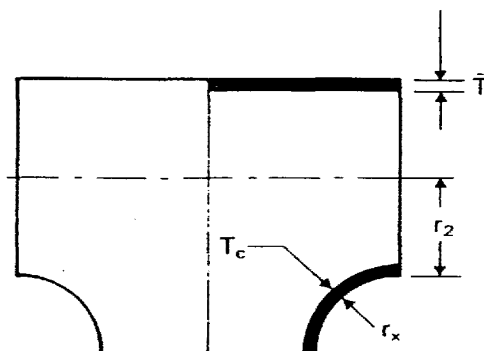

Butt welding fittings**Table 1.1**

Dimensions of welding ends for all butt welding components

16 bar rating (see also fig. 1.1).

For tolerances see table 1.3

Size* A	pipe wall thickness t		inside diameter at welding ends B	
	specified OD	minimum	maximum	minimum
30	Use 20 bar SEE TABLE 1.2			
38				
44.5				
57				
76.1				
88.9				
108				
159	3.0	2.63	154.5	153.0
219.1	4.0	3.50	211.9	210.4
267	4.5	3.94	258.7	257.2
323.9	5.5	4.81	313.6	312.0
368	6.5	5.69	355.2	353.2
419	7.0	6.13	405.0	403.0
457.2	8.0	7.00	443.0	440.0
508	8.5	7.44	492.0	489.0
610	10.5	9.19	591.0	588.0
711	12.0	10.50	689.0	686.0
813	13.5	11.81	788.0	785.0
914	15.5	13.56	885.0	882.0

Note: Ovality – The ovality of finished butt welding fittings shall be such that the difference between the maximum and minimum diameters measured on the same cross section shall not exceed 2% of the specified size in column 1 of this table.

* For inch/millimetre correlation – see foreword. All dimensions in millimetres

Table 1.2

Dimensions of welding ends for all butt welding components

20 bar rating (see also fig 1.1).

For tolerances see table 1.3

Size* A	Pipe wall thickness t		Inside diameter at welding ends B	
	specified OD	minimum	maximum	minimum
30	2.5	2.25	25.555	24.475
38	2.5	2.25	33.57	32.49
44.5	2.5	2.25	40.07	38.99
57	2.5	2.25	52.70	51.62
76.1	2.5	2.25	71.80	70.65
88.9	2.5	2.25	84.65	83.50
108	3.0	2.70	102.85	101.40
159	3.5	3.06	153.0	151.50
219.1	4.5	3.94	210.9	209.40
267	5.5	4.81	256.7	255.20
323.9	7.0	6.13	310.5	309.0
368	8.0	7.00	352.0	350.0
419	9.0	7.88	401.0	399.0
457.2	9.5	8.31	440.0	437.0
508	11.0	9.63	488.0	485.0
610	13.0	11.38	586.0	583.0
711	15.0	13.13	683.0	680.0
813	17.0	14.88	781.0	778.0
914	19.0	16.63	878.0	875.0


Note: Ovality – The ovality of finished butt welding fittings shall be such that the difference between the maximum and minimum diameters measured on the same cross section shall not exceed 2% of the specified size in column 1 of this table.

* For inch/millimetre correlation – see foreword.
All dimensions in millimetres.

Butt welding fittings**Table 1.3**
Tolerances – fittings

Size *	90 deg & 45 deg elbows & tees (see tables 1.4, 1.6 & 1.7)	reducers (see table 1.9)	end caps (see table 1.8)
Specified OD	centre-to-end dimension D, E, C & M	overall length H	overall length h1 + h2
up to and including 267	± 2	± 2	$+0.015 D_o$ -0
323.9 up to and including 711	± 3	± 3	
813 up to and including 914	± 5	± 5	

Size *	angularity	
Specified OD	off angle Q	off plane P
up to and including 108	± 1	± 2
over 108 up to and including 219.1	± 2	± 4
267 up to and including 323.9	± 3	± 5
368 up to and including 419	± 3	± 7
457.2 up to and including 610	± 4	± 10
711	± 5	± 10
813 up to and including 914	± 5	± 13

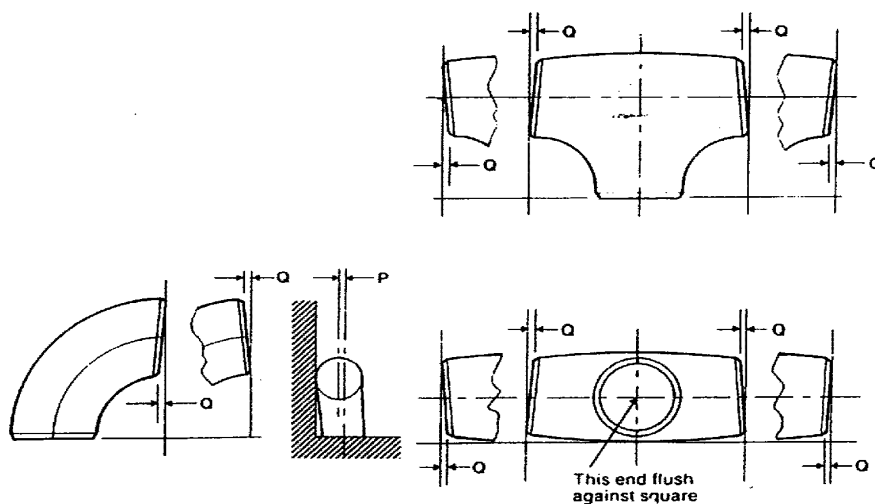


All dimensions in millimetres

* For inch/millimetre correlation – see foreword

Table 1.4
Dimensions of long radius elbows

Size* Specified OD	Centre-to-end					
	90 deg elbows D			45 deg elbows E		
	max	nom	min	max	nom	min
30	40	38	36	24	22	20
38	50	48	46	27	25	23
44.5	59	57	55	31	29	27
57	78	76	74	37	35	33
76.1	97	95	93	46	44	42
88.9	116	114	112	53	51	49
108	154	152	150	66	64	62
159	231	229	227	97	95	93
219.1	307	305	303	129	127	125
267	383	381	379	161	159	157
323.9	460	457	454	193	190	187
368	536	533	530	225	222	219
419	613	610	607	257	254	251
457.2	689	686	683	289	286	283
508	765	762	759	321	318	315
610	917	914	911	384	381	378
711	1070	1067	1064	441	438	435
813	1224	1219	1214	507	502	497
914	1377	1372	1367	570	565	560

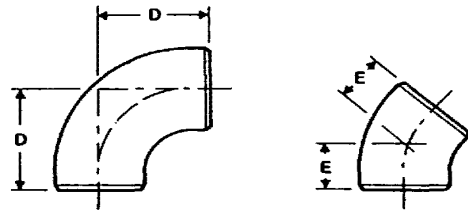

All dimensions in millimetres

Notes: For inside diameters at the plain or bevelled ends – see tables 1.1 & 1.2 and figure 1.1.


See table 1.5 for elbow wall thicknesses.

* For inch/millimetre correlation – see foreword.

Butt welding fittings**Table 1.5**

Intrados thickness of long radius elbows

Size * Specified OD	Thickness		Thickness	
	minimum t intrados	minimum tube wall	minimum t intrados	minimum tube wall
	see note 1	see note 2	see note 1	see note 2
	16 bar		20 bar	
30	USE 20 bar		2.25	2.25
38			2.25	2.25
44.5			2.25	2.25
57			2.25	2.25
76.1			2.25	2.25
88.9			2.25	2.25
108			2.70	2.70
159	2.83	2.63	3.40	3.06
219.1	3.74	3.50	4.54	3.94
267	4.42	3.95	5.38	4.81
323.9	5.27	4.81	6.45	6.13
368	5.88	5.69	7.20	7.00
419	6.61	6.13	8.12	7.88
457.2	7.10	7.00	8.73	8.31
508	7.84	7.44	9.65	9.63
610	9.31	9.19	11.49	11.38
711	10.76	10.50	—	—
813	12.24	11.81	—	—
914	13.70	13.56	—	—




All dimensions in millimetres * For inch/millimetre correlation – see foreword

Note 1: See appendix B for basis for the calculation of "t" – intrados thickness. The minimum thickness at the centre of the intrados of an elbow shall not be less than the thickness shown in the above table.**Note 2:** The minimum allowable thickness of an elbow at any point shall not be less than the minimum allowable thickness of the corresponding tube.**Note 3:** For inside diameters at the plain or bevelled ends – see tables 1.1 and 1.2 and figure 1.1

Butt welding fittings

Table 1.6
Dimensions of straight (equal) tees

Size * Specified OD	Centre-to-end					
	run C			outlet M		
	max	nom	min	max	nom	min
30	40	38	36	40	38	36
38	50	48	46	50	48	46
44.5	59	57	55	59	57	55
57	66	64	62	66	64	62
76.1	78	76	74	78	76	74
88.9	88	86	84	88	86	84
108	107	105	103	107	105	103
159	145	143	141	145	143	141
219.1	180	178	176	180	178	176
267	218	216	214	218	216	214
323.9	257	254	251	257	254	251
368	282	279	276	282	279	276
419	308	305	302	308	305	302
457.2	346	343	340	346	343	340
508	384	381	378	384	381	378
610	435	432	429	435	432	429
711	524	521	518	524	521	518
813	602	597	592	602	597	592
914	678	673	668	678	673	668

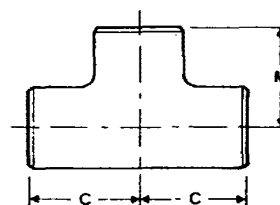

All dimensions in millimetres


Note: For inside diameters at the plain or bevelled ends — see tables 1.1 & 1.2 and figure 1.1.

* For inch/millimetre correlation — see foreword

Butt welding fittings**Table 1.7.1**

Dimensions of reducing outlet tees – sizes up to 159 × 159 × 108.

Size * Specified OD			Centre-to-end					
			run C			outlet M		
run	run	outlet	max	nom	min	max	nom	min
30	30	25	40	38	36	40	38	36
38	38	30	50	48	46	50	48	46
38	38	25						
44.5	44.5	38	59	57	55	59	57	55
44.5	44.5	30						
44.5	44.5	25						
57	57	44.5	66	64	62	62	60	58
57	57	38				59	57	55
57	57	30				53	51	49
76.1	76.1	57	78	76	74	72	70	68
76.1	76.1	44.5				69	67	65
76.1	76.1	38				66	64	62
88.9	88.9	76.1	88	86	84	85	83	81
88.9	88.9	57				78	76	74
88.9	88.9	44.5				75	73	71
108	108	88.9	107	105	103	100	98	96
108	108	76.1				97	95	93
108	108	57				91	89	87
159	159	108	145	143	141	132	130	128
159	159	88.9				126	124	122
159	159	76.1				123	121	119

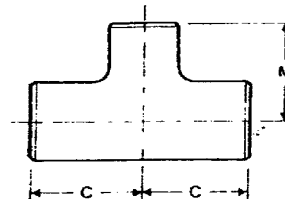

All dimensions in millimetres

Note: For inside diameters at the plain or bevelled ends – see tables 1.1 & 1.2 and fig. 1.1.

* For inch/millimetre correlation – see foreword