

INTERNATIONAL STANDARD



Electrical insulating materials – Thermal endurance properties – Part 5: Determination of relative temperature index (RTI) of an insulating material



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2022 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Secretariat
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch

Discover our powerful search engine and read freely all the publications previews. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 300 terminological entries in English and French, with equivalent terms in 19 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.



IEC 60216-5

Edition 4.0 2022-11
COMMENTED VERSION

INTERNATIONAL STANDARD



**Electrical insulating materials – Thermal endurance properties –
Part 5: Determination of relative temperature index (RTI) of an insulating material**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 19.020; 29.020; 29.035.01

ISBN 978-2-8322-6112-5

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD	4
1 Scope	6
2 Normative references	6
3 Terms, definitions, symbols and units ~~and abbreviations~~	7
3.1 Terms, ~~abbreviations~~ , and definitions	7
3.2 Symbols and units	8
4 Objectives of ~~RTE~~ RTI determination	10
5 Experimental procedures	10
5.1 Selection of reference EIM	10
5.2 Selection of diagnostic test for extent of ageing	10
5.3 Ageing procedures	10
6 Calculation procedures	13
6.1 Thermal endurance data – Calculation of intermediate parameters	13
6.2 Calculation of ~~RTE~~ RTI	14
6.3 Statistical and numerical tests	15
6.3.1 Tests of IEC 60216-3	15
6.3.2 Precision of correlation time	15
6.3.3 Lower confidence interval of ~~RTE~~ RTI	15
6.3.4 Extrapolation	16
7 Results and report	16
7.1 Results of statistical and numerical tests	16
7.2 Results	16
7.3 Report	17
8 Material testing by short-term thermal ageing	17
9 Insulation classification	17
Annex A (informative) Repeatability of correlation time	18
A.1 Overview	18
A.2 <i>F</i> -test for ~~equality of variances~~ linearity	18
A.3 Standard error of the difference of two means	18
A.4 Student's <i>t</i> -test for difference of two means	19
A.5 Combination of data	20
Annex B (informative) Thermal class assignment	21
Annex C (informative) Computer program	24
C.1 General	24
C.1.1 Overview	25
C.1.2 Convenience program execution	26
C.2 Structure of data files used by the program	27
C.3 Executing the calculation of RTI	28
C.4 Output files and graph	28
Annex D (informative) Selection of the reference EIM	30
D.1 Overview	30
D.2 Designation of reference EIM	30
D.3 Reporting items for reference EIM	30
Bibliography	31
List of comments	32

Figure 1 – Thermal endurance graphs.....12

Figure 2 – Unacceptable thermal endurance graphs.....13

Figure C.1 – Shortcut property dialog for program launch 27

Figure C.2 – Thermal endurance graphs 28

Figure C.3 – Example thermal endurance graphs 29

Table 1 – Input parameters for the calculations concerning ~~RTE~~ RTI.....14

Table B.1 – Thermal class equivalents for insulating material 21

Table B.2 – F - function; $p = 0,05$ 22

Table B.3 – t -function 23

INTERNATIONAL ELECTROTECHNICAL COMMISSION

ELECTRICAL INSULATING MATERIALS –
THERMAL ENDURANCE PROPERTIES –**Part 5: Determination of ~~relative thermal endurance~~
~~index (RTE)~~ relative temperature index (RTI) 1 of an insulating material**

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

This commented version (CMV) of the official standard IEC 60216-5:2022 edition 4.0 allows the user to identify the changes made to the previous IEC 60216-5:2008 edition 3.0. Furthermore, comments from IEC TC 112 experts are provided to explain the reasons of the most relevant changes, or to clarify any part of the content.

A vertical bar appears in the margin wherever a change has been made. Additions are in green text, deletions are in strikethrough red text. Experts' comments are identified by a blue-background number. Mouse over a number to display a pop-up note with the comment.

This publication contains the CMV and the official standard. The full list of comments is available at the end of the CMV.

IEC 60216-5 has been prepared by IEC technical committee 112: Evaluation and qualification of electrical insulating materials and systems. It is an International Standard.

This fourth edition cancels and replaces the third edition published in 2008. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) Annex C “Computer program” has been completely reworked;
- b) in 3.1, the terms “ATE” and “RTE” were replaced by “ATI” and “RTI” to emphasize their reference to an electrical insulating material (EIM).

This standard is to be read in conjunction with IEC 60216-1:2013, IEC 60216-2:2005 and IEC 60216-3:2021.

The text of this International Standard is based on the following documents:

Draft	Report on voting
112/582/FDIS	112/588/RVD

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this International Standard is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/standardsdev/publications.

A list of all parts in the IEC 60216 series, published under the general title *Electrical insulating materials – Thermal endurance properties*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The “colour inside” logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

ELECTRICAL INSULATING MATERIALS – THERMAL ENDURANCE PROPERTIES –

Part 5: Determination of ~~relative thermal endurance index (RTE)~~ relative temperature index (RTI) of an insulating material

1 Scope

This part of IEC 60216 specifies the experimental and calculation procedures to be used for deriving the relative ~~thermal endurance~~ temperature index of a material from experimental data obtained in accordance with the instructions of IEC 60216-1 and IEC 60216-2. The calculation procedures are supplementary to those of IEC 60216-3.

Guidance is also given for assessment of thermal ageing after a single fixed time and temperature, without extrapolation.

The experimental data ~~may~~ can 2 in principle be obtained using destructive, non-destructive or proof tests, although destructive tests have been much more extensively employed. Data obtained from non-destructive or proof tests ~~may~~ can 3 be “censored”, in that measurement of times taken to reach the endpoint ~~may~~ 4 have been terminated at some point after the median time but before all specimens have reached end-point (see IEC 60216-1).

Guidance is given for preliminary assignment of a thermal class for an electrical insulating material (EIM) 5, based upon the thermal ageing performance.

While the thermal classification of an EIM is not directly related to the thermal classification of an electrical insulation system (EIS), the thermal classification of an EIS follows the same concepts as presented in this part of the 60216 series. 6 The calculation procedures of this standard apply to the determination of the thermal class of an EIS when the thermal stress is the prevailing ageing factor.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60216-1:2004/2013 7, *Electrical insulating materials – Thermal endurance properties – Part 1: Ageing procedures and evaluation of test results*

IEC 60216-2:2005 8, *Electrical insulating materials – Thermal endurance properties – Part 2: Determination of thermal endurance properties of electrical insulating materials – Choice of test criteria*

IEC 60216-3:2006/2021 9, *Electrical insulating materials – Thermal endurance properties – Part 3: Instructions for calculating thermal endurance characteristics*

3 Terms, definitions, symbols and units ~~and abbreviations~~ 10

3.1 Terms, ~~abbreviations~~, and definitions

For the purposes of this document, the following terms and definitions, ~~symbols, units and abbreviated terms~~ apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp> 11

3.1.1 electrical insulating material EIM

~~solid or fluid with negligibly low electric conductivity, or a simple combination of such materials, used to separate conducting parts at different electrical potential in electrotechnical devices~~

material of low electric conductivity, used to separate conducting parts at different electric potentials or to isolate such parts from the surroundings 12

3.1.2 ~~assessed thermal endurance index~~ ATE

~~numerical value of the temperature in degrees Celsius, up to which the reference EIM possesses known, satisfactory service performance in the specified application~~

~~NOTE 1 The value of the ATE may vary between applications for the same material.~~

~~NOTE 2 Sometimes referred to as “absolute” thermal endurance index.~~

3.1.2 assessed temperature index ATI

numerical value of the temperature index in degrees Celsius of the reference EIM

Note 1 to entry: The value of the ATI can vary between applications for the same material. 13

3.1.3 candidate EIM

material for which an estimate of the thermal endurance is required to be determined

Note 1 to entry: The determination is made by simultaneous thermal ageing of the material and a reference EIM.

3.1.4 reference EIM

material with known thermal endurance, ~~preferably~~ (derived from service experience or previous RTI or TI evaluation) 14, used as a reference for comparative tests with the candidate EIM

3.1.5 central second moment of a data group

sum of the squares of the differences between the data values and the value of the group mean divided by the number of data in the group

3.1.6 correlation time for RTI 15

estimated time to endpoint of the reference EIM at a temperature equal to its ~~assessed thermal endurance (ATE)~~ ATI in degrees Celsius

3.1.7

degrees of freedom

number of data values minus the number of parameter values

3.1.8

standard error

standard error of an estimate of the true value of a data group property is the value of the standard deviation of the hypothetical sampling population of which the group property ~~may~~ can **16** be considered to be a member

Note 1 to entry: For the group mean it is equal to the group standard deviation divided by the square root of the number of data in the group, and indicates the uncertainty in the true value of the mean.

Note 2 to entry: This standard is concerned only with means and the difference between two means (see Clause A.3).

3.1.9

standard deviation

square root of the variance of a data group or sub-group

~~3.1.10~~

~~relative thermal endurance index~~

~~RTE~~

~~numerical value of the temperature in degrees Celsius at which the estimated time to endpoint of the candidate EIM is the same as the estimated time to endpoint of the reference EIM at a temperature equal to its assessed thermal endurance (ATE)~~

3.1.10

relative temperature index

RTI

determined by test in relation to the thermal performance of a known reference EIM **17**

3.1.11

variance of a data group

sum of the squares of the deviations of the data from a reference level defined by one or more parameters, divided by the number of degrees of freedom

Note 1 to entry: The reference level ~~may~~ can **18**, for example, be a mean value (1 parameter) or a line (2 parameters, in this document, the slope and the intercept with the y axis).

3.2 Symbols and units

a_A	Regression coefficient (y-intercept) of thermal endurance equation for reference EIM
a_B	Regression coefficient (y-intercept) of thermal endurance equation for candidate EIM
b_A	Regression coefficient (slope) of thermal endurance equation for reference EIM
b_B	Regression coefficient (slope) of thermal endurance equation for candidate EIM
X	Variable for statistical analysis equal to $1/(g + \theta_0)$
Y	Variable for statistical analysis equal to $\ln(\tau)$
g	Ageing temperature in determination of ~~RTE~~ RTI
θ_0	Temperature on Kelvin scale equal to 0 °C

τ	Time to endpoint
τ_c	Estimated time to endpoint of reference EIM at a temperature equal to ~~ATE~~ ATI
$\mu_{2(A)}$	Central second moment of x values for reference EIM
$\mu_{2(B)}$	Central second moment of x values for candidate EIM
n_A	Number of y values for reference EIM data
n_B	Number of y values for candidate EIM data
T	Student's t distributed stochastic variable
S	Standard error of the difference of two means
s_A^2	Variance of y values for reference EIM data
s_B^2	Variance of y values for candidate EIM data
$\bar{x}_A$	General mean of x -values for reference EIM data
$\bar{x}_B$	General mean of x -values for candidate EIM data
$\bar{y}_A$	General mean of y -values for reference EIM data
$\bar{y}_B$	General mean of y -values for candidate EIM data
θ_A	Temperature in degrees Celsius equal to ~~ATE~~ ATI
θ_B	Temperature in degrees Celsius equal to ~~RTE~~ RTI
$\hat{x}_B$	x value corresponding to θ_B
$\hat{x}_A$	x value corresponding to θ_A
$\theta_{c(B)}$	Lower confidence limit of θ_B
$\theta_{c(A)}$	Lower confidence limit of θ_A
$X_{L(B)}$	x value corresponding to lower confidence limit of θ_B
$X_{L(A)}$	x value corresponding to lower confidence limit of θ_A
Δ_B	Lower confidence interval of θ_B
Δ_A	Lower confidence interval of θ_A
$HIC_{B(c)}$	Halving interval of candidate EIM at a time equal to τ_c
s_D^2	Variance associated with the difference between the mean y -values for the two materials

n_D	Degrees of freedom of s_D^2
v_A, v_B	Logarithms of the longest mean times to endpoint for materials A and B
b_r	Intermediate variable: adjusted value of b for calculation of temperature confidence interval
s_r	Intermediate variable: adjusted value of s for calculation of temperature confidence interval

4 Objectives of ~~RTE~~ RTI determination

The objectives of the determination are as follows.

- a) To exploit an assumed relationship between thermal endurance (with an appropriate test criterion for ageing) and service performance, and to use this to predict a value for a preliminary assessment of service temperature of a material for which there is relatively little service experience (by comparison with a known reference EIM, see Clauses 5 and 6).

NOTE 19 In the majority of cases, this will involve extrapolation to a longer time and/or lower temperature than in the experimental data. This extrapolation should be kept to a minimum by appropriate choice of ageing temperatures and times since the uncertainty in the result increases rapidly as the extrapolation is increased. However, even when there is no extrapolation, the uncertainty is still finite, on account of the variances of the experimental data and experimental errors.

- b) To improve the precision of a thermal endurance determination by reduction of systematic errors in the ageing process. If, after ageing, the results for the reference EIM are found to be significantly different from earlier experience, this may indicate changes in material or equipment. This may be investigated and possibly corrected. In any case, the simultaneous ageing of reference and candidate will at least partially compensate for the systematic changes. Statistical procedures for use in assessing the significance of changes are given in Annex A.
- c) To provide instructions for assigning a thermal class to an EIM.

5 Experimental procedures

5.1 Selection of reference EIM

The primary requirement for the reference EIM is that it has a known ~~thermal endurance index (ATE)~~ temperature index (ATI) for the application under consideration. The ~~thermal endurance temperature index~~, if determined by an ~~RTE~~ RTI procedure, is preferably supported by actual service experience (see Annex D).

The expected ageing mechanisms and rates of both materials shall be similar, and relevant to the application.

5.2 Selection of diagnostic test for extent of ageing

The diagnostic test shall be one considered relevant to the application for which the ~~RTE~~ RTI is required. The same test shall be applied to both reference and candidate EIM.



5.3 Ageing procedures

The number and type of test specimens of each material and the ageing temperatures and times shall be in accordance with the requirements of IEC 60216-1:2013, 5.3.2, 5.4 and the first paragraph of 5.5. At each common **20** ageing temperature, the oven load shall comprise appropriate numbers of test specimens of both materials in the same oven. The specimens shall be evenly distributed in the oven so that there is likely to be no systematic difference between

the ageing conditions applied to the specimens of the two materials. It is important that test specimens of both materials are aged simultaneously at a minimum of three temperatures to be included in the calculations.

NOTE As an example, while the data represented in Figure 1 would be acceptable for analysis of the data represented by Figure 2, the lowest temperature group of the candidate EIM and the highest temperature group of the reference cannot be included, since in each case, the specimen group is made up of only one material or one of the two materials did not reach the chosen end point within the test time.

If, when ageing at the selected temperatures is completed, the results from either material do not meet the requirements of **criteria b)** in 7.1 of this document, a further specimen group shall be aged, within the same oven, at an appropriate temperature. This group shall again be composed of the required number and type of specimens of each material.

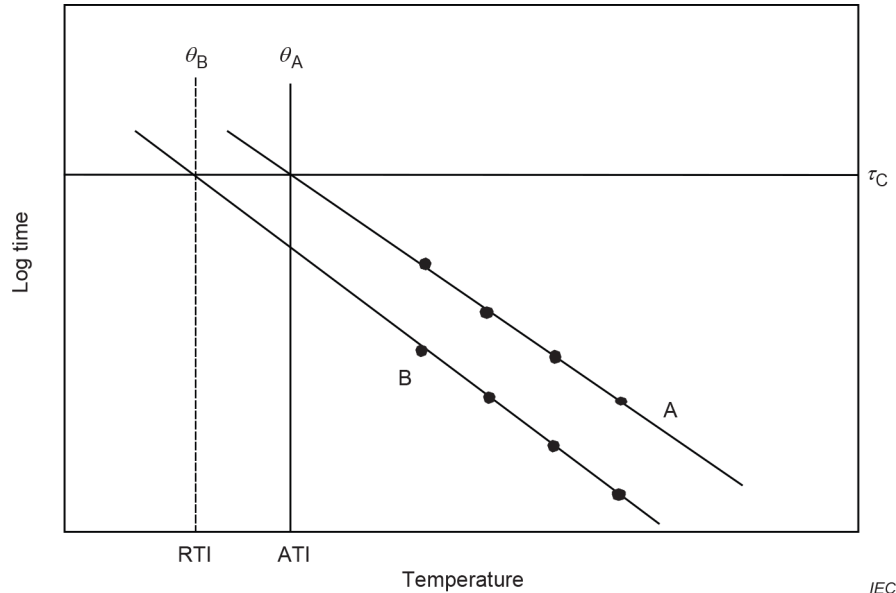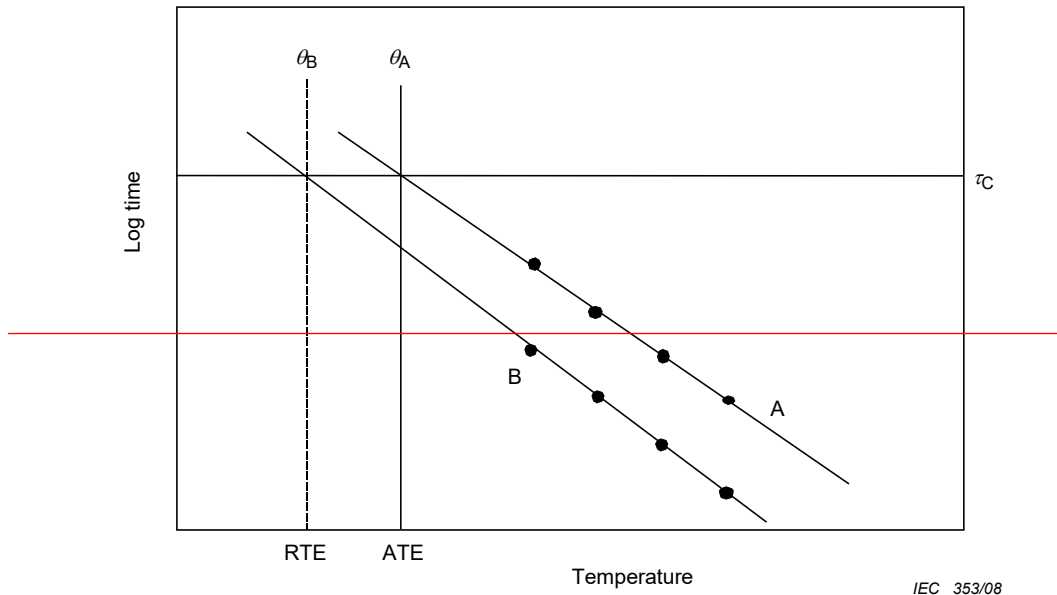


Key


A = reference EIM

B = candidate EIM

Figure 1 – Thermal endurance graphs 21

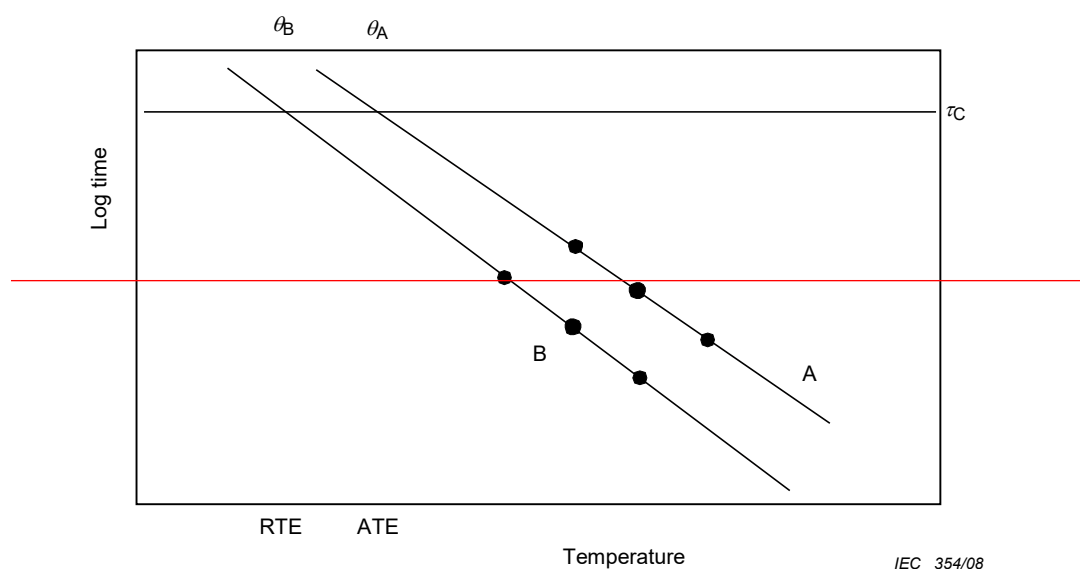

IEC 354/08

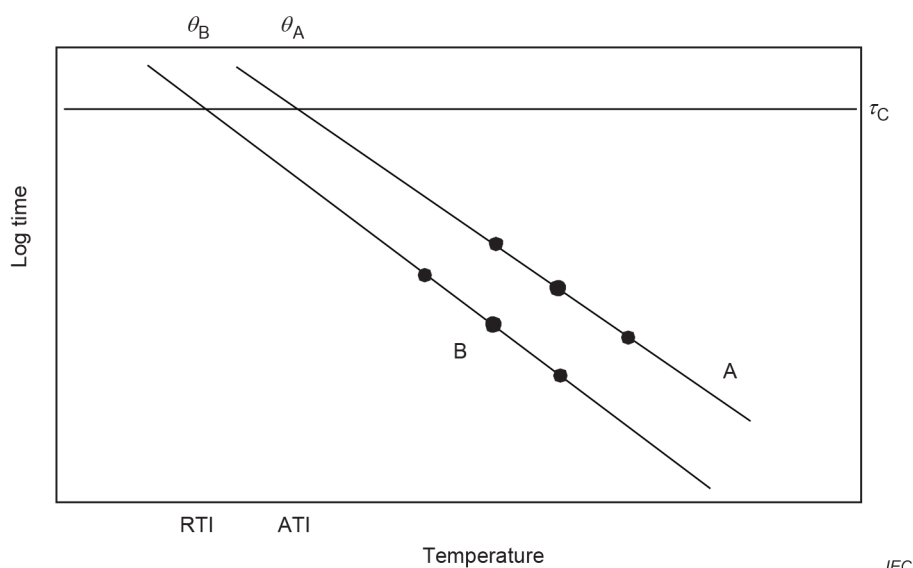

IEC

Key

A = reference EIM

B = candidate EIM

NOTE The test specimens of both materials are not aged simultaneously at a minimum of three temperatures.

Figure 2 – Unacceptable thermal endurance graphs 22**6 Calculation procedures****6.1 Thermal endurance data – Calculation of intermediate parameters**

Calculation of the thermal endurance equations shall be made in accordance with the instructions of IEC 60216-3.

The following input parameters as set out in Table 1 are needed for the calculations relevant to ~~RTE~~ RTI and should be recorded (each of the symbols may have either subscript A for reference EIM or B for candidate EIM).

Table 1 – Input parameters for the calculations concerning ~~RTE~~ RTI

Parameter	Symbol in IEC 60216-3	Equation in IEC 60216-3	Symbol in IEC 60216-5	
Slope of regression line	b	(33)	b_A	b_B
Intercept of regression line	a	(34)	a_A	a_B
Weighted mean of x values	$\bar{x}$	(26)	$\bar{x}_A$	$\bar{x}_B$
Central 2 nd moment of x values	$\mu_2(x)$	(31)	$\mu_{2(A)}$	$\mu_{2(B)}$
Weighted mean of y values	$\bar{y}$	(27)	$\bar{y}_A$	$\bar{y}_B$
Variance of y values	s^2	(41)	s_A^2	s_B^2
Number of y values	N	(25)	n_A	n_B
Halving interval	HIC	(53)	–	HIC _{B(c)}
Largest mean log time to endpoint	$\bar{y}_k$	–	ν_A	ν_B
Lower confidence limit of θ	$\hat{\theta}_c$	(50)	$\theta_{c(A)}$	$\theta_{c(B)}$
NOTE If the calculations of IEC 60216-3 are performed by the recommended computer programme of Annex C 23, ~~subroutines should be included to record the parameters in a data file which can be recalled for the purposes of the present calculations. Alternatively,~~ the values of $\theta_{c(A)}$ and $\theta_{c(B)}$ may be calculated directly in that program.				

The result of the linearity test (IEC 60216-3:2021, 6.3.2) is also ~~needed~~ necessary 24.

6.2 Calculation of ~~RTE~~ RTI

Calculation of the coefficients of the thermal endurance equations shall be made for both reference and candidate EIMs in accordance with the instructions of 6.1 and 6.2 of IEC 60216-3:2021 (see 6.1 of this document). From these coefficients, the values of τ_c and θ_B shall be calculated as below (see also Figure 1).

- a) From the regression coefficients of the reference EIM, calculate the time τ_c corresponding to its ~~ATE~~ ATI:

$$\ln \tau_c = a_A + \frac{b_A}{(\theta_A + \theta_0)} \quad (1)$$

- b) From the regression coefficients of the candidate EIM, calculate the temperature corresponding to the time τ_c :

$$\theta_B = \frac{b_B}{[\ln(\tau_c) - a_B]} - \theta_0 \quad (2)$$

The required ~~RTE~~ RTI is equal to the value of θ_B in degrees Celsius.

6.3 Statistical and numerical tests

6.3.1 Tests of IEC 60216-3

The statistical and numerical tests of IEC 60216-3 shall be carried out before the calculations of this standard, and their results employed in compiling the report of 7.3.

6.3.2 Precision of correlation time

Where a reference EIM has been tested on a previous occasion, with the same diagnostic test and ~~ATE~~ ATI, the values of τ_c should be compared using the Student's t -test for the difference of two means. A significant difference may imply a change in the reference EIM itself, a change in the oven equipment or a change in the test apparatus. The cause should be investigated and reported.

Statistical procedures for assessing the significance of differences between values are given in Annex A.

6.3.3 Lower confidence interval of ~~RTE~~ RTI

The lower confidence limit of ~~RTE~~ RTI is calculated from the lower confidence limits of temperature estimates equal to θ_A and θ_B (IEC 60216-3:2021, 6.3.3 b), Equations (46) to (50)).

The lower confidence limit of θ_B , $\theta_{c(B)}$, is calculated as in IEC 60216-3:2021, 6.3.3 b) for a time equal to τ_c and subtracted from θ_B to give the confidence interval Δ_B .

$$X_{L(B)} = \bar{x}_B + \frac{(Y - \bar{y}_B)}{b_r} + \frac{t s_r}{b_r} \quad (3)$$

$$Y = \ln \tau_c \quad ; \quad \hat{X}_B = (Y - a_B) / b_B \quad (4)$$

$$\text{where } b_r = b_B - \frac{t^2 s_B^2}{b_B \mu_{2(B)}} \quad (5)$$

$$s_r^2 = s_B^2 \left(\frac{b_r}{b_B} + \frac{(\hat{X}_B - \bar{x}_B)^2}{\mu_{2(B)}} \right) \quad (6)$$

Where

t is the value of Student's t for n_B degrees of freedom and a significance level of 0,05 (see Table B.3);

$\mu_{2(B)}$ is the central second moment of the x values:

$$\mu_{2(B)} = \frac{1}{n_B} \sum_{i=1}^k n_{i(B)} (x_{i(B)} - \bar{x}_{(B)})^2 \quad (7)$$

(see IEC 60216-3:2021, 6.2.2 for details).

The lower confidence limit of θ_A , $\theta_{c(A)}$ is calculated as above for a time equal to τ_c and subtracted from θ_A to give the confidence interval Δ_A .

The lower confidence interval of ~~RTE~~ RTI, Δ_R , is then equal to the “Pythagorean” (orthogonal) vector sum of the above two intervals:

$$\Delta_R = \sqrt{\Delta_A^2 + \Delta_B^2} \quad (8)$$

6.3.4 Extrapolation

The extrapolation required to estimate the correlation time is calculated for both reference and candidate EIMs as the difference between the logarithm of the correlation time and the greatest value of the mean of the logarithms of the ageing times to endpoint (ν_A or ν_B). The extrapolation required is the greater of these two values.

7 Results and report 25

7.1 Results of statistical and numerical tests

The following criteria apply:

- linearity of thermal endurance relationships and confidence intervals of TI results of both reference and candidate EIMs (see IEC 60216-3:2021, 6.3.2 and 6.3.3) which shall satisfy the requirements of IEC 60216-3, 7.3.1 and 7.3.2;
- extrapolation to the correlation time (see 6.3.4 above): the extrapolation, expressed as the ratio of correlation time to greatest geometric mean ageing time shall be less than 4;
- lower confidence interval of ~~RTE~~ RTI (see 6.3.3 above): The value of Δ_R shall be less than the halving interval ($HIC_{B(c)}$) of the candidate EIM at a time equal to the correlation time (see IEC 60216-3:2021, 7.1).

$$HIC_{B(c)} = b_B \left[\frac{1}{((\ln \tau_c / 2) - a_B)} - \frac{1}{(\ln \tau_c - a_B)} \right] \quad (9)$$

7.2 Results

The results shall be determined from the calculations of 6.2 and 6.3.3 as follows.

- If all three test criteria (see 7.1) are met, the result shall be the value of ~~RTE~~ RTI. The result shall be reported in the format: "~~RTE~~ RTI according to IEC 60216-5 = xxx" rounded to one full degree Celsius 26.
- If one of the test criteria is not met, the result shall be the lower 95 % confidence limit of ~~RTE~~ RTI. The result shall be reported in the format: "~~RTE~~ RTI lower 95 % confidence limit = xxx" rounded to one full degree Celsius 27.
- If two or more of the criteria are not met, a result in accordance with the requirements of IEC 60216-5 cannot be reported. The result may be reported in the format: "~~RTE~~ RTI = xxx. (Result not validated by the statistical analysis)".

7.3 Report

The report shall comprise the following:

- a) the result;
- b) the identification of the reference EIM and its ~~ATE~~ ATI (see Annex D);
- c) the diagnostic test employed and the endpoint;
- d) the thermal endurance reports according to IEC 60216-1 for the reference and candidate EIMs;
- e) the details of the failure of statistical validation for a result in category 7.2 c).

8 Material testing by short-term thermal ageing

There is often a need for short-term thermal ageing tests on materials, e.g. to compare thermal performances of materials having slight chemical modifications with respect to a known reference EIM, or in quality reference testing of insulation containing anti-oxidant constituents, where ageing at the rated temperature of the material for a period of a few thousand hours could be employed.

The interpretation of such tests can be quite difficult, particularly if the ageing is at a single temperature, with property measurement after a single fixed time. The absence of testing for compliance with a chemical kinetic model leads to a liability to systematic errors caused by equipment or material changes.

It is recommended that in such cases, a reference EIM of similar type and rating as the test material should be aged simultaneously and tested after the same time. A similar analysis to that of Annex A can then be applied to the two sets of property values to establish whether there are significant differences between

- a) the candidate EIM and the reference EIM, or
- b) the current test values of the reference EIM and the historical values obtained on the same material.

In this analysis, s_1^2 and s_2^2 are the variances of the groups of property values after ageing at the test temperature; $\bar{y}_1$ and $\bar{y}_2$ are the means of these groups (see Equations (A.1) to (A.4)).

Unless otherwise specified, the test for significant difference shall be made at a level of 0,05 (see ~~Table B.1~~ Table B.2).

If significant differences are not found, it ~~may~~ can 28 be assumed that the thermal endurance performances of the two materials being compared are the same. If significant differences are found in case a) above, it is likely that the performance of the candidate EIM will not be the same as that of the reference. If significant differences are found in case b) above, then it is likely that the ageing conditions differ in some way from those originally employed: they should be investigated, and the cause established.

9 Insulation classification

When required, the candidate EIM may be assigned to an insulation thermal class in accordance with Annex B, Table B.1.

Annex A (informative)

Repeatability of correlation time

A.1 Overview

Where a reference EIM has been tested on a previous occasion, the values of τ_c should be compared. A significant difference ~~may~~ **can** 29 imply a change in the reference EIM itself, or possibly a change in the oven equipment or a change in the test apparatus. The cause should be investigated and reported.

The comparison is made using the Student's t -test for the difference of two means, by the procedures below. The suffixes 1 and 2 refer to the two sets of data. In the equations, the values $\bar{y}_1$ and $\bar{y}_2$ are the logarithms of the two values of correlation time.

A.2 ~~F-test for equality of variances~~ **linearity** 30

The variances of the y -values for the reference EIMs in the present and previous determinations (s_1^2 and s_2^2) shall be calculated in accordance with the instructions of IEC 60216-3:2021 [6.3.2, Equation (41) or (42)]. Their ratio is then tested for **linearity** i.e. equality of the variances by the F -test on a significance level of 0,05 with degrees of freedom n_1-2 and n_2-2 (see ~~Table B.1~~ **Table B.2**).

NOTE The symbols s_1^2 and s_2^2 here refer to the estimates of variance for the material on occasions 1 and 2, and not to the within and between classes as given in IEC 60216-3:2021, Equations (41) and (42).

A.3 Standard error of the difference of two means

The values of variance are combined using Equations (A.1) and (A.2) if the values are not significantly different:

$$s_D^2 = \frac{s_1^2 (n_1 - 1) + s_2^2 (n_2 - 1)}{(n_1 + n_2 - 2)} \left(\frac{1}{n_1} + \frac{1}{n_2} \right) \quad (\text{A.1})$$

$$n_D = (n_1 + n_2 - 2) \quad (\text{A.2})$$

If the values of variance are significantly different, then Equations (A.3) and (A.4) shall be used. In this case the value n_D may not be an integer. The nearest integer (rounded up or down as appropriate) shall then be employed in subsequent calculations.

$$s_D^2 = \frac{s_1^2}{n_1} + \frac{s_2^2}{n_2} \quad (\text{A.3})$$

$$n_D = \frac{(s_D^2)^2}{\frac{\left(\frac{s_1^2}{n_1}\right)^2}{n_1-1} + \frac{\left(\frac{s_2^2}{n_2}\right)^2}{n_2-1}} \quad (\text{A.4})$$

The square root of the value of s_D^2 is the standard error, s , of the difference of the general means of the y -values.

NOTE When the values of n_1 and n_2 are equal, Equations (A.1) and (A.3) become identical.

A.4 Student's t -test for difference of two means

When two estimates of a mean value (which in this case includes estimates by linear regression) are obtained from separate sets of data and the true values are expected to be the same, their equality may be tested by the Student's t -test. The principle of this test is to calculate the ratio of the difference of the mean estimates to the standard error of this difference. The variances of the two data sets are combined in the same way as the variances in Clause A.3 and the standard error calculated.

The value of t is the ratio of the difference of the means to the standard error:

$$t = \frac{(\bar{y}_1 - \bar{y}_2)}{\sqrt{s_D^2}} \quad (\text{A.5})$$

The associated number of degrees of freedom is n_D or the nearest integer. If the value of t is greater than the value for a significance level of 0,05 given in ~~Table B.2~~ Table B.3, the difference is considered to be significant and its cause should be investigated.

For the purposes of 6.3.2, in the calculations of Equations (A.1) to (A.5), the values of s_1^2 and s_2^2 are obtained using Equation (45) of IEC 60216-3:2021, 6.3.3, which is:

$$s_Y^2 = \frac{s^2}{N} \left[1 + \frac{(X - \bar{x})^2}{\mu_2(x)} \right]$$

$$s_1^2 = \left| N s_Y^2 \right|_1 \quad \text{and} \quad s_2^2 = \left| N s_Y^2 \right|_2 \quad (\text{A.6})$$

The values of $\bar{y}_1$ and $\bar{y}_2$ are the logarithms of the two values of τ_c .

A.5 Combination of data

If the two results for correlation time and the two values of variance are not significantly different, a more precise estimate of the logarithm of correlation time may be obtained by merging the two sets of data:

$$\bar{y} = \frac{(n_1 \bar{y}_1 + n_2 \bar{y}_2)}{(n_1 + n_2)} \quad (\text{A.7})$$

$$s^2 = \frac{s_1^2 (n_1 - 1) + s_2^2 (n_2 - 1)}{(n_1 + n_2 - 2)} \quad (\text{A.8})$$

Annex B (informative)

Thermal class assignment

Table B.1 relates the thermal class assignment, when required, to the value of ~~ATE/RTE~~ ~~ATI/RTI~~, in accordance with IEC 60085.

Table B.1 – Thermal class equivalents for insulating material

~~ATE/RTE~~ ~~ATI/RTI~~ °C		Thermal class °C	Letter designation
≥90	<105	90	Y
≥105	<120	105	A
≥120	<130	120	E
≥130	<155	130	B
≥155	<180	155	F
≥180	<200	180	H
≥200	<220	200	N
≥220	<250	220	R
≥250	<275	250	
^a If desired, the letter designation may be added in parentheses, e.g. Class 180 (H). Where space is a factor, such as on a nameplate, the product TC may elect to use only the letter designation. ^b Designations of thermal classes over 250 shall increase by increments of 25 and be designated accordingly.			

Table B.2 and Table B.3 give the values of F and of Student's t for significance levels of 0,05 and 0,005.

NOTE 1 The significance, p , is equal to $1-P$, where P is the probability of the stochastic variable (F or t) being less than the tabulated value.

The columns of the F table (Table B.2) represent the number of degrees of freedom of the numerator and the rows the number of degrees of freedom of the denominator.

The columns of the t table (Table B.3) represent the number of degrees of freedom and the rows the significance level (p).

NOTE 2 The tables include significance levels of 0,05 and 0,005 in case they ~~should~~ are needed at any time ~~be~~ needed. For present purposes, the 0,005 values ~~may~~ can be deleted, but they are on record for future use.

Table B.2 – F - function; $p = 0,05$

	10	11	12	13	14	15	16	17	18	19	20	25	30	40	50	100	500
10	2,978	2,943	2,913	2,887	2,865	2,845	2,828	2,812	2,798	2,785	2,774	2,730	2,700	2,661	2,637	2,588	2,548
11	2,854	2,818	2,788	2,761	2,739	2,719	2,701	2,685	2,671	2,658	2,646	2,601	2,570	2,531	2,507	2,457	2,415
12	2,753	2,717	2,687	2,660	2,637	2,617	2,599	2,583	2,568	2,555	2,544	2,498	2,466	2,426	2,401	2,350	2,307
13	2,671	2,635	2,604	2,577	2,554	2,533	2,515	2,499	2,484	2,471	2,459	2,412	2,380	2,339	2,314	2,261	2,218
14	2,602	2,565	2,534	2,507	2,484	2,463	2,445	2,428	2,413	2,400	2,388	2,341	2,308	2,266	2,241	2,187	2,142
15	2,544	2,507	2,475	2,448	2,424	2,403	2,385	2,368	2,353	2,340	2,328	2,280	2,247	2,204	2,178	2,123	2,078
16	2,494	2,456	2,425	2,397	2,373	2,352	2,333	2,317	2,302	2,288	2,276	2,227	2,194	2,151	2,124	2,068	2,022
17	2,450	2,413	2,381	2,353	2,329	2,308	2,289	2,272	2,257	2,243	2,230	2,181	2,148	2,104	2,077	2,020	1,973
18	2,412	2,374	2,342	2,314	2,290	2,269	2,250	2,233	2,217	2,203	2,191	2,141	2,107	2,063	2,035	1,978	1,929
19	2,378	2,340	2,308	2,280	2,256	2,234	2,215	2,198	2,182	2,168	2,155	2,106	2,071	2,026	1,999	1,940	1,891
20	2,348	2,310	2,278	2,250	2,225	2,203	2,184	2,167	2,151	2,137	2,124	2,074	2,039	1,994	1,966	1,907	1,856
25	2,236	2,198	2,165	2,136	2,111	2,089	2,069	2,051	2,035	2,021	2,007	1,955	1,919	1,872	1,842	1,779	1,725
30	2,165	2,126	2,092	2,063	2,037	2,015	1,995	1,976	1,960	1,945	1,932	1,878	1,841	1,792	1,761	1,695	1,637
40	2,077	2,038	2,003	1,974	1,948	1,924	1,904	1,885	1,868	1,853	1,839	1,783	1,744	1,693	1,660	1,589	1,526
50	2,026	1,986	1,952	1,921	1,895	1,871	1,850	1,831	1,814	1,798	1,784	1,727	1,687	1,634	1,599	1,525	1,457
100	1,927	1,886	1,850	1,819	1,792	1,768	1,746	1,726	1,708	1,691	1,676	1,616	1,573	1,515	1,477	1,392	1,308
500	1,850	1,808	1,772	1,740	1,712	1,686	1,664	1,643	1,625	1,607	1,592	1,528	1,482	1,419	1,376	1,275	1,159

F - function; $p = 0,005$

	10	11	12	13	14	15	16	17	18	19	20	25	30	40	50	100	500
10	5,847	5,746	5,661	5,589	5,526	5,471	5,422	5,379	5,340	5,305	5,274	5,153	5,071	4,966	4,902	4,772	4,666
11	5,418	5,320	5,236	5,165	5,103	5,049	5,001	4,959	4,921	4,886	4,855	4,736	4,654	4,551	4,488	4,359	4,252
12	5,085	4,988	4,906	4,836	4,775	4,721	4,674	4,632	4,595	4,561	4,530	4,412	4,331	4,228	4,165	4,037	3,931
13	4,820	4,724	4,643	4,573	4,513	4,460	4,413	4,372	4,334	4,301	4,270	4,153	4,073	3,970	3,908	3,780	3,674
14	4,603	4,508	4,428	4,359	4,299	4,247	4,200	4,159	4,122	4,089	4,059	3,942	3,862	3,760	3,698	3,569	3,463
15	4,424	4,329	4,250	4,181	4,122	4,070	4,024	3,983	3,946	3,913	3,883	3,766	3,687	3,585	3,523	3,394	3,287
16	4,272	4,179	4,099	4,031	3,972	3,920	3,875	3,834	3,797	3,764	3,734	3,618	3,539	3,437	3,375	3,246	3,139
17	4,142	4,050	3,971	3,903	3,844	3,793	3,747	3,707	3,670	3,637	3,607	3,492	3,412	3,311	3,248	3,119	3,012
18	4,030	3,938	3,860	3,793	3,734	3,683	3,637	3,597	3,560	3,527	3,498	3,382	3,303	3,201	3,139	3,009	2,901
19	3,933	3,841	3,763	3,696	3,638	3,587	3,541	3,501	3,465	3,432	3,402	3,287	3,208	3,106	3,043	2,913	2,804
20	3,847	3,756	3,678	3,611	3,553	3,502	3,457	3,416	3,380	3,347	3,318	3,203	3,123	3,022	2,959	2,828	2,719
25	3,537	3,447	3,370	3,304	3,247	3,196	3,151	3,111	3,075	3,043	3,013	2,898	2,819	2,716	2,652	2,519	2,406
30	3,344	3,255	3,179	3,113	3,056	3,006	2,961	2,921	2,885	2,853	2,823	2,708	2,628	2,524	2,459	2,323	2,207
40	3,117	3,028	2,953	2,888	2,831	2,781	2,737	2,697	2,661	2,628	2,598	2,482	2,401	2,296	2,230	2,088	1,965
50	2,988	2,900	2,825	2,760	2,703	2,653	2,609	2,569	2,533	2,500	2,470	2,353	2,272	2,164	2,097	1,951	1,821
100	2,744	2,657	2,583	2,518	2,461	2,411	2,367	2,326	2,290	2,257	2,227	2,108	2,024	1,912	1,840	1,681	1,529
500	2,562	2,476	2,402	2,337	2,281	2,230	2,185	2,145	2,108	2,075	2,044	1,922	1,835	1,717	1,640	1,460	1,260

Table B.3 – *t*-function

	10	11	12	13	14	15	16	17	18	19	20	25	30	40	50	100	500
<i>p</i> = 0,05	1,812	1,796	1,782	1,771	1,761	1,753	1,746	1,740	1,734	1,729	1,725	1,708	1,697	1,684	1,676	1,660	1,648
<i>p</i> = 0,005	3,169	3,106	3,055	3,012	2,977	2,947	2,921	2,898	2,878	2,861	2,845	2,787	2,750	2,704	2,678	2,626	2,586

Annex C (informative)

Computer program

~~C.1 Computer programs for IEC 60216-5:2008 (RTE)~~

~~C.1.1 General~~

~~The standard is accompanied by a CDROM.~~

~~This CDROM contains three programs for calculation of the Relative Thermal Endurance Index of an insulating material, from data in accordance with IEC 60216-1 and 60216-3. It also contains a pair of data files for trial purposes. 31~~

~~All programs are supplied as source code, suitable for Microsoft Quick Basic 4.5 or Professional Basic v.7 (to enable use with Visual Basic, considerable editing will probably be required) and as executable program files to run in a DOS window under any variety of Windows. For optimum performance, the DOS window should be full screen.~~

~~C.1.2 Entry.exe and Entry.bas~~

~~This is identical to the data entry file supplied in an annex of IEC 60216-3. A separate set of data is required for each material, Control and Candidate.~~

~~C.1.3 IEC 216-5.exe and IEC 216-5.bas~~

~~This program is an enhanced version of the program supplied in an annex of IEC 60216-3. It has been enhanced by addition of a procedure to record to a data file the intermediate data required for calculation of RTE. When the experimental data are processed, the intermediate data are automatically saved to a file with the same name as the experimental data file and the ending ".int". For example, a data file n3.dst of destructive test data would generate an intermediate file n3.int. The thermal endurance graph is drawn to screen for each material, and the statistical test results are reported.~~

~~C.1.4 RTE.exe and RTE.bas~~

~~This program requests the intermediate data files for Control and Candidate, and performs the calculations of IEC 60216-5, giving the RTE and its confidence interval, the halving intervals of both materials (HIC), the correlation time and the ratio of the correlation time to the longest time to endpoint (extrapolation). These values are required for the purposes of 6.1 and 6.2 of the standard.~~

~~C.2 Data file structure~~

~~C.2.1 Experimental data~~

~~The structure of these files is explained in IEC 60216-3.~~

~~C.2.2 Intermediate data~~

~~The following values are recorded, one to each line in the file, which is a simple ASCII text file.~~

~~General mean of x values (reciprocal Kelvin temperatures): $\bar{x}$~~

~~General mean of y values (logarithm of time values): $\bar{y}$~~

~~Moyenne générale des valeurs de y (logarithme des durées): $\bar{y}$~~

~~Non-regression variance of y values: s~~

~~Number of y values: n~~

~~Regression slope: b~~

~~Regression intercept: a~~

~~Longest ageing time to endpoint: t_{∞}~~

C.3 Data files

~~There are two data files, Control.dta and Candidate.dta. For simplicity, these are non-destructive test data, although in practice, destructive tests are much more widely used in RTE work. If used as input for iec216-5.exe, they will generate the corresponding intermediate variable files (which are also provided on the diskette for confirmation purposes).~~

~~The operation of RTE.exe can be demonstrated using these files Control.int and Candidate.int.~~

C.1 General

C.1.1 Overview

The program supplementing this document as well as IEC 60216-3:2021 and IEC 60216-6:–, is written in the programming language Java^{®1} and makes use of the JavaFX technology for graphical user interfaces. It is for use in conjunction with a Java Runtime Environment (JRE) from Oracle[®] in version 1.8.101 or later. The JRE is available for download at <https://www.java.com/download> for several operating systems² running on either 32-bit or 64-bit computers.

The package itself is available for download from <https://www.iec.ch/tc112/supportingdocuments> **32**. The downloaded files are stored in the standard unencrypted zip-format. Such file archives can be extracted with any zip tool, see for example <https://download.cnet.com/s/zip-tools/>.

NOTE 1 All hyperlinks can be subjected to change, which is not under control of the authors of this document.

The package consists of the following parts:

- Compiled Java code and 3rd party program libraries:
 - IEC60216fx.jar (main program)
 - IEC60216fx.exe (optional program launcher for Windows)
 - lib/commons-math3-3.6.1 (statistical functions)
 - lib/poi-3.17.jar (Import and Export in OOXML format (*.xlsx))
- Example data files
 - Cenex3.dta – see IEC 60216-3:2021, Table D.1
 - Test2.dta – see IEC 60216-3:2021, Table D.2
 - N3.dst and N3_selected.xlsx – see IEC 60216-3:2021, Table D.3
 - Control.dta – example reference EIM raw data (non-destructive test method)

¹ Java[®] and Oracle[®] are registered trademarks of Oracle and/or its affiliates. This information is given for the convenience of users of this document and does not constitute an endorsement by IEC of the products named. Equivalent products may be used if they can be shown to lead to the same results.

² Microsoft Windows[®], Linux[®] and Apple macOS[®] are examples of suitable products available. This information is given for the convenience of users of this document and does not constitute an endorsement by IEC of these products.

- Candidate.dta – example candidate EIM raw data (non-destructive test method)
 - Control.ftd and Control_selected.xlsx – see IEC 60216-6
 - The usage of the deprecated intermediate file formats such as *.int and *.ftc is not supported in the graphical user interface. However, the application programming interface (API) implements methods to read and write these file formats.
- Java source code
 - Package: datamodel – class AgingData and subclasses to comprise raw data
 - Package: mathematics – calculate results
 - Package: fxmml_gui – the JavaFX graphical user interface
 - Package: ressources – example files as listed above
 - Javadoc
 - A number of automatically generated linked html pages for offline usage with a web browser. They describe the classes, constructors and methods of the packages 'datamodel' and 'mathematics' for use by Java programmers. New or modified user interfaces can be developed which use the tested class AgingData to store and evaluate aging data.
 - JUnit tests
 - The testing refers to packages 'datamodel' and 'mathematics'. The output of all JUnit tests is compiled in one document named Testing_2017-10-12.pdf.

The IEC60216fx.jar is suitable for direct execution by the JRE. In a terminal window change to the directory or folder, where this file is stored and type <JRE8 root path>\jre\bin\java.exe -jar "IEC60216fx.jar". Thereby, <JRE8 root path> stands for the directory or folder, where the JRE is stored.

NOTE 2 In Windows, the directory separator is a "\", while in Linux and macOS it is a "/".

There are three different ways, how to make the execution of the program more convenient. They are described in C.1.2. The first is the recommended method, because it implies the least system requirements.

C.1.2 Convenience program execution

C.1.2.1 First (and default) method

It is important to know, that Java programs do not need installation/setup in a conventional way. Instead, the JAR files residing in one folder and the JRE residing in another folder just need to be linked together:

- download and decompress the file dist_v100.zip in a folder with write access (e.g. Documents\IEC60216fx\dist);
- download and decompress the JRE in any other folder with write access (e.g. Documents\JRE);
- create a new shortcut on the Desktop
 - a) Command: <JRE8 root path>\jre\bin\java.exe -jar "IEC60216fx.jar"
 - b) Folder Path: <Application root path>\dist.

In MS-Windows (screenshot: Windows 7, English language version), the shortcut properties look like:

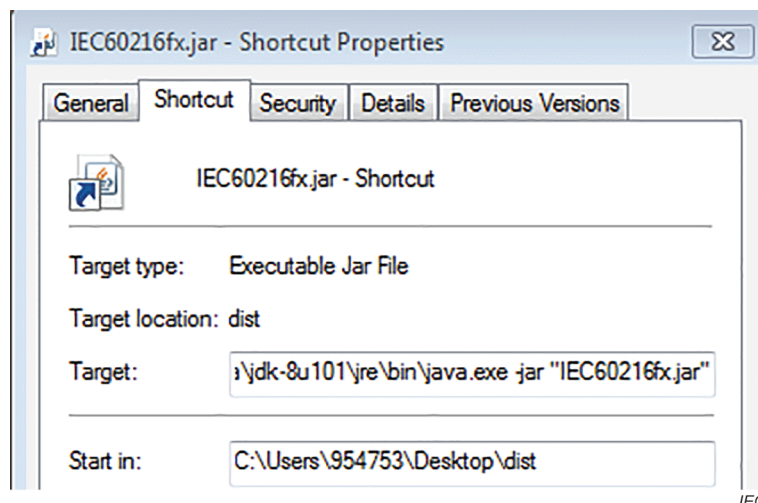


Figure C.1 – Shortcut property dialog for program launch

A double-click on the short-cut launches the application. Likewise, such a shortcut can be created in other operating systems and used for convenience program execution.

C.1.2.2 Second method

The IEC60216fx.exe is provided with the IEC60216fx.jar file in the same zip archive. It is a convenience launcher for MS-Windows, that runs the program directly with a double-click. It requires one of the following:

- a) The JRE version 1.8.101 or later is properly installed (i.e. registered) on the computer.
OR
- b) Administrator privileges are granted: in that case, the launcher will first download and install the appropriate JRE and then run the program. For the second and further launches, Administrator privileges are no longer required, unless the JRE was uninstalled meanwhile.

NOTE If the JRE is installed correctly, a double-click on the IEC60216fx.jar file will also launch the application.

C.1.2.3 Third method

Similarly, a double-click on the file IEC60216fx.html provided with the IEC60216fx.jar in the same zip archive, attempts to launch the program in the default web browser of the system. However, this functionality is blocked in many browsers by default. It needs to be enabled manually in the browser properties and may create a system vulnerability.

NOTE The file IEC60216fx.jnlp is a text file in XML format to configure this functionality.

C.2 Structure of data files used by the program 33

The required data files and formats are described in IEC 60216-3:2021, Clause E.2. Examples are given in IEC 60216-3:2021, Clause E.3.