IEC 60793-1-31

Edition 3.0 2019-02

INTERNATIONAL STANDARD

NORME INTERNATIONALE

Optical fibres –
Part 1-31: Measurement methods and test procedures –Tensile strength

Fibres optiques –
Partie 1-31: Méthodes de mesure et procédures d'essai –Résistance à la traction

IEC 60793-1-31:2019-02(en-fr)

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2019 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de l'IEC ou du Comité national de l'IEC du pays du demandeur. Si vous avez des questions sur le copyright de l'IEC ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de l'IEC de votre pays de résidence.

IEC Central Office
3, rue de Varembé
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC
The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications
The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform
The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,…). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished
Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc
If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

Electropedia - www.electropedia.org
The world's leading online dictionary on electrotechnology, containing more than 22 000 terminological entries in English and French, with equivalent terms in 16 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary
67 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

A propos de l'IEC
La Commission Electrotechnique Internationale (IEC) est la première organisation mondiale qui élabore et publie des Normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications IEC
Le contenu technique des publications IEC est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

Recherche de publications IEC - webstore.iec.ch/advsearchform
La recherche avancée permet de trouver des publications IEC en utilisant différents critères (numéro de référence, texte, comité d'études,…). Elle donne aussi des informations sur les projets et les publications remplacées ou retirées.

IEC Just Published - webstore.iec.ch/justpublished
Restez informé sur les nouvelles publications IEC. Just Published détaille les nouvelles publications parues. Disponible en ligne et une fois par mois par email.

Service Clients - webstore.iec.ch/csc
Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions contactez-nous: sales@iec.ch.

Electropedia - www.electropedia.org
Le premier dictionnaire d'électrotechnologie en ligne au monde, avec plus de 22 000 articles terminologiques en anglais et en français, ainsi que les termes équivalents dans 16 langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International (IEV) en ligne.

Glossaire IEC - std.iec.ch/glossary
67 000 entrées terminologiques électrotechniques, en anglais et en français, extraites des articles Termes et Définitions des publications IEC parues depuis 2002. Plus certaines entrées antérieures extraites des publications des CE 37, 77, 86 et CISPR de l'IEC.

AVA Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

IEC 60793-1-31

Edition 3.0 2019-02

INTERNATIONAL STANDARD

NORME INTERNATIONALE

Optical fibres –
Part 1-31: Measurement methods and test procedures –Tensile strength

Fibres optiques –
Partie 1-31: Méthodes de mesure et procédures d'essai –Résistance à la traction

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

COMMISSION
ELECTROTECHNIQUE
INTERNATIONALE

ICS 33.180.10

ISBN 978-2-8322-6529-1

Warning! Make sure that you obtained this publication from an authorized distributor.
Attention! Veuillez vous assurer que vous avez obtenu cette publication via un distributeur agréé.

® Registered trademark of the International Electrotechnical Commission
Marque déposée de la Commission Electrotechnique Internationale

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

CONTENTS

FOREWORD 4
INTRODUCTION 6
1 Scope 7
2 Normative references 7
3 Terms and definitions 7
4 Hazards 7
5 Apparatus 8
5.1 General 8
5.2 Gripping the fibre at both ends 8
5.3 Sample support 8
5.4 Stretching the fibre 8
5.5 Measuring the force at failure 9
5.6 Environmental control equipment 9
6 Sample preparation 10
6.1 Definition 10
6.2 Sample size and gauge length 10
6.3 Auxiliary measurements 11
6.4 Environment 11
7 Procedure 11
7.1 Preliminary steps 11
7.2 Procedure for a single specimen 11
7.3 Procedure for completing all samples for a given nominal strain rate 12
8 Calculations 12
8.1 Conversion of tensile load to failure stress 12
8.2 Preparation of a Weibull plot 13
8.3 Computation of Weibull parameters 13
9 Results 14
9.1 Details to be reported 14
9.2 Details to be recorded 15
10 Specification information 15
Annex A (informative) Typical testing apparatus of tensile strength under dynamic loading 16
Annex B (informative) Guidelines on gripping the fibre 18
Annex C (informative) Guidelines on stress rate 22
Bibliography 24

Figure 1 – Bimodal tensile strength Weibull plot for a 20 m gauge length test set-up at 5 %/min strain rate 10
Figure A.1 – Capstan design 16
Figure A.2 – Translation test apparatus 16
Figure A.3 – Rotating capstan apparatus 17
Figure A.4 – Rotating capstan apparatus for long lengths 17
Figure A.5 – Ganged rotating capstan tester 17
Figure B.1 – Gradual slippage 18

AVA Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

Figure B.2 – Irregular slippage 18
Figure B.3 – Sawtooth slippage 19
Figure B.4 – Acceptable transfer function 19
Figure B.5 – Typical capstan 20
Figure B.6 – Isostatic compression 20
Figure B.7 – Escargot wrap 21
Figure C.1 – System to control stress rate 22
Figure C.2 – Time variation of load and loading speed 23

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

INTERNATIONAL ELECTROTECHNICAL COMMISSION

OPTICAL FIBRES –

Part 1-31: Measurement methods and test procedures – Tensile strength

FOREWORD

1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
6) All users should ensure that they have the latest edition of this publication.
7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 60793-1-31 has been prepared by subcommittee 86A: Fibres and cables, of IEC technical committee 86: Fibre optics.

This third edition cancels and replaces the second edition published in 2010. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

a) correction of Formulae (3b) and (4b) and renumbering of formulae.

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

The text of this International Standard is based on the following documents:

FDIS	Report on voting
86A/1908/FDIS	86A/1926/RVD

Full information on the voting for the approval of this International Standard can be found in the report on voting indicated in the above table.

This document has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all parts in the IEC 60793 series, published under the general title *Optical fibres*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under "http://webstore.iec.ch" in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

INTRODUCTION

Failure stress distributions can be used to predict fibre reliability in different conditions. IEC TR 62048 shows mathematically how this can be done. To complete a given reliability projection, the tests used to characterize a distribution are controlled for the following:

- population of fibre, for example coating, manufacturing period, diameter;
- gauge length, i.e. length of section that is tested;
- stress or strain rates;
- testing environment;
- preconditioning or aging treatments;
- sample size.

This method measures the strength of optical fibre at a specified constant strain rate. It is a destructive test, and is not a substitute for proof-testing.

This method is used for those typical optical fibres for which the median fracture stress is greater than 3,1 GPa (450 kpsi[1]) in 0,5 m gauge lengths at the highest specified strain rate of 25 %/min. For fibres with lower median fracture stress, the conditions herein have not demonstrated sufficient precision.

Typical testing is conducted on "short lengths", up to 1 m, or on "long lengths", from 10 m to 20 m with sample size ranging from 15 to 30.

The test environment and any preconditioning or aging are critical to the outcome of this test. There is no agreed upon model for extrapolating the results for one environment to another environment. For failure stress at a given stress or strain rate, however, as the relative humidity increases, failure stress decreases. Both increases and decreases in the measured strength distribution parameters have been observed as the result of preconditioning at elevated temperature and humidity for even a day or two.

This test is based on the theory of fracture mechanics of brittle materials and on the power-law description of flaw growth (see IEC TR 62048). Although other theories have been described elsewhere, the fracture mechanics based on power-law theory is the most generally accepted.

A typical population consists of fibre that has not been deliberately damaged or environmentally aged. A typical fibre has a nominal diameter of 125 mm, with a 250 mm or less diameter acrylate coating. Default conditions are given for such typical populations. Non-typical populations might include alternative coatings, environmentally aged fibre, or deliberately damaged or abraded fibre. Guidance for non-typical populations is also provided.

[1] kpsi = kilopounds per square inch.

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

OPTICAL FIBRES –

Part 1-31: Measurement methods and test procedures – Tensile strength

1 Scope

This part of IEC 60793 provides values of the tensile strength under dynamic loading of optical fibre samples. The method tests individual lengths of uncabled and unbundled glass optical fibre. Sections of fibre are broken with controlled increasing stress or strain that is uniform over the entire fibre length and cross section. The stress or strain is increased at a nominally constant rate until breakage occurs.

The distribution of the tensile strength values of a given fibre strongly depends on the sample length, loading velocity and environmental conditions. The test can be used for inspection where statistical data on fibre strength is required. Results are reported by means of statistical quality control distribution. Normally, the test is carried out after temperature and humidity conditioning of the sample. However, in some cases, it can be sufficient to measure the values at ambient temperature and humidity conditions.

This method is applicable to categories A1, A2, and A3, and classes B and C optical fibres.

The object of this document is to establish uniform requirements for the mechanical characteristic: tensile strength.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60793-1-20, *Optical fibres – Part 1-20: Measurement methods and test procedures – Fibre geometry*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at http://www.electropedia.org/
- ISO Online browsing platform: available at http://www.iso.org/obp

4 Hazards

This test involves stretching sections of optical fibre until breakage occurs. Upon breakage, glass fragments can be distributed in the test area. Protective screens are recommended. Safety glasses shall be worn at all times in the testing area.

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

5 Apparatus

5.1 General

Clause 5 specifies the fundamental requirements of the equipment used for dynamic strength testing. There are many configurations that can meet these requirements. Some examples are presented in Annex A. The choice of a specific configuration will depend on such factors as

- the gauge length of a specimen,
- the stress or strain rate range,
- the environmental conditions, and
- the strength of the specimens.

5.2 Gripping the fibre at both ends

Grip the fibre to be tested at both ends and stretch it until failure occurs in the gauge length section. The grip shall not allow the fibre to slip out prior to failure and shall minimize failure at the grip.

Record a break that occurs at the grip, but do not use it in subsequent calculations. Since fibre strain is increasing during the test, some slippage occurs at the grip. At higher stress levels, associated with short gauge lengths, slippage can induce damage and cause gripping failures that are difficult to ascertain. The frequency of such failures can often vary with stress or strain rate. Careful inspection of the residual fibre pieces, or other means, is required to prevent the possibility of including gripping failures in the analysis.

Use a capstan, typically covered with an elastomeric sheath, to grip the fibre (see Figure A.1). Wrap a section of fibre that will not be tested around the capstan several times and secure the fibre at the ends with, for example, an elastic band. Wrap the fibre with no crossovers. The capstan surface shall be tough enough so that the fibre does not cut into it when fully loaded. The amount of slippage and capstan failures depends on the interaction of the fibre coating and the capstan surface material, thickness, and number of wraps. Careful preliminary testing is required to confirm the choice of a capstan surface.

Design the diameter of the capstan and pulley so that the fibre does not break on the capstan due to bend stress. For typical silica-clad fibres, the bend stresses shall not exceed 0,175 GPa.

EXAMPLE For a typical 125 µm cladding/250 µm coating silica fibre, the minimum capstan diameter is 50 mm.

A particular gripping implementation is given in Annex B.

5.3 Sample support

Attach the specimen to the two grips. The gauge length is the length of fibre between the axes of the gripping capstans before it is stretched. To reduce the space required to perform the test on long gauge lengths, one or more pulleys may be used to support the specimen (see Figure A.4). The pulleys shall be designed, and their surfaces kept free of debris, so the fibre is not damaged by them. The remainder of the fibre, away from pulleys and capstans, shall not be touched.

When multiple fibres are tested simultaneously, as in Figure A.5, a baffle arrangement is required to prevent a broken fibre from snapping into, or otherwise perturbing the other fibres under test.

5.4 Stretching the fibre

Stretch the fibre at a fixed nominal strain rate until it breaks. The nominal strain rate is expressed as the percent increase in length per minute, relative to the gauge length.

AVA Documents
Document Sharing Hub
Full document details: IEC 60793-1-31 2019

There are two basic alternatives for stretching the fibre.

– Method A: Increase the separation between the gripping capstans by moving them apart at a fixed rate of speed, with the starting separation equal to the gauge length (Figure A.2).
– Method B: Rotate a capstan at a fixed rate to take up the fibre and strain the section between capstans (Figures A.3 to A.5). The rotation shall not result in crossovers on the capstan.

Calibrate the strain rate to within ±10 % of the nominal strain rate. Some equipment configurations are computer-controlled and allow dynamic control of the capstan motion to produce a constant stress rate. A particular implementation of this is given in Annex C.

The strain rate shall be agreed between customer and supplier. A strain rate range of either 2,5 % to 5 % or 15 % to 25 % is typically used.

5.5 Measuring the force at failure

Measure the tensile load (force in tension) at failure for each specimen by a calibrated load cell, to within ±1 % of the actual load. This can be done with a variety of methods:

- strip chart recorder;
- peak and hold meter;
- computer sampling.

Provide a means of measuring the tensile load as a function of time to determine the stress rate. This is not required for each individual test, but shall be done occasionally.

Calibrate the load cell to within 0,5 % of the failure, or maximum load, for each range of failure loads, while it is oriented in the same manner as when testing a fibre. Do this by substituting a string attached to a known weight for the test specimen. For method B, a light, low-friction pulley can be used in place of the capstan that is not attached to the load cell. The string, with one end attached to the load cell capstan and the other end attached to a known weight, shall duplicate the direction of a test specimen and be of a diameter comparable to that of a test specimen. A minimum of three calibration weights, bracketing the typical failures, is recommended.

5.6 Environmental control equipment

Measured failure stress and fatigue characteristics are known to vary with temperature and humidity of the fibre, both of which shall be controlled during both preconditioning and test. Many equipment configurations can be used to provide the required controls, including controls on the entire room in which testing is conducted.

The following are the typical control requirements:

- temperature: 23 °C ± 2 °C;
- relative humidity: 50 % ± 5 %.

Alternative test environments, such as high non-precipitating humidity, can be achieved by enclosing the test specimen and injecting water vapour into the enclosure. Figure A.5 shows a ganged tester that includes an enclosure over a circulating water bath.

Documents
Document Sharing Hub
Full document details: IEC 60793-1-31 2019

6 Sample preparation

6.1 Definition

A sample is one or more fibres from a population. Each sample provides a result by cutting it into smaller lengths called specimens. Testing results on these specimens are combined to yield an overall result for the sample. The term "sample size" is used to indicate the number of specimens tested in the rest of the document.

For ribbonized fibre, select the specimens uniformly across the ribbon structure. Exercise caution in removing fibre from the ribbon to avoid inadvertent strength reduction.

6.2 Sample size and gauge length

The result of testing is a statistical distribution of failure stress values. Hence all reported parameters are statistical in nature, with inherent variability that is a function of the sample size and the variability of the flaw size within the sample. The weakest site, or largest flaw, within a specimen will fail, and the typical failure stress decreases as gauge length increases.

A given population can have flaws generated from multiple causes. An example is a bi-modal aggregate distribution as shown in the Weibull plot of Figure 1 (see also 8.2) obtained for a 20 m gauge length set-up. The narrow near vertical distribution on the right (around 5 GPa) is called the intrinsic region; the wider distribution below this 5 GPa is the extrinsic region.

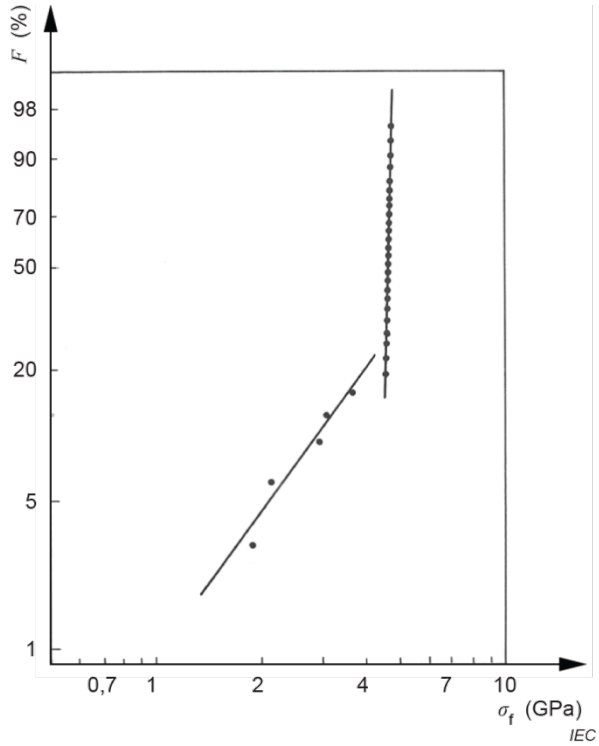

Figure 1 – Bimodal tensile strength Weibull plot for a 20 m gauge length test set-up at 5 %/min strain rate

Testing on gauge lengths of 0,5 m does not typically result in measuring flaws from the extrinsic region. From time to time, however, the failure stress of an extrinsic flaw is measured and appears as an "outlier". If the outlier is included in the data analysis, errors in the parameters will occur. For typical testing, uniform outlier removal techniques are recommended.

Documents
Document Sharing Hub
Full document details: IEC 60793-1-31 2019

For tests which are designed to measure the characteristics of the extrinsic region, large sample sizes (hundreds of specimens) and long gauge lengths (20 m) are recommended. For characterization of the intrinsic region as per this document, a gauge length of 0,5 m is often used. For the dynamic strength, a sample size of 30 is often used. Any deviation from these values is to be specified in the detail specification.

Statistical analysis can be performed to determine whether a given precision has been achieved.

6.3 Auxiliary measurements

Failure stress calculations require a conversion of tensile load to the stress on the cross section of the glass portion of the fibre. The cladding diameter, as measured by IEC 60793-1-20, shall be used in this calculation to compute the cross sectional area. The coating also bears part of the tensile load that decreases the stress on the glass cross section. Subclause 8.1 contains formulae for stress calculations.

The coating correction factor is a function of the coating thickness, measured by IEC 60793-1-21 and Young's modulus of each coating layer and the modulus of the glass. The modulus of cured coating is often characterized by the manufacturer. For typical fibre, the contribution of coating effects is less than 5 % of total load, and compensation (hence measurement) for coating is not required (see 8.1). When this is done, the reported failure stress is larger than the actual by a fixed percentage. When coating effects are compensated, average or nominal values may be used for all specimens. The contribution of the coating modulus to failure stress can change with the stress or strain rate. If the contribution at any stress or strain rate is greater than 5 % of the total load, then the coating effect shall be included in the computation.

6.4 Environment

There are two key environmental considerations: aging environment and test environment.

Fibre aging is sometimes required. Even brief accelerated aging can produce increases or decreases in the measured strength of some fibres. The causes of these phenomena are not well understood. As a consequence, extrapolation methodologies from accelerated aging environments to other environments are under study.

After extensive aging, the coating surface friction can be altered. After any aging and before any testing, fibre specimens should be pre-conditioned in the test environment for at least 12 h.

The typical test environment is 23 °C ± 2 °C and 50 % ± 5 % RH. Alternative environments, such as high non-precipitating relative humidity, can yield significantly different failure stress values.

7 Procedure

7.1 Preliminary steps

1) Age the specimens if required.
2) Precondition the specimens.

7.2 Procedure for a single specimen

1) Mount the specimen in the capstans, making sure the fibre does not cross over itself or become damaged in the gauge length by mounting.
2) Verify equipment settings for the desired nominal strain rate.
3) Reset the tension recording display.

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

4) Begin capstan motion. For nominal strain rates of 0,03 %/min or less, the specimen may be pre-loaded at 0,3 %/min to about half of the expected failure stress at the slower rate. The expected failure stress may be projected from results at higher strain rates. When testing damaged fibre, pre-loading is not recommended unless the expected time to failure is in excess of 4 h.
5) At failure, stop the capstan and record the failure load and, if necessary, the stress rate.
6) Verify that the break did not occur on the capstan. If it did, mark the measurement so it will not be used in calculations.
7) Remove the residual fibre from the capstans and complete any auxiliary measurements, if necessary, as in 6.3.

7.3 Procedure for completing all samples for a given nominal strain rate

1) Record the nominal strain rate and any population identifications.
2) Determine if coating effects will be compensated. If so, record the appropriate coating parameters (see 8.1). Record the nominal cladding diameter if the nominal value is used to compute stress.
3) Complete 5.2 for each specimen.
4) Using 8.1, compute the failure stress for each specimen, and sort in increasing order.
5) Complete the Weibull plot (see Figure 1), if required, using 8.2. If required, compute the Weibull parameters, m_d and S_0, using 8.3.
6) If required for handleability requirements, compute the median failure stress σ_{50} and the 15-percentile failure stress σ_{15} according to 8.2.

8 Calculations

8.1 Conversion of tensile load to failure stress

The following symbols and units are used:

- fibre dimensions: mm;
- gauge length: m;
- stress σ and failure stress σ_f: GPa;
- tension T and failure tension T_f N.

Method A

When the load is substantially aligned with the tension T and D_g is the cladding diameter, Formula (1) provides the stress without compensating for the coating:

$$\sigma = \frac{4 \times 10^3 T}{\pi D_g^2} \text{ in GPa} \tag{1}$$

Method B

When coating is compensated, the following formulae are used. Calculate the fraction

$$R = \frac{E_0 A_0}{E_0 A_0 + \sum_{j=1}^{N} E_j A_j} \quad , \tag{2}$$

Documents
Document Sharing Hub
Full document details: IEC 60793-1-31 2019

where

E_0 is Young's modulus of the glass, typically 70,3 GPa for silica;

A_0 is the cross sectional area of the glass fibre.

For N coating layers indexed with j, E_j and A_j are the Young's modulus and layer cross sectional area, for each layer, respectively.

The coating compensated stress is given by

$$\sigma_c = \sigma R \tag{3}$$

8.2 Preparation of a Weibull plot

Figure 1 shows a typical Weibull plot, where the line drawn through the data represents an ideal Weibull distribution. While Weibull plots are typically used to display the data for a given nominal strain rate, the actual distribution may not be Weibull.

1) Sort the failure stress values in order of increasing value.
2) Let k represent the rank of a given failure stress, for example, k = 1, 2, 3..., N, and σ_{fk} be the kth failure stress.
3) Let

$$x_k = \ln \sigma_{fk} \tag{4}$$

and

$$y_k = \ln\left(-\ln\left[1 - \frac{k - 0{,}5}{N}\right]\right) \tag{5}$$

4) Plot y_k versus x_k. Label the axes with the associated probability levels and failure stress values.

NOTE The median failure stress σ_{50} and the 15-percentile failure stress σ_{15} are calculated if applicable.

If $0{,}5N + 0{,}5$ is an integer, $\sigma_{50} = \sigma_{0{,}5N + 0{,}5}$. Otherwise, σ_{50} is determined by an appropriate interpolation between $\sigma_{0{,}5N}$ and $\sigma_{0{,}5N + 1}$.

If $0{,}15N + 0{,}5$ is an integer, $\sigma_{15} = \sigma_{0{,}15N + 0{,}5}$. Otherwise, σ_{15} is determined by an appropriate interpolation between $\sigma_{[0{,}15N + 0{,}5]}$ and $\sigma_{[0{,}15N + 0{,}5] + 1}$, where square brackets stand for the greatest integer function.

8.3 Computation of Weibull parameters

The Weibull distribution cumulative frequency function is given by:

$$F = 1 - \exp\left[-\left(\frac{\sigma}{S_0}\right)^{m_d}\right] \tag{6}$$

where F corresponds to $\frac{k - 0{,}5}{N}$ of Formula (5). Consequently,

$$y_k = m_d \ln\left(\frac{\sigma_{fk}}{S_0}\right) \tag{7}$$

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

Method A – Simple rank method

For the sample sizes that are typically used (see 6.1), the following method can be used. Determine the values

$$\begin{aligned} k_1 &= 0{,}15N + 0{,}5 \\ k_2 &= 0{,}85N + 0{,}5 \\ k_3 &= 0{,}5N + 0{,}5 \end{aligned} \tag{8}$$

Compute

$$m_\mathrm{d} = \frac{y_{k_2} - y_{k_1}}{x_{k_2} - x_{k_1}} \tag{9}$$

and

$$S_0 = \exp\left[\frac{0{,}366512}{m_\mathrm{d}} + x_{k_3}\right] \tag{10}$$

Method B – Maximum likelihood estimation (MLE) method

The logarithm of the likelihood function is

$$\ln\left[L\left(m_\mathrm{d}, S_0\right)\right] = N\ln\left(m_\mathrm{d}\right) - Nm_\mathrm{d}\ln\left(S_0\right) + \left(m_\mathrm{d} - 1\right)\sum_{k=1}^{N}\ln\left(\sigma_{fk}\right) - S_0^{-m_\mathrm{d}}\sum_{k=1}^{N}\sigma_{fk}^{m_\mathrm{d}} \tag{11}$$

Select m_d and S_0 to maximize Formula (11). For a given value of m_d, the optimal value for S_0 is

$$S_0 = \frac{1}{N}\sum_{k=1}^{N}\sigma_{fk}^{m_\mathrm{d}} \tag{12}$$

The optimum value for m_d is determined by an iterative method.

9 Results

9.1 Details to be reported

Report the following information for each test:

– fibre identification;

– date and title;

– strength values – report the stress value under which the fibre breaks as the strength of fibre (Weibull plot and, if applicable, Weibull parameters m_d and S_0).

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019

9.2 Details to be recorded

Provide the following information for each test:

– length of sample;
– pulling speed (strain rate);
– type of clamping fixtures;
– relative humidity and ambient temperature;
– any special conditioning.

10 Specification information

The detail specification shall specify the following information:

– any deviations from the procedure that apply;
– failure or acceptance criteria.

Documents
Document Sharing Hub

Full document details: IEC 60793-1-31 2019