IEC 62576

Edition 1.0 2009-08

INTERNATIONAL STANDARD

NORME INTERNATIONALE

colour inside

Withdrawn

Electric double-layer capacitors for use in hybrid electric vehicles – Test methods for electrical characteristics

Condensateurs électriques à double couche pour véhicules électriques hybrides – Méthodes d'essai des caractéristiques électriques

IEC 62576:2009

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2009 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester.
If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

Droits de reproduction réservés. Sauf indication contraire, aucune partie de cette publication ne peut être reproduite ni utilisée sous quelque forme que ce soit et par aucun procédé, électronique ou mécanique, y compris la photocopie et les microfilms, sans l'accord écrit de la CEI ou du Comité national de la CEI du pays du demandeur.
Si vous avez des questions sur le copyright de la CEI ou si vous désirez obtenir des droits supplémentaires sur cette publication, utilisez les coordonnées ci-après ou contactez le Comité national de la CEI de votre pays de résidence.

IEC Central Office
3, rue de Varembé
CH-1211 Geneva 20
Switzerland
Email: inmail@iec.ch
Web: www.iec.ch

Withdrawn

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigenda or an amendment might have been published.

- Catalogue of IEC publications: www.iec.ch/searchpub
The IEC on-line Catalogue enables you to search by a variety of criteria (reference number, text, technical committee,…). It also gives information on projects, withdrawn and replaced publications.
- IEC Just Published: www.iec.ch/online_news/justpub
Stay up to date on all new IEC publications. Just Published details twice a month all new publications released. Available on-line and also by email.
- Electropedia: www.electropedia.org
The world's leading online dictionary of electronic and electrical terms containing more than 20 000 terms and definitions in English and French, with equivalent terms in additional languages. Also known as the International Electrotechnical Vocabulary online.
- Customer Service Centre: www.iec.ch/webstore/custserv
If you wish to give us your feedback on this publication or need further assistance, please visit the Customer Service Centre FAQ or contact us:
Email: csc@iec.ch
Tel.: +41 22 919 02 11
Fax: +41 22 919 03 00

A propos de la CEI

La Commission Electrotechnique Internationale (CEI) est la première organisation mondiale qui élabore et publie des normes internationales pour tout ce qui a trait à l'électricité, à l'électronique et aux technologies apparentées.

A propos des publications CEI

Le contenu technique des publications de la CEI est constamment revu. Veuillez vous assurer que vous possédez l'édition la plus récente, un corrigendum ou amendement peut avoir été publié.

- Catalogue des publications de la CEI: www.iec.ch/searchpub/cur_fut-f.htm
Le Catalogue en-ligne de la CEI vous permet d'effectuer des recherches en utilisant différents critères (numéro de référence, texte, comité d'études,…). Il donne aussi des informations sur les projets et les publications retirées ou remplacées.
- Just Published CEI: www.iec.ch/online_news/justpub
Restez informé sur les nouvelles publications de la CEI. Just Published détaille deux fois par mois les nouvelles publications parues. Disponible en-ligne et aussi par email.
- Electropedia: www.electropedia.org
Le premier dictionnaire en ligne au monde de termes électroniques et électriques. Il contient plus de 20 000 termes et définitions en anglais et en français, ainsi que les termes équivalents dans les langues additionnelles. Egalement appelé Vocabulaire Electrotechnique International en ligne.
- Service Clients: www.iec.ch/webstore/custserv/custserv_entry-f.htm
Si vous désirez nous donner des commentaires sur cette publication ou si vous avez des questions, visitez le FAQ du Service clients ou contactez-nous:
Email: csc@iec.ch
Tél.: +41 22 919 02 11
Fax: +41 22 919 03 00

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

IEC 62576

Edition 1.0 2009-08

INTERNATIONAL STANDARD

NORME INTERNATIONALE

colour inside

withdrawn

Electric double-layer capacitors for use in hybrid electric vehicles – Test methods for electrical characteristics

Condensateurs électriques à double couche pour véhicules électriques hybrides – Méthodes d'essai des caractéristiques électriques

INTERNATIONAL ELECTROTECHNICAL COMMISSION

COMMISSION ELECTROTECHNIQUE INTERNATIONALE

PRICE CODE
CODE PRIX U

ICS 31.090.99; 43.120

ISBN 978-2-88910-766-7

® Registered trademark of the International Electrotechnical Commission
Marque déposée de la Commission Electrotechnique Internationale

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

CONTENTS

FOREWORD 4
INTRODUCTION 6
1 Scope 7
2 Normative references 7
3 Terms and definitions 7
4 Tests and measurement procedures 10
4.1 Capacitance, internal resistance, and maximum power density 10
4.1.1 Circuit for measurement 10
4.1.2 Test equipment 11
4.1.3 Measurement procedure 11
4.1.4 Measurement 12
4.1.5 Calculation method for capacitance 12
4.1.6 Calculation method for internal resistance 12
4.1.7 Calculation method for maximum power density 13
4.2 Voltage maintenance characteristics 13
4.2.1 Circuit for measurement 13
4.2.2 Test equipment 14
4.2.3 Measurement procedures 14
4.2.4 Measurement 15
4.2.5 Calculation of voltage maintenance rate 15
4.3 Energy efficiency 15
4.3.1 Circuit for test 15
4.3.2 Test equipment 15
4.3.3 Measurement procedures 16
4.3.4 Measurement 17
4.3.5 Calculation of energy efficiency 17
Annex A (informative) Endurance test (continuous application of rated voltage at high temperature) 18
Annex B (informative) Heat equilibrium time of capacitors 20
Annex C (informative) Charging/discharging efficiency and measurement current 22
Annex D (informative) Procedures for setting the measurement current of capacitor with uncertain nominal internal resistance 24
Bibliography 25

Figure 1 – Basic circuit for measuring capacitance, internal resistance and maximum power density 10
Figure 2 – Voltage-time characteristics between capacitor terminals in capacitance and internal resistance measurement 11
Figure 3 – Basic circuit for measuring the voltage maintenance characteristics 13
Figure 4 – Time characteristics of voltage between capacitor terminals in voltage maintenance test 14
Figure 5 – Voltage-time characteristics between capacitor terminals in charging/discharging efficiency test 16
Figure B.1 – Heat equilibrium times of capacitors (85 °C→25 °C) 20
Figure B.2 – Heat equilibrium times of capacitors (–40 °C→25 °C) 21
Figure B.3 – Temperature changes of capacitors' central portions (85 °C→25 °C) 22

Withdrawn
AVA Documents
Document Sharing Hub
Full document details: IEC 62576 2009

Figure B.4 – Temperature changes of capacitors' central portions (–40 °C→25 °C) 21

Table D.1 – Example of setting current for measurement of capacitor 24

withdrawn

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

INTERNATIONAL ELECTROTECHNICAL COMMISSION

ELECTRIC DOUBLE-LAYER CAPACITORS FOR USE IN HYBRID ELECTRIC VEHICLES – TEST METHODS FOR ELECTRICAL CHARACTERISTICS

FOREWORD

1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
5) IEC provides no marking procedure to indicate its approval and cannot be rendered responsible for any equipment declared to be in conformity with an IEC Publication.
6) All users should ensure that they have the latest edition of this publication.
7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 62576 has been prepared by IEC technical committee 69: Electric road vehicles and electric industrial trucks.

The text of this standard is based on the following documents:

CDV	Report on voting
69/158/CDV	69/162/RVC

Full information on the voting for the approval of this standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

Withdrawn

Documents
Document Sharing Hub
Full document details: IEC 62576 2009

The committee has decided that the contents of this publication will remain unchanged until the maintenance result date indicated on the IEC web site under "http://webstore.iec.ch" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The "colour inside" logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this publication using a colour printer.

withdrawn

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

INTRODUCTION

The Electric double-layer capacitor (EDLC) is a promising energy storage system for hybrid electric vehicles (HEVs), and EDLC-installed HEVs have begun to be commercialized with an eye to improving fuel economy by recovering regenerative energy. Although a standards series (IEC 62391 series) for EDLC already exists, those for HEVs involve patterns of use, usage environment, and values of current that are quite different from those assumed in the existing standards. Standard evaluation and test methods will be useful for both the auto manufacturers and capacitor suppliers to speed up the development and lower the costs of such EDLCs. With these points in mind, this standard aims to provide basic and minimum specifications in terms of the methods for testing electrical characteristics, and to create an environment that supports expanding market of HEVs and large capacity EDLCs. Additional practical test items to be standardized should be reconsidered after technology and market stabilization of EDLCs for HEVs. In terms of endurance that is important in practical use, just basic concept is set forth in the informative annexes.

Withdrawn

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

ELECTRIC DOUBLE-LAYER CAPACITORS FOR USE IN HYBRID ELECTRIC VEHICLES – TEST METHODS FOR ELECTRICAL CHARACTERISTICS

Withdrawn

1 Scope

This standard describes the methods for testing electrical characteristics of electric double-layer capacitor cells (hereinafter referred to as capacitor) to be used for peak power assistance in hybrid electric vehicles.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60068-1:1988, *Environmental testing – Part 1: General and guidance*

Amendment 1(1992)

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1
reference temperature
reference temperature (°C) to be used in the test

3.2
ambient temperature
ambient temperature of the surrounding space in which a capacitor is placed

3.3
upper category temperature
highest ambient temperature that a capacitor is designed to operate continuously

3.4
lower category temperature
lowest ambient temperature that a capacitor is designed to operate continuously

3.5
applied voltage
voltage (V) applied between the terminals of a capacitor

3.6
rated voltage
U_R
maximum d.c. voltage (V) that may be applied continuously for a certain time under the upper category temperature to a capacitor so that a capacitor can exhibit specified demand characteristics. This voltage is the setting voltage in capacitor design

NOTE The endurance test using the rated voltage is described in Annex A.

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

3.7
charge current
I_c
current (A) required to charge a capacitor

3.8
discharge current
I_d
current (A) required to discharge a capacitor

3.9
stored energy
energy (J) stored in a capacitor

3.10
charge accumulated electrical energy
amount of charged energy (J) accumulated from the beginning to the end of charging

3.11
discharge accumulated electrical energy
amount of discharged energy (J) accumulated from the beginning to the end of discharging

3.12
calculation start voltage
voltage (V) at a selected start point for calculating the characteristics including capacitance under a state of voltage decrease during discharge

3.13
calculation end voltage
voltage (V) at a selected end point for calculating the characteristics including capacitance under a state of voltage decrease during discharge

3.14
capacitance
ability of a capacitor to store electrical charge (*F*)

3.15
nominal capacitance
C_N
nominal capacitance value (C_N) to be used in design and measurement condition setting (*F*), generally, at the reference temperature

3.16
internal resistance
combined resistance (Ω) of constituent material specific resistance and inside connection resistance of a capacitor

3.17
nominal internal resistance
R_N
nominal value of the internal resistance (R_N) to be used in design and measurement condition setting (Ω), generally at the reference temperature

3.18
constant voltage charging
method of charging a capacitor at specified voltage continuously

Withdrawn

AVA Documents
Document Sharing Hub

3.19
pre-conditioning
discharging and storage of a capacitor under specified ambient conditions (temperature, humidity, and pressure) before testing

NOTE Generally, pre-conditioning implies that a capacitor is discharged and stored until its inner temperature attains thermal equilibrium with the surrounding temperature, before its electrical characteristics are measured.

3.20
voltage treatment
voltage application before measurement of a capacitor's electrical characteristics

NOTE Generally, this treatment is applied to a capacitor that has been stored for a long time or to a capacitor whose history is not clear.

3.21
post-treatment (recovery)
discharging and storage of a capacitor under specified ambient conditions (temperature, humidity, and pressure) after tests

NOTE Generally, post-treatment implies that a capacitor is discharged and stored until its inner temperature attains thermal equilibrium with the surrounding temperature before its electrical characteristics are measured.

3.22
charging efficiency
efficiency under specified charging conditions, and ratio (%) of stored energy to charge accumulated electrical energy. This value is calculated from the internal resistance of a capacitor

NOTE Refer to Equation C.8 in Annex C.

3.23
discharging efficiency
efficiency under specified discharging conditions, and ratio (%) of discharge accumulated electrical energy to stored energy. This value is calculated from the internal resistance of a capacitor

NOTE Refer to Equation C.10 in Annex C.

3.24
energy efficiency
E_f
ratio (%) of discharge accumulated electrical energy to charge accumulated electrical energy under specified charging and discharging conditions

3.25
voltage maintenance characteristics
voltage maintenance characteristics of a capacitor when its terminals are open after charging

3.26
voltage maintenance rate
ratio of voltage maintenance
ratio of the voltage at the open-ended terminals to the charge voltage after a specified time period subsequent to the charging of a capacitor

3.27
power density
electrical power per unit mass (W/kg) or per unit volume (W/l) that can be recovered from a charged capacitor

Withdrawn

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

3.28
rated power density
specified maximum power density (W/kg or W/l). Generally, it is calculated by using the nominal internal resistance and the rated voltage

3.29
maximum power density
P_{dm}
maximum power density (W/kg or W/l) that can be recovered from a charged capacitor. Generally, it is calculated by using the internal resistance and the rated voltage

4 Tests and measurement procedures

4.1 Capacitance, internal resistance, and maximum power density

4.1.1 Circuit for measurement

The capacitance and the internal resistance shall be measured by using the constant current charging and discharging methods. Figure 1 shows the basic circuit to be used for the measurement.

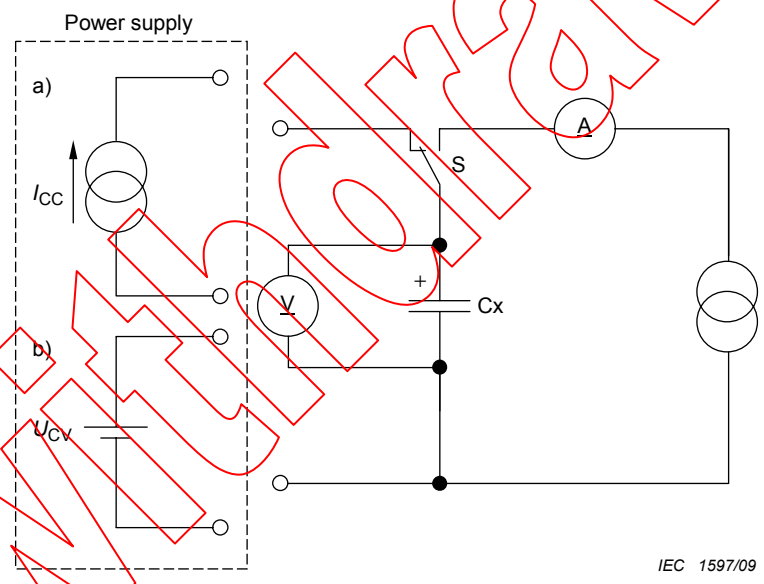

Key

I_{CC} constant-current

U_{CV} constant-voltage

Ⓐ d.c. ammeter

Ⓥ d.c. voltage recorder

S changeover switch

Cx capacitor under test

⊖ constant current discharger

a) constant current charging

b) constant voltage charging

Figure 1 – Basic circuit for measuring capacitance, internal resistance and maximum power density

Withdrawn

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

4.1.2 Test equipment

The test equipment shall be capable of constant current charging, constant voltage charging, constant current discharging, and continuous measurement of the current and the voltage between the capacitor terminals in time-series as shown in Figure 2. The test equipment shall be able to set and measure the current and the voltage with the accuracy equal to ± 1 % or less.

The power supply shall provide the constant charge current for the capacitor charge with 95 % efficiency, set the duration of constant voltage charge, and provide a discharge current corresponding to the specified discharge efficiency. The d.c. voltage recorder shall be capable of conducting measurements and recording with a 5 mV resolution and sampling interval of 100 ms or less.

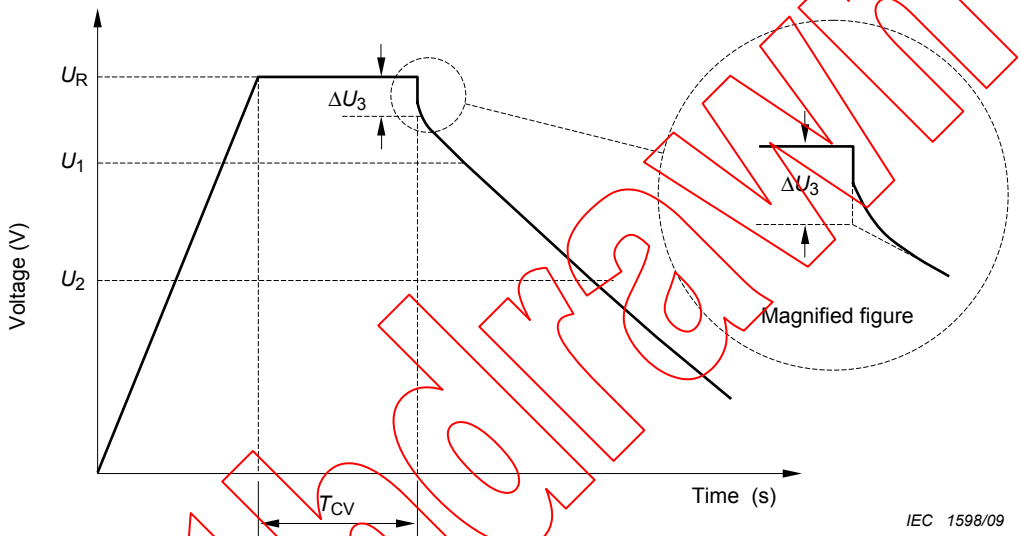

Key

U_R rated voltage (V)

U_1 calculation start voltage (V)

U_2 calculation end voltage (V)

ΔU_3 voltage drop (V)

T_{CV} constant voltage charging duration (s)

Figure 2 – Voltage-time characteristics between capacitor terminals in capacitance and internal resistance measurement

4.1.3 Measurement procedure

Measurements shall be carried out in accordance with the following procedures using the test equipment specified in 4.1.2.

a) Pre-conditioning

Before measurement, the capacitors shall be fully discharged and then incubated for 2 h to 6 h under the reference temperature, set at 25 °C ± 2 °C, as specified in 5.2 in IEC 60068-1, or that specified by the related standards.

NOTE 1 The heat equilibrium time which provides a reference for the soaking time is described in Annex B.

b) Sample setting

Fit the sample capacitors with the test equipment.

c) Test equipment set-up

Withdrawn

Documents
Document Sharing Hub

Full document details: IEC 62576 2009

Unless specified otherwise by related standards, the test equipment shall be set-up in the following manner.

1) Set the constant current I_c for charging. At this current, the capacitors shall be able to charge with 95 % charging efficiency based on their nominal internal resistance R_N. The current value is calculated by $I_c = U_R/38R_N$.

   NOTE 2 The general concept for 95 % charging or discharging efficiency is described in Annex C. When the rated value of internal resistance of a capacitor is uncertain, the current for the measurement can be set according to the advisable procedures described in Annex D.

2) Set the maximum voltage for constant current charging as the rated voltage U_R.

3) Set the duration of constant voltage charging T_{CV} to 300 s.

4) Set the constant current discharge value. This value shall allow for a 95 % discharging efficiency based on the capacitor's nominal internal resistance R_N , and is calculated by $I_d = U_R/40R_N$.

5) Set the sampling interval to 100 ms or less, and set the test-equipment so as to measure the voltage drop characteristics up to 0,5 U_R.

4.1.4 Measurement

After the setting as specified above, the voltage-time characteristics between capacitor terminals as shown in Figure 2 shall be measured.

4.1.5 Calculation method for capacitance

The capacitance C shall be calculated using Equation (1) based on the voltage-time characteristics between capacitor terminals obtained in 4.1.4.

NOTE This calculation method is called "energy conversion capacitance method."

$$C = \frac{2W}{(0{,}9\,U_R)^2 - (0{,}7\,U_R)^2} \tag{1}$$

where

C is the capacitance (F) of capacitor;

W is the measured discharged energy (J) from calculation start voltage (0,9 U_R) to calculation end voltage (0,7 U_R);

U_R is the rated voltage (V).

4.1.6 Calculation method for internal resistance

The internal resistance R shall be calculated using Equation (2) based on the voltage-time characteristics between capacitor terminals obtained in 4.1.4.

$$R = \frac{\Delta U_3}{I_d} \tag{2}$$

where

R is the internal resistance (Ω) of capacitor;

I_d is the discharge current (A).

ΔU_3 Apply the straight-line approximation to the voltage drop characteristics from the calculation start voltage (0,9 U_R) to the calculation end voltage (0,7 U_R) by using the least squares method. Obtain the intercept (voltage value) of the straight line at the discharge start time. ΔU_3 is the difference of voltages (V) between the intercept voltage value and the set value of constant voltage charging.

Withdrawn

AVA Documents Document Sharing Hub

Full document details: IEC 62576 2009

NOTE This calculation method is called “least squares internal resistance method.”

4.1.7 Calculation method for maximum power density

The maximum power density P_{dm} is calculated by using the internal resistance value calculated in 4.1.6 and Equation (3).

NOTE This calculation method is called “matched impedance power density method.”

$$P_{dm} = \frac{0{,}25\, U_R^2}{RM} \tag{3}$$

where

P_{dm} is the maximum power density of capacitor (W/kg or W/l) ;

U_R is the rated voltage (V);

R is the calculated internal resistance (Ω);

M is the mass or volume of capacitor (kg or l).

4.2 Voltage maintenance characteristics

4.2.1 Circuit for measurement

Figure 3 shows the basic circuit for measuring the voltage maintenance characteristics.

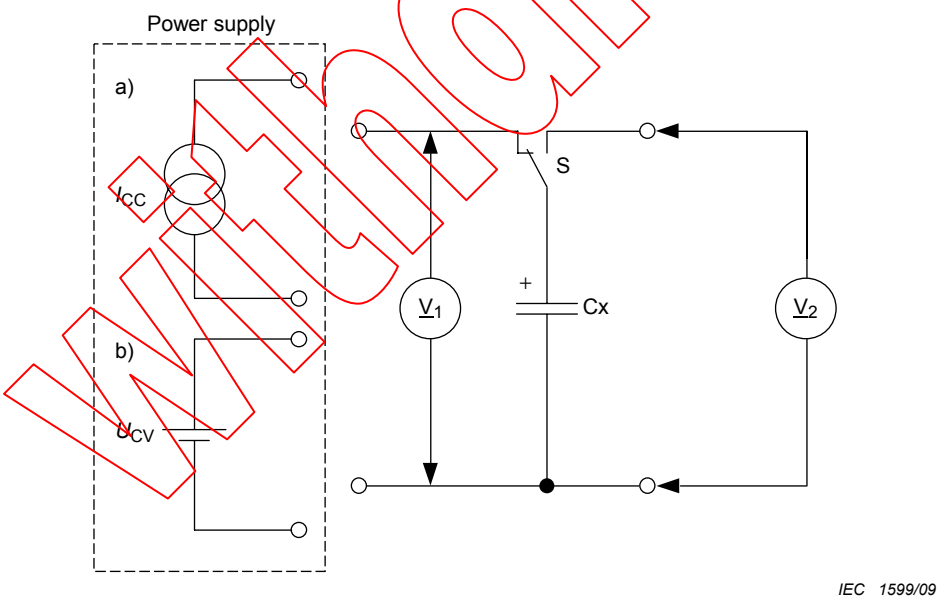

Key

I_{CC}	constant-current
U_{CV}	constant-voltage
V_1 V_2	d.c. voltmeter
S	changeover switch
Cx	capacitor under test
a)	constant current charging
b)	constant voltage charging

Figure 3 – Basic circuit for measuring the voltage maintenance characteristics

Withdrawn
AVA Documents Document Sharing Hub
Full document details: IEC 62576 2009

4.2.2 Test equipment

The test equipment shall be capable of constant current charging, constant voltage charging, and continuous measurement of the voltage between the capacitor terminals in time-series as shown in Figure 4. The power supply shall provide the constant charge current for the capacitor charge with 95 % efficiency and set the duration of constant voltage charging. The test equipment shall be able to set and measure the current and the voltage by the accuracy equal to ±1 % or less.

The d.c. voltage recorders V_1 and V_2 shall have a resolution of 5 mV or less for voltage measurement. The input impedance of the recorder shall be sufficiently high so that measurement errors are negligible.

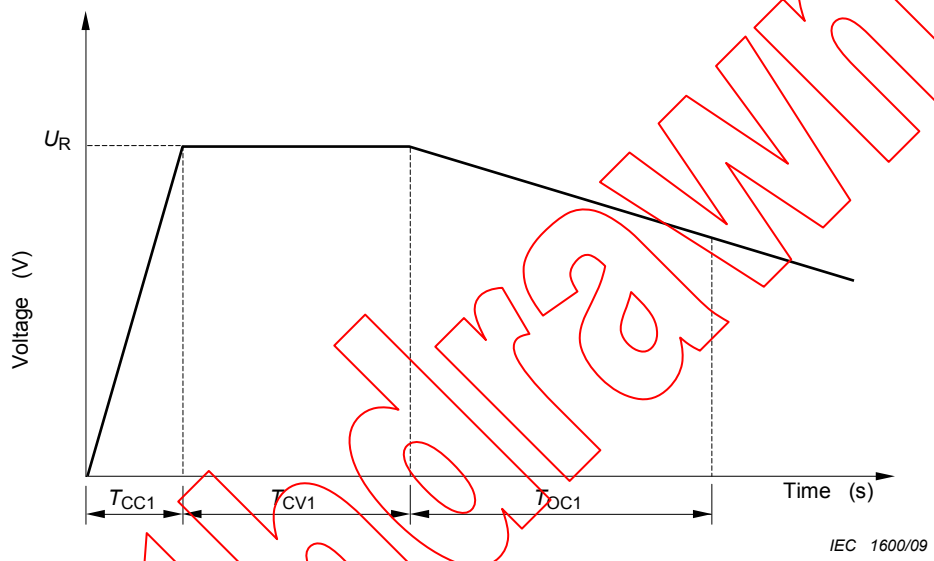

Key

U_R rated voltage (V)

T_{CC1} charging duration with 95 % efficiency (s)

T_{CV1} duration of constant voltage charging (s)

T_{OC1} duration of measurement (h)

Figure 4 – Time characteristics of voltage between capacitor terminals in voltage maintenance test

Withdrawn

4.2.3 Measurement procedures

The measurements shall be carried out in accordance with the following procedures using the test equipment specified in 4.2.2.

a) Pre-conditioning

Before measurement, the capacitors shall be fully discharged and then incubated for 2 h to 6 h under the reference temperature, set at 25 °C ± 2 °C, as specified in 5.2 in IEC 60068-1, or that specified by the related standards.

NOTE 1 The heat equilibrium time which provides a reference for the soaking time is described in Annex B.

b) Sample setting

Fit the sample capacitors with the test equipment.

c) Test equipment set-up

Documents
Document Sharing Hub
Full document details: IEC 62576 2009

Unless specified otherwise by related standards, the test equipment shall be set-up in the following manner.

1) Set the constant current value for charging. At this current, the capacitors shall be able to charge with 95 % charging efficiency based on their nominal internal resistance. The current value is calculated by $I_c = U_R/38R_N$.

   NOTE 2 The general concept for 95 % charging or discharging efficiency is described in Annex C. When the rated value of internal resistance of a capacitor is uncertain, the current for the measurement can be set according to the advisable procedures described in Annex D.

2) Set the maximum voltage for constant current charging to the rated voltage U_R.
3) Set the duration of constant voltage charging T_{CV1} to 300 s.
4) After specified charging duration, set the capacitor terminals open.

4.2.4 Measurement

After the setting as specified above, measure the voltage between capacitor terminals when T_{OC1} in Figure 4 is 72 h.

4.2.5 Calculation of voltage maintenance rate

The voltage maintenance rate A is calculated by Equation (4).

$$A = \frac{U_{end}}{U_R} \times 100 \qquad (4)$$

where

A is the voltage maintenance rate (%);

U_{end} is the voltage between open capacitor terminals after 72 h (T_{OC1}) has elapsed ;

U_R is the rated voltage (V).

4.3 Energy efficiency

4.3.1 Circuit for test

The energy efficiency test shall be conducted by the constant current charging and discharging. Figure 1 shows the basic circuit required for this test.

4.3.2 Test equipment

The test equipment shall be as specified in 4.1.2.

The test equipment shall be capable of constant current charging, constant voltage charging, constant current discharging, and continuous measurement of the current and the voltage between the capacitor terminals in time-series as shown in Figure 5. The test equipment shall be able to set and measure the current and the voltage by the accuracy equal to ±1 % or less.

The power supply shall provide the constant charge current for the capacitor charge with 95 % efficiency, set the duration of constant voltage charge, and provide a discharge current corresponding to the specified–discharge efficiency. The d.c. voltage recorder shall be capable of conducting measurements and recording with a 5 mV resolution and sampling interval of 100 ms or less.

Withdrawn

AVA Documents Document Sharing Hub

Full document details: IEC 62576 2009