

TECHNICAL REPORT



**Electrical insulating materials – Thermal endurance properties –
Part 7-2: Accelerated determination of relative thermal endurance using
analytical test methods (RTEA) – Results of the round robin tests to validate
procedures of IEC TS 60216-7-1 by non-isothermal kinetic analysis of
thermogravimetric data**



THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2024 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Secretariat
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, ...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC Products & Services Portal - products.iec.ch

Discover our powerful search engine and read freely all the publications previews, graphical symbols and the glossary. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 500 terminological entries in English and French, with equivalent terms in 25 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

TECHNICAL REPORT



**Electrical insulating materials – Thermal endurance properties –
Part 7-2: Accelerated determination of relative thermal endurance using
analytical test methods (RTEA) – Results of the round robin tests to validate
procedures of IEC TS 60216-7-1 by non-isothermal kinetic analysis of
thermogravimetric data**

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 19.020; 29.020; 29.035.01

ISBN 978-2-8322-9761-2

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD.....	4
INTRODUCTION.....	2
1 Scope.....	7
2 Normative references	7
3 Terms and definitions	7
4 Test specimens	8
5 Test apparatus	9
5.1 Thermogravimetric analyser (TGA)	9
5.2 Purge gas supplied into the TGA furnace	9
6 Test procedures	10
6.1 General.....	10
6.2 Preconditioning of test samples	10
6.3 TGA tests with multiple heating rates	10
6.4 Calculation of the activation energy (E_a)	10
6.5 Determination of thermal endurance using TGA	11
6.5.1 General	11
6.5.2 Determination of RTE_A by given degree of conversion from reference material (Method A)	11
6.5.3 Determination of TI_A by fixed degree of conversion at 0,05 (Method B)	12
7 Round robin test results.....	12
7.1 TGA test results	12
7.2 Degree of conversion correlated to the activation energy from conventional heat ageing data	12
7.3 HIC_A determined by Method A and Method B	13
7.4 RTE_A determined by Method A and TI_A by Method B.....	14
7.5 Difference between RTE_A and TI determined by the conventional heat ageing tests	16
8 Observations from the round robin test results.....	18
8.1 General.....	18
8.2 Sample weight variation	18
8.3 Humidity and hydrolysis of the sample	20
8.4 Considerations on repeatability of TGA curves.....	20
8.5 Baseline drift and responsiveness to heating rates of TGA.....	21
9 Conclusion and recommendation	25
Annex A (informative) Additional round robin studies with polybutylene terephthalate	26
A.1 Objectives.....	26
A.2 Test specimens.....	26
A.3 Test apparatus.....	26
A.4 Test procedures	27
A.5 Test results	27
A.6 Observations	32
Bibliography.....	35

Figure 1 – Fitting curve of plots between degree of conversion and activation energy determined by ISO 11358-2 [3] (example).....

Figure 2 – Correlation between the initial sample mass of sample A and the difference of RTE_A (TI_A) from TI	19
Figure 3 – Correlation between the initial sample mass of sample B and the difference of RTE_A (TI_A) from TI	19
Figure 4 – Overlay charts of TGA curves in multiple heating rates in multiple laboratories (enlarged).....	22
Figure 5 – Logarithm plots for activation energy calculation	23
Figure 6 – Fitting curves of degree of conversion versus activation energy by TGA	24
Figure A.1 – Effect of sample amount on E_a (data provided by laboratory E)	33
Figure A.2 – Summary of factors affecting the TGA kinetic study for determination of RTE_A and TI_A	34
Table 1 – Heat ageing properties of the test specimens by the conventional procedure described in IEC 60216-5 [4].....	9
Table 2 – Degree of conversion identical to the activation energy of the conventional heat ageing.....	13
Table 3 – HIC_A determined by Method A and Method B for dielectric strength	13
Table 4 – HIC_A determined by Method A and Method B for tensile strength	14
Table 5 – HIC_A determined by Method A and Method B for impact strength	14
Table 6 – RTE_A determined by Method A and TI_A by Method B for dielectric strength	15
Table 7 – RTE_A determined by Method A and TI_A by Method B for tensile strength	15
Table 8 – RTE_A determined by Method A and TI_A by Method B for impact strength	16
Table 9 – Difference between RTE_A or TI_A , and TI for dielectric strength	16
Table 10 – Difference between RTE_A or TI_A , and TI for tensile strength	17
Table 11 – Difference between RTE_A or TI_A , and TI for impact strength	17
Table 12 – Comparison of degree of conversion with original or rerun data at 8 K/min	21
Table A.1 – Heat ageing properties of the PBT test specimens by the conventional procedure in accordance with IEC 60216-5 [4]	26
Table A.2 – Degrees of conversion at the activation energy identical to that from conventional heat ageing	27
Table A.3 – HIC_A determined by Method A and Method B for dielectric strength	28
Table A.4 – HIC_A determined by Method A and Method B for tensile strength.....	28
Table A.5 – HIC_A determined by Method A and Method B for impact strength.....	29
Table A.6 – RTE_A determined by Method A and TI_A by Method B for dielectric strength	29
Table A.7 – RTE_A determined by Method A and TI_A by Method B for tensile strength.....	30
Table A.8 – RTE_A determined by Method A and TI_A by Method B for impact strength.....	30
Table A.9 – Difference between RTE_A or TI_A , and TI for dielectric strength	31
Table A.10 – Difference between RTE_A or TI_A , and TI for tensile strength.....	31
Table A.11 – Difference between RTE_A or TI_A , and TI for impact strength.....	32

INTERNATIONAL ELECTROTECHNICAL COMMISSION

ELECTRICAL INSULATING MATERIALS – THERMAL ENDURANCE PROPERTIES –

Part 7-2: Accelerated determination of relative thermal endurance using analytical test methods (RTEA) – Results of the round robin tests to validate procedures of IEC TS 60216-7-1 by non-isothermal kinetic analysis of thermogravimetric data

FOREWORD

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) IEC draws attention to the possibility that the implementation of this document may involve the use of (a) patent(s). IEC takes no position concerning the evidence, validity or applicability of any claimed patent rights in respect thereof. As of the date of publication of this document, IEC had not received notice of (a) patent(s), which may be required to implement this document. However, implementers are cautioned that this may not represent the latest information, which may be obtained from the patent database available at <https://patents.iec.ch>. IEC shall not be held responsible for identifying any or all such patent rights.

This redline version of the official IEC Standard allows the user to identify the changes made to the previous edition IEC TR 60216-7-2:2016. A vertical bar appears in the margin wherever a change has been made. Additions are in green text, deletions are in strikethrough red text.

IEC TR 60216-7-2 has been prepared by IEC technical committee 112: Evaluation and qualification of electrical insulating materials and systems. It is a Technical Report.

This second edition cancels and replaces the first edition published in 2016. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) Annex A (informative) has been added to provide a round robin test with a different polymer type – polybutylene terephthalate (PBY) – as an additional use case of the method in accordance with IEC TS 60216-7-1;
- b) Tables 3 to 11 have been corrected by adding units, and texts have been refined for more technical clarifications of the procedures and observations.

The text of this Technical Report is based on the following documents:

Draft	Report on voting
112/651/DTR	112/658/RVDTR

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this Technical Report is English.

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/publications.

A list of all parts in the IEC 60216 series, published under the general title *Electrical insulating materials – Thermal endurance properties*, can be found on the IEC website.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn, or
- revised.

IMPORTANT – The "colour inside" logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

INTRODUCTION

IEC technical committee 112, (IEC TC 112) has been working on the development of IEC TS 60216-7-1 [1]¹ that considers the use of activation energy determined through thermal analytical tools plus abbreviated conventional heat ageing to determine a thermal index on a polymeric compound. At the same time, the Underwriters Laboratories Long-Term Thermal Aging Forum (UL LTТА Forum) has been discussing alternative methods that ~~could~~ can speed up the determination of a thermal index. Members of the IEC TC 112 and of the UL LTТА Forum have made joint efforts to determine whether the Technical Specification developed by IEC TC 112 can be used to offer an alternative method of evaluating polymeric compounds for a thermal index.

Members of IEC TC 112 and the UL LTТА Forum decided to conduct a round robin test (RRT) using thermogravimetric analysis (TGA) according to ISO 11358-2 [3] on a known compound, with a known activation energy determined through conventional ageing with a view to validate the acceptability of IEC TS 60216-7-1, and to determine whether a similar thermal index ~~could~~ can be calculated. The round robin testing was conducted with conventional TGA by multiple heating rates. However, running isothermal tests can be a follow-up of this RRT.

¹ Numbers in square brackets refer to the Bibliography.

ELECTRICAL INSULATING MATERIALS – THERMAL ENDURANCE PROPERTIES –

Part 7-2: Accelerated determination of relative thermal endurance using analytical test methods (RTEA) – Results of the round robin tests to validate procedures of IEC TS 60216-7-1 by non-isothermal kinetic analysis of thermogravimetric data

1 Scope

This part of IEC 60216 is intended to validate the procedures of IEC TS 60216-7-1 in providing a similar temperature index to conventional methods used in other parts of the IEC 60216 series.

The round robin test results do not provide statistical analysis for precision. The round robin test focuses on preliminary studies to understand the evaluation and calculation procedures, influence on apparatus, and data variance among laboratories before determination of precision.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

3.1

activation energy

Arrhenius activation energy

E_a

empirical parameter characterizing the exponential temperature dependence of the reaction rate constant

~~[SOURCE: IUPAC “Goldbook”]~~

3.2

end-point

limit for a diagnostic property value based on which the thermal endurance is evaluated

3.3

time to end-point

failure time

time to reach the end-point or conventional failure

3.4 relative temperature endurance index

RTE

numerical value of the temperature in degrees Celsius at which the estimated time to end-point of the candidate material is the same as the estimated time to end-point of the reference material at a temperature equal to its assessed temperature index

Note 1 to entry: RTE_A is the relative temperature endurance index calculated through the analytical procedure.

3.5 temperature endurance index

TI

numerical value of the temperature in degrees Celsius derived from the thermal endurance relationship at a time of 20 000 h (or other specified time)

Note 1 to entry: TI_A is the temperature index calculated through the analytical procedure.

[SOURCE: IEC 60050-212:2010, 212-12-11 [2], modified — ~~the two notes have been deleted and replaced by a new note~~ "characterizing the thermal capability of an insulating material or an insulation system" has been replaced with "derived from the thermal endurance relationship at a time of 20 000 h (or other specified time)" and the two notes to entry have been replaced by a new note to entry.]

3.6 halving interval

HIC

numerical value of the temperature interval in kelvin which expresses the halving of the time to end-point taken at the temperature equal to TI

Note 1 to entry: HIC_A is the halving interval calculated through the analytical procedure.

3.7 degree of conversion

α

quantity of products present at a particular time and temperature during a reaction compared with the final quantity of the products

[SOURCE: ISO 11358-2:2014/2021, 3.3 [3], modified – The symbol "C" has been replaced with " α " and the notes to entry have been deleted.]

4 Test specimens

For the round robin test, one generic type of polymer, liquid crystal polyester (LCP), was pre-selected. Although it is known that materials can undergo more than one transition, the round robin test verified the assumption that one single thermal degradation reaction is predominant and directly correlated to the end-point of dielectric strength as a diagnostic property.

NOTE Since different materials can undergo more than one transition, the validity of results obtained from the evaluation of thermal endurance properties using TGA are assessed for the different materials.

LCP originally has very little entwining of molecules exhibiting crystalline properties as a liquid. Hence, there is less thermal transformation between solid and liquid, or between oven ageing conditions of conventional thermal endurance test and TGA conditions at higher temperature ranges. In addition, LCP molecular chains align themselves when moulded, and this generates a self-reinforcing effect, thereby resulting in high mechanical and electrical stress resistance.

In this round robin, two LCP materials (LCP sample A, LCP sample B) were chosen as test samples which already have the conventional heat oven ageing data of dielectric strength, tensile strength, and impact strength to validate the acceptability of whether or not RTE_A can be similar to RTE. Both sample A and sample B consist of 30 % glass fibres reinforced materials. Configurations of monomers are the only differences between the samples which influence the difference in thermal resistance, as shown in Table 1.

The samples were homogenized by freeze-pulverization from test plaques. 100 mg each of freeze-pulverized powders from the same batch were prepared and provided to eleven testing laboratories for evaluation, after pre-drying at 140 °C for 4 h.

Table 1 – Heat ageing properties of the test specimens by the conventional procedure described in IEC 60216-5 [4]

Temperature in ovens	Time to end-point at 50 % retention of initial dielectric strength		Time to end-point at 50 % retention of initial tensile strength		Time to end-point at 50 % retention of initial impact strength	
	h		h		h	
°C	LCP Sample A	LCP Sample B	LCP Sample A	LCP Sample B	LCP Sample A	LCP Sample B
290		1 141		1 215		1 860
285	2 896		1 789		2 870	
280		1 917		3 229		2 655
275	5 591		3 083		4 164	
270		4 300		4 597		3 920
265	8 255		6 706		8 412	
260		5 848		7 625		6 640
250						9 600
TI (°C)	250,0	241,5	249,1	246,2	249,1	234,7
E_a (kJ/mol)	130,6	142,3	165,2	145,9	134,5	102,9

5 Test apparatus

5.1 Thermogravimetric analyser (TGA)

A thermogravimetric analyser (TGA) in accordance with ISO 11358-1 [5] was used for the determination of RTE_A concerning the test samples. In fact, a number of commercial instruments suitable for the ~~document~~ measurement are available and various models of TGAs were used for evaluation of the test samples by the participating laboratories. Before the RRT, weight and temperature calibrations were implemented based on ISO 11358-1 and TGA apparatus manufacturer's guidance.

5.2 Purge gas supplied into the TGA furnace

For purge gas into the TGA furnace, air was chosen to assume oxidative thermal degradation, as well as degradation of electrical and mechanical strengths with test specimens in oven ageing. Most of the laboratory participants selected dry air (water content less than 1 ppm²), but air supplied from the facility (compressed air with or without an air dryer) was used in a few laboratories.

² ppm = parts per million.

6 Test procedures

6.1 General

Thermal analysis with TGA of the test samples was evaluated with reference to ISO 11358-2 [3] and IEC TS 60216-7-1 in principle. A few modifications of test conditions and more detailed procedures were added as follows.

6.2 Preconditioning of test samples

5 mg $\pm$ 0,5 mg of the test sample were initially measured in each laboratory and mounted on the empty pan in the furnace opened. Then the furnace was closed and pre-conditioned in equilibrium at 100 °C for 1 h before heating tests were started. The weight value just before the heating test (time at 0 s in the heating run, or 60 min at the end of the equilibrium) was used for calculation on the degree of conversion.

NOTE ISO 11358-2 [3] requires using test samples of identical mass $\pm$ 1 % of the initial weight in multiple heating conditions which is much narrower than the above. Influence on the initial mass deviation is taken into consideration in 7.2.

6.3 TGA tests with multiple heating rates

Multiple heating rates testing at 1 K/min, 2 K/min, 4 K/min, 6 K/min and 8 K/min were selected for evaluation which resulted in the lowest and highest heating rates differing by a factor of 8, in accordance with ISO 11358-2 [3]. Evaluation temperature range was set between 100 °C and 700 °C. Each heating rate test was run one time each for sample A and sample B, but 8 K/min was evaluated twice as an approximate check and to consider repeatability.

6.4 Calculation of the activation energy (E_a)

After TGA data with multiple heating rates were obtained, the activation energies were calculated for given degrees of conversion in accordance with Equation (2) in ISO 11358-2:20142021 [3]. Then, both values of degree of conversion and the activation energies were plotted between 1 % and 19 % with 2 % interval of degree of conversion ~~to analyse the cubic approximation for drawing the fitting curve of the plots~~ and a cubic curve fitting approximately was performed as shown in Figure 1. Equation (2) in ISO 11358-2:20142021 [3] was used for the selection of appropriate activation energy and degree of conversion to determine RTE_A .

For example, if the activation energy of a reference material was already determined as 150 kJ/mol by the conventional heat ageing (e.g. dielectric strength), the corresponding degree of conversion of the reference material can be read and obtained with the equation of the fitting curve graph (see Figure 1). Then the corresponding degree of conversion for this reference material can be used for reading the activation energy of a candidate material from another graph which was also evaluated with ISO 11358-2 [3] and had ~~another fitting curve of activation energy and~~ a similar degree of conversion versus the activation energy fitting curve for the candidate material.

All TGA raw data were submitted by eleven participating laboratories and analysis with ISO 11358-2 [3] was carried out by one of the laboratories with the analytical tool, to avoid any discrepancy among various software calculations.

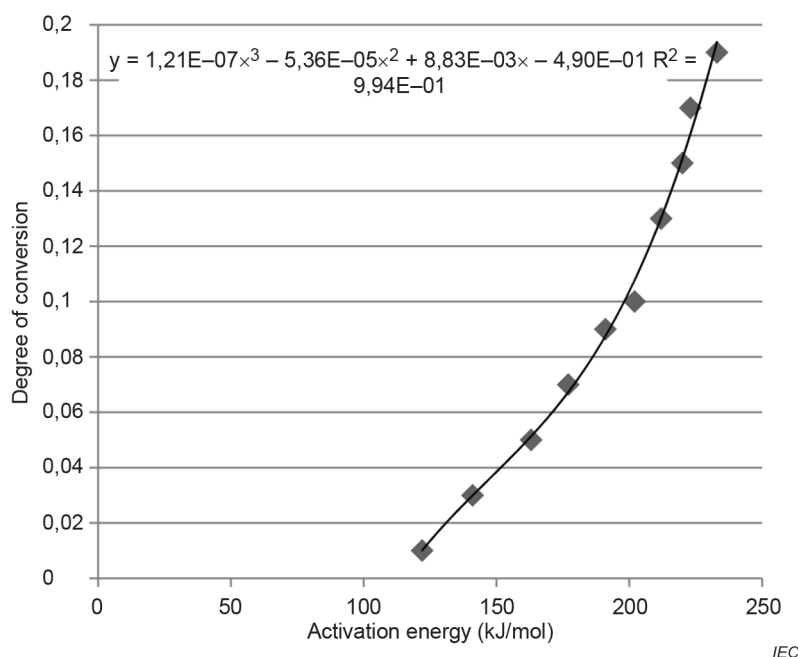


Figure 1 – Fitting curve of plots between degree of conversion and activation energy determined by ISO 11358-2 [3] (example)

6.5 Determination of thermal endurance using TGA

6.5.1 General

The activation energy given by the above procedure can be used for the determination of RTE_A by calculating with time to end-point at the highest temperature, which was determined by the conventional heat ageing test under IEC 60216-5 [4], and procedures in accordance with IEC TS 60216-7-1.

In accordance with ISO 11358-2 [3], various activation energies can be obtained per certain degrees of conversion calculated with multiple heating rate data of TGA. Therefore, degrees of conversion were chosen appropriately to be correlated to thermal degradation derived by properties and the conventional heat ageing data which are described in 6.5.2 (Method A). On the other hand, the fixed degree of conversion at 0,05 and activation energy are sometimes used experimentally for prediction of end-point of properties [6], [7], which is described in 6.5.3 (Method B).

6.5.2 Determination of RTE_A by given degree of conversion from reference material (Method A)

After the cubic approximation between the degree of conversion and the activation energy is determined (see 6.4), the degree of conversion for the reference material is given from the equation where the activation energy is the same as that from the Arrhenius equation of conventional heat ageing data. The activation energy of the candidate material is then determined from the cubic approximation of the candidate material where the degree of conversion for the candidate material is assumed to be the same as the given degree of conversion for the reference material. In Method A, RTE_A can be obtained.

NOTE The assumption that the degree of conversion for the candidate material is the same as the given degree of conversion for the reference material, is validated since the candidate material can be of the same type of the reference material.

6.5.3 Determination of TI_A by fixed degree of conversion at 0,05 (Method B)

In Method B, the fixed degree of conversion at 0,05 can be selected to calculate the activation energy of the candidate material, with regard to practical experiences [7], [8]. In Method B it is unnecessary to use reference material data to determine the activation energy of the candidate material in accordance with ISO 11358-2 [3] and the thermal indices of materials can be determined as TI_A by the activation energy when the degree of conversion is 0,05.

In this round robin test, TI_A and RTE_A at 20 000 h of LCP sample A and sample B were determined by using Method A and Method B respectively.

7 Round robin test results

7.1 TGA test results

All the raw TGA test data were obtained from eleven laboratories (a, b, c, d, e, f, g, h, i, j and k). Figure 4 shows typical examples of overlay TGA curves at multiple heating rates magnified to show the degrees of conversion between 0 and 0,02. Figure 5 provides typical examples of logarithm graphs between reciprocal temperatures and heating rates for certain degrees of conversions. Figure 6 shows cubic approximation between degree of conversions and activation energies to read appropriate activation energy for the determination of RTE_A or TI_A .

7.2 Degree of conversion correlated to the activation energy from conventional heat ageing data

Degrees of conversion at the activation energy identical to that from conventional heat ageing were determined with reference to ISO 11358-2 [3] and IEC TS 60216-7-1 which are shown in Table 2.

It was observed that both sample A and sample B had very low initial thermal degradation under TGA (around 3 % or 4 % mass loss) which were correlated to thermal degradation of the dielectric strength under a heating oven, in terms of the identical activation energies. For reproducibility in laboratories, however, relatively high deviations are observed (around 30 % of the average degree of conversion) for both sample A and sample B. In addition, three laboratories (b, d, and j) were not able to obtain a degree of conversion identical to that of the activation energy of conventional heat ageing, because all of the activation energies were found to be higher than the ones determined by heat ageing in the considered range.

Table 2 – Degree of conversion identical to the activation energy of the conventional heat ageing

Laboratory	Degree of conversion identical to activation energy of the conventional heating, sample A	Degree of conversion identical to activation energy of the conventional heating, sample B
a	0,032 7	0,019 9
b	N/A	0,039 3
c	0,040 8	0,043 7
d	N/A	0,037 8
e	0,037 7	0,024 4
f	0,021 9	0,040 6
g	0,036 7	0,024 6
h	0,034 2	0,037 1
i	0,051 5	0,032 1
j	N/A	0,015 0
k	0,060 0	0,031 1
Average	0,032 7	0,031 4
Standard deviation	0,013 6	0,009 3
NOTE N/A means that in the cubic approximation of activation versus the degree of conversion, the equation did not provide a solution.		

7.3 HIC_A determined by Method A and Method B

HIC_A determined by Method A and Method B according to IEC TS 60216-7-1 is shown in Table 3, Table 4 and Table 5 for dielectric strength, tensile strength and impact strength, respectively.

Table 3 – HIC_A determined by Method A and Method B for dielectric strength

Laboratory	Method A		Method B	
	HIC _A of sample A	HIC _A of sample B	HIC _A of sample A	HIC _A of sample B
	K	K	K	K
a	10,4	9,5	9,8	7,9
b	8,8	N/A	8,6	7,6
c	12,1	11,7	11,6	10,6
d	8,6	N/A	7,9	9,7
e	14,4	9,0	12,6	8,1
f	10,6	16,7	10,0	9,1
g	13,5	10,3	10,0	9,0
h	12,2	9,2	11,5	7,0
i	20,7	8,6	13,0	8,8
j	11,0	N/A	9,1	7,7
k	11,7	12,7	10,4	9,6
Average	12,2	11,0	10,4	8,6
Standard deviation	3,2	2,5	1,5	1,0
NOTE N/A means that in the cubic approximation of activation versus the degree of conversion, the equation did not provide a solution.				

Table 4 – HIC_A determined by Method A and Method B for tensile strength

Laboratory	Method A		Method B	
	HIC_A of sample A K	HIC_A of sample B K	HIC_A of sample A K	HIC_A of sample B K
a	10,0	9,1	9,6	7,9
b	8,7	7,5	8,3	7,6
c	11,5	9,3	11,3	10,7
d	8,5	16,4	7,9	9,7
e	13,9	7,8	12,2	8,4
f	10,1	8,8	9,8	9,2
g	12,6	9,1	9,7	7,9
h	11,9	6,3	11,2	7,1
i	18,8	7,9	12,6	8,8
j	10,1	11,0	8,8	7,8
k	11,1	9,3	10,1	9,6
Average	11,6	9,3	10,1	8,6
Standard deviation	2,9	2,6	1,5	1,1

Table 5 – HIC_A determined by Method A and Method B for impact strength

Laboratory	Method A		Method B	
	HIC_A of sample A K	HIC_A of sample B K	HIC_A of sample A K	HIC_A of sample B K
a	9,3	8,4	9,8	8,1
b	8,3	6,6	8,5	7,7
c	20,5	11,6	11,6	11,0
d	10,0	N/A	8,1	9,9
e	12,7	9,2	12,6	8,6
f	11,6	16,6	10,0	9,4
g	14,8	10,3	10,0	9,2
h	N/A	8,0	11,5	7,2
i	32,4	8,9	13,0	9,0
j	10,5	N/A	9,0	7,9
k	12,2	16,4	10,4	9,8
Average	14,2	10,7	10,4	8,9
Standard deviation	7,3	3,6	1,6	1,1

7.4 RTE_A determined by Method A and TI_A by Method B

RTE_A determined by Method A and TI_A by Method B are shown in Table 6, Table 7, and Table 8 for dielectric strength, tensile strength, and impact strength, respectively.

Table 6 – RTE_A determined by Method A and TI_A by Method B for dielectric strength

Laboratory	Method A		Method B	
	RTE_A of sample A °C	RTE_A of sample B °C	TI_A of sample A °C	TI_A of sample B °C
a	255,0	249,2	256,7	256,4
b	259,7	N/A	260,4	257,7
c	249,9	238,9	251,2	243,8
d	260,2	N/A	262,3	248,2
e	242,8	251,4	248,3	255,2
f	254,3	213,7	256,1	250,7
g	245,5	245,3	256,2	251,4
h	249,5	250,5	251,6	260,1
i	222,7	253,0	247,1	252,4
j	253,0	N/A	258,8	257,0
k	251,1	234,2	254,9	248,7
Average	249,3	243,1	254,9	253,3
Standard deviation	10,3	13,2	4,9	4,9

Table 7 – RTE_A determined by Method A and TI_A by Method B for tensile strength

Laboratory	Method A		Method B	
	RTE_A of sample A °C	RTE_A of sample B °C	TI_A of sample A °C	TI_A of sample B °C
a	250,7	250,7	252,4	256,1
b	255,6	257,8	256,8	257,5
c	245,3	249,6	246,1	243,4
d	256,2	215,2	258,2	247,9
e	236,3	256,5	242,8	253,9
f	250,5	252,0	251,7	250,4
g	241,4	243,6	251,8	250,1
h	243,8	263,2	246,6	259,9
i	216,9	256,3	241,5	252,1
j	250,6	241,8	255,2	256,6
k	247,0	249,8	250,4	248,4
Average	244,9	248,8	250,3	252,4
Standard deviation	11,0	12,7	5,5	4,9

Table 8 – RTE_A determined by Method A and TI_A by Method B for impact strength

Laboratory	Method A		Method B	
	RTE_A of sample A °C	RTE_A of sample B °C	TI_A of sample A °C	TI_A of sample B °C
a	257,8	259,3	256,3	260,7
b	260,7	266,2	260,1	261,9
c	222,3	247,0	250,7	249,6
d	255,7	N/A	261,5	253,6
e	247,4	256,4	247,8	258,8
f	250,8	227,1	255,7	255,7
g	240,8	252,1	255,7	256,4
h	N/A	260,9	251,1	264,1
i	179,8	257,7	246,6	257,2
j	254,3	N/A	258,8	261,2
k	248,9	227,6	254,5	254,0
Average	241,9	250,5	254,4	257,6
Standard deviation	24,4	14,2	4,9	4,3

7.5 Difference between RTE_A and TI determined by the conventional heat ageing tests

Differences between RTE_A or TI_A and TI , which is a numerical value remaining after TI is deducted from RTE_A or TI_A , are shown in Table 9, Table 10, and Table 11 for dielectric strength, tensile strength, and impact strength, respectively.

Table 9 – Difference between RTE_A or TI_A , and TI for dielectric strength

Laboratory	Method A		Method B	
	$RTE_A - TI$ of sample A °C	$RTE_A - TI$ of sample B °C	$TI_A - TI$ of sample A °C	$TI_A - TI$ of sample B °C
a	5	7,7	6,7	14,9
b	9,7	N/A	10,4	16,2
c	-0,1	-2,6	1,2	2,3
d	10,2	N/A	12,3	6,7
e	-7,2	9,9	-1,7	13,7
f	4,3	-27,8	6,1	9,2
g	-4,5	3,8	6,2	9,9
h	-0,5	9,0	1,6	18,6
i	-27,3	11,5	-2,9	10,9
j	3,0	N/A	8,8	15,5
k	1,1	-7,3	4,9	7,2
Average	-0,6	0,5	4,9	11,4
Mean	1,1	5,8	6,1	10,9
Standard deviation	10,3	13,2	4,9	4,9

Table 10 – Difference between RTE_A or TI_A , and TI for tensile strength

Laboratory	Method A		Method B	
	RTE_A -TI of sample A °C	RTE_A -TI of sample B °C	TI_A -TI of sample A °C	TI_A -TI of sample B °C
a	0,7	9,2	2,4	14,6
b	5,6	N/A	6,8	16,0
c	-4,7	8,1	-3,9	1,9
d	6,2	N/A	8,2	6,4
e	-13,7	15,0	-7,2	12,4
f	0,5	10,5	1,7	8,9
g	-8,6	2,1	1,8	8,6
h	-6,2	21,7	-3,4	18,4
i	-33,1	14,8	-8,5	10,6
j	0,6	N/A	5,2	15,1
k	-3,0	8,3	0,4	6,9
Average	-5,1	11,2	0,3	10,9
Mean	-3,0	9,8	1,7	10,6
Standard deviation	11,0	5,9	5,5	4,9

Table 11 – Difference between RTE_A or TI_A , and TI for impact strength

Laboratory	Method A		Method B	
	RTE_A -TI of sample A °C	RTE_A -TI of sample B °C	TI_A -TI of sample A °C	TI_A -TI of sample B °C
a	7,8	17,8	6,3	19,2
b	10,7	N/A	10,1	20,4
c	-27,7	5,5	0,7	8,1
d	5,7	N/A	11,5	12,1
e	-2,6	14,9	-2,2	17,3
f	0,8	-14,4	5,7	14,2
g	-9,2	10,6	5,7	14,9
h	N/A	19,4	1,1	22,6
i	-70,2	16,2	-3,4	15,7
j	4,3	N/A	8,8	19,7
k	-1,1	-13,9	4,5	12,5
Average	-8,2	7,0	4,4	16,1
Mean	-0,1	12,8	5,7	15,7
Standard deviation	24,4	13,8	4,9	4,3

8 Observations from the round robin test results

8.1 General

In the round robin test, the following productive points were observed for the validation of IEC TS 60216-7-1:

- both RTE_A and TI_A determined in these round robin tests mostly had similar values to TI by conventional heat ageing with a difference in temperature of 20 °C or less in most cases, and
- Method A using the degree of conversion given by the calculation failed to provide solutions of RTE_A in a few laboratories and their standard deviations were also relatively high, whereas Method B using the fixed degree of conversion based on experiences at 0,05 provided lower standard variations between laboratories.

It is noted, however, that results show differences between the laboratories, with differences in temperature exceeding 20 °C in some instances of the report.

In particular, the difference of within 20 °C from the conventional heat ageing is useful, because the conventional RTE in accordance with the IEC 60216 series also contains this level of reproducibility issues due to variation factors of heating ovens, test plaques and lot-to-lot variation of materials, etc.

As a practical example of implementing long term thermal endurance evaluation according to IEC 60216-8 [9], a certification of the thermal endurance properties provides the industry with a temperature classification with some increments according to the temperature assigned such as 20 °C increments over 180 °C of RTI, 10 °C increments from 130 °C through 180 °C and 5 °C increments up to 130 °C [10].

As TI of the two LCP materials evaluated in this document have been determined over 180 °C, 20 °C or less difference between RTE_A or TI_A and TI , conformity with the temperature classification in accordance with the above conventional heat ageing methods can be established.

On the other hand, the round robin test also raised technical concerns as follows:

- laboratory i determined an RTE_A of the LCP sample A significantly different from those by other laboratories in all the three properties, and
- a few laboratories ~~could~~ were not able to determine RTE_A of sample B, because the degree of conversion was not appropriately calculated from the fitting curve in 6.4.

The round robin test participants discussed the rationale, and the following potential factors which ~~could~~ can have an influence on the above issues were raised and then checked as follows:


- 1) sample weight variation,
- 2) humidity and hydrolysis of the sample,
- 3) repeatability of TGA curves, and
- 4) baseline drift and spacing between multiple curves of TGA.

8.2 Sample weight variation

ISO 11358-2 [3] provides the tolerance of the sample weight per one run of TGA as ± 1 % with less than 10 mg, however, the round robin test applied a wider tolerance of 5 mg $\pm$ 0,5 mg (10 % tolerance). Therefore, the sample weight variation was identified as one of the potential variation factors.


The scatter plot between the standard deviation of sample mass and the difference between TI and RTE_A (TI_A) was evaluated, however, less correlation was observed between the two factors which are shown in Figure 2 and Figure 3.

Because of these facts, the sample weight variation ~~may~~ can be considered with respect to ISO 11358-2, [3], but not as a significant factor with regard to the technical concerns of reproducibility in laboratories mentioned above.

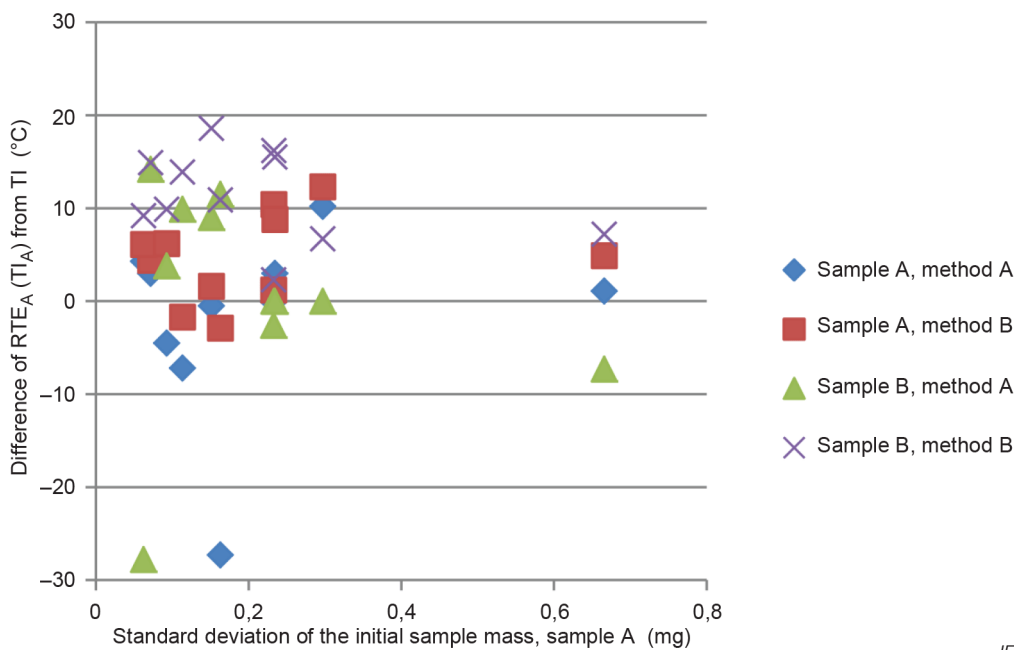

IEC

Figure 2 – Correlation between the initial sample mass of sample A and the difference of RTE_A (TI_A) from TI

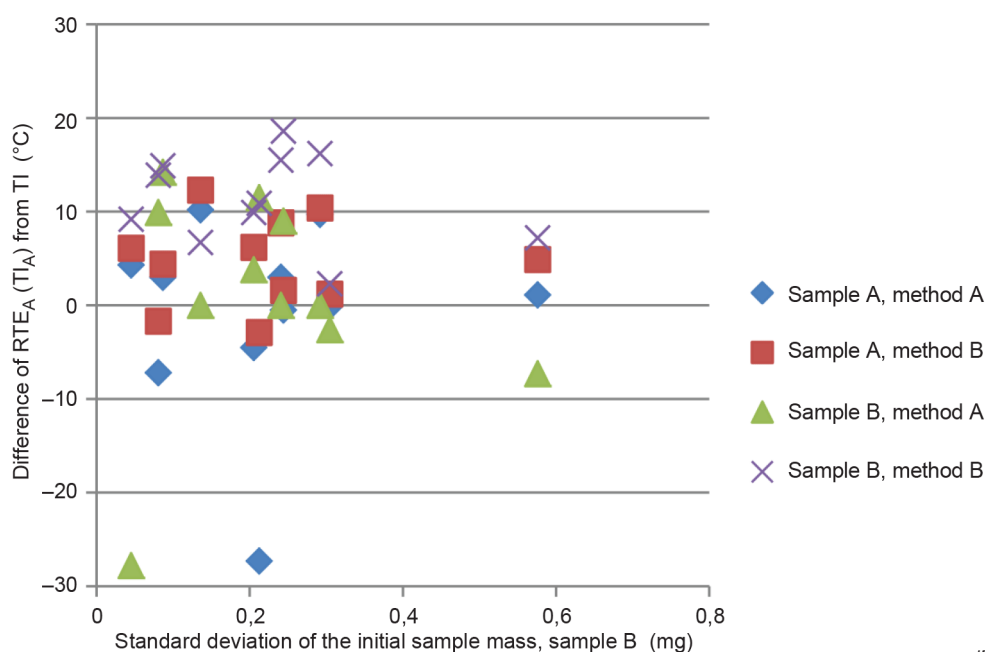

IEC

Figure 3 – Correlation between the initial sample mass of sample B and the difference of RTE_A (TI_A) from TI

8.3 Humidity and hydrolysis of the sample

The round robin test samples were liquid crystal polyesters, and ~~since~~ moisture ~~could~~ can accelerate the polymer degradation with hydrolysis, humidity and hydrolysis were therefore pointed out as the factors ~~potentially influencing the~~ reproducibility at specific laboratories.

At first, all of samples A and samples B provided to the laboratories were homogenized and pre-dried at 140 °C for 4 h to remove absorbed water during freeze-pulverization and then put into vials before shipment. Natural moisture absorption of LCP is very small, for instance, the equilibrium moisture content of the LCP polymer is approximately 0,03 % (300 ppm) at 23 °C and 50 % RH. Sample A and sample B are 30 % glass filled grades and the actual equilibrium moisture after the vials are opened is expected to be lower than this value. In addition, the sample loaded to TGA was pre-conditioned at 100 °C for 1 h in the furnace. At the above point, absorbed moisture from the sample cannot be considered a major factor of RTE_A and TI_A variation.

Next, atmosphere in the TGA furnace ~~could~~ can be another factor which has an influence on hydrolysis of the polymer around the thermal decomposition temperature in the TGA furnace. In fact it was different in each laboratory, because the round robin test requested participants to report, if possible, what kind of air was used to supply purge gas into the TGA furnace. Not all laboratories responded, however, and it was determined that some of the laboratories (a, b, and f) used dry air (moisture content guaranteed less than 1 ppm or 2 ppm) while others (laboratories e, g, and h) used compressed air with or without an air dryer. In fact, there was no relation observed between the specific laboratories mentioned above and the difference in air supply. However, dry air is useful and its use was recommended to all of the participants to decrease a side effect factor of reproducibility issues. For reference, dry air is given as an example of purge gas in ISO 11358-1.

8.4 Considerations on repeatability of TGA curves

In the round robin test based on IEC TS 60216-7-1 and ISO 11358-2 [3], multiple TGA curves with different heating rates were used for the calculation of the degree of conversion and the activation energy of the candidate material. If one TGA curve has low repeatability, correlation between the degree of conversion and the activation energy ~~could~~ can also be changed to determine RTE_A or TI_A.

Taking this factor into consideration, supplemental measurement was rerun at 8 K/min for both sample A and sample B in every participating laboratory. A summary of the degree of conversion is shown in Table 12.

NOTE The rerun data at 8 K/min were not reported by laboratory i.

Table 12 – Comparison of degree of conversion with original or rerun data at 8 K/min

Laboratory	Degree of conversion for E_a of sample A at 130,6 kJ/mol		Degree of conversion for E_a of sample B at 142,3 kJ/mol	
	Original data at 8 K/min	Rerun data at 8 K/min	Original data at 8 K/min	Rerun data at 8 K/min
a	0,032 7	0,084 7	0,019 9	0,019 5
b	N/A	N/A	0,039 3	0,033 6
c	0,040 8	0,022 1	0,043 7	0,038 4
d	N/A	N/A	0,037 8	0,037 2
e	0,037 7	0,051 7	0,024 4	0,024 4
f	0,021 9	0,020 5	0,040 6	0,040 1
g	0,036 7	0,035 1	0,024 6	0,020 9
h	0,034 2	0,037 2	0,037 1	0,017 2
i	0,051 5	-	0,032 1	-
j	N/A	N/A	0,016 7	0,013 7
k	0,060 0	N/A	0,031 1	0,026 0
Average	0,039	0,042	0,032	0,027
Standard deviation	0,012	0,024	0,009	0,010

As shown in Table 12, two laboratories (a and e) had a significant change in the given degree of conversion for sample A by rerun data at 8 K/min, which exceeded the degree of conversion at 0,05 (Method B). Another laboratory k ~~could~~ was not able to obtain the results of the degree of conversion for sample A, even though the laboratory obtained the given degree of conversion with the original data at 8 K/min. From those observations, it is suggested that the repeatability of TGA raw data can have a significant impact on the calculation of the degree of conversion which affects repeatable determination of RTE_A or TI_A , as well. In this study, only one test condition of heating rates (8 K/min) was retested for a preliminary review of repeatability check. It is suggested that the repeatability ~~should~~ be further evaluated also with retesting at other heating rates for an assessment of the precision.

On the above point, population of the TGA raw curve data (e.g. evaluation of 2 or 3 runs at the same heating rate) and normalization of those raw data can be further considered before analysis in accordance with ISO 11358-2 [3] is conducted in each laboratory, if repeatability and reproducibility improvements are necessary.

It is suggested that repeatability of the TGA curve is checked at all heating rates to decrease variations of the degree of conversion and the activation energy determined by TGA.

8.5 Baseline drift and responsiveness to heating rates of TGA

To examine the remaining reasons why no result of degree of conversion and RTE_A by Method A was provided to sample A in three laboratories (b, d and j) for dielectric strength, the raw TGA curves, logarithm graphs according to ISO 11358-2 [3], and the fitting curve example given in Figure 1 were plotted as shown in Figure 4, Figure 5 and Figure 6 respectively, with the comparative examples of three other laboratories data which obtained a degree of conversion and RTE_A .