IEC TR 63367

Edition 1.0 2021-11

TECHNICAL REPORT

colour inside

Fibre optic interconnecting devices and passive components – Summarising results of round robin on connector end face scratch recognition and verification by automated microscopes

Documents
Document Sharing Hub

IEC TR 63367:2021-11(en)

Full document details: IEC TR 63367-2021

THIS PUBLICATION IS COPYRIGHT PROTECTED
Copyright © 2021 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office
3, rue de Varembé
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC
The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications
The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform
The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee, …). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished
Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc
If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

IEC online collection - oc.iec.ch
Discover our powerful search engine and read freely all the publications previews. With a subscription you will always have access to up to date content tailored to your needs.

Electropedia - www.electropedia.org
The world's leading online dictionary on electrotechnology, containing more than 22 000 terminological entries in English and French, with equivalent terms in 18 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

Documents
Document Sharing Hub

Full document details: IEC TR 63367-2021

IEC TR 63367

Edition 1.0 2021-11

TECHNICAL REPORT

colour inside

Fibre optic interconnecting devices and passive components – Summarising results of round robin on connector end face scratch recognition and verification by automated microscopes

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 33.180.10

ISBN 978-2-8322-1053-5

Warning! Make sure that you obtained this publication from an authorized distributor.

® Registered trademark of the International Electrotechnical Commission

Documents
Document Sharing Hub

Full document details: IEC TR 63367-2021

CONTENTS

FOREWORD 5
INTRODUCTION 7
1 Scope 8
2 Normative references 8
3 Terms and definitions 8
4 Round robin procedure 8
5 Specimen preparation 9
5.1 General 9
5.2 Multimode specimens 9
5.3 Single-mode specimens 11
6 Results 13
6.1 Reported data 13
6.2 Multimode specimens 13
Observations of specimen MM20-2 14
Observations of specimen MM12 15
Observations of MM14-4 16
6.3 Single-mode specimens 16
Observations of specimen SM9 17
Observations of specimen SM15-4 18
7 Observations and conclusions 18
7.1 Multimode observations 18
Remarks 19
7.2 Single-mode observations 19
Remarks 19
7.3 Conclusions 19
8 Items to be studied 20
Annex A (informative) Measurement procedure 21
Annex B (informative) Performance and geometry data of test specimens 23
Annex C (informative) Reported scratch results for all specimens 35
Bibliography 40

Figure 1 – Multimode single-fibre test specimen grouping 10
Figure 2 – Multimode multi-fibre test specimen grouping 11
Figure 3 – Single-mode single-fibre test specimen grouping 12
Figure 4 – Single-mode multi-fibre test specimen grouping 13
Figure 5 – Image of specimen end face MM20-2 14
Figure 6 – Number of out-of-specification scratches reported for multimode multi-fibre specimen MM20-2, zone A 14
Figure 7 – Image of specimen end face MM12 15
Figure 8 – Number of out-of-specification scratches reported for multimode single-fibre specimen MM12, zone A 15
Figure 9 – Image of specimen end face MM14-4 16
Figure 10 – Number of out-of-specification scratches reported for multimode multi-fibre specimen MM14-4, zone A 16
Figure 11 – Image of specimen end face SM9 17

AVA Documents
Document Sharing Hub
Full document details: IEC TR 63367-2021

Figure 12 – Number of out-of-specification scratches reported for single-mode single-fibre specimen SM9, zone A 17
Figure 13 – Image of specimen end face SM15-4 18
Figure 14 – Number of out-of-specification scratches reported for single-mode multi-fibre specimen SM15-4, zone A 18
Figure A.1 – Measurement procedure workflow 22
Figure B.1 – Initial attenuation of multimode single-fibre specimens 24
Figure B.2 – Initial return loss of multimode single-fibre specimens 24
Figure B.3 – Multimode multi-fibre test interface identification key 25
Figure B.4 – Initial attenuation of multimode multi-fibre specimens 27
Figure B.5 – Initial return loss of multimode multi-fibre specimens 27
Figure B.6 – Initial attenuation of single-mode single-fibre specimens 29
Figure B.7 – Initial return loss of single-mode single-fibre specimens 30
Figure B.8 – Single-mode multi-fibre test interface identification key 31
Figure B.9 – Initial attenuation of single-mode multi-fibre specimens 32
Figure B.10 – Initial return loss of single-mode multi-fibre specimens 33
Figure C.1 – (All specimens) – Number of out-of-specification scratches reported for multimode single-fibre specimens, zone A 35
Figure C.2 – (All specimens) – Number of out-of-specification scratches reported for multimode single-fibre specimens, zone B 36
Figure C.3 – (All specimens) – Number of out-of-specification scratches reported for multimode multi-fibre specimens, zone A 36
Figure C.4 – (All specimens) – Number of out-of-specification scratches reported for multimode multi-fibre specimens, zone B 37
Figure C.5 – (All specimens) – Number of out-of-specification scratches reported for single-mode single-fibre specimens, zone A 37
Figure C.6 – (All specimens) – Number of out-of-specification scratches reported for single-mode single-fibre specimens, zone B 38
Figure C.7 – (All specimens) – Number of out-of-specification scratches reported for single-mode multi-fibre specimens, zone A 38
Figure C.8 – (All specimens) – Number of out-of-specification scratches reported for single-mode multi-fibre specimens, zone B 39

Table 1 – Multimode test specimen categorisation 9
Table 2 – Single-mode test specimen categorisation 12
Table A.1 – Scratch size limits 21
Table B.1 – Initial optical performance of multimode single-fibre specimens 23
Table B.2 – End-face geometry of multimode single-fibre specimens 25
Table B.3 – Attenuation of multimode multi-fibre specimens 26
Table B.4 – Return loss of multimode multi-fibre specimens 26
Table B.5 – End-face geometry parameter of multimode multi-fibre specimens 28
Table B.6 – Fibre height of multimode multi-fibre specimens 28
Table B.7 – Core dip of multimode multi-fibre specimens 28
Table B.8 – Initial optical performance of single-mode single-fibre specimens 29
Table B.9 – End-face geometry of single-mode single-fibre specimens 30
Table B.10 – Attenuation of single-mode multi-fibre specimens at 1 310 nm wavelength 31

AVA Documents
Document Sharing Hub
Full document details: IEC TR 63367-2021

Table B.11 – Attenuation of single-mode multi-fibre specimens at 1 550 nm wavelength 31
Table B.12 – Return Loss of single-mode multi-fibre specimens at 1 310 nm wavelength 32
Table B.13 – Return loss of single-mode multi-fibre specimens at 1 550 nm wavelength 32
Table B.14 – End-face geometry parameter of single-mode multi-fibre specimens 33
Table B.15 – Fibre height of single-mode multi-fibre specimens 33
Table B.16 – Fibre tip radii of single-mode multi-fibre specimens 34

Documents
Document Sharing Hub
Full document details: IEC TR 63367-2021

INTERNATIONAL ELECTROTECHNICAL COMMISSION

FIBRE OPTIC INTERCONNECTING DEVICES AND PASSIVE COMPONENTS – SUMMARISING RESULTS OF ROUND ROBIN ON CONNECTOR END FACE SCRATCH RECOGNITION AND VERIFICATION BY AUTOMATED MICROSCOPES

FOREWORD

1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
6) All users should ensure that they have the latest edition of this publication.
7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

IEC TR 63367 has been prepared by subcommittee 86B: Fibre optic interconnecting devices and passive components, of IEC technical committee 86: Fibre optics. It is a Technical Report.

The text of this Technical Report is based on the following documents:

Draft	Report on voting
86B/4492/DTR	86B/4521/RVDTR

Full information on the voting for its approval can be found in the report on voting indicated in the above table.

The language used for the development of this Technical Report is English.

Documents
Document Sharing Hub

Full document details: IEC TR 63367-2021

This document was drafted in accordance with ISO/IEC Directives, Part 2, and developed in accordance with ISO/IEC Directives, Part 1 and ISO/IEC Directives, IEC Supplement, available at www.iec.ch/members_experts/refdocs. The main document types developed by IEC are described in greater detail at www.iec.ch/standardsdev/publications.

The committee has decided that the contents of this document will remain unchanged until the stability date indicated on the IEC website under webstore.iec.ch in the data related to the specific document. At this date, the document will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

IMPORTANT – The "colour inside" logo on the cover page of this document indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

Documents
Document Sharing Hub

Full document details: IEC TR 63367-2021

INTRODUCTION

It is known that contamination and scratches on connector end face can result in degradation of optical performance as described in IEC TR 62627-05. It is important to inspect and clean, when necessary, each connector before mating with another connector to ensure they are fit for function. The visual inspection methods and criteria for fibre optic connectors and fibre-stub transceivers are defined in IEC 61300-3-35. Three different methods can be used for visual inspection: direct view optical microscopy (method A), video microscopy (method B) and automated analysis microscopy (method C). All methods are susceptible to system variability: methods A and B are operator dependent; method C is operator independent but relies on software analysis for measurement results. The uncertainty inherent to imaging equipment, processing methods, and detection software can lead to measurement variability among different brands and even the same types of microscopy. For all methods, the fibre microscopes can be certified for use in either low- and high-resolution applications with a purpose-built certification artefact.

There is industry concern about the veracity of the results of the visual inspection of the same part using different automated inspection equipment and software for method C. The IEC SC 86B task force group on scratch recognition was organized to investigate automated inspection system variability and provide recommendations to improve repeatability and reproducibility of the inspection. The task force group specifically limited its investigation to inspection using method C.

The task force group consisted of the following members (in alphabetical order): Arden, CommScope, Corning, Data Pixel, Exfo, Fibre QA, Fluke Corporation, Sumix, University College of London, and decided to perform this investigation by means of a round robin. The round robin involved inspection systems from multiple vendors in a blind study to determine the baseline performance of the systems with regard to automated scratch detection relative to IEC criteria of pre-selected samples.

This report summarizes the results (data collection and analysis) of end face scratch recognition and verification round robin performed by the following task force contributors (5 fibre inspection system manufactures). The following sequence in which the contributors are listed does not represent the order in which the data is presented in the results section. One contributor provided results from four unique inspection systems, each having their own participant ID (eight ID’s in total):

- Data-Pixel;
- Exfo;
- FiberQA;
- Fluke Corporation;
- Sumix.

Documents
Document Sharing Hub

Full document details: IEC TR 63367-2021

FIBRE OPTIC INTERCONNECTING DEVICES AND PASSIVE COMPONENTS – SUMMARISING RESULTS OF ROUND ROBIN ON CONNECTOR END FACE SCRATCH RECOGNITION AND VERIFICATION BY AUTOMATED MICROSCOPES

1 Scope

This document summarises the results of a round robin on connector end face scratch recognition and verification by automated microscopes. The prime objectives of the study were:

- determine the amount of variability (repeatability and reproducibility) when different state-of-the-art inspection systems are assessed against IEC 61300-3-35:2015;
- evaluate any system-to-system variation in the quantity of reported scratches;
- provide recommendations to improve the repeatability and reproducibility of fibre optic inspection systems.

2 Normative references

There are no normative references in this document.

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at https://www.iso.org/obp
- IEC Electropedia: available at http://www.electropedia.org/

4 Round robin procedure

The round robin workflow consisted of the following steps.

a) Specimen preparation (see Clause 5): Multimode and single-mode single-fibre and multi-fibre test specimens were produced. An image of each end face was captured by high resolution microscope, attenuation and return loss were measured for each fibre, and end-face geometry was determined to verify that the specimens met the IEC interface requirements.

b) Circulation initiation: Measurement procedure and results template (see Annex A) were developed and approved by the group. The order of participants for specimen circulation was agreed.

c) Measurements: Specimens were circulated among round robin participants. Every participant performed measurements and collected image data according to the agreed procedure.

d) Analysis of results: The results were gathered from all participants. Data analysis was performed, and the synthesis report was composed.

Documents
Document Sharing Hub

Full document details: IEC TR 63367-2021

5 Specimen preparation

5.1 General

The round-robin test specimens were fabricated to consider various interface configurations and conditions. Specimens were arranged into both cylindrical ferrule single fibre (1,25 mm zirconia material) and rectangular ferrule multi-fibre types (12-fibre MT with polyphenylene sulphide [PPS] material). Both multimode (50 µm core diameter) and single-mode specimens were produced.

5.2 Multimode specimens

The multimode specimens were further organised into categories that had pristine fibre end-face surface quality, and ones with low-level, light scratches (produced with a 1 µm diamond film) which still meet functional performance criteria. Furthermore, specimens were created with 1 to 3 heavy scratches (produced with a 5 µm diamond suspension), as well as a control without detectable heavy scratches. A summary describing all of the multimode variants is provided in Table 1. A total of twelve multimode single-fibre specimens and twelve multi-fibre specimens (with three specimens per group) were produced. Images for each of the specimens are given in Figure 1 for the single-fibre and Figure 2 for the multi-fibre groups. All images were taken with an end face inspection system utilizing blue-light illumination, an objective having an NA of 0,40 and a magnification of 400 x (see Figure 1 to Figure 4).

Table 1 – Multimode test specimen categorisation

Group identification	Ferrule type	Ferrule material	Light scratches	Heavy scratches
A MM	1,25 mm	Zirconia	No	No
B MM	1,25 mm	Zirconia	No	Yes
C MM	1,25 mm	Zirconia	Yes	No
D MM	1,25 mm	Zirconia	Yes	Yes
E MM	MT (PPS)	PPS	No	No
F MM	MT (PPS)	PPS	No	Yes
G MM	MT (PPS)	PPS	Yes	No
H MM	MT (PPS)	PPS	Yes	Yes

Documents
Document Sharing Hub
Full document details: IEC TR 63367-2021

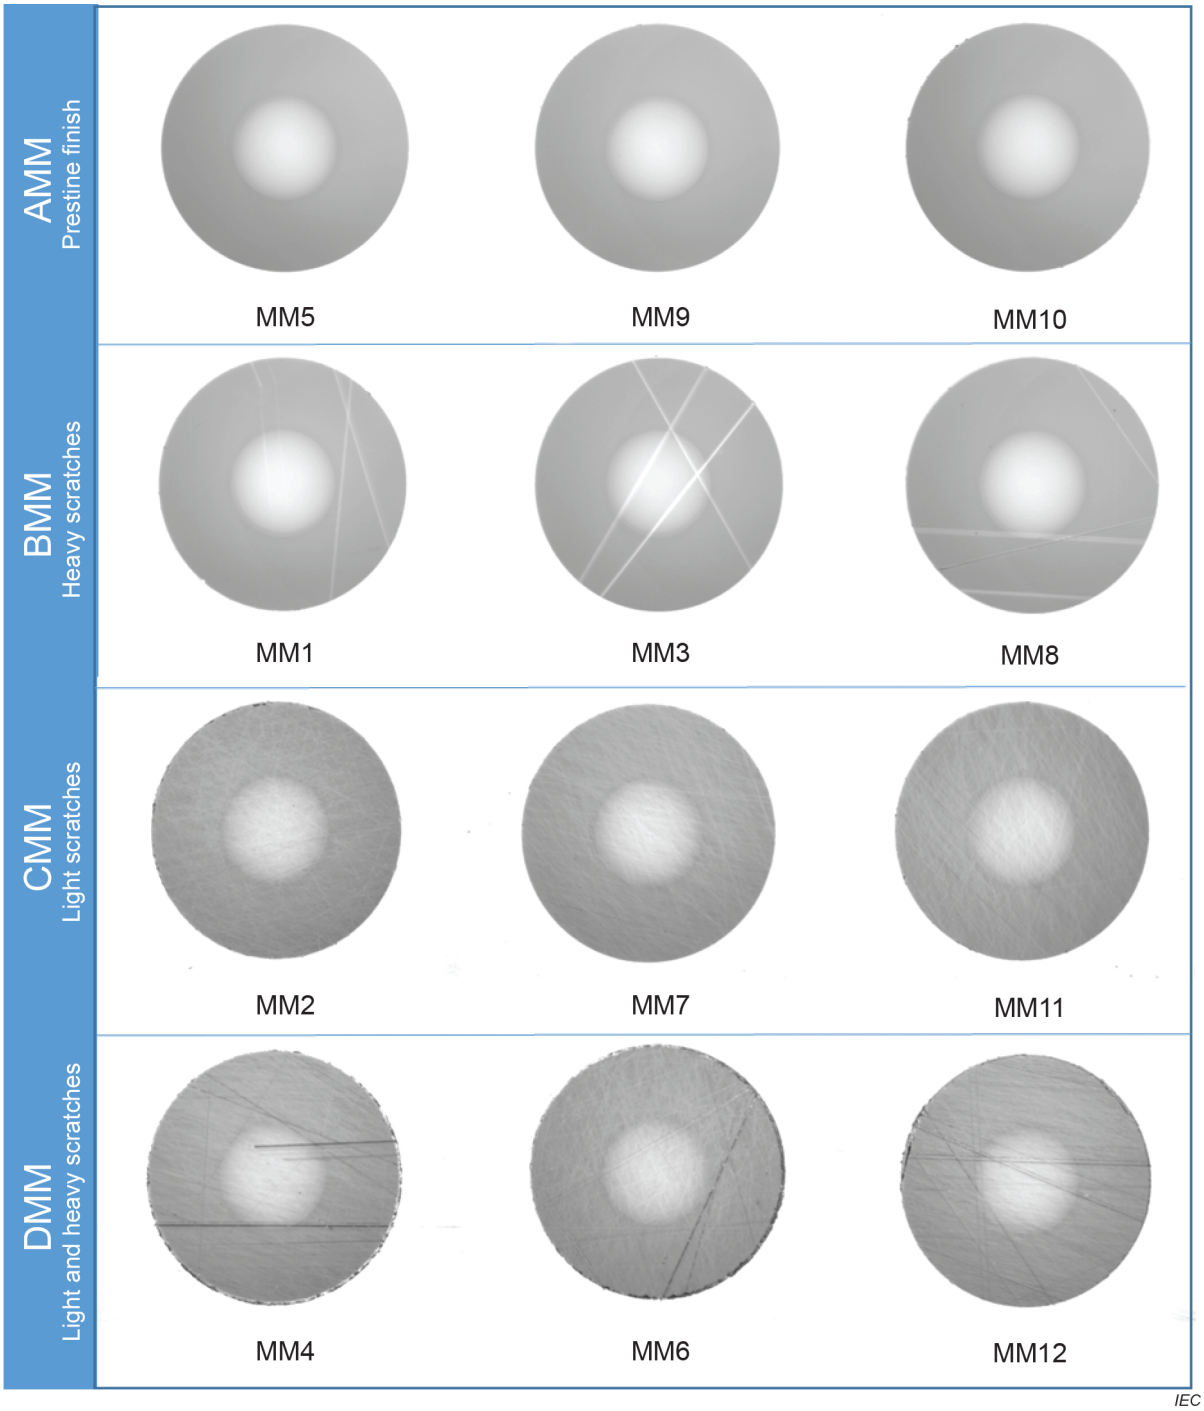

Figure 1 – Multimode single-fibre test specimen grouping

Following visual inspection, the optical performance of each specimen was qualified at 850 nm wavelength and the end-face geometry was determined. The attenuation and return loss were measured per IEC 61300-3-4, insertion method (B), and IEC 61300-3-6, method 1: OCWR, respectively. The results for the single-fibre specimens is reported in Annex B (Table B.1 and Figure B.1 to Figure B.2). End face geometry of the single-fibre specimens was estimated using IEC 61300-3-47 and summarized in Annex B (Table B.2).

The multi-fibre specimens had specific fibres of each ferrule identified for the study. However, attenuation, return loss, and geometry measurements were made across all fibres of the interconnection. A key to identify the fibre specimen inspected during the round robin is provided in Annex B (Figure B.3). Attenuation and return loss values are given in Annex B (Table B.3 to Table B.4 and Figure B.4 to Figure B.5), with the round robin fibre inspection

Documents
Document Sharing Hub
Full document details: IEC TR 63367-2021

interfaces highlighted. The end-face geometry of the multi-fibre interfaces was determined using IEC 61300-3-30. The relevant geometric parameters, fibre heights, and core dip results are summarised in Annex B (Table B.5 to Table B.7).

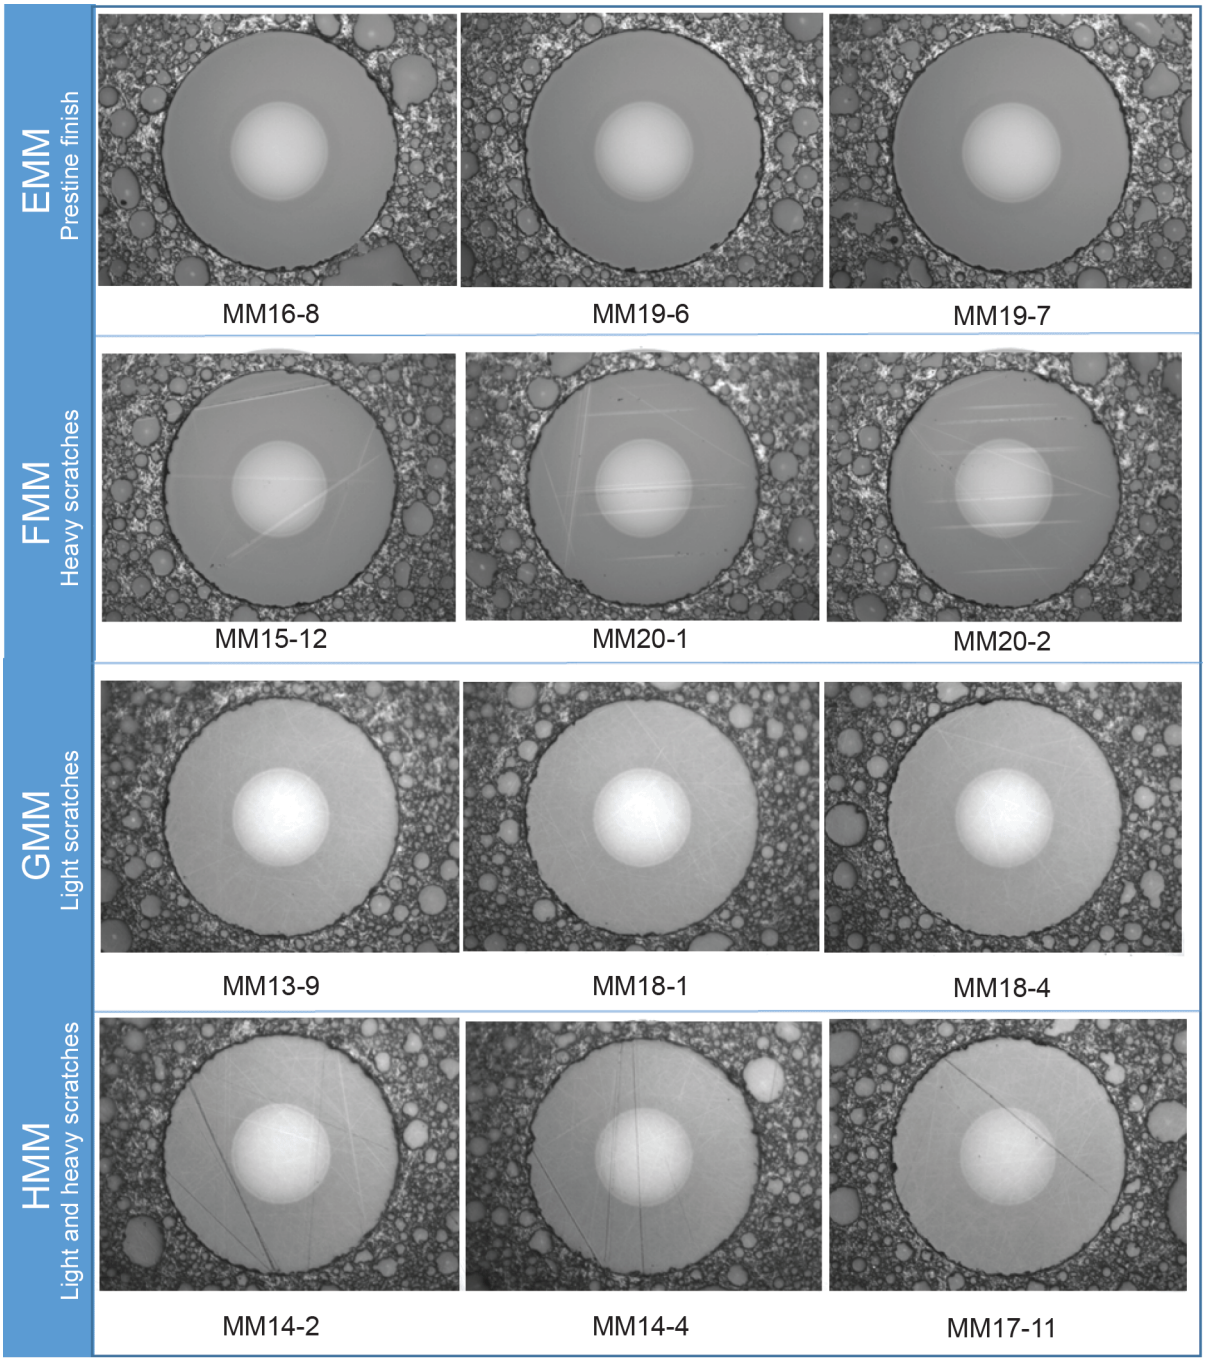

Figure 2 – Multimode multi-fibre test specimen grouping

5.3 Single-mode specimens

The single-mode end faces were binned into categories, which either had 1 to 3 scratches that pass through the fibre core or pass through zone A (without intersecting the core). These scratches were approximately 1 µm width. In addition, a single-mode specimen group without any observable scratches was produced. A summary describing all of the single-mode variants is provided in Table 2. A total of nine single-mode, single-fibre specimens were produced and nine multi-fibre interfaces (with three specimens per group). Images for each of the specimens are given in Figure 3 for single-fibre and Figure 4 for the multi-fibre groups.

AVA Documents
Document Sharing Hub
Full document details: IEC TR 63367-2021

Table 2 – Single-mode test specimen categorisation

Group identification	Ferrule type	Ferrule material	Core scratches	Zone A scratches
A SM	1,25 mm	Zirconia	No	No
B SM	1,25 mm	Zirconia	No	Yes
C SM	1,25 mm	Zirconia	Yes	Yes
D SM	MT	PPS	No	No
E SM	MT	PPS	No	Yes
F SM	MT	PPS	Yes	Yes

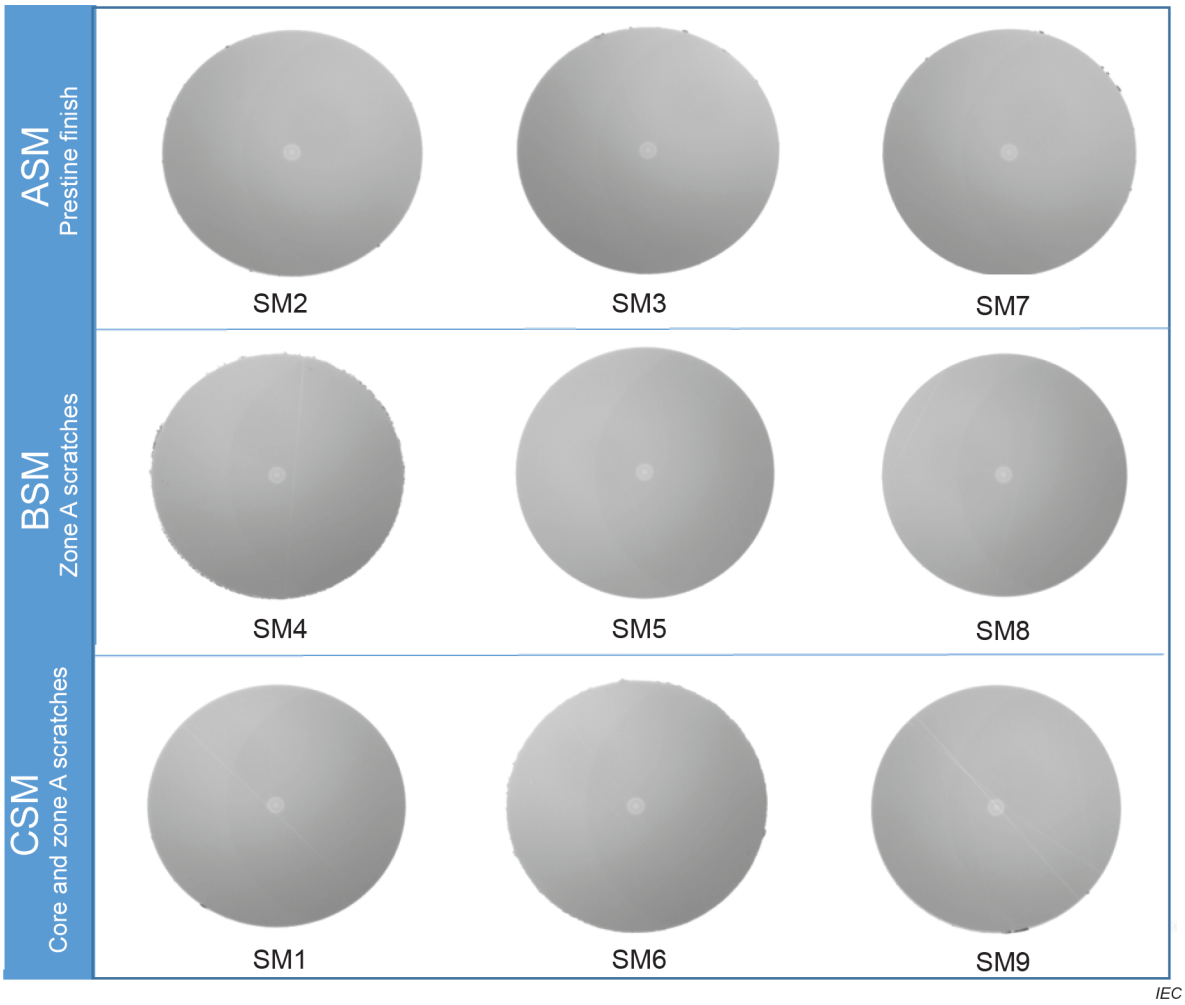

Figure 3 – Single-mode single-fibre test specimen grouping

Following visual inspection, the optical performance of each specimen was qualified at 1 310 nm and 1 550 nm wavelengths, and the end-face geometry was determined. The attenuation and return loss was measured per IEC 61300-3-4, insertion method (B), and IEC 61300-3-6, method 1: OCWR, respectively. The results for the single-fibre specimens are reported in Annex B (Table B.8 and Figure B.6 to Figure B.7). End face geometry of the single-fibre specimens was estimated using IEC 61300-3-47 and summarized in Annex B (Table B.9).

The multi-fibre specimens had specific fibres of each ferrule identified for the study. However, attenuation, return loss, and geometry measurements were made across all fibres of the interconnection. A key to identify the fibre interface inspected during the round robin is provided in Annex B (Figure B.8). Attenuation and return loss values are given in Annex B (Table B.10

Documents
Document Sharing Hub
Full document details: IEC TR 63367-2021