

INTERNATIONAL STANDARD

ISO
1431-2

Second edition
1994-01-15

Rubber, vulcanized or thermoplastic — Resistance to ozone cracking —

Part 2: Dynamic strain test

*Caoutchouc vulcanisé ou thermoplastique — Résistance au craquelage par
l'ozone —*

Partie 2: Essai de déformation dynamique



Reference number
ISO 1431-2:1994(E)



Documents

Document Sharing Hub

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 1431-2 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Physical and degradation tests*.

This second edition cancels and replaces the first edition (ISO 1431-2:1982), of which it constitutes a technical revision.

ISO 1431 consists of the following parts, under the general title *Rubber, vulcanized or thermoplastic — Resistance to ozone cracking*:

- *Part 1: Static strain test*
- *Part 2: Dynamic strain test*
- *Part 3: Reference method for determining the ozone concentration in laboratory test chambers*

Annex A of this part of ISO 1431 is for information only.

© ISO 1994

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization
Case Postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Rubber, vulcanized or thermoplastic — Resistance to ozone cracking —

Part 2: Dynamic strain test

1 Scope

This part of ISO 1431 specifies a method intended for use in estimating the resistance of vulcanized or thermoplastic rubbers to cracking when exposed, under dynamic tensile strain, to air containing a definite concentration of ozone and at a definite temperature in circumstances that exclude the effects of direct light.

Great caution is necessary in attempting to relate standard test results to service performance since the relative ozone resistance of different rubbers can vary markedly depending on the conditions, especially ozone concentration and temperature. In addition, tests are carried out on thin test pieces deformed in tension and the significance of attack for articles in service may be quite different owing to the effects of size and of the type and magnitude of deformation. Explanatory notes on the nature of ozone cracking are given in informative annex A.

Methods for determining resistance to ozone cracking under static strain conditions are specified in ISO 1431-1. A reference method for estimating the ozone concentration will form the subject of ISO 1431-3.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 1431. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 1431 are encouraged to investigate the

possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 37:1977, *Rubber, vulcanized — Determination of tensile stress-strain properties.*

ISO 471:1983, *Rubber — Standard temperatures, humidities and times for the conditioning and testing of test pieces.*

ISO 1431-1:1989, *Rubber, vulcanized or thermoplastic — Resistance to ozone cracking — Part 1: Static strain test.*

ISO 4661-1:1993, *Rubber, vulcanized or thermoplastic — Preparation of samples and test pieces — Part 1: Physical tests.*

3 Definition

For the purposes of this part of ISO 1431, the following definition applies.

3.1 dynamic strain: A strain (normally a tensile strain) with a sinusoidal nature varying with time at some selected repetition rate or frequency.

NOTE 1 The maximum strain and the repetition rate are used to describe the dynamic strain conditions.

4 Principle

Test pieces are exposed, either under continuous dynamic strain or under alternate periods of dynamic and

static strain, in a closed chamber at a constant temperature, to an atmosphere containing a fixed concentration of ozone. The test pieces are examined periodically for cracking.

Two alternative evaluation procedures are described for selected values of ozone concentration and exposure temperature:

- Determination of the presence or absence of cracks after exposure for a fixed period of time at a given dynamic strain or combination of dynamic and static strains.
- Determination of the time to the first appearance of cracks at any given dynamic strain or combination of dynamic and static strains.

5 Apparatus (see figure 1)

WARNING — Attention is drawn to the highly toxic nature of ozone. Efforts should be made to minimize the exposure of workers at all times. In the absence of more stringent or contrary national safety regulations in member body countries, it is recommended that 10 parts of ozone per hundred million parts of air of the surrounding atmosphere by volume be regarded as an absolute maximum concentration whilst the maximum average concentration should be appreciably lower. Unless a totally enclosed system is being used, an exhaust vent to remove ozone-laden air is advised.

5.1 Test chamber.

This shall be a closed, non-illuminated chamber, thermostatically controlled to within $\pm 2^\circ\text{C}$ of the test temperature, lined with, or constructed of, a material (for example aluminium) that does not readily decompose ozone. Dimensions shall be such that the requirements of 5.5 are met. The chamber may be provided with a window through which the surface of the test pieces can be observed. A light to examine test pieces may be installed, but this shall remain switched off at all other times.

5.2 Source of ozonized air.

Either of the following items of apparatus may be used:

- an ultra-violet lamp;
- a silent-discharge tube.

The use of oxygen is necessary when using the discharge tube in order to avoid the formation of nitrogen oxides. The ozonized oxygen or air may be diluted with air to attain the required ozone concentration. Air used for generation of ozone or dilution shall first be purified by passing it over activated charcoal and shall be free from any contaminants likely to affect the ozone concentration, cracking or estimation of ozone.

The temperature of the source shall be kept constant to within $\pm 2^\circ\text{C}$.

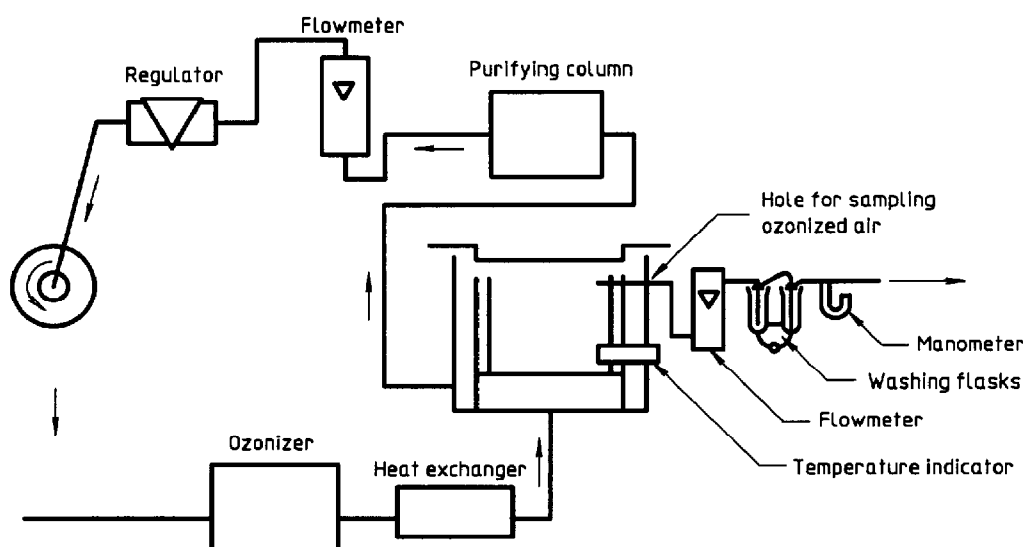


Figure 1 — Schematic diagram of the apparatus