TECHNICAL SPECIFICATION

ISO/TS 4699

First edition
2022-08

Hard Coal — Determination of plastometric indices — Manual method

Houille — Détermination des indices plastométriques — Méthode manuelle

Reference number
ISO/TS 4699:2022(E)

Documents
Document Sharing Hub
© ISO 2022

Full document details: ISO_TS 4699_2022



COPYRIGHT PROTECTED DOCUMENT

© ISO 2022

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
CP 401 • Ch. de Blandonnet 8
CH-1214 Vernier, Geneva
Phone: +41 22 749 01 11
Email: copyright@iso.org
Website: www.iso.org

Published in Switzerland

© ISO 2022 – All rights reserved

Documents
Document Sharing Hub
Full document details: ISO_TS 4699_2022

Contents

Page

Foreword ... **iv**
Introduction ... **v**
1 Scope ... **1**
2 Normative references ... **1**
3 Terms and definitions ... **1**
4 Principle ... **2**
5 Reagent and materials ... **2**
6 Apparatus ... **3**
6.1 Plastometric apparatus ... 3
6.1.1 Electric Furnace ... 4
6.1.2 Heating elements ... 5
6.1.3 Pressure lever assembly ... 5
6.1.4 Retort ... 5
6.1.5 Thermocouples ... 10
6.1.6 Thermocouple tube ... 10
6.1.7 Probe ... 10
6.1.8 Recording device ... 11
6.2 Programmed temperature controller ... 11
6.3 Exhaust device ... 11
6.4 Mass measurement device ... 11
6.5 Spirit level gauge ... 11
6.6 Callipers ... 11
6.7 Double roll crusher ... 11
6.8 1,5 mm round hole sieve ... 11
6.9 Sampling shovel ... 11
7 Sample preparation ... **12**
8 Preparation for testing ... **12**
8.1 Cleaning retort ... 12
8.2 Preparation of paper tube ... 12
8.3 Preparation of refractory round pad ... 12
8.4 Loading retort ... 12
8.5 Adjusting the rotary drum (if applicable) ... 13
8.6 Determining the height of the coal sample in the retort ... 13
9 Test procedure ... **15**
10 Expression of result ... **17**
10.1 Processing of plastometric graph ... 17
10.2 Displacement curve types ... 18
10.3 Calculation and record ... 19
11 Precision ... **20**
11.1 Repeatability limit ... 20
11.2 Reproducibility limit ... 20
12 Test report ... **20**
Annex A (informative) **Visual assessmentfor the technical characteristics of the coke block** ... **21**
Annex B (informative) **Methods for checking cross-section load on the coal sample** ... **24**
Bibliography ... **26**

© ISO 2022 – All rights reserved

Documents
Document Sharing Hub
Full document details: ISO_TS 4699_2022

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 27, *Coal and coke,* Subcommittee SC 5, *Methods of analysis*.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

© ISO 2022 – All rights reserved
Documents
Document Sharing Hub
Full document details: ISO_TS 4699_2022

Introduction

The determination of plastic layer indices has been performed in GB/T 479[5] and GOST 1186[6] for many years. First, a manual detection of the height of the upper and lower interfaces of the plastic layer is performed, then curves for the upper and lower layers are established and finally the maximum thickness of plastic matter is calculated.

Instrumental methods for a more rapid determination of plastic layer indices are now available. If such a method is to be used, it is important to demonstrate that the method is free from bias, when compared to a reference method. In addition, it should give levels of repeatability and reproducibility which are the same as, or better than, those quoted for the reference method (see Clause 11).

The objective of this document is to provide a reference method for determination of the plastometric indices.

© ISO 2022 – All rights reserved

Documents
Document Sharing Hub
Full document details: ISO_TS 4699_2022

Documents
Document Sharing Hub

Full document details: ISO_TS 4699_2022

Hard Coal — Determination of plastometric indices — Manual method

1 Scope

This document specifies a manual method for the determination of plastometric indices. These indices are the maximum thickness of the plastic layer (*Y*, mm) and the final contraction value (*X*, mm).

This document is applicable for hard coals with a determined ash level less than 15 % on a dry basis, as described in ISO 11722 and ISO 1171.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1213-2, *Solid mineral fuels — Vocabulary — Part 2: Terms relating to sampling, testing and analysis*

ISO 3310-2, *Test sieves — Technical requirements and testing — Part 2: Test sieves of perforated metal plate*

ISO 13909-1, *Hard coal and coke — Mechanical sampling — Part 1: General introduction*

ISO 13909-2, *Hard coal and coke — Mechanical sampling — Part 2: Coal — Sampling from moving streams*

ISO 13909-3, *Hard coal and coke — Mechanical sampling — Part 3: Coal — Sampling from stationary lots*

ISO 13909-4, *Hard coal and coke — Mechanical sampling — Part 4: Coal — Preparation of test samples*

ISO 18283, *Coal and coke — Manual sampling*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 1213-2 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at https://www.iso.org/obp

— IEC Electropedia: available at https://www.electropedia.org/

3.1
displacement curve of the plastic layer
curve of displacement of the packed coal bed changing with the temperature during the determination of plastometric indices

3.2
maximum thickness of plastic layer
Y
maximum perpendicular distance between the upper and lower plastic layer

© ISO 2022 – All rights reserved

Documents
Document Sharing Hub
Full document details: ISO_TS 4699_2022

3.3
final contraction value
plastometric shrinkage
X
perpendicular distance from the end of the displacement curve at 730 °C to the zero line (at 250 °C)

Note 1 to entry: This distance is 3 times that of the actual displacement of the plastic layer.

3.4
zero line
original height curve of the packed coal bed paralleling the X-axis drawn at a temperature of 250 °C

4 Principle

The coal sample is heated unidirectionally from the base at a standard rate under constant pressure whilst the plastic layer develops. The plastic layer thickness (referred to as *Y'*) is manually measured periodically throughout the test using a rounded end blunt probe. The displacement curve of the plastic layer is recorded. The curves representing changes of the upper and lower layers are generated by the least squares method. The maximum thickness of the plastic layer (referred to as *Y*) is calculated by the maximum perpendicular distance between the upper and lower layers. The final contraction (referred to as *X*) is calculated by the perpendicular distance from the end of the displacement curve at 730 °C to the zero line (at 250 °C).

5 Reagent and materials

5.1 Cigarette rolling paper, (also known as blanks), which are small sheets, rolls, or leaves of paper sold for rolling cigarettes either by hand or with a rolling machine.

5.2 Filter paper, qualitative filter paper, dimensions of at least 60 mm wide and 190 mm to 200 mm long, used to line the inner wall of the retort (6.1.4).


NOTE The width of filter paper can be adjusted to keep bending the paper over the upper heat-resistant refractory round pad.

5.3 Thin steel rod, 3 mm in diameter and at least 150 mm long. Cigarette rolling paper is wrapped around the rod to make a tube. The resultant paper tube is then placed into the retort (6.1.4) and is surrounded by the coal after loading.

5.4 Refractory round pad. Heat resistant refractory ceramic pads or other refractory and porous pads, with thickness of 0,5 mm to 1,0 mm and diameter of 59 mm for use on the top and bottom of the coal sample in the retort (6.1.4). The pads can be made by manual or mechanical means. Each base pad requires a hole to allow the thermocouple tube (6.1.6) to fit through and a mark corresponding the probe hole of the pressure plate. Each top pad requires two holes, one to allow the thermocouple tube to fit through and one to allow the paper tube to fit through (see Figure 1).

© ISO 2022 – All rights reserved
Documents
Document Sharing Hub
Full document details: ISO_TS 4699_2022

Dimensions in millimetres

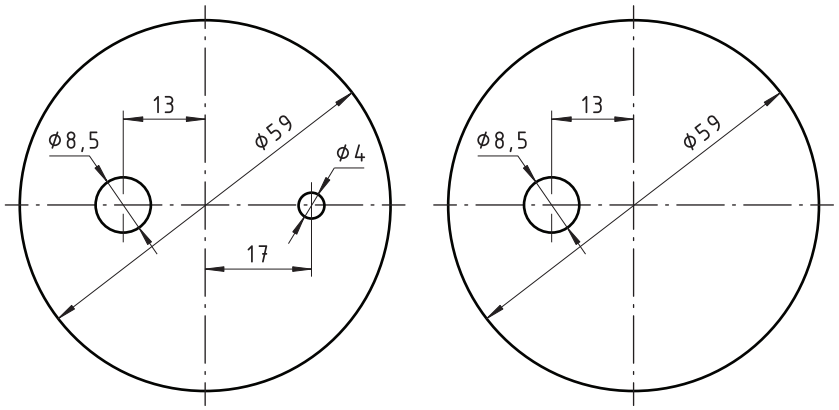

Key

1 top pad

2 base pad

Figure 1 — Refractory round pad

5.5 Abrasive cloth. Emery cloth P80 grade is suitable for removing coke residue from the retort (6.1.4) and associated components.

5.6 Displacement curve recording paper. A type of standard millimetre coordinate paper, with a height the same as the height of rotary drum (6.1.8) and length is slightly longer than the perimeter of the rotary drum.

5.7 Ceramic cord and ceramic wool

6 Apparatus

6.1 Plastometric apparatus


Typically, two types of manual plastometers are used in daily analysis of plastometric indices, one of which is with a balance mass (see Figure 2), the other is without a balance mass (the setup is the same as Figure 2 except without the balance masses).

The pressure applied to the cross section of the loaded coal sample during the measurement of the plastometric indices shall be 9,8 $\times 10^4$ Pa (1 kg/cm^2).

The pressure cross section on the loaded coal sample should be checked when the apparatus is newly purchased, moved to a new location OR when major parts have been replaced. Annex B provides guidance on how to check the cross-sectional load on the coal sample.

© ISO 2022 – All rights reserved

Documents
Document Sharing Hub
Full document details: ISO_TS 4699_2022

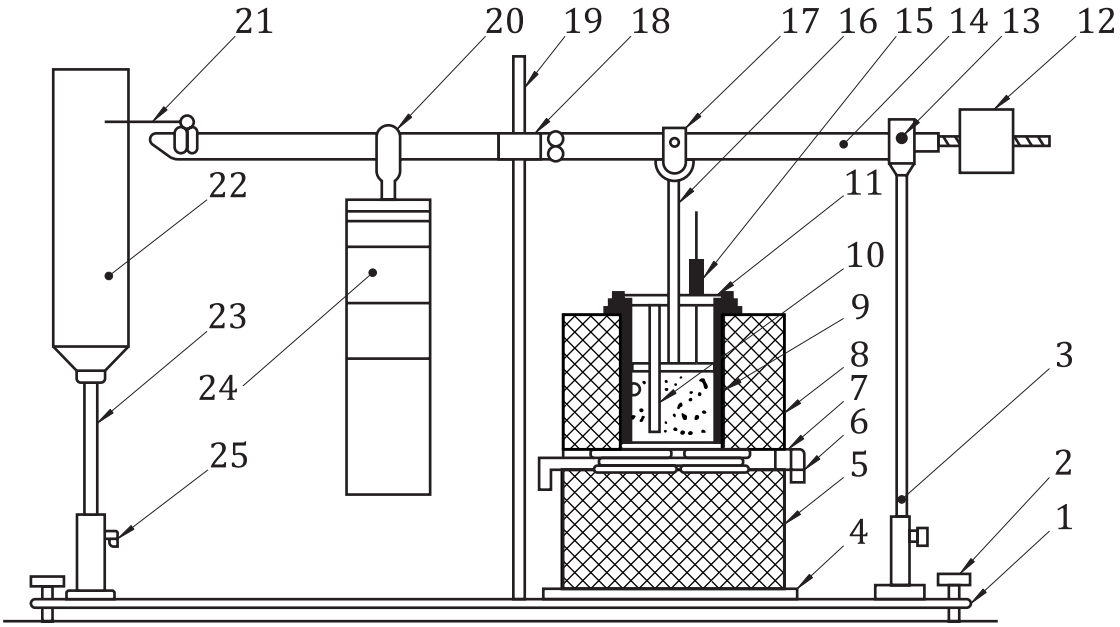

Key

1	pedestal	14	lever
2	horizontal screws	15	probe
3	upright column	16	pressure plate
4	refractory pad	17	articulated joint
5	lower brick layer	18	direction control panel
6	connecting clamp	19	direction pillar
7	silicon carbide rod	20	masses hook
8	upper brick layer	21	recording pen
9	retort	22	rotary drum (with a clockwork)
10	thermocouple tube	23	rotary drum support
11	steel clamping bar	24	loaded masses
12	balance masses	25	set screw
13	connecting shaft		

Figure 2 — Schematic of a plastometric apparatus with balance masses


6.1.1 Electric Furnace

The furnace shall consist of two layers of rectangular furnace firebricks, each measuring 200 mm × 290 mm × 110 mm. The lower layer has a longitudinal groove to allow for visual inspection, and four latitudinal grooves that support the four heating elements. The upper firebrick layer sits over the lower firebrick layer and has two cylindrical holes that accommodate the retorts (6.1.4). The upper firebricks (Figure 3) surface shall be flat and very carefully positioned, to ensure the alignment of the rolling paper tube, relative to the probe.

NOTE Typically the furnace firebrick has a refractoriness of 1 670 °C to 1 710 °C, in which the content of Al_2O_3 is not less than 40 %, and appearance porosity is not more than 26 %. Other refractory bricks can be used provided the furnace can achieve these temperature specifications

© ISO 2022 – All rights reserved
Documents
Document Sharing Hub
Full document details: ISO_TS 4699_2022

Dimensions in millimetres

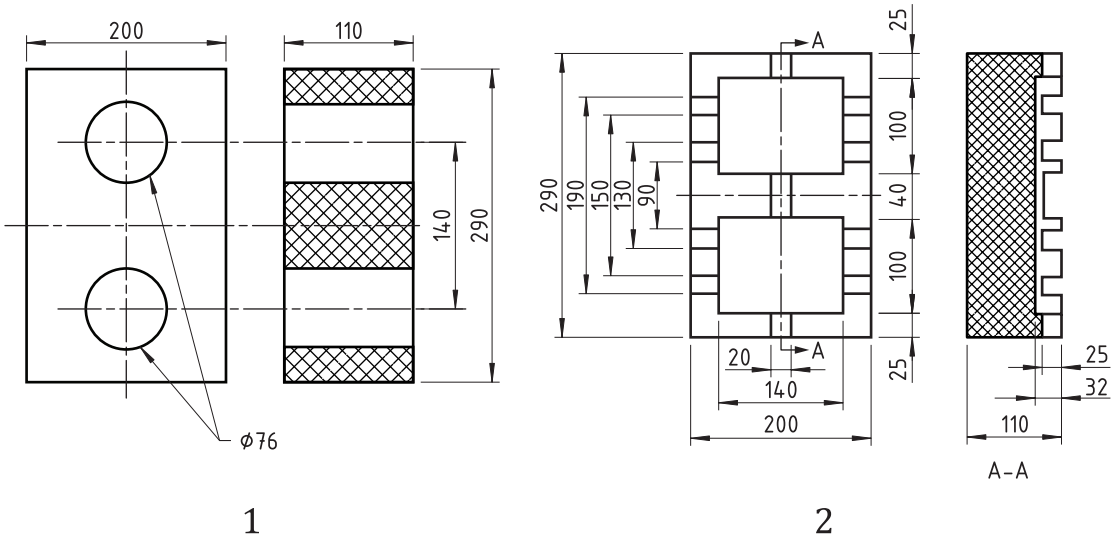

Key

1 upper firebrick layer

2 lower firebrick layer

Figure 3 — Sketch of electric furnace fire bricks

6.1.2 Heating elements

There are four silicon carbide elements each protected by a quartz glass tube of 200 mm × 20 mm. The difference of resistance between the two series elements under each retort (6.1.4) is not more than 0,5 Ω. The elements shall have a resistance of 6 Ω to 8 Ω with an active length of 150 mm and diameter of 8 mm, providing a limiting incandescence temperature of up to 1 200 °C to 1 400 °C. The length of the cold end should be 60 mm long and diameter of 16 mm. The incandescence intensity of the heating elements decreases at a distance of 15 mm from the cold end. The resistance of the heating elements shall be checked at time intervals to ensure compliance with these temperature specifications.

NOTE Heating elements made from different materials can be used provided they can achieve these temperature specifications.

6.1.3 Pressure lever assembly

The pressure lever assembly consists of lever, loaded masses and horizontal adjustor as shown in Figure 2.

6.1.4 Retort

Component parts made with steel conforming to C45E4 in ISO 683-1 shall consist of 6.1.4.1 to 6.1.4.3.

6.1.4.1 Retort body

Specifications are shown in Figure 4. The external diameter is 70 mm. The height from the inside base of the retort bottom to the top of the retort body shall be 110 mm. The retort body shall be tapered, the internal diameter at the bottom shall be 59 mm and the internal diameter, at a height 50 mm from the bottom and top, shall be 60 mm. The inner wall of the body should be smooth without scratches and/or dents. The internal diameter of the working range of the retort body shall be measured for conformance to specifications every 50 determinations. To check the diameter, measure six points (every 10 mm from bottom) on the retort body. The variations between the average results of 6 points

© ISO 2022 – All rights reserved

Documents
Document Sharing Hub
Full document details: ISO_TS 4699_2022