PD IEC/TR 62627-05:2013

BSI Standards Publication

Fibre optic interconnecting devices and passive components

Part 05: Investigation on impact of contamination and scratches on optical performance of single-mode (SM) and multimode (MM) connectors

bsi.

...making excellence a habit.™

Document Sharing Hub

Full document details: PD IEC/TR 62627-05:2013

National foreword

This Published Document is the UK implementation of IEC/TR 62627-05:2013.

The UK participation in its preparation was entrusted by Technical Committee GEL/86, Fibre optics, to Subcommittee GEL/86/2, Fibre optic interconnecting devices and passive components.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2013.
Published by BSI Standards Limited 2013

ISBN 978 0 580 79344 8
ICS 33.180.20

Compliance with a British Standard cannot confer immunity from legal obligations.

This Published Document was published under the authority of the Standards Policy and Strategy Committee on 31 October 2013.

Amendments/corrigenda issued since publication

Date	Text affected

Documents
Document Sharing Hub

Full document details: PD IEC/TR 62627-05:2013

IEC/TR 62627-05

Edition 1.0 2013-10

TECHNICAL REPORT

colour inside

Fibre optic interconnecting devices and passive components – Part 05: Investigation on impact of contamination and scratches on optical performance of single-mode (SM) and multimode (MM) connectors

INTERNATIONAL ELECTROTECHNICAL COMMISSION

PRICE CODE V

ICS 33.180.20

ISBN 978-2-8322-1159-5

Warning! Make sure that you obtained this publication from an authorized distributor.

® Registered trademark of the International Electrotechnical Commission

Documents
Document Sharing Hub

Full document details: PD IEC/TR 62627-05:2013

CONTENTS

FOREWORD 4
INTRODUCTION 6
1 Scope 7
2 Normative references 7
3 Abbreviations 7
4 Experimental methodology 8
5 The impact of scratches on A and RL of single-mode connectors 9
6 Effects of scratches on RL of MM connectors 10
7 Investigation of impact of contamination on optical performance of 2,5 mm and 1,25 mm connectors 11
7.1 General 11
7.2 Zone definitions 11
7.3 Experimental data for 2,5 mm ferrule connectors 12
7.4 Experimental data for 1,25 mm ferrule connectors (LC, MU) 13
7.5 Image analysis 16
7.6 Gaussian weighted per cent occluded area 16
7.7 Inspection criteria matrix 17
8 Correlation study between contamination and signal degradation in single-mode APC connectors 18
8.1 General 18
8.2 Experimental data and analysis for SM APC connectors 18
8.3 Inspection criteria matrix 20
9 Development of cleanliness specifications for single-mode, angled physical contact MPO connectors 21
9.1 General 21
9.2 Core zone analysis 21
9.3 Cladding zone analysis 21
9.4 MT APC scratch analysis 23
10 Conclusion 24
Annex A (informative) The nature of particle redistribution during series of matings/dematings 26
A.1 General 26
A.2 Accumulation of particles near the core during repetitive fibre matings and de-matings for 2,5 mm ferrule connectors 26
A.3 Redistribution of particles during series of repetitive matings/de-matings for MPO connectors 28
A.4 Attenuation changes and separation factor 29
Bibliography 30

Figure 1 – Block diagram of design of experiment 8
Figure 2 – Connector endface with the scratches outside the MFD area 9
Figure 3 – Connector endface with scratches passing through the core 10
Figure 4 – Examples of characterized endfaces using confocal microscope [7] 10
Figure 5 – RL random mated connectors, λ=1 300 nm [7] 11
Figure 6 – Influence of the particle location on performance 12

AVA Documents
Document Sharing Hub
Full document details: PD IEC/TR 62627-05:2013

Figure 7 – FC01 images of DUT and reference fibre after contamination and fifth mating 13
Figure 8 – FC04 images of DUT and reference fibre after contamination and second mating 13
Figure 9 – LC07 images of the DUT and the T07 reference fibre after contamination and first mating 14
Figure 10 – LC07 images of the DUT and the T07 reference fibre after contamination and third mating 15
Figure 11 – LC07 images of the DUT (Figure 11a) and the T07 reference fibre (Figure 11b) after contamination and fifth mating 15
Figure 12 – Labelled detected particles with 5 μm annular rings and fibrescope image for LC07-WD-5M 16
Figure 13 – Delta attenuation versus GWPOA 17
Figure 14 – Left to right: Group A, Group B and average return loss decrease by group 18
Figure 15 – Behaviour of relatively large particles versus small particles 19
Figure 16 – Test connector in pristine condition (RL= 67,5 dB) and after scratches applied (RL= 68,5 dB) 20
Figure 17 – Impact of contamination in core zone for SM APC MPO connectors 21
Figure 18 – Contamination failures due to loss of physical contact by fibre position for connections of angled MT ferrules 22
Figure 19 – Endface images of DUT and reference connector showing no impact to signal performance 22
Figure 20 – Minimal MT/APC contamination on limit sample #1 with signal degradation 23
Figure 21 – Typical lack of impact on signal performance of light scratches on MT/APC connections 24
Figure A.1 – Experimental methodology block diagram 26
Figure A.2 – Relationship between the particle centre moving speed and the charge 27
Figure A.3 – Particle migration and the A signal degradation of MPO connector (channel 2) after series of matings/de-matings 28
Figure A.4 – Evolution of particle centre position for channel 1-11 of an MPO connector pair 28
Figure A.5 – Measured and calculated delta attenuation as functions of GWPOA 29

Table 1 – Summary of the result 7
Table 2 – A and RL statistics for representative samples 14
Table 3 – Inspection criteria for SMF pigtail and patch cord connectors, RL >45 dB 18
Table 4 – Inspection criteria for single-mode APC pigtail and patch cord connectors 20

Documents
Document Sharing Hub
Full document details: PD IEC/TR 62627-05:2013

INTERNATIONAL ELECTROTECHNICAL COMMISSION

FIBRE OPTIC INTERCONNECTING DEVICES AND PASSIVE COMPONENTS –

Part 05: Investigation on impact of contamination and scratches on optical performance of single-mode (SM) and multimode (MM) connectors

FOREWORD

1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as "IEC Publication(s)"). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
6) All users should ensure that they have the latest edition of this publication.
7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

The main task of IEC technical committees is to prepare International Standards. However, a technical committee may propose the publication of a technical report when it has collected data of a different kind from that which is normally published as an International Standard, for example "state of the art".

IEC/TR 62627-05, which is a technical report, has been prepared by subcommittee 86B: Fibre optic interconnecting devices and passive components, of IEC technical committee 86: Fibre optics.

AVA Documents
Document Sharing Hub

Full document details: PD IEC/TR 62627-05:2013

The text of this technical report is based on the following documents:

Enquiry draft	Report on voting
86B/3442/DTR	86B/3489A/RVC

Full information on the voting for the approval of this technical report can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all the parts in the IEC 62627 series, published under the general title *Fibre optic interconnecting devices and passive components* can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC web site under "http://webstore.iec.ch" in the data related to the specific publication. At this date, the publication will be

- reconfirmed,
- withdrawn,
- replaced by a revised edition, or
- amended.

A bilingual version of this publication may be issued at a later date.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

Documents
Document Sharing Hub

Full document details: PD IEC/TR 62627-05:2013

INTRODUCTION

Contaminated optical connectors result in degradation of optical performance, which can be quantified by return loss (RL) and attenuation (A), functional failures and increased deployment costs. Fibre optic connector endface cleaning is recognized as a necessity for optimal signal performance. It is known that contamination impacts signal performance by blocking the core and impeding light transmission, as well as by preventing direct physical contact creating an air gap between the two connector enfaces [1, 2][1]. If an air gap exists, optical performance will be impacted due to the change in transmission medium. As contaminated connectors are mated and demated, contamination can be redistributed around the connectors' endface and block the fibre core. This presents a risk of signal performance degradation during the service life.

Since 2002, the iNEMI (International Electronics Manufacturing Initiative) working group has done substantial work, both theoretical and experimental, on impact of scratches and contamination on connector optical performance (A and RL). The following connector types have been used for this research: single-mode (SM) physical contact (PC) connectors, SM angle polished connectors (APC) and SM APC MPO connector. The impact of polishing scratches has been investigated for SM and multimode (MM) connectors. The work presented in this technical report was used as a base work for the development of IPC-8497-1 [3] and IEC 61300-3-35 [4].

[1] Figures in square brackets refer to the Bibliography.

Documents
Document Sharing Hub
Full document details: PD IEC/TR 62627-05:2013

FIBRE OPTIC INTERCONNECTING DEVICES AND PASSIVE COMPONENTS –

Part 05: Investigation on impact of contamination and scratches on optical performance of single-mode (SM) and multimode (MM) connectors

1 Scope

This part of IEC 62627, which is a technical report, summarizes the extensive industry research on development of cleanliness specifications for single-mode (SM) and multimode (MM) connectors.

The summary of the result shows Table 1.

Table 1 – Summary of the result

Samples		Scratch/Contamination/Defect	A/RL	Clause	Reference
SM/MM	Single-fibre/ multi-fibre				
SM PC	Single-fibre	Scratch	RL	3	[1], [5], [6]
MM PC	Single-fibre	Scratch	RL	4	[7]
SM PC	Single-fibre	Contamination	A and RL	5	[2], [6]. [8]
SM APC	Single-fibre	Contamination	A	7	[11]
SM APC	Single-fibre	Scratch	RL	7.2	[11]
SM APC	Multi-fibre	Contamination	A and RL	8	[12]

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 61300-3-6, *Fibre optic interconnecting devices and passive components – Basic test and measurement procedures – Part 3-6: Examinations and measurements – Return loss*

IEC 61755-3-1, *Fibre optic connector optical interfaces – Part 3-1: Optical interface, 2,5 mm and 1,25 mm diameter cylindrical full zirconia PC ferrule, single mode fibre*

3 Abbreviations

A	attenuation
APC connector	angle polished connector
DUT	device under the test
GWPOA	gaussian weighted per cent occluded area
MFD	mode field diameter
MM connector	multimode connector

AVA Documents
Document Sharing Hub

OTDR	optical time-domain reflectometer
OCWR	optical continuous-wave reflectometry
PC	physical contact
RL	return loss
SM connector	single-mode connector

4 Experimental methodology

In order to collect the data required to enable correlation between changes in optical performance (A and RL) with fibre optic images of the corresponding connectors, the experiment followed a multi-step process that involved

a) initially inspecting, cleaning and imaging connectors being tested (DUTs) and reference connectors; making multiple matings and dematings of each DUT with a reference connector, and recording A and RL data after each cycle,

b) manually applying dust to the cleaned endfaces of the DUTs, then

c) mating contaminated DUTs with clean reference connectors at least five times, taking A and RL measurements after each mating and saving fibre endface images for both connectors. The block diagram of the experiment is shown in Figure 1.

All DUTs and reference connectors were initially inspected and cleaned using a cleaning cassette. Endface images were saved using fibrescope and image analysis software. This software was used to accurately measure the number of particles, their size and their location at the connector endfaces. More than 80 cables with SC simplex connectors (the DUTs) were used for the experiment. A small group of DUTs (five cables) with FC connectors, ten DUTs with LC connectors, and five DUTs with MU connectors were added.

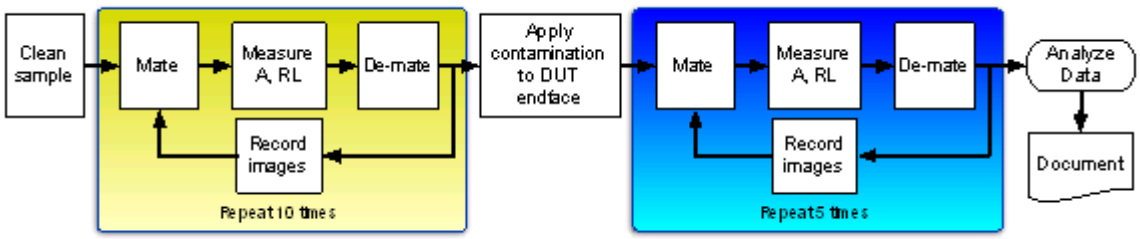

Figure 1 – Block diagram of design of experiment

After clean measurements and images were recorded, Airzona test dust was manually applied to the cleaned endface of the DUT. The two grades of Airzona test dust used for the experiment were ultra-fine (1-5 μm) and fine (6-25 μm). The contaminated DUT was mated with a clean reference connector. A and RL data were recorded. Each DUT and reference connector pair was mated and demated five times. After each mating, A and RL measurements were taken. After demating, the images of the DUT and reference connector endfaces were saved.

If the change in A or RL exceeded three times the standard deviation of A or RL for clean connector, the connector was judged a failure due to contamination. The pass criteria were achieved when both delta A and delta RL were within three standard deviations of A and RL.

The experimental methodology for SM APC connectors and for SM, APC MPO connectors was also based on design of the experiment shown in Figure 1. The details of the experimental procedure for these connector types are described in Clauses 8 and 9. The details of the experimental methodology for MM connectors are provided in Clause 6.

AVA Documents
Document Sharing Hub
Full document details: PD IEC/TR 62627-05:2013

5 The impact of scratches on A and RL of single-mode connectors

A quantitative description of surface defects such as scratches and digs on optical performance was developed based on theory of surface scattering [5]. Further development led to a complete model for analysis of scratches impact on RL performance [6]. The model was based on the Gaussian distribution of incident power and included the effects from scratch location, size and number of the scratches. Based on the model it was predicted that the scratches through the fibre core cause some severe degradation, the scratches outside but near the core have some impact on RL, while scratches beyond 25 μm diameter centre area show little impact on RL performance [6]. These predictions were supported by experimental data [1]. To properly characterize the impact of scratches on performance parameters of mated optical connectors, first the optical performance parameters of pristine optical connectors were measured. Then, after applying scratches at different locations on the fibre endface, the optical performance parameters were measured again.

A sample set of 24 optical cable assemblies and launch cables were polished to PC performance using standard polishing process. The samples were divided into two groups. Scratches were induced only within the cladding region of the first group of connector endfaces, while for second group of optical cable assemblies the scratches were applied to the fibre mode field diameter (MFD).

The results of this study indicated that

a) polishing scratches and scratches made during connector cleaning, outside the fibre MFD, have no impact on A and RL of the mated optical connectors,

b) scratches 2 μm wide or less within the mode field diameter have no impact on A; the A change observed is within the measurement uncertainty of the test equipment,

c) scratches, within the fibre MFD, can degrade the RL of the mated connectors. The level of degradation depends on the size (width and depth), and the number of scratches crossing the fibre MFD. Figure 2 and Figure 3 provide the images of the connector endface with the scratches outside the MFD area and scratches through the fibre core correspondingly.

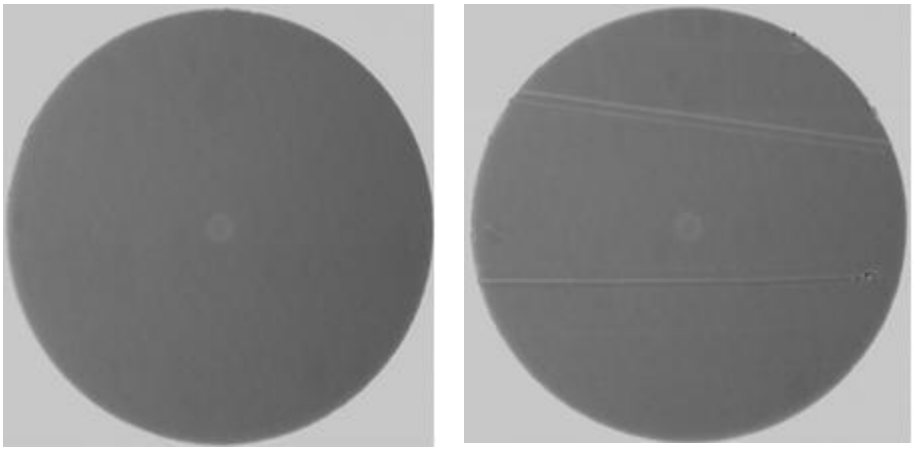

Key A = 0,14 dB; RL = 54,7 dB

Figure 2a – Pristine connector

Key A = 0,11 dB; RL = 54,8 dB

Figure 2b – Scratched connector

Figure 2 – Connector endface with the scratches outside the MFD area

Documents
Document Sharing Hub
Full document details: PD IEC/TR 62627-05:2013