

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be revised, reaffirmed, stabilized, or cancelled. SAE invites your written comments and suggestions.

REV.
C

AS4671™

FEDERAL SUPPLY CLASS
4730

RATIONALE

ADDED CONDUCTIVE HIGH PURITY ALUMINUM COATING FOR ALUMINUM ALLOY FITTINGS.

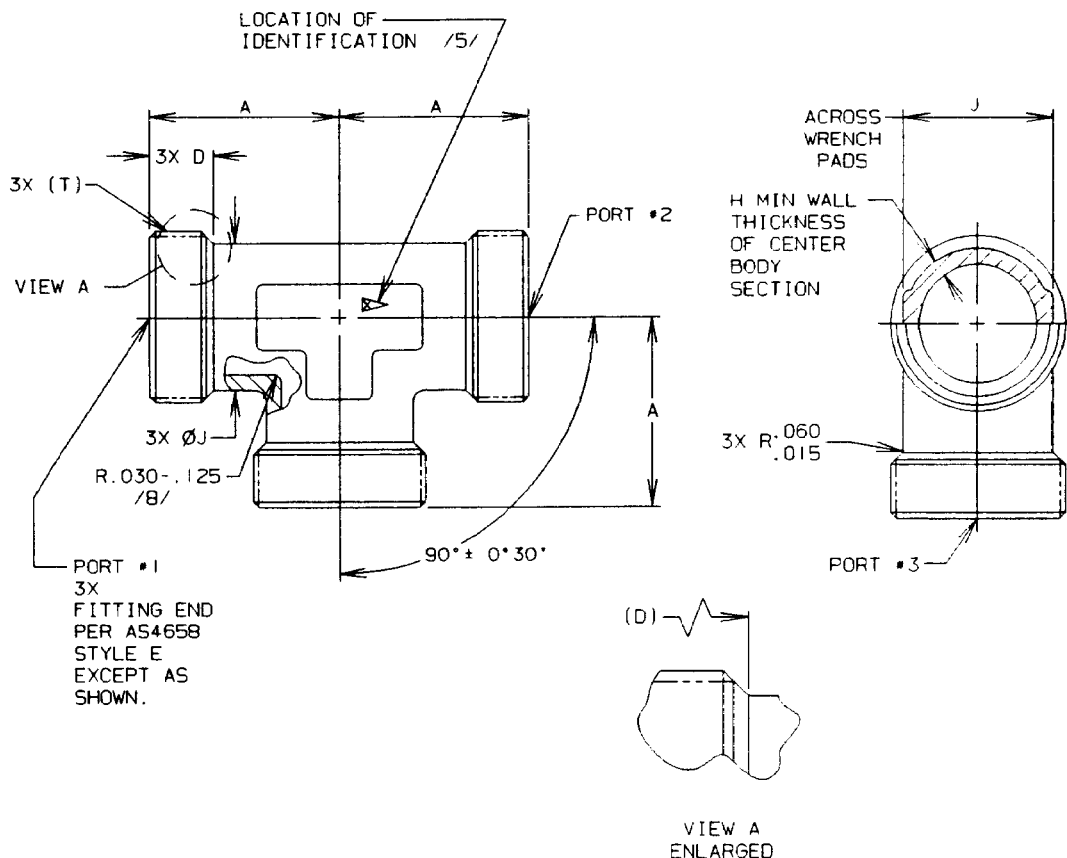



FIGURE 1 – FITTING, TEE

TABLE 1 – DIMENSIONS AND WEIGHTS

BASIC NO. AS4671	/9/ /18/ SIZE CODE	(NOMINAL TUBE SIZE)	T THREAD PER AS8879 CLASS 3A	A	D	H	J +.005/ -.020	LB/EA APPROX REF ALUM	LB/EA APPROX REF CRES	LB/EA APPROX REF TI
20		1.250	1.5625-12UNJ	1.673	.517	.122	1.375	.331	.960	.575
24		1.500	1.8125-12UNJ	1.798	.614	.154	1.688	.497	1.441	.833

SAE values your input. To provide feedback on this
Technical Report, please visit
<http://standards.sae.org/AS4671C>

THIRD ANGLE PROJECTION



CUSTODIAN: G-3/G-3B

PROCUREMENT SPECIFICATION: AS18280 /4/



AEROSPACE STANDARD

FITTING, TEE, SHORT FLARELESS

AS4671™
SHEET 1 OF 3

REV.
C

Documents

Copyright © 2017 SAE International
All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER: Tel: 877-606-7323 (inside USA and Canada)
Fax: 724-776-0790

Tel: +1 724-776-4970 (outside USA)
Email: CustomerService@sae.org

SAE WEB ADDRESS: <http://www.sae.org>

NOTES

NOTICE

THIS DOCUMENT REFERENCES A PART WHICH CONTAINS CADMIUM AS A PLATING MATERIAL. CONSULT LOCAL OFFICIALS IF YOU HAVE QUESTIONS CONCERNING CADMIUM'S USE.

/1/ MATERIAL:

- a. CODE LETTER T: TYPE 6AL-4V TITANIUM ALLOY FORGING OR BAR PER AMS4928
- b. CODE LETTER V: TYPE 15-5PH CORROSION RESISTANT STEEL FORGING OR BAR PER AMS5659
- c. CODE LETTER W: TYPE 7075-T73 ALUMINUM ALLOY FORGING PER AMS4141 OR TYPE 7075-T7351 ALUMINUM ALLOY BAR PER AMS4124

2. HEAT TREATMENT:

- a. MATERIAL CODE LETTER T: NONE
- b. MATERIAL CODE LETTER V: HEAT TREAT TO CONDITION H-1075 PER AMS2759/3
- c. MATERIAL CODE LETTER W: NONE

/3/ FINISH:

- a. MATERIAL CODE LETTER T - FLUORIDE PHOSPHATE CONVERSION COAT PER AMS2486
- b. MATERIAL CODE LETTER V:
 - (1) V CODE PARTS TO BE PASSIVATED ONLY WILL HAVE NO FINISH CODE LETTER AFTER THE SIZE CODE IN THE PART NUMBER. THE FINISH WILL BE: PASSIVATE PER AMS2700 TYPE 2 OR 8.
 - (2) V CODE PARTS TO BE CADMIUM PLATED ONLY WILL HAVE THE FINISH CODE LETTER "P" AFTER THE SIZE CODE IN THE PART NUMBER. THE FINISH WILL BE: CADMIUM PLATE PER AMS-QQ-P-416, TYPE II, CLASS 2.
- c. MATERIAL CODE LETTER W:
 - (1) W CODE PARTS TO BE ANODIZED ONLY WILL HAVE NO FINISH CODE LETTER AFTER THE SIZE CODE IN THE PART NUMBER. THE FINISH WILL BE ANODIZE PER AMS2472 OR PER MIL-A-8625, TYPE II, CLASS 2 DYED BROWN, SIMILAR TO COLOR 10080 OF AMS-STD-595.
 - (2) W CODE PARTS TO BE COATED WITH HIGH PURITY ALUMINUM ONLY WILL HAVE THE FINISH CODE LETTER "V" AFTER THE SIZE CODE IN THE PART NUMBER. SEE PROCUREMENT SPECIFICATION FOR REQUIREMENTS.

/4/ PROCUREMENT SPECIFICATION: AS18280 EXCEPT AS SPECIFIED ON THIS STANDARD. PRODUCT SUPPLIED TO THIS SPECIFICATION SHALL BE MANUFACTURED BY AN ACCREDITED MANUFACTURER AS LISTED IN THE PERFORMANCE REVIEW INSTITUTE (PRI) QUALIFIED PRODUCTS LIST (QPL) PRI-QPL-AS18280 FOR THIS STANDARD. SEE www.eAuditNet.com FOR CURRENT QPL ONLINE.

/5/ IDENTIFICATION AT LOCATION SHOWN: MARK PER AS478 CLASS C OR D OR METHOD 7A3, 15A3, OR 15B. MANUFACTURER'S NAME, TRADEMARK OR CAGE CODE, BASIC PART NUMBER, AND MATERIAL CODE LETTER.

6. INTENDED USE: THIS PART IS DESIGNED FOR USE IN TUBING CONNECTION SYSTEMS WITH OPERATING PRESSURES AS FOLLOWS:

- a. SIZES -20 AND -24 TITANIUM ALLOY AND CORROSION RESISTANT STEEL AT 3000 PSI
- b. SIZES -20 AND -24 ALUMINUM ALLOY AT 600 PSI

7. WHEN MACHINED FROM BAR OR OVERSIZED FORGINGS THE CENTER BODY SECTION SHALL CONFORM TO AS1376 TABLE 10.

/8/ RADIUS APPLICABLE FOR TITANIUM PARTS ONLY.

/9/ THIS IS A NON-REDUCER FITTING. ALL PORTS OF ANY GIVEN PART WILL BE THE SAME SIZE. FOR REDUCERS USE AS4688.

	AEROSPACE STANDARD	AS4671™ SHEET 2 OF 3	REV. 6
	FITTING, TEE, SHORT FLARELESS		



Documents

Document Sharing Hub