

Spring Type Straight Pins

1. Scope

2. References—There are no referenced publications specified herein.

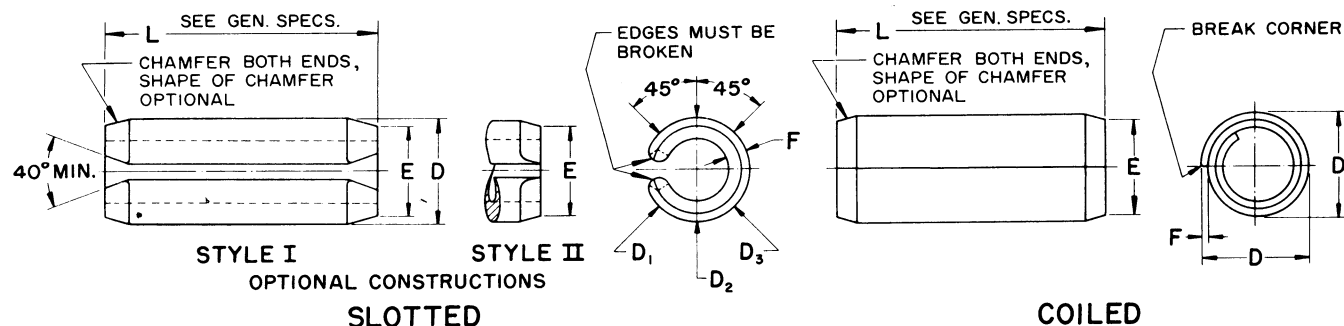


FIGURE 1—

SAE Technical Standards Board Rules provide that: "This report is published by SAE to advance the state of technical and engineering sciences. The use of this report is entirely voluntary, and its applicability and suitability for any particular use, including any patent infringement arising therefrom, is the sole responsibility of the user."

SAE reviews each technical report at least every five years at which time it may be reaffirmed, revised, or cancelled. SAE invites your written comments and suggestions.

Copyright © 2004 SAE International

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of SAE.

TO PLACE A DOCUMENT ORDER:

Tel: 877-606-7323 (inside USA and Canada)
Tel: 724-776-4970 (outside USA)
Fax: 724-776-0790
Email: custsvc@sae.org
<http://www.sae.org>

SAE WEB ADDRESS:

TABLE 1—PIN DIMENSIONS

Nominal Pin Size	D ^a								E	F						Double Shear Strength (lb) ^e			Recommended Hole Size				
	Slotted		Coiled						Slotted and Coiled	Slotted			Coiled			Slotted and Coiled			Slotted		Coiled		
	Series A ^b and B ^b		Series A		Series B		Series C		Series A, B, and C	Series A	Series B		Series A	Series B	Series C	Series A	Series B	Series C	Series A and B		Series A, B, and C		
	Max	Min ^c	Max	Min	Max	Min	Max	Min	Max	Nominal	Style I Nominal	Style II Nominal	Nominal	Nominal	Nominal	Min	Min	Min	Max	Min	Max	Min	
1/32	—	—	—	—	0.035	0.033	—	—	0.029 ^d	—	—	—	—	0.003	—	—	75	—	—	—	—	0.0325	0.0310
3/64	—	—	—	—	0.052	0.049	—	—	0.045 ^d	—	—	—	—	0.004	—	—	170	—	—	—	—	0.0485	0.0470
0.052	—	—	—	—	0.057	0.054	—	—	0.050 ^d	—	—	—	—	0.004	—	—	230	—	—	—	—	0.0535	0.0520
1/16	0.069	0.066	0.070	0.066	0.071	0.067	0.072	0.067	0.059	0.012	—	0.006	0.007	0.005	0.003	425	300	160	0.065	0.062	0.065	0.061	
5/64	0.086	0.083	0.086	0.082	0.087	0.083	0.088	0.083	0.075	0.018	—	0.008	0.007	0.005	0.003	650	480	260	0.081	0.078	0.081	0.077	
3/32	0.103	0.099	0.103	0.098	0.104	0.099	0.105	0.099	0.091	0.022	0.012	0.012	0.010	0.007	0.005	1000	690	370	0.097	0.094	0.097	0.093	
7/64	0.118	0.113	0.118	0.113	0.119	0.114	0.120	0.114	0.106	0.022	—	0.018	0.010	0.007	0.005	1410	940	510	0.112	0.109	0.112	0.108	
1/8	0.135	0.131	0.136	0.130	0.137	0.131	0.138	0.131	0.122	0.028	0.012	0.018	0.014	0.010	0.007	1840	1000	660	0.129	0.125	0.129	0.124	
9/64	0.149	0.145	0.151	0.145	0.152	0.146	0.153	0.146	0.136	0.028	—	0.022	0.014	0.010	0.007	2200	1550	830	0.141	0.140	0.144	0.139	
5/32	0.167	0.162	0.168	0.161	0.170	0.163	0.171	0.163	0.152	0.032	0.018	0.022	0.017	0.011	0.007	2880	1750	1040	0.160	0.156	0.160	0.155	
3/16	0.199	0.194	0.202	0.194	0.204	0.196	0.206	0.196	0.182	0.040	0.022	0.028	0.020	0.015	0.010	4140	2500	1500	0.192	0.187	0.192	0.185	
7/32	0.232	0.226	0.235	0.226	0.238	0.229	0.240	0.229	0.214	0.048	0.028	0.032	0.024	0.017	0.011	5640	3760	2040	0.224	0.219	0.224	0.217	
1/4	0.264	0.258	0.268	0.258	0.270	0.260	0.272	0.260	0.245	0.048	0.028	0.032	0.028	0.020	0.015	7360	4600	2660	0.256	0.250	0.256	0.248	
5/16	0.328	0.321	0.340	0.327	0.341	0.327	0.342	0.327	0.306	0.062	—	0.040	0.032	0.024	0.017	11500	7670	4160	0.318	0.312	0.318	0.308	
3/8	0.392	0.385	0.407	0.391	0.408	0.391	0.409	0.391	0.368	0.077	—	0.048	0.040	0.028	0.020	16580	11040	6000	0.382	0.375	0.382	0.368	
7/16	0.456	0.448	0.475	0.457	0.476	0.457	0.478	0.457	0.430	0.077	—	0.048	0.047	0.036	0.024	20000	15020	8160	0.445	0.437	0.445	0.429	
1/2	0.521	0.513	0.542	0.522	0.543	0.522	0.545	0.522	0.490	0.094	—	0.062	0.055	0.040	0.028	25800	19600	10640	0.510	0.500	0.510	0.490	

^a Maximum D shall be checked by a "GO" ring gage.

^b Series designation applies to stock thickness, A being heaviest.

^c Minimum D shall be the average of the D₁, D₂, and D₃ diameters.

^d Series B coiled.

^e Applies to pins made from SAE 1070 to 1095 steel and SAE 51410 or AISI 420 corrosion resistant steel. SAE 30302 stainless steel has a minimum shear strength equal to 85% of values shown for coiled pins.

3. **Length and Availability**—Table 3, Practical Length Increments and Ranges, indicates spring pin sizes. Information on availability of individual lengths in the various types, weights, and materials may be obtained from suppliers.

The tolerance on length for coiled type spring pins shall be ± 0.010 in. for sizes up to and including 5/16 in.; and ± 0.015 in. for sizes larger than 5/16 in.

The tolerance on length for slotted type spring pins shall be in accordance with the following tabulation:

Length Range	3/16 to 1 Incl	Over 1 To 2 Incl	Over 2 To 3 Incl	Over 3 to 4 Incl	Over 4 in
Tolerance					
On Length	± 0.015	± 0.020	± 0.025	± 0.030	± 0.035

4. **Surface Treatment**—Where corrosion preventive treatment applied to carbon steel spring pins is such that it might produce hydrogen embrittlement, the spring pins shall be baked or treated in such a manner as to obviate such embrittlement.
5. **Material and Hardness**—Hardness shall be tested in the following manner: For slotted pins the readings shall be taken near the center of a longitudinal flat ground on the pin at right angles to the slot. Coiled pins shall be ground or cut in half along the longitudinal axis and the hardness readings shall be taken on the inside surface of the outer half coil. Table 2 designates materials and the proper Rockwell scale to be used for the various wall thickness ranges.